

به نام خدا



مرکز دانلود رایگان مهندسی متالورژی و مواد

www.Iran-mavad.com





2013 ASME Boiler and Pressure Vessel Code

AN INTERNATIONAL CODE

IX

Welding, Brazing, and Fusing Qualifications

Qualification Standard for Welding, Brazing, and Fusing Procedures; Welders; Brazers; and Welding, Brazing, and Fusing Operators

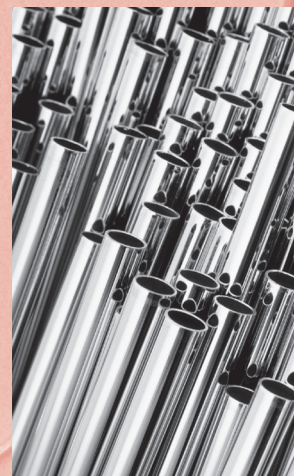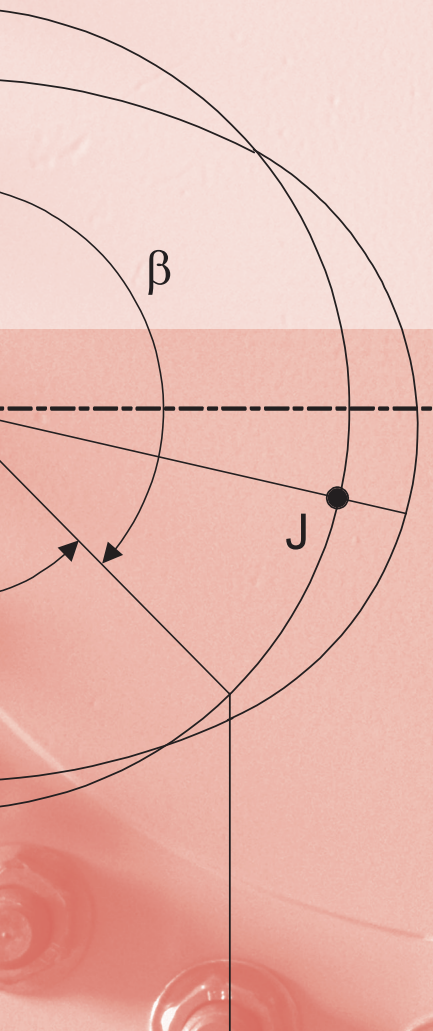

www.iran-mavad.com

مرجع دانشجویان و مهندسين مواد

ASME
SETTING THE STANDARD

INTENTIONALLY LEFT BLANK

AN INTERNATIONAL CODE

2013 ASME Boiler & Pressure Vessel Code

2013 Edition

July 1, 2013

IX

Qualification Standard for Welding, Brazing, and Fusing Procedures; Welders; Brazers; and Welding, Brazing, and Fusing Operators

ASME Boiler and Pressure Vessel Committee
on Welding, Brazing, and Fusing



The American Society of
Mechanical Engineers

Two Park Avenue • New York, NY • 10016 USA

www.iran-mavad.com

مرجع دانشجویان و مهندسين مواد

Date of Issuance: July 1, 2013

This international code or standard was developed under procedures accredited as meeting the criteria for American National Standards and it is an American National Standard. The Standards Committee that approved the code or standard was balanced to assure that individuals from competent and concerned interests have had an opportunity to participate. The proposed code or standard was made available for public review and comment that provides an opportunity for additional public input from industry, academia, regulatory agencies, and the public-at-large.

ASME does not “approve,” “rate,” or “endorse” any item, construction, proprietary device, or activity.

ASME does not take any position with respect to the validity of any patent rights asserted in connection with any items mentioned in this document, and does not undertake to insure anyone utilizing a standard against liability for infringement of any applicable letters patent, nor assume any such liability. Users of a code or standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, is entirely their own responsibility.

Participation by federal agency representative(s) or person(s) affiliated with industry is not to be interpreted as government or industry endorsement of this code or standard.

ASME accepts responsibility for only those interpretations of this document issued in accordance with the established ASME procedures and policies, which precludes the issuance of interpretations by individuals.

The endnotes in this document (if any) are part of this American National Standard.



ASME collective membership mark



Certification Mark

The above ASME symbol is registered in the U.S. Patent Office.

“ASME” is the trademark of The American Society of Mechanical Engineers.

No part of this document may be reproduced in any form, in an electronic retrieval system or otherwise, without the prior written permission of the publisher.

Library of Congress Catalog Card Number: 56-3934
Printed in the United States of America

Adopted by the Council of The American Society of Mechanical Engineers, 1914; latest edition 2013.

The American Society of Mechanical Engineers
Two Park Avenue, New York, NY 10016-5990

Copyright © 2013 by
THE AMERICAN SOCIETY OF MECHANICAL ENGINEERS
All rights reserved

TABLE OF CONTENTS

List of Sections	x
Foreword	xii
Statement of Policy on the Use of the Certification Mark and Code Authorization in Advertising	xiv
Statement of Policy on the Use of ASME Marking to Identify Manufactured Items	xiv
Submittal of Technical Inquiries to the Boiler and Pressure Vessel Standards Committees	xv
Personnel	xvii
Introduction	xxxii
Summary of Changes	xxxv
List of Changes in BC Order	xxxix
Cross-Referencing and Stylistic Changes in the Boiler and Pressure Vessel Code	xl
Part QG	
General Requirements	1
QG-100 Scope	1
QG-109 Definitions	4
Part QW	
Welding	14
Article I	
Welding General Requirements	14
QW-100 Scope	14
QW-110 Weld Orientation	14
QW-120 Test Positions for Groove Welds	14
QW-130 Test Positions for Fillet Welds	15
QW-140 Types and Purposes of Tests and Examinations	15
QW-150 Tension Tests	16
QW-160 Guided-Bend Tests	17
QW-170 Notch-Toughness Tests	18
QW-180 Fillet-Weld Tests	18
QW-190 Other Tests and Examinations	19
Article II	
Welding Procedure Qualifications	27
QW-200 General	27
QW-210 Preparation of Test Coupon	30
QW-220 Hybrid Laser-GMAW Welding	31
QW-250 Welding Variables	32
QW-290 Temper Bead Welding	70
Article III	
Welding Performance Qualifications	74
QW-300 General	74
QW-310 Qualification Test Coupons	76
QW-320 Retests and Renewal of Qualification	76
QW-350 Welding Variables for Welders	77
QW-360 Welding Variables for Welding Operators	79
QW-380 Special Processes	80
Article IV	
Welding Data	82
QW-400 Variables	82
QW-410 Technique	92
QW-420 Base Metal Groupings	96
QW-430 F-Numbers	166
QW-440 Weld Metal Chemical Composition	176
QW-450 Specimens	177

QW-460	Graphics	183
QW-470	Etching — Processes and Reagents	228
QW-490	redesignated as QG-109	229
Article V	Standard Welding Procedure Specifications (SWPSs)	230
QW-500	General	230
QW-510	Adoption of SWPSs	230
QW-520	Use of SWPSs Without Discrete Demonstration	230
QW-530	Forms	231
QW-540	Production Use of SWPSs	231
Part QB	Brazing	232
Article XI	Brazing General Requirements	232
QB-100	Scope	232
QB-110	Braze Orientation	232
QB-120	Test Positions for Lap, Butt, Scarf, or Rabbet Joints	232
QB-140	Types and Purposes of Tests and Examinations	233
QB-150	Tension Tests	233
QB-160	Guided-Bend Tests	234
QB-170	Peel Tests	235
QB-180	Sectioning Tests and Workmanship Coupons	235
Article XII	Brazing Procedure Qualifications	236
QB-200	General	236
QB-210	Preparation of Test Coupon	237
QB-250	Brazing Variables	238
Article XIII	Brazing Performance Qualifications	242
QB-300	General	242
QB-310	Qualification Test Coupons	243
QB-320	Retests and Renewal of Qualification	243
QB-350	Brazing Variables for Brazers and Brazing Operators	243
Article XIV	Brazing Data	244
QB-400	Variables	244
QB-410	Technique	245
QB-420	P-Numbers	245
QB-430	F-Numbers	245
QB-450	Specimens	248
QB-460	Graphics	252
Part QF	Plastic Fusing	271
Article XXI	Plastic Fusing General Requirements	271
QF-100	Scope	271
QF-110	Fused Joint Orientation	271
QF-120	Test Positions	271
QF-130	Data Acquisition and Evaluation	271
QF-140	Examinations and Tests	272
Article XXII	Fusing Procedure Qualifications	274
QF-200	General	274
QF-220	Standard Fusing Procedure Specification (SFPS)	275
QF-250	Fusing Variables	277
Article XXIII	Plastic Fusing Performance Qualifications	279
QF-300	General	279
QF-301	Tests	279
QF-302	Type of Test Required	279
QF-303	Limits of Qualified Positions and Diameters (See QF-461)	279

QF-305	Fusing Machine Operators	279
QF-310	Qualification Test Coupons	280
QF-311	Test Coupons	280
QF-320	Retests and Renewal of Qualification	280
QF-321	Retests	280
QF-322	Expiration and Renewal of Qualification	280
QF-360	Essential Variables for Performance Qualification of Fusing Machine Operators	280
QF-361	General	280
Article XXIV	Plastic Fusing Data	281
QF-400	Variables	281
QF-401	General	281
QF-402	Joints	281
QF-403	Material	281
QF-404	Position	281
QF-405	Thermal Conditions	281
QF-406	Equipment	281
QF-407	Technique	281
QF-420	Material Groupings	281
QF-450	Pipe Fusing Limits	282
QF-460	Graphics	282
QF-461	Positions	282
QF-480	Forms	289
QF-490	Definitions	293
QF-491	General	293
QF-492	Definitions	293
Nonmandatory Appendix B	Welding and Brazing Forms	295
Nonmandatory Appendix D	P-Number Listing	306
Mandatory Appendix E	Permitted SWPSs	324
Mandatory Appendix F	Standard Units for Use in Equations	327
Nonmandatory Appendix G	Guidance for the Use of U.S. Customary and SI Units in the ASME Boiler and Pressure Vessel Code	328
Nonmandatory Appendix H	Waveform Controlled Welding	331
Mandatory Appendix J	Guideline for Requesting P-Number Assignments for Base Metals not Listed in Table QW/QB-422	333
Nonmandatory Appendix K	Guidance on Invoking Section IX Requirements in Other Codes, Standards, Specifications, and Contract Documents	334
 FIGURES		
QG-109.2.1	Typical Single and Multibead Layers	13
QG-109.2.2	Typical Single Bead Layers	13
QW-191.1.2.2(b)(4)	Rounded Indication Charts	21
QW-461.1	Positions of Welds — Groove Welds	183
QW-461.2	Positions of Welds — Fillet Welds	184
QW-461.3	Groove Welds in Plate — Test Positions	185
QW-461.4	Groove Welds in Pipe — Test Positions	185
QW-461.5	Fillet Welds in Plate — Test Positions	186
QW-461.6	Fillet Welds in Pipe — Test Positions	187
QW-461.7	Stud Welds — Test Positions	188
QW-461.8	Stud Welds — Welding Positions	188
QW-461.10	Rotating Tool Design Characteristics (FSW) Referenced in QW-410	190
QW-462.1(a)	Tension — Reduced Section — Plate	191

QW-462.1(b)	Tension — Reduced Section — Pipe	191
QW-462.1(c)	Tension — Reduced Section Alternate for Pipe	192
QW-462.1(d)	Tension — Reduced Section — Turned Specimens	192
QW-462.1(e)	Tension — Full Section — Small Diameter Pipe	193
QW-462.2	Side Bend	194
QW-462.3(a)	Face and Root Bends — Transverse	195
QW-462.3(b)	Face and Root Bends — Longitudinal	196
QW-462.4(a)	Fillet Welds in Plate — Procedure	196
QW-462.4(b)	Fillet Welds in Plate — Performance	197
QW-462.4(c)	Fillet Welds in Pipe — Performance	197
QW-462.4(d)	Fillet Welds in Pipe — Procedure	198
QW-462.5(a)	Chemical Analysis and Hardness Specimen Corrosion-Resistant and Hard-Facing Weld Metal Overlay	199
QW-462.5(b)	Chemical Analysis Specimen, Hard-Facing Overlay Hardness, and Macro Test Location (s) for Corrosion-Resistant and Hard-Facing Weld Metal Overlay	200
QW-462.5(c)	Pipe Bend Specimen — Corrosion-Resistant Weld Metal Overlay	201
QW-462.5(d)	Plate Bend Specimens — Corrosion-Resistant Weld Metal Overlay	202
QW-462.5(e)	Plate Macro, Hardness, and Chemical Analysis Specimens — Corrosion-Resistant and Hard-Facing Weld Metal Overlay	203
QW-462.7.1	Resistance Seam Weld Test Coupon	203
QW-462.7.2	Seam Weld Section Specimen Removal	204
QW-462.7.3	Resistance Weld Nugget Section Test Specimens	204
QW-462.8.1	Spot Welds in Sheets	205
QW-462.8.2	Seam Weld Peel Test Specimen and Method	206
QW-462.9	Spot Welds in Sheet	207
QW-462.12	Nomenclature for Temper Bead Welding	211
QW-462.13	Measurement of Temper Bead Overlap	212
QW-463.1(a)	Plates — Less Than $\frac{3}{4}$ in. (19 mm) Thickness Procedure Qualification	212
QW-463.1(b)	Plates — $\frac{3}{4}$ in. (19 mm) and Over Thickness and Alternate From $\frac{3}{8}$ in. (10 mm) but Less Than $\frac{3}{4}$ in. (19 mm) Thickness Procedure Qualification	212
QW-463.1(c)	Plates — Longitudinal Procedure Qualification	213
QW-463.1(d)	Procedure Qualification	213
QW-463.1(e)	Procedure Qualification	214
QW-463.1(f)	Notch-Toughness Test Specimen Location	214
QW-463.2(a)	Plates — Less Than $\frac{3}{4}$ in. (19 mm) Thickness Performance Qualification	215
QW-463.2(b)	Plates — $\frac{3}{4}$ in. (19 mm) and Over Thickness and Alternate From $\frac{3}{8}$ in. (10 mm) but Less Than $\frac{3}{4}$ in. (19 mm) Thickness Performance Qualification	215
QW-463.2(c)	Plates — Longitudinal Performance Qualification	216
QW-463.2(d)	Performance Qualification	216
QW-463.2(e)	Performance Qualification	217
QW-463.2(f)	Pipe — NPS 10 (DN 250) Assembly Performance Qualification	217
QW-463.2(g)	NPS 6 (DN 150) or NPS 8 (DN 200) Assembly Performance Qualification	218
QW-463.2(h)	Performance Qualification	219
QW-464.1	Procedure Qualification Test Coupon and Test Specimens	220
QW-464.2	Performance Qualification Test Coupons and Test Specimens	221
QW-466.1	Test Jig Dimensions	222
QW-466.2	Guided-Bend Roller Jig	224
QW-466.3	Guided-Bend Wrap Around Jig	224
QW-466.4	Stud-Weld Bend Jig	225
QW-466.5	Torque Testing Arrangement for Stud Welds	226
QW-466.6	Suggested Type Tensile Test Figure for Stud Welds	227
QW-469.1	Butt Joint	227
QW-469.2	Alternative Butt Joint	227
QB-461.1	Flow Positions	252
QB-461.2	Test Flow Positions	253
QB-462.1(a)	Tension — Reduced Section for Butt and Scarf Joints — Plate	254

QB-462.1(b)	Tension — Reduced Section for Butt, Lap, and Scarf Joints — Pipe	255
QB-462.1(c)	Tension — Reduced Section for Lap and Rabbet Joints — Plate	256
QB-462.1(e)	Tension — Full Section for Lap, Scarf, and Butt Joints — Small Diameter Pipe	257
QB-462.1(f)	Support Fixture for Reduced-Section Tension Specimens	258
QB-462.2(a)	Transverse First and Second Surface Bends — Plate and Pipe	259
QB-462.2(b)	Longitudinal First and Second Surface Bends — Plate	259
QB-462.3	Lap Joint Peel Specimen	260
QB-462.4	Lap Joint Section Specimen (see QB-181)	260
QB-462.5	Workmanship Coupons	261
QB-463.1(a)	Plates Procedure Qualification	262
QB-463.1(b)	Plates Procedure Qualification	262
QB-463.1(c)	Plates Procedure Qualification	263
QB-463.1(d)	Plates Procedure Qualification	264
QB-463.1(e)	Pipe — Procedure Qualification	265
QB-463.2(a)	Plates Performance Qualification	266
QB-463.2(b)	Plates Performance Qualification	267
QB-463.2(c)	Pipe Performance Qualification	268
QB-466.1	Guided-Bend Jig	269
QB-466.2	Guided-Bend Roller Jig	270
QB-466.3	Guided-Bend Wrap Around Jig	270
QF-221.1	Required Minimum Melt Bead Size	276
QF-461.1	Fusing Positions	282
QF-461.2	Fusing Test Positions	283
QF-462	Cross Section of Upset Beads for Butt-Fused PE Pipe	284
QF-463	Bend Test Specimen Removal, Configuration, and Testing	285
QF-464	HSTIT Specimen Configuration and Dimensions	287
QF-465	HSTIT Specimen Failure Examples	288

TABLES

QW-252	Welding Variables Procedure Specifications (WPS) — Oxyfuel Gas Welding (OFW)	33
QW-252.1	Welding Variables Procedure Specifications (WPS) — Oxyfuel Gas Welding (OFW)	34
QW-253	Welding Variables Procedure Specifications (WPS) — Shielded Metal-Arc Welding (SMAW)	35
QW-253.1	Welding Variables Procedure Specifications (WPS) — Shielded Metal-Arc Welding (SMAW)	36
QW-254	Welding Variables Procedure Specifications (WPS) — Submerged-Arc Welding (SAW)	37
QW-254.1	Welding Variables Procedure Specifications (WPS) — Submerged-Arc Welding (SAW)	39
QW-255	Welding Variables Procedure Specifications (WPS) — Gas Metal-Arc Welding (GMAW and FCAW)	40
QW-255.1	Welding Variables Procedure Specifications (WPS) — Gas Metal-Arc Welding (GMAW and FCAW)	42
QW-256	Welding Variables Procedure Specifications (WPS) — Gas Tungsten-Arc Welding (GTAW)	43
QW-256.1	Welding Variables Procedure Specifications (WPS) — Gas Tungsten-Arc Welding (GTAW)	45
QW-257	Welding Variables Procedure Specifications (WPS) — Plasma-Arc Welding (PAW)	46
QW-257.1	Welding Variables Procedure Specifications (WPS) — Plasma-Arc Welding (PAW)	48
QW-258	Welding Variables Procedure Specifications (WPS) — Electroslag Welding (ESW)	50
QW-258.1	Welding Variables Procedure Specifications (WPS) — Electroslag Welding (ESW)	51
QW-259	Welding Variables Procedure Specifications (WPS) — Electrode Gas Welding (EGW)	52
QW-260	Welding Variables Procedure Specifications (WPS) — Electron Beam Welding (EBW)	53
QW-261	Welding Variables Procedure Specifications (WPS) — Stud Welding	54
QW-262	Welding Variables Procedure Specifications (WPS) — Inertia and Continuous Drive Friction Welding	55
QW-263	Welding Variables Procedure Specifications (WPS) — Resistance Welding	56
QW-264	Welding Variables Procedure Specifications (WPS) — Laser Beam Welding (LBW)	57
QW-264.1	Welding Variables Procedure Specifications (WPS) — Laser Beam Welding (LBW)	58
QW-265	Welding Variables Procedure Specifications (WPS) — Flash Welding	59
QW-266	Welding Variables Procedure Specifications (WPS) — Diffusion Welding (DFW)	60
QW-267	Welding Variables Procedure Specifications — Friction Stir Welding (FSW)	61

QW-268	Welding Variables Procedure Specifications (WPS) — Hybrid Laser-GMAW	62
QW-269	Welding Variables Procedure Specifications (WPS) — Hybrid Plasma-GMAW	64
QW-269.1	Welding Variables Procedure Specifications (WPS) — Hybrid Plasma-GMAW	66
QW-290.4	Welding Variables for Temper Bead Procedure Qualification	71
QW-352	Oxyfuel Gas Welding (OFW)	78
QW-353	Shielded Metal-Arc Welding (SMAW)	78
QW-354	Semiautomatic Submerged-Arc Welding (SAW)	78
QW-355	Semiautomatic Gas Metal-Arc Welding (GMAW)	78
QW-356	Manual and Semiautomatic Gas Tungsten-Arc Welding (GTAW)	78
QW-357	Manual and Semiautomatic Plasma-Arc Welding (PAW)	79
QW-416	Welding Variables	95
QW/QB-422	Ferrous/Nonferrous P-Numbers	97
QW-432	F-Numbers	167
QW-442	A-Numbers	176
QW-451.1	Groove-Weld Tension Tests and Transverse-Bend Tests	177
QW-451.2	Groove-Weld Tension Tests and Longitudinal-Bend Tests	178
QW-451.3	Fillet-Weld Tests	178
QW-451.4	Fillet Welds Qualified by Groove-Weld Tests	178
QW-452.1(a)	Test Specimens	179
QW-452.1(b)	Thickness of Weld Metal Qualified	179
QW-452.3	Groove-Weld Diameter Limits	180
QW-452.4	Small Diameter Fillet-Weld Test	180
QW-452.5	Fillet-Weld Test	180
QW-452.6	Fillet Qualification by Groove-Weld Tests	181
QW-453	Procedure/Performance Qualification Thickness Limits and Test Specimens for Hard-Facing (Wear-Resistant) and Corrosion-Resistant Overlays	181
QW-461.9	Performance Qualification — Position and Diameter Limitations	189
QW-462.10(a)	Shear Strength Requirements for Spot or Projection Weld Specimens	208
QW-462.10(b)	Shear Strength Requirements for Spot or Projection Weld Specimens	209
QW-462.10(c)	Shear Strength Requirements for Spot or Projection Weld Specimens	210
QW-473.3-1	Makeup of Equations for Aqua Regia and Lepito's Etch	228
QB-252	Torch Brazing (TB)	238
QB-253	Furnace Brazing (FB)	239
QB-254	Induction Brazing (IB)	239
QB-255	Resistance Brazing (RB)	240
QB-256	Dip Brazing — Salt or Flux Bath (DB)	240
QB-257	Dip Brazing — Molten Metal Bath (DB)	241
QB-432	F-Numbers	246
QB-451.1	Tension Tests and Transverse-Bend Tests — Butt and Scarf Joints	248
QB-451.2	Tension Tests and Longitudinal Bend Tests — Butt and Scarf Joints	248
QB-451.3	Tension Tests and Peel Tests — LAP Joints	249
QB-451.4	Tension Tests and Section Tests — Rabbet Joints	249
QB-451.5	Section Tests — Workmanship Coupon Joints	250
QB-452.1	Peel or Section Tests — Butt, Scarf, Lap, Rabbet Joints	251
QB-452.2	Section Tests — Workmanship Specimen Joints	251
QF-144.2	Testing Speed Requirements	273
QF-221.2	Maximum Heater Plate Removal Time for Pipe-to-Pipe Fusing	277
QF-254	Fusing Variables Procedure Specification	278
QF-362	Essential Variables Applicable to Fusing Machine Operators	280
QF-422	Material Grouping	281
QF-452.3	Pipe Fusing Diameter Limits	282
F-100	Standard Units for Use in Equations	327
FORMS		
QF-482	289
QF-483	290

QF-483	291
QF-484	292
QF-485	293
QW-482	296
QW-483	298
QW-484A	300
QW-484B	301
QW-485	302
QB-482	303
QB-483	304
QB-484	305
INDEX	336

LIST OF SECTIONS

SECTIONS

- I Rules for Construction of Power Boilers
- II Materials
 - Part A — Ferrous Material Specifications
 - Part B — Nonferrous Material Specifications
 - Part C — Specifications for Welding Rods, Electrodes, and Filler Metals
 - Part D — Properties (Customary)
 - Part D — Properties (Metric)
- III Rules for Construction of Nuclear Facility Components
 - Subsection NCA — General Requirements for Division 1 and Division 2
 - Appendices
 - Division 1
 - Subsection NB — Class 1 Components
 - Subsection NC — Class 2 Components
 - Subsection ND — Class 3 Components
 - Subsection NE — Class MC Components
 - Subsection NF — Supports
 - Subsection NG — Core Support Structures
 - Subsection NH — Class 1 Components in Elevated Temperature Service
 - Division 2 — Code for Concrete Containments
 - Division 3 — Containments for Transportation and Storage of Spent Nuclear Fuel and High Level Radioactive Material and Waste
 - Division 5 — High Temperature Reactors
- IV Rules for Construction of Heating Boilers
- V Nondestructive Examination
- VI Recommended Rules for the Care and Operation of Heating Boilers
- VII Recommended Guidelines for the Care of Power Boilers
- VIII Rules for Construction of Pressure Vessels
 - Division 1
 - Division 2 — Alternative Rules
 - Division 3 — Alternative Rules for Construction of High Pressure Vessels
- IX Welding, Brazing, and Fusing Qualifications
- X Fiber-Reinforced Plastic Pressure Vessels
- XI Rules for Inservice Inspection of Nuclear Power Plant Components
- XII Rules for Construction and Continued Service of Transport Tanks

INTERPRETATIONS

ASME issues written replies to inquiries concerning interpretation of technical aspects of the Code.

Interpretations of the Code are posted in January and July at <http://cstools.asme.org/interpretations.cfm>. Any Interpretations issued during the previous two calendar years are included with the publication of the applicable Section of the Code. Interpretations of Section III, Divisions 1 and 2 and Section III Appendices are included with Subsection NCA.

CODE CASES

The Boiler and Pressure Vessel Code committees meet regularly to consider proposed additions and revisions to the Code and to formulate Cases to clarify the intent of existing requirements or provide, when the need is urgent, rules for materials or constructions not covered by existing Code rules. Those Cases that have been adopted will appear in the appropriate 2013 Code Cases book: "Boilers and Pressure Vessels" or "Nuclear Components." Supplements will be sent automatically to the purchasers of the Code Cases books up to the publication of the 2015 Code.

FOREWORD

(This Foreword is provided as an aid to the user and is not part of the rules of this Code.)

In 1911, The American Society of Mechanical Engineers established the Boiler and Pressure Vessel Committee to formulate standard rules for the construction of steam boilers and other pressure vessels. In 2009, the Boiler and Pressure Vessel Committee was superseded by the following committees:

- (a) Committee on Power Boilers (I)
- (b) Committee on Materials (II)
- (c) Committee on Construction of Nuclear Facility Components (III)
- (d) Committee on Heating Boilers (IV)
- (e) Committee on Nondestructive Examination (V)
- (f) Committee on Pressure Vessels (VIII)
- (g) Committee on Welding, Brazing, and Fusing (IX)
- (h) Committee on Fiber-Reinforced Plastic Pressure Vessels (X)
- (i) Committee on Nuclear Inservice Inspection (XI)
- (j) Committee on Transport Tanks (XII)

Where reference is made to "the Committee" in this Foreword, each of these committees is included individually and collectively.

The Committee's function is to establish rules of safety relating only to pressure integrity, which govern the construction^{*} of boilers, pressure vessels, transport tanks, and nuclear components, and the inservice inspection of nuclear components and transport tanks. The Committee also interprets these rules when questions arise regarding their intent. This Code does not address other safety issues relating to the construction of boilers, pressure vessels, transport tanks, or nuclear components, or the inservice inspection of nuclear components or transport tanks. Users of the Code should refer to the pertinent codes, standards, laws, regulations, or other relevant documents for safety issues other than those relating to pressure integrity. Except for Sections XI and XII, and with a few other exceptions, the rules do not, of practical necessity, reflect the likelihood and consequences of deterioration in service related to specific service fluids or external operating environments. In formulating the rules, the Committee considers the needs of users, manufacturers, and inspectors of pressure vessels. The objective of the rules is to afford reasonably certain protection of life and property, and to provide a margin for deterioration in service to give a reasonably long, safe period of usefulness. Advancements in design and materials and evidence of experience have been recognized.

This Code contains mandatory requirements, specific prohibitions, and nonmandatory guidance for construction activities and inservice inspection and testing activities. The Code does not address all aspects of these activities and those aspects that are not specifically addressed should not be considered prohibited. The Code is not a handbook and cannot replace education, experience, and the use of engineering judgment. The phrase *engineering judgement* refers to technical judgments made by knowledgeable engineers experienced in the application of the Code. Engineering judgments must be consistent with Code philosophy, and such judgments must never be used to overrule mandatory requirements or specific prohibitions of the Code.

The Committee recognizes that tools and techniques used for design and analysis change as technology progresses and expects engineers to use good judgment in the application of these tools. The designer is responsible for complying with Code rules and demonstrating compliance with Code equations when such equations are mandatory. The Code neither requires nor prohibits the use of computers for the design or analysis of components constructed to the requirements of the Code. However, designers and engineers using computer programs for design or analysis are cautioned that they are responsible for all technical assumptions inherent in the programs they use and the application of these programs to their design.

^{*} *Construction*, as used in this Foreword, is an all-inclusive term comprising materials, design, fabrication, examination, inspection, testing, certification, and pressure relief.

The rules established by the Committee are not to be interpreted as approving, recommending, or endorsing any proprietary or specific design, or as limiting in any way the manufacturer's freedom to choose any method of design or any form of construction that conforms to the Code rules.

The Committee meets regularly to consider revisions of the rules, new rules as dictated by technological development, Code Cases, and requests for interpretations. Only the Committee has the authority to provide official interpretations of this Code. Requests for revisions, new rules, Code Cases, or interpretations shall be addressed to the Secretary in writing and shall give full particulars in order to receive consideration and action (see Submittal of Technical Inquiries to the Boiler and Pressure Vessel Standards Committees). Proposed revisions to the Code resulting from inquiries will be presented to the Committee for appropriate action. The action of the Committee becomes effective only after confirmation by ballot of the Committee and approval by ASME. Proposed revisions to the Code approved by the Committee are submitted to the American National Standards Institute (ANSI) and published at <http://cstools.asme.org/csconnect/public/index.cfm?PublicReview=Revisions> to invite comments from all interested persons. After public review and final approval by ASME, revisions are published at regular intervals in Editions of the Code.

The Committee does not rule on whether a component shall or shall not be constructed to the provisions of the Code. The scope of each Section has been established to identify the components and parameters considered by the Committee in formulating the Code rules.

Questions or issues regarding compliance of a specific component with the Code rules are to be directed to the ASME Certificate Holder (Manufacturer). Inquiries concerning the interpretation of the Code are to be directed to the Committee. ASME is to be notified should questions arise concerning improper use of an ASME Certification Mark.

When required by context in this Section, the singular shall be interpreted as the plural, and vice versa, and the feminine, masculine, or neuter gender shall be treated as such other gender as appropriate.

STATEMENT OF POLICY ON THE USE OF THE CERTIFICATION MARK AND CODE AUTHORIZATION IN ADVERTISING

ASME has established procedures to authorize qualified organizations to perform various activities in accordance with the requirements of the ASME Boiler and Pressure Vessel Code. It is the aim of the Society to provide recognition of organizations so authorized. An organization holding authorization to perform various activities in accordance with the requirements of the Code may state this capability in its advertising literature.

Organizations that are authorized to use the Certification Mark for marking items or constructions that have been constructed and inspected in compliance with the ASME Boiler and Pressure Vessel Code are issued Certificates of Authorization. It is the aim of the Society to maintain the standing of the Certification Mark for the benefit of the users, the enforcement jurisdictions, and the holders of the Certification Mark who comply with all requirements.

Based on these objectives, the following policy has been established on the usage in advertising of facsimiles of the Certification Mark, Certificates of Authorization, and reference to Code construction. The American Society of Mechanical Engineers does not “approve,” “certify,” “rate,” or “endorse” any item, construction, or activity and there shall be no statements or implications that might so indicate. An organization holding the Certification Mark and/or a Certificate of Authorization may state in advertising literature that items, constructions, or activities “are built (produced or performed) or activities conducted in accordance with the requirements of the ASME Boiler and Pressure Vessel Code,” or “meet the requirements of the ASME Boiler and Pressure Vessel Code.” An ASME corporate logo shall not be used by any organization other than ASME.

The Certification Mark shall be used only for stamping and nameplates as specifically provided in the Code. However, facsimiles may be used for the purpose of fostering the use of such construction. Such usage may be by an association or a society, or by a holder of the Certification Mark who may also use the facsimile in advertising to show that clearly specified items will carry the Certification Mark. General usage is permitted only when all of a manufacturer’s items are constructed under the rules.

STATEMENT OF POLICY ON THE USE OF ASME MARKING TO IDENTIFY MANUFACTURED ITEMS

The ASME Boiler and Pressure Vessel Code provides rules for the construction of boilers, pressure vessels, and nuclear components. This includes requirements for materials, design, fabrication, examination, inspection, and stamping. Items constructed in accordance with all of the applicable rules of the Code are identified with the official Certification Mark described in the governing Section of the Code.

Markings such as “ASME,” “ASME Standard,” or any other marking including “ASME” or the Certification Mark shall not be used on any item that is not constructed in accordance with all of the applicable requirements of the Code.

Items shall not be described on ASME Data Report Forms nor on similar forms referring to ASME that tend to imply that all Code requirements have been met when, in fact, they have not been. Data Report Forms covering items not fully complying with ASME requirements should not refer to ASME or they should clearly identify all exceptions to the ASME requirements.

(13) SUBMITTAL OF TECHNICAL INQUIRIES TO THE BOILER AND PRESSURE VESSEL STANDARDS COMMITTEES

1 INTRODUCTION

(a) The following information provides guidance to Code users for submitting technical inquiries to the committees. See Guideline on the Approval of New Materials Under the ASME Boiler and Pressure Vessel Code in Section II, Parts C and D for additional requirements for requests involving adding new materials to the Code. Technical inquiries include requests for revisions or additions to the Code rules, requests for Code Cases, and requests for Code Interpretations, as described below.

(1) *Code Revisions.* Code revisions are considered to accommodate technological developments, address administrative requirements, incorporate Code Cases, or to clarify Code intent.

(2) *Code Cases.* Code Cases represent alternatives or additions to existing Code rules. Code Cases are written as a question and reply, and are usually intended to be incorporated into the Code at a later date. When used, Code Cases prescribe mandatory requirements in the same sense as the text of the Code. However, users are cautioned that not all jurisdictions or owners automatically accept Code Cases. The most common applications for Code Cases are:

(-a) to permit early implementation of an approved Code revision based on an urgent need

(-b) to permit the use of a new material for Code construction

(-c) to gain experience with new materials or alternative rules prior to incorporation directly into the Code

(3) *Code Interpretations.* Code Interpretations provide clarification of the meaning of existing rules in the Code, and are also presented in question and reply format. Interpretations do not introduce new requirements. In cases where existing Code text does not fully convey the meaning that was intended, and revision of the rules is required to support an interpretation, an Intent Interpretation will be issued and the Code will be revised.

(b) The Code rules, Code Cases, and Code Interpretations established by the committees are not to be considered as approving, recommending, certifying, or endorsing any proprietary or specific design, or as limiting in any way the freedom of manufacturers, constructors, or owners to choose any method of design or any form of construction that conforms to the Code rules.

(c) Inquiries that do not comply with these provisions or that do not provide sufficient information for a committee's full understanding may result in the request being returned to the inquirer with no action.

2 INQUIRY FORMAT

Submittals to a committee shall include:

(a) *Purpose.* Specify one of the following:

(1) revision of present Code rules

(2) new or additional Code rules

(3) Code Case

(4) Code Interpretation

(b) *Background.* Provide the information needed for the committee's understanding of the inquiry, being sure to include reference to the applicable Code Section, Division, Edition, Addenda (if applicable), paragraphs, figures, and tables. Preferably, provide a copy of the specific referenced portions of the Code.

(c) *Presentations.* The inquirer may desire or be asked to attend a meeting of the committee to make a formal presentation or to answer questions from the committee members with regard to the inquiry. Attendance at a committee meeting shall be at the expense of the inquirer. The inquirer's attendance or lack of attendance at a meeting shall not be a basis for acceptance or rejection of the inquiry by the committee.

3 CODE REVISIONS OR ADDITIONS

Requests for Code revisions or additions shall provide the following:

(a) *Proposed Revisions or Additions.* For revisions, identify the rules of the Code that require revision and submit a copy of the appropriate rules as they appear in the Code, marked up with the proposed revision. For additions, provide the recommended wording referenced to the existing Code rules.

(b) *Statement of Need.* Provide a brief explanation of the need for the revision or addition.

(c) *Background Information.* Provide background information to support the revision or addition, including any data or changes in technology that form the basis for the request that will allow the committee to adequately evaluate the proposed revision or addition. Sketches, tables, figures, and graphs should be submitted as appropriate. When applicable, identify any pertinent paragraph in the Code that would be affected by the revision or addition and identify paragraphs in the Code that reference the paragraphs that are to be revised or added.

4 CODE CASES

Requests for Code Cases shall provide a Statement of Need and Background Information similar to that defined in 3(b) and 3(c), respectively, for Code revisions or additions. The urgency of the Code Case (e.g., project underway or imminent, new procedure, etc.) must be defined and it must be confirmed that the request is in connection with equipment that will bear the Certification Mark, with the exception of Section XI applications. The proposed Code Case should identify the Code Section and Division, and be written as a *Question* and a *Reply* in the same format as existing Code Cases. Requests for Code Cases should also indicate the applicable Code Editions and Addenda (if applicable) to which the proposed Code Case applies.

5 CODE INTERPRETATIONS

(a) Requests for Code Interpretations shall provide the following:

(1) *Inquiry.* Provide a condensed and precise question, omitting superfluous background information and, when possible, composed in such a way that a “yes” or a “no” *Reply*, with brief provisos if needed, is acceptable. The question should be technically and editorially correct.

(2) *Reply.* Provide a proposed *Reply* that will clearly and concisely answer the *Inquiry* question. Preferably, the *Reply* should be “yes” or “no,” with brief provisos if needed.

(3) *Background Information.* Provide any background information that will assist the committee in understanding the proposed *Inquiry* and *Reply*.

(b) Requests for Code Interpretations must be limited to an interpretation of a particular requirement in the Code or a Code Case. The committee cannot consider consulting type requests such as the following:

(1) a review of calculations, design drawings, welding qualifications, or descriptions of equipment or parts to determine compliance with Code requirements;

(2) a request for assistance in performing any Code-prescribed functions relating to, but not limited to, material selection, designs, calculations, fabrication, inspection, pressure testing, or installation;

(3) a request seeking the rationale for Code requirements.

6 SUBMITTALS

Submittals to and responses from the committees shall meet the following:

(a) *Submittal.* Inquiries from Code users shall be in English and preferably be submitted in typewritten form; however, legible handwritten inquiries will also be considered. They shall include the name, address, telephone number, fax number, and e-mail address, if available, of the inquirer and be mailed to the following address:

Secretary

ASME Boiler and Pressure Vessel Committee

Two Park Avenue

New York, NY 10016-5990

As an alternative, inquiries may be submitted via e-mail to: SecretaryBPV@asme.org.

(b) *Response.* The Secretary of the appropriate committee shall acknowledge receipt of each properly prepared inquiry and shall provide a written response to the inquirer upon completion of the requested action by the committee.

PERSONNEL

ASME Boiler and Pressure Vessel Standards Committees, Subgroups, and Working Groups

January 1, 2013

TECHNICAL OVERSIGHT MANAGEMENT COMMITTEE (TOMC)

J. G. Feldstein, <i>Chair</i>	J. F. Henry
T. P. Pastor, <i>Vice Chair</i>	G. G. Karcher
J. S. Brzuszkiewicz, <i>Staff Secretary</i>	W. M. Lundy
R. W. Barnes	J. R. Mackay
R. J. Basile	U. R. Miller
J. E. Batey	W. E. Norris
T. L. Bedeaux	G. C. Park
D. L. Berger	M. D. Rana
D. A. Canonico	B. W. Roberts
A. Chaudouet	S. C. Roberts
R. P. Deubler	F. J. Schaaf, Jr.
D. A. Douin	A. Selz
R. E. Gimple	B. F. Shelley
M. Gold	W. J. Sperko
T. E. Hansen	R. W. Swayne

HONORARY MEMBERS (MAIN COMMITTEE)

F. P. Barton	M. H. Jawad
R. J. Cepulich	A. J. Justin
T. M. Cullen	W. G. Knecht
W. D. Doty	J. LeCoff
J. R. Farr	T. G. McCarty
G. E. Feigel	G. C. Millman
R. C. Griffin	R. A. Moen
O. F. Hedden	R. F. Reedy, Sr.

ADMINISTRATIVE COMMITTEE

J. G. Feldstein, <i>Chair</i>	J. F. Henry
T. P. Pastor, <i>Vice Chair</i>	U. R. Miller
J. S. Brzuszkiewicz, <i>Staff Secretary</i>	G. C. Park
R. W. Barnes	M. D. Rana
J. E. Batey	B. F. Shelley
T. L. Bedeaux	W. J. Sperko
D. L. Berger	

MARINE CONFERENCE GROUP

H. N. Patel, <i>Chair</i>	G. Nair
J. S. Brzuszkiewicz, <i>Staff Secretary</i>	J. D. Reynolds
J. G. Hungerbuhler, Jr.	

CONFERENCE COMMITTEE

D. A. Douin — Ohio, <i>Secretary</i>	K. T. Lau — Alberta, Canada
J. T. Amato — Minnesota	B. E. Logan — Massachusetts
B. P. Anthony — Rhode Island	W. McGivney — New York
R. D. Austin — Arizona	S. V. Nelson — Colorado
G. Baumgardner — Michigan	C. C. Novak — Illinois
W. K. Brigham — New Hampshire	T. Oda — Washington
C. W. Bryan — Tennessee	W. R. Owens — Louisiana
M. A. Burns — Florida	R. P. Pate — Alabama
J. H. Burpee — Maine	R. L. Perry — Nevada
C. B. Cantrell — Nebraska	J. F. Porcella — West Virginia
D. C. Cook — California	D. C. Price — Yukon Territories, Canada
B. J. Crawford — Georgia	D. Pringnitz — Oklahoma
E. L. Creaser — New Brunswick, Canada	R. S. Pucek — Wisconsin
W. E. Crider, Jr. — Vermont	R. D. Reetz — North Dakota
P. L. Dodge — Nova Scotia, Canada	C. F. Reyes — California
S. Donovan — Northwest Territories, Canada	T. W. Rieger — Manitoba, Canada
D. Eastman — Newfoundland and Labrador, Canada	K. A. Rudolph — Hawaii
B. Fierheller — Manitoba, Canada	M. J. Ryan — Illinois
C. Fulton — Alaska	M. H. Sansone — New York
G. M. Given, Jr. — North Carolina	T. S. Scholl — Ontario, Canada
M. Graham — Oregon	G. Scribner — Missouri
R. J. Handy — Kentucky	C. S. Selinger — Saskatchewan, Canada
D. R. Hannon — Arkansas	R. Spiker — North Carolina
E. G. Hilton — Virginia	T. Stewart — Montana
I. M. Hinkle — South Dakota	R. K. Sturm — Utah
E. Hurd — British Columbia, Canada	S. R. Townsend — Prince Edward Island, Canada
D. T. Jagger — Ohio	W. Vallance — Michigan
D. J. Jenkins — Kansas	M. J. Verhagen — Wisconsin
A. P. Jones — Texas	M. Washington — New Jersey
L. R. Kline — Pennsylvania	K. L. Watson — Mississippi
M. R. Klosterman — Iowa	R. W. Whitman, Jr. — Delaware
K. J. Kraft — Maryland	D. J. Willis — Indiana

INTERNATIONAL INTEREST REVIEW GROUP

V. Felix	C. Minu
Y.-G. Kim	T. S. G. Narayannen
S. H. Leong	Y.-W. Park
W. Lin	R. Reynaga
O. F. Manafa	P. Williamson

PROJECT TEAM ON HYDROGEN TANKS

A. P. Amato, <i>Staff Secretary</i>	E. Uptis
F. L. Brown	C. T. I. Webster
D. A. Canonico	W. Yoru
D. C. Cook	R. C. Biel, <i>Contributing Member</i>
J. Coursen	M. Duncan, <i>Contributing Member</i>
J. W. Felbaum	D. R. Frikken, <i>Contributing Member</i>
N. L. Newhouse	L. E. Hayden, Jr., <i>Contributing Member</i>
A. S. Olivares	K. T. Lau, <i>Contributing Member</i>
G. B. Rawls, Jr.	K. Nibur, <i>Contributing Member</i>
B. F. Shelley	K. Oyamada, <i>Contributing Member</i>
J. R. Sims, Jr.	C. H. Rivkin, <i>Contributing Member</i>
N. Sirosch	C. San Marchi, <i>Contributing Member</i>
J. H. Smith	B. Somerday, <i>Contributing Member</i>
S. Staniszewski	
T. Tahara	
D. W. Treadwell	

Subgroup on General Requirements (BPV I)

R. E. McLaughlin, <i>Chair</i>	D. Tompkins
T. E. Hansen, <i>Vice Chair</i>	S. V. Torkildson
F. Massi, <i>Secretary</i>	D. E. Tuttle
P. D. Edwards	M. Wadkinson
W. L. Lowry	R. V. Wielgoszinski
E. M. Ortman	D. J. Willis
J. T. Pillow	C. F. Jeerings, <i>Contributing Member</i>

Subgroup on Heat Recovery Steam Generators (BPV I)

T. E. Hansen, <i>Chair</i>	C. T. McDaris
S. V. Torkildson, <i>Secretary</i>	B. W. Moore
J. L. Arnold	Y. Oishi
J. P. Bell	E. M. Ortman
B. G. Carson	R. D. Schueler, Jr.
L. R. Douglas	D. Tompkins
J. Gertz	B. C. Turczynski
G. B. Komora	

COMMITTEE ON POWER BOILERS (BPV I)

D. L. Berger, <i>Chair</i>	F. Massi
R. E. McLaughlin, <i>Vice Chair</i>	P. A. Molvie
U. D'Urso, <i>Staff Secretary</i>	Y. Oishi
J. L. Arnold	E. M. Ortman
S. W. Cameron	J. T. Pillow
D. A. Canonico	B. W. Roberts
K. K. Coleman	R. D. Schueler, Jr.
P. D. Edwards	J. M. Tanzosh
P. Fallouey	D. E. Tuttle
J. G. Feldstein	R. V. Wielgoszinski
G. W. Galanes	D. J. Willis
T. E. Hansen	G. Ardizzioia, <i>Delegate</i>
J. F. Henry	H. Michael, <i>Delegate</i>
J. S. Hunter	D. N. French, <i>Honorary Member</i>
W. L. Lowry	T. C. McGough, <i>Honorary Member</i>
J. R. MacKay	R. L. Williams, <i>Honorary Member</i>

Subgroup on Locomotive Boilers (BPV I)

L. Moedinger, <i>Chair</i>	G. M. Ray
S. M. Butler, <i>Secretary</i>	J. E. Rimmasch
P. Boschan	R. D. Schueler, Jr.
J. Braun	R. B. Stone
R. C. Franzen, Jr.	M. W. Westland
D. W. Griner	W. L. Withuhn
S. D. Jackson	R. Yuill
M. A. Janssen	R. D. Reetz, <i>Contributing Member</i>
S. A. Lee	

Subgroup on Materials (BPV I)

G. W. Galanes, <i>Chair</i>	O. X. Li
K. K. Coleman, <i>Vice Chair</i>	J. R. MacKay
J. S. Hunter, <i>Secretary</i>	F. Masuyama
S. H. Bowes	D. W. Rahoi
D. A. Canonico	B. W. Roberts
P. Fallouey	J. M. Tanzosh
K. L. Hayes	J. Vattappilly
J. F. Henry	

Subgroup on Design (BPV I)

P. A. Molvie, <i>Chair</i>	B. W. Moore
J. Vattappilly, <i>Secretary</i>	D. A. Olson
D. I. Anderson	R. D. Schueler, Jr.
P. Dhorajia	S. V. Torkildson
J. P. Glaspie	M. Wadkinson
G. B. Komora	C. F. Jeerings, <i>Contributing Member</i>
J. C. Light	

Subgroup on Piping (BPV I)

D. Tompkins, <i>Chair</i>	G. W. Galanes
B. Mollitor, <i>Secretary</i>	T. E. Hansen
D. L. Berger	T. G. Kosmatka
J. A. Byers	W. L. Lowry
P. D. Edwards	F. Massi

Subgroup on Fabrication and Examination (BPV I)

J. T. Pillow, <i>Chair</i>	J. Hainsworth
J. L. Arnold, <i>Secretary</i>	T. E. Hansen
G. W. Galanes, <i>Secretary</i>	C. T. McDaris
D. L. Berger	R. E. McLaughlin
S. W. Cameron	R. J. Newell
K. Craver	Y. Oishi
G. T. Dunker	R. V. Wielgoszinski
P. F. Gilston	

Subgroup on Solar Boilers (BPV I)

J. S. Hunter, <i>Chair</i>	J. C. Light
S. V. Torkildson, <i>Secretary</i>	Y. Magen
G. W. Galanes	F. Massi
R. E. Hearne	M. J. Slater
D. J. Koza	J. T. Trimble, Jr.

Task Group on Modernization of BPVC Section I

D. I. Anderson, <i>Chair</i>	R. E. McLaughlin
U. D'Urso, <i>Staff Secretary</i>	P. A. Molvie
J. L. Arnold	E. M. Ortman
S. W. Cameron	J. T. Pillow
G. W. Galanes	B. W. Roberts
J. P. Glaspie	D. E. Tuttle
J. F. Henry	

Subgroup on International Material Specifications (BPV II)

A. Chaudouet, <i>Chair</i>	M. Ishikawa
O. X. Li, <i>Vice Chair</i>	W. M. Lundy
T. F. Miskell, <i>Secretary</i>	A. R. Nywening
S. W. Cameron	R. D. Schueler, Jr.
D. A. Canonico	E. Uptis
P. Fallouey	O. Oldani, <i>Delegate</i>
A. F. Garbolevsky	H. Lorenz, <i>Contributing Member</i>
D. O. Henry	

COMMITTEE ON MATERIALS (BPV II)

J. F. Henry, <i>Chair</i>	M. J. Slater
D. W. Rahoi, <i>Vice Chair</i>	R. C. Sutherlin
N. Lobo, <i>Staff Secretary</i>	R. W. Swindeman
F. Abe	J. M. Tanzosh
A. Appleton	D. Tyler
J. Cameron	D. Kwon, <i>Delegate</i>
D. A. Canonico	O. Oldani, <i>Delegate</i>
A. Chaudouet	W. R. Apblett, Jr., <i>Contributing Member</i>
P. Fallouey	H. D. Bushfield, <i>Contributing Member</i>
J. R. Foulds	M. L. Nayyar, <i>Contributing Member</i>
D. W. Gandy	E. G. Nisbett, <i>Contributing Member</i>
M. H. Gilkey	E. Uptis, <i>Contributing Member</i>
M. Gold	T. M. Cullen, <i>Honorary Member</i>
J. F. Grubb	W. D. Doty, <i>Honorary Member</i>
J. A. Hall	W. D. Edsall, <i>Honorary Member</i>
M. Katcher	G. C. Hsu, <i>Honorary Member</i>
F. Masuyama	R. A. Moen, <i>Honorary Member</i>
R. K. Nanstad	C. E. Spaeder, Jr., <i>Honorary Member</i>
B. W. Roberts	A. W. Zeuthen, <i>Honorary Member</i>
E. Shapiro	
M. H. Skillingberg	

Subgroup on Nonferrous Alloys (BPV II)

R. C. Sutherlin, <i>Chair</i>	L. Paul
H. Anada	D. W. Rahoi
J. Calland	W. Ren
D. Denis	E. Shapiro
M. H. Gilkey	M. H. Skillingberg
J. F. Grubb	D. Tyler
A. Heino	R. Zawierucha
M. Katcher	W. R. Apblett, Jr., <i>Contributing Member</i>
J. Kissell	H. D. Bushfield, <i>Contributing Member</i>
T. M. Malota	
J. A. McMaster	

Subgroup on Physical Properties (BPV II)

J. F. Grubb, <i>Chair</i>	P. Fallouey
H. D. Bushfield	E. Shapiro
D. Denis	

Subgroup on Strength, Ferrous Alloys (BPV II)

J. M. Tanzosh, <i>Chair</i>	K. Kimura
M. J. Slater, <i>Secretary</i>	F. Masuyama
F. Abe	D. W. Rahoi
H. Anada	B. W. Roberts
D. A. Canonico	J. P. Shingledecker
A. Di Rienzo	R. W. Swindeman
P. Fallouey	T. P. Vassallo, Jr.
J. R. Foulds	W. R. Apblett, Jr., <i>Contributing Member</i>
M. Gold	H. Murakami, <i>Contributing Member</i>
J. A. Hall	
J. F. Henry	

Subgroup on External Pressure (BPV II)

R. W. Mikitka, <i>Chair</i>	M. H. Jawad
D. L. Kurle, <i>Vice Chair</i>	C. R. Thomas
J. A. A. Morrow, <i>Secretary</i>	M. Wadkinson
L. F. Campbell	M. Katcher, <i>Contributing Member</i>
D. S. Griffin	C. H. Sturgeon, <i>Contributing Member</i>
J. F. Grubb	
J. R. Harris III	

Subgroup on Ferrous Specifications (BPV II)

A. Appleton, <i>Chair</i>	W. C. Mack
S. Hochreiter, <i>Secretary</i>	J. K. Mahaney
B. M. Dingman	A. S. Melilli
M. J. Dosdourian	E. G. Nisbett
P. Fallouey	K. E. Orie
J. D. Fritz	J. Shick
T. Graham	E. Uptis
J. M. Grocki	J. D. Wilson
J. F. Grubb	P. Wittenbach
K. M. Hottle	R. Zawierucha
D. S. Janikowski	R. M. Davison, <i>Contributing Member</i>
L. J. Lavezzi	

Subgroup on Strength of Weldments (BPV II & BPV IX)

W. F. Newell, Jr., <i>Chair</i>	J. F. Henry
S. H. Bowes	D. W. Rahoi
K. K. Coleman	B. W. Roberts
P. D. Flenner	J. P. Shingledecker
J. R. Foulds	W. J. Sperko
D. W. Gandy	J. P. Swezy, Jr.
M. Gold	J. M. Tanzosh
K. L. Hayes	

Working Group on Materials Database (BPV II)

R. W. Swindeman, <i>Chair</i>	B. W. Roberts
N. Lobo, <i>Staff Secretary</i>	R. C. Sutherlin
F. Abe	D. Andrei, <i>Contributing Member</i>
J. R. Foulds	W. Hoffelner, <i>Contributing Member</i>
M. Gold	T. Lazar, <i>Contributing Member</i>
J. F. Henry	D. T. Peters, <i>Contributing Member</i>
M. Katcher	W. Ren, <i>Contributing Member</i>

China International Working Group (BPV II)

T. Xu, <i>Secretary</i>	G. Yang
W. Fang	R. Ye
S. Huo	L. Yin
S. Li	H. Zhang
M. Lu	X.-H. Zhang
B. Shou	Yingkai Zhang
S. Tan	Yong Zhang
C. Wang	Q. Zhao
X. Wang	S. Zhao
Z. Wu	R. Zhou
F. Yang	J. Zou

Subgroup on Component Design (BPV III)

R. S. Hill III, <i>Chair</i>	R. J. Masterson
T. M. Adams, <i>Vice Chair</i>	D. E. Matthews
S. Pellet, <i>Secretary</i>	W. N. McLean
G. A. Antaki	J. C. Minichiello
S. Asada	T. Nagata
C. W. Bruny	A. N. Nguyen
J. R. Cole	E. L. Pleins
A. A. Dermenjian	I. Saito
R. P. Deubler	G. C. Slagis
P. Hirschberg	J. D. Stevenson
R. I. Jetter	J. P. Tucker
R. B. Keating	K. R. Wichman
H. Kobayashi	C. Wilson
R. A. Ladefian	J. Yang
K. A. Manoly	D. F. Landers, <i>Contributing Member</i>

COMMITTEE ON CONSTRUCTION OF NUCLEAR FACILITY COMPONENTS (III)

R. W. Barnes, <i>Chair</i>	M. N. Mitchell
J. R. Cole, <i>Vice Chair</i>	M. Morishita
A. Byk, <i>Staff Secretary</i>	D. K. Morton
T. Adams	T. Nagata
A. Appleton	R. F. Reedy, Sr.
W. H. Borter	I. Saito
T. D. Burchell	C. T. Smith
R. P. Deubler	W. K. Sowder, Jr.
A. C. Eberhardt	W. J. Sperko
B. A. Erler	J. D. Stevenson
G. M. Foster	K. R. Wichman
R. S. Hill III	C. S. Withers
W. Hoffelner	Y. H. Choi, <i>Delegate</i>
R. M. Jesse	T. Ius, <i>Delegate</i>
R. I. Jetter	H.-T. Wang, <i>Delegate</i>
R. B. Keating	C. C. Kim, <i>Contributing Member</i>
G. H. Koo	E. B. Branch, <i>Honorary Member</i>
V. Kostarev	G. D. Cooper, <i>Honorary Member</i>
W. C. LaRochelle	W. D. Doty, <i>Honorary Member</i>
K. A. Manoly	D. F. Landers, <i>Honorary Member</i>
D. E. Matthews	R. A. Moen, <i>Honorary Member</i>
W. N. McLean	C. J. Pieper, <i>Honorary Member</i>
J. C. Minichiello	

Working Group on Supports (SG-D) (BPV III)

R. J. Masterson, <i>Chair</i>	A. N. Nguyen
U. S. Bandyopadhyay, <i>Secretary</i>	I. Saito
K. Avrithi	J. R. Stinson
T. H. Baker	T. G. Terryah
F. J. Birch	G. Z. Tokarski
R. P. Deubler	C.-I. Wu

Working Group on Core Support Structures (SG-D) (BPV III)

J. Yang, <i>Chair</i>	H. S. Mehta
J. F. Kielb, <i>Secretary</i>	M. D. Snyder
F. G. Al-Chammas	A. Tsirigotis
D. Keck	J. T. Land, <i>Contributing Member</i>

Working Group on Design Methodology (SG-D) (BPV III)

R. B. Keating, <i>Chair</i>	D. H. Roarty
S. D. Snow, <i>Secretary</i>	E. A. Rodriguez
K. Avrithi	P. K. Shah
R. D. Blevins	J. D. Stevenson
M. R. Breach	A. Tsirigotis
D. L. Caldwell	S. Wang
H. T. Harrison III	T. M. Wiger
P. Hirschberg	K. Wright
M. Kassir	J. Yang
J. Kim	M. K. Au-Yang, <i>Contributing Member</i>
H. Kobayashi	D. F. Landers, <i>Contributing Member</i>
J. F. McCabe	W. S. Lapay, <i>Contributing Member</i>
A. N. Nguyen	
W. D. Reinhardt	

Subgroup on Containment Systems for Spent Fuel and High-Level Waste Transport Packagings (BPV III)

G. M. Foster, <i>Chair</i>	D. W. Lewis
G. J. Solovey, <i>Vice Chair</i>	P. E. McConnell
D. K. Morton, <i>Secretary</i>	A. B. Meichler
G. Abramczyk	R. E. Nickell
D. J. Ammerman	E. L. Pleins
G. Bjorkman	T. Saegusa
W. H. Borter	N. M. Simpson
G. R. Cannell	R. H. Smith
R. S. Hill III	J. D. Stevenson
S. Horowitz	C. J. Temus

Working Group on Design of Division 3 Containments (SG-D) (BPV III)

E. L. Pleins, <i>Chair</i>	D. K. Morton
D. J. Ammerman	C. J. Temus
G. Bjorkman	I. D. McInnes, <i>Contributing Member</i>
S. Horowitz	R. E. Nickell, <i>Contributing Member</i>
D. W. Lewis	H. P. Shrivastava, <i>Contributing Member</i>
J. C. Minichiello	

Working Group on Piping (SG-D) (BPV III)

G. A. Antaki, <i>Chair</i>	J. F. McCabe
G. Z. Tokarski, <i>Secretary</i>	J. C. Minichiello
T. M. Adams	I.-K. Nam
C. Basavaraju	E. R. Nelson
J. Catalano	A. N. Nguyen
F. Claeys	M. S. Sills
J. R. Cole	G. C. Slagis
R. G. Gilada	N. C. Sutherland
M. A. Gray	E. A. Wais
R. W. Haupt	C.-I. Wu
P. Hirschberg	D. F. Landers, <i>Contributing Member</i>
M. Kassab	J. J. Martinez, <i>Contributing Member</i>
J. Kawahata	R. D. Patel, <i>Contributing Member</i>
R. B. Keating	N. J. Shah, <i>Contributing Member</i>
V. Kostarev	E. C. Rodabaugh, <i>Honorary Member</i>
Y. Liu	

Working Group on Probabilistic Methods in Design (SG-D) (BPV III)

R. S. Hill III, <i>Chair</i>	A. McNeill III
N. A. Palm, <i>Secretary</i>	M. Morishita
T. Asayama	P. J. O'Regan
K. Avrithi	I. Saito
B. M. Ayyub	A. Tsirigotis
M. R. Graybeal	R. M. Wilson
D. O. Henry	D. Hofer, <i>Contributing Member</i>
S. D. Kulat	

Working Group on Pumps (SG-D) (BPV III)

R. A. Ladefian, <i>Chair</i>	M. Higuchi
P. W. Behnke	J. W. Leavitt
R. E. Cornman, Jr.	S. Mauvais
M. D. Eftychiou	R. A. Patrick
A. Fraser	J. Sulley
M. A. Gaydon	R. Udo
R. Ghanbari	A. G. Washburn

Working Group on Valves (SG-D) (BPV III)

J. P. Tucker, <i>Chair</i>	C. A. Mizer
J. O'Callaghan, <i>Secretary</i>	K. E. Reid II
G. A. Jolly	S. N. Shields
J. Klein	H. R. Sonderegger
W. N. McLean	P. Vock
T. A. McMahon	

Working Group on Vessels (SG-D) (BPV III)

D. E. Matthews, <i>Chair</i>	D. Keck
R. M. Wilson, <i>Secretary</i>	O.-S. Kim
C. Basavaraju	K. Matsunaga
C. W. Bruny	P. K. Shah
J. V. Gregg, Jr.	C. Turlyo
W. J. Heilker	D. Vlaicu
W. T. Jessup, Jr.	W. F. Weitze
A. Kalnins	T. Yamazaki
R. B. Keating	

Special Working Group on Environmental Effects (SG-D) (BPV III)

W. Culp, <i>Chair</i>	J. E. Nestell
B. D. Frew, <i>Secretary</i>	W. Z. Novak
K. Avrithi	M. S. Shelton
W. J. Heilker	Y. H. Choi, <i>Delegate</i>
R. S. Hill III	

Subgroup on General Requirements (BPV III & 3C)

R. P. McIntyre, <i>Chair</i>	W. C. LaRochelle
L. M. Plante, <i>Secretary</i>	M. R. Minick
V. Apostolescu	E. C. Renaud
A. Appleton	D. J. Roszman
J. R. Berry	C. T. Smith
J. V. Gardiner	W. K. Sowder, Jr.
G. Gratti	G. E. Szabatura
J. W. Highlands	T. G. Terryah
G. L. Hollinger	D. M. Vickery
G. V. Imbro	C. S. Withers
K. A. Kavanagh	H. Michael, <i>Delegate</i>

Working Group on Duties and Responsibilities (SG-GR) (BPV III)

J. V. Gardiner, <i>Chair</i>	K. A. Kavanagh
G. L. Hollinger, <i>Secretary</i>	L. M. Plante
J. R. Berry	D. J. Roszman
Y. Diaz-Castillo	S. Scardigno
E. L. Farrow	T. G. Terryah
G. Gratti	

Working Group on Quality Assurance, Certification, and Stamping (SG-GR) (BPV III)

C. T. Smith, <i>Chair</i>	M. R. Minick
C. S. Withers, <i>Secretary</i>	R. B. Patel
V. Apostolescu	E. C. Renaud
A. Appleton	J. Rogers
S. Bell	W. K. Sowder, Jr.
B. K. Bobo	J. F. Strunk
S. M. Goodwin	M. F. Sullivan
J. W. Highlands	G. E. Szabatura
R. P. McIntyre	D. M. Vickery

Special Working Group on Regulatory Interface (BPV III)

G. V. Imbro, <i>Chair</i>	J. A. Schulz
S. Bell, <i>Secretary</i>	R. R. Stevenson
A. Cardillo	D. Terao
A. A. Dermenjian	M. L. Wilson
K. Matsunaga	R. A. Yonekawa
D. E. Matthews	

Subgroup on Materials, Fabrication, and Examination (BPV III)

R. M. Jessee, <i>Chair</i>	M. Lau
S. Hunter, <i>Secretary</i>	H. Murakami
W. H. Borter	J. Ossmann
G. R. Cannell	C. Pearce
R. H. Davis	N. M. Simpson
G. M. Foster	W. J. Sperko
B. D. Frew	J. R. Stinson
G. B. Georgiev	J. F. Strunk
S. E. Gingrich	K. B. Stuckey
C. C. Kim	H. Michael, <i>Delegate</i>

Subgroup on Pressure Relief (BPV III)

J. F. Ball, *Chair*
A. L. Szeplin

D. G. Thibault

**Executive Committee on Strategy and Project Management
(BPV III, Divisions 1 and 2)**

J. R. Cole, *Chair*
C. A. Sanna, *Staff Secretary*
T. Adams
R. W. Barnes
B. K. Bobo
N. Broom
B. A. Erler
C. M. Faigy
R. S. Hill III
E. V. Imbro
R. M. Jessee
R. B. Keating

G. H. Koo
K. A. Manoly
D. K. Morton
J. Ramirez
R. F. Reedy, Sr.
C. T. Smith
W. K. Sowder, Jr.
Y. Urabe
C. S. Withers
C. Yan
M. F. Sullivan, *Contributing Member*

China International Working Group (BPV III)

J. Yan, *Chair*
W. Tang, *Vice Chair*
C. A. Sanna, *Staff Secretary*
Y. He, *Secretary*
H. Ge
Z. Han
J. Jian
Y. Jing
F. Kai
D. Kang
Y. Lee
X. Li
B. Liang
H. Lin
S. Lin
J. Liu
S. Liu
W. Liu
K. Mao

G. Sun
G. Tang
Y. Tu
Y. Wang
H. Wu
X. Wu
Z. Wu
S. Xue
Z. Yan
C. Ye
Z. Yin
S. Zaozhan
G. Zhang
K. Zhang
W. Zhang
G. Zhao
W. Zhao
Y. Zhong
Z. Zhong

Korea International Working Group (BPV III)

G. H. Koo, *Chair*
H. S. Byun
J.-Y. Hong
N.-S. Huh
S. S. Hwang
C. Jang
I. I. Jeong
H. J. Kim
J. Kim
O.-S. Kim
Y.-B. Kim
D. Kwon

B. Lee
D. Lee
S. Lee
D. J. Lim
I.-K. Nam
B. Noh
C.-K. Oh
C. Park
J.-S. Park
S. Song
O. Yoo

**Special Working Group for New Advanced Light Water Reactor Plant
Construction Issues (BPV III)**

E. L. Pleins, *Chair*
M. C. Scott, *Secretary*
A. Cardillo
B. Gilligan
J. Honcharik
G. V. Imbro
Y. Katsura
O.-S. Kim
M. Kris

J. C. Minichiello
D. W. Sandusky
C. A. Sanna
R. R. Stevenson
E. R. Willis
M. L. Wilson
J. Yan
J. A. Schulz, *Contributing Member*

Subgroup on Editing and Review (BPV III)

D. K. Morton, *Chair*
R. L. Bratton
R. P. Deubler
A. C. Eberhardt
R. I. Jetter
J. C. Minichiello

L. M. Plante
R. F. Reedy, Sr.
W. K. Sowder, Jr.
J. D. Stevenson
C. Wilson

Subgroup on Management Resources (BPV III)

R. M. Jessee, *Chair*
J. F. Bernardo
L. C. Cadwallader
J. B. Carr
M. Cusick
H. S. Farrow
S. Fincher
J. Fink
L. Hartless
M. A. Hayes, Jr.
M. Hokazono
B. N. Juarez
Y. S. Kim

J. M. Lyons
B. McGlone
A. A. Mostala
M. Osterfoss
J. D. Pasek
C. Pearce
J. Rogers
B. S. Sandhu
V. Suri
Z. Taylor
J. Webb, Jr.
R. A. West
R. Z. Ziegler

Working Group on International Meetings (BPV III)

R. S. Hill III, *Chair*
A. Byk, *Staff Secretary*
T. D. Burchell
J. R. Cole
R. L. Crane

G. M. Foster
M. N. Mitchell
R. F. Reedy, Sr.
C. A. Sanna
C. T. Smith

Subgroup on Polyethylene Pipe (BPV III)

T. M. Adams, *Chair*
D. Burwell, *Secretary*
W. I. Adams
C. Basavaraju
S. J. Boros
J. M. Craig
E. L. Farrow
E. M. Focht
M. Golliet
A. N. Haddad
P. Krishnaswamy
M. Lashley
E. Lever

K. Lively
M. Martin
E. W. McElroy
D. P. Munson
T. M. Musto
J. E. O'Sullivan
F. J. Schaaf, Jr.
H. E. Svetlik
M. Troughton
D. M. Vickery
Z. J. Zhou
L. J. Petroff, *Alternate*
S. Sandstrum, *Alternate*

Working Group on Research and Development

A. N. Haddad, <i>Chair</i>	K. Lively
W. I. Adams	K. A. Manoly
A. Amato	L. Mizell
S. J. Boros	D. P. Munson
J. M. Craig	T. M. Musto
E. M. Focht	F. J. Schaaf, Jr.
R. M. Jessee	M. Troughton
D. Keller	Z. J. Zhou
M. Lamborn	L. J. Petroff, <i>Alternate</i>
S. Lefler	S. Sandstrum, <i>Alternate</i>
E. Lever	

Working Group on Nondestructive Examination and Fusion of HDPE (BPV III)

M. Lashley, <i>Chair</i>	R. M. Jessee
W. H. Borter	M. D. Moles
J. M. Craig	F. J. Schaaf, Jr.
N. Y. Faransso	J. C. Spanner, Jr.
N. A. Finney	Z. J. Zhou
J. F. Halley	D. K. Zimmerman

Working Group on High Temperature Gas-Cooled Reactors (BPV III)

J. E. Nestell, <i>Chair</i>	T. R. Lupold
N. Broom	S. N. Malik
T. D. Burchell	D. L. Marriott
R. S. Hill III	D. K. Morton
W. Hoffelner	T.-L. Sham
E. V. Imbro	Y. Tachibana
R. I. Jetter	T. Yuhara
Y. W. Kim	

Subgroup on Graphite Core Components (BPV III)

T. D. Burchell, <i>Chair</i>	S. T. Gonczy
M. N. Mitchell, <i>Vice Chair</i>	M. P. Hindley
C. A. Sanna, <i>Staff Secretary</i>	Y. Katoh
R. L. Bratton, <i>Secretary</i>	N. N. Nemeth
T. Albers	T. Oku
A. Appleton	J. Ossmann
S.-H. Chi	M. Roemmler
A. Covac	N. Salstrom
M. W. Davies	T. Shibata
S. W. Doms	M. Srinivasan
S. F. Duffy	A. G. Steer
B. D. Frew	S. Wendel
O. Gelineau	S. Yu

Subgroup on Industry Experience for New Plants (BPV III & BPV XI)

G. M. Foster, <i>Chair</i>	O.-S. Kim
J. T. Lindberg, <i>Chair</i>	K. Matsunaga
H. L. Gustin, <i>Secretary</i>	D. E. Matthews
V. L. Armentrout	R. E. McLaughlin
T. L. Chan	J. Ossmann
D. R. Graham	E. L. Pleins
P. J. Hennessey	D. W. Sandusky
D. O. Henry	D. M. Swann
J. Honcharik	T. Tsuruta
E. V. Imbro	E. R. Willis
C. G. Kim	S. M. Yee

Subgroup on Fusion Energy Devices (BPV III)

W. K. Sowder, Jr., <i>Chair</i>	S. Lee
D. Andrei, <i>Staff Secretary</i>	G. Li
D. J. Roszman, <i>Secretary</i>	X. Li
R. W. Barnes	P. Mokaria
M. Higuchi	S. J. Salvador
G. Holtmeier	M. Trosen
K. A. Kavanagh	I. J. Zatz
H. J. Kim	

Subgroup on High-Temperature Reactors (BPV III)

M. Morishita, <i>Chair</i>	W. Hoffelner
R. I. Jetter, <i>Vice Chair</i>	G. H. Koo
T.-L. Sham, <i>Secretary</i>	D. K. Morton
N. Broom	J. E. Nestell
T. D. Burchell	N. N. Ray

Working Group on High Temperature Liquid-Cooled Reactors (BPV III)

T.-L. Sham, <i>Chair</i>	R. I. Jetter
T. Asayama, <i>Secretary</i>	G. H. Koo
R. W. Barnes	M. Li
P. Carter	S. Majumdar
C. M. Faigy	M. Morishita
W. Hoffelner	J. E. Nestell
A. B. Hull	D. K. Williams

Subgroup on Elevated Temperature Design (BPV III)

R. I. Jetter, <i>Chair</i>	A. B. Hull
T.-L. Sham, <i>Secretary</i>	M. H. Jawad
J. J. Abou-Hanna	G. H. Koo
T. Asayama	W. J. Koves
C. Becht IV	M. Li
F. W. Brust	S. Majumdar
P. Carter	D. L. Marriott
J. F. Cervenka	T. E. McGreevy
D. S. Griffin	J. E. Nestell
B. F. Hantz	W. J. O'Donnell
W. Hoffelner	R. W. Swindeman

Working Group on High Temperature Flaw Evaluation (BPV III)

F. W. Brust, <i>Chair</i>	D. L. Rudland
N. Broom	P. J. Rush
P. Carter	D.-J. Shim
W. Hoffelner	S. X. Xu
S. N. Malik	

Working Group on Allowable Stress Criteria (BPV III)

R. W. Swindeman, <i>Chair</i>	J. E. Nestell
M. Li, <i>Secretary</i>	W. Ren
J. R. Foulds	B. W. Roberts
K. Kimura	T.-I. Sham
S. N. Malik	

Working Group on Analysis Methods (BPV III)

P. Carter, <i>Chair</i>	S. Krishnamurthy
M. R. Beach	T.-I. Sham
R. I. Jetter	D. K. Williams

Working Group on Creep-Fatigue and Negligible Creep (BPV III)

T. Asayama, <i>Chair</i>	G. H. Koo
M. Li, <i>Secretary</i>	S. N. Malik
F. W. Brust	T.-I. Sham
R. I. Jetter	

Subgroup on Fatigue Strength (BPV III)

W. J. O'Donnell, <i>Chair</i>	G. Kharshafdjian
S. A. Adams	S. Majumdar
G. S. Chakrabarti	S. N. Malik
T. M. Damiani	R. Nayal
P. R. Donavin	D. H. Roarty
S. R. Gosselin	M. S. Shelton
R. J. Gurdal	G. Taxacher
C. F. Heberling II	A. Tsirigotis
C. E. Hinnant	K. Wright
D. P. Jones	H. H. Ziada

Working Group on Environmental Fatigue Evaluation Methods (BPV III)

T. M. Adams	H. S. Mehta
S. Asada	J.-S. Park
K. Avrithi	V. S. Ready
J. R. Cole	D. H. Roarty
C. M. Faigy	I. Saito
T. D. Gilman	D. Vlaicu
S. R. Gosselin	W. F. Weitze
M. A. Gray	K. Wright
Y. He	

Subcommittee on Design (BPV III)

R. P. Deubler, <i>Chair</i>	R. A. Ladefian
G. L. Hollinger, <i>Secretary</i>	K. A. Manoly
T. M. Adams	R. J. Masterson
G. A. Antaki	D. E. Matthews
R. L. Bratton	M. N. Mitchell
R. S. Hill III	W. J. O'Donnell
P. Hirschberg	E. L. Pleins
M. H. Jawad	J. P. Tucker
R. I. Jetter	J. Yang
R. B. Keating	

Special Working Group on HDPE Design of Components (BPV III)

T. M. Adams, <i>Chair</i>	E. W. McElroy
T. M. Musto, <i>Secretary</i>	J. C. Minichiello
W. I. Adams	D. P. Munson
T. A. Bacon	J. Ossmann
C. Basavaraju	L. J. Petroff
D. Burwell	H. E. Svetlik
P. Krishnaswamy	K. Lively
M. Martin	L. Mizell

Special Working Group on Computational Modeling for Explicit Dynamics (BPV III)

G. Bjorkman, <i>Chair</i>	P. Y.-K. Shih
D. J. Ammerman, <i>Secretary</i>	S. D. Snow
G. Broz	C.-F. Tso
J. Jordan	M. C. Yaksh
D. Molitoris	U. Zencker
J. Piottter	

Subgroup on Elevated Temperature Construction (BPV III)

M. H. Jawad, <i>Chair</i>	R. I. Jetter
B. Mollitor, <i>Secretary</i>	S. Krishnamurthy
D. I. Anderson	D. L. Marriott
R. G. Brown	M. N. Mitchell
J. P. Gaspie	D. K. Morton
B. F. Hantz	C. Nadarajah

Subcommittee on General Requirements (BPV III)

W. C. LaRochelle, <i>Chair</i>	L. M. Plante
A. Appleton, <i>Secretary</i>	C. T. Smith
J. V. Gardiner	D. M. Vickery
R. P. McIntyre	

JOINT ACI-ASME COMMITTEE ON CONCRETE COMPONENTS FOR NUCLEAR SERVICE (BPV 3C)

A. C. Eberhardt, <i>Chair</i>	N. Orbovic
C. T. Smith, <i>Vice Chair</i>	B. B. Scott
A. Byk, <i>Staff Secretary</i>	J. D. Stevenson
N. Alchaar	J. F. Strunk
J. F. Artuso	T. Tonyan
C. J. Bang	T. J. Ahl, <i>Contributing Member</i>
F. Farzam	T. D. Al-Shawaf, <i>Contributing Member</i>
P. S. Ghosal	B. A. Erler, <i>Contributing Member</i>
M. F. Hessheimer	J. Gutierrez, <i>Contributing Member</i>
B. D. Hovis	T. E. Johnson, <i>Contributing Member</i>
T. C. Inman	T. Muraki, <i>Contributing Member</i>
O. Jovall	M. R. Senecal, <i>Contributing Member</i>
N.-H. Lee	M. K. Thumm, <i>Contributing Member</i>
J. McLean	
J. Munshi	

Working Group on Design (BPV 3C)

J. Munshi, <i>Chair</i>	T. C. Inman
N. Alchaar	O. Jovall
S. Bae	N.-H. Lee
L. J. Colarusso	J. D. Stevenson
J. Colinares	T. E. Johnson, <i>Contributing Member</i>
A. C. Eberhardt	B. R. Laskewitz, <i>Contributing Member</i>
F. Farzam	M. K. Thumm, <i>Contributing Member</i>
P. S. Ghosal	
M. F. Hessheimer	
B. D. Hovis	

Working Group on Materials, Fabrication, and Examination (BPV 3C)

J. F. Artuso, <i>Chair</i>	B. B. Scott
P. S. Ghosal, <i>Vice Chair</i>	C. T. Smith
M. Allam	J. F. Strunk
A. C. Eberhardt	T. Tonyan
J. Gutierrez	

Working Group on Modernization (BPV 3C)

O. Jovall, <i>Chair</i>	J.-B. Damage
J. McLean, <i>Secretary</i>	N. Orbovic
A. Adediran	C. T. Smith
N. Alchaar	M. A. Ugalde
J. F. Artuso	S. Wang
J. J. Braun	U. Ricklefs, <i>Contributing Member</i>
J. Colinares	

COMMITTEE ON HEATING BOILERS (BPV IV)

T. L. Bedeaux, <i>Chair</i>	P. A. Molvie
J. A. Hall, <i>Vice Chair</i>	B. W. Moore
G. Moino, <i>Staff Secretary</i>	R. E. Olson
J. Calland	T. M. Parks
J. P. Chicoine	M. Wadkinson
C. M. Dove	R. V. Wielgoszinski
B. G. French	H. Michael, <i>Delegate</i>
A. Heino	D. Picart, <i>Delegate</i>
B. J. Iske	J. L. Kleiss, <i>Alternate</i>
D. J. Jenkins	M. T. Roby, <i>Alternate</i>
M. R. Klosterman	W. L. Haag, Jr., <i>Honorary Member</i>
K. M. McTague	

COMMITTEE ON NONDESTRUCTIVE EXAMINATION (BPV V)

J. E. Batey, <i>Chair</i>	R. W. Kruzic
F. B. Kovacs, <i>Vice Chair</i>	J. R. McGimpsey
J. S. Brzuszkiewicz, <i>Staff Secretary</i>	M. D. Moles
S. J. Akrin	A. B. Nagel
C. A. Anderson	T. L. Plasek
A. S. Birks	F. J. Sattler
P. L. Brown	G. M. Gatti, <i>Delegate</i>
M. A. Burns	X. Guiping, <i>Delegate</i>
B. Caccamise	B. D. Laite, <i>Alternate</i>
N. Y. Faransso	H. C. Graber, <i>Honorary Member</i>
N. A. Finney	O. F. Hedden, <i>Honorary Member</i>
A. F. Garbolevsky	J. R. MacKay, <i>Honorary Member</i>
G. W. Hembree	T. G. McCarty, <i>Honorary Member</i>
J. W. Houf	

Subgroup on Care and Operation of Heating Boilers (BPV IV)

M. Wadkinson, <i>Chair</i>	M. R. Klosterman
T. L. Bedeaux	P. A. Molvie
J. Calland	B. W. Moore
J. A. Hall	T. M. Parks

Subgroup on General Requirements/Personnel Qualifications and Inquiries (BPV V)

F. B. Kovacs, <i>Chair</i>	N. A. Finney
S. J. Akrin	G. W. Hembree
C. A. Anderson	J. W. Houf
J. E. Batey	J. P. Swezy, Jr., <i>Contributing Member</i>
A. S. Birks	
N. Y. Faransso	

Subgroup on Cast Iron Boilers (BPV IV)

K. M. McTague, <i>Chair</i>	B. G. French
T. L. Bedeaux, <i>Vice Chair</i>	J. A. Hall
J. P. Chicoine	J. L. Kleiss
C. M. Dove	M. R. Klosterman
J. M. Downs	M. T. Roby, <i>Alternate</i>

Subgroup on Surface Examination Methods (BPV V)

S. J. Akrin, <i>Chair</i>	S. Johnson
A. S. Birks	R. W. Kruzic
P. L. Brown	B. D. Laite
B. Caccamise	L. E. Mullins
N. Y. Faransso	A. B. Nagel
N. Farenbaugh	F. J. Sattler
N. A. Finney	G. M. Gatti, <i>Delegate</i>
G. W. Hembree	

Subgroup on Materials (BPV IV)

J. A. Hall, <i>Chair</i>	B. J. Iske
M. Wadkinson, <i>Vice Chair</i>	J. L. Kleiss
J. Calland	E. Rightmier
J. M. Downs	

Subgroup on Volumetric Methods (BPV V)

G. W. Hembree, <i>Chair</i>	S. Johnson
S. J. Akrin	F. B. Kovacs
J. E. Batey	R. W. Kruzic
P. L. Brown	J. R. McGimpsey
B. Caccamise	M. D. Moles
N. Y. Faransso	L. E. Mullins
N. A. Finney	A. B. Nagel
A. F. Garbolevsky	T. L. Plasek
J. F. Halley	F. J. Sattler
R. W. Hardy	G. M. Gatti, <i>Delegate</i>

Subgroup on Water Heaters (BPV IV)

J. Calland, <i>Chair</i>	K. M. McTague
J. P. Chicoine	R. E. Olson
B. G. French	T. E. Trant
B. J. Iske	M. T. Roby, <i>Alternate</i>

Working Group on Acoustic Emissions (SG-VM) (BPV V)

N. Y. Faransso, <i>Chair</i>	S. R. Doctor
J. E. Batey, <i>Vice Chair</i>	R. K. Miller

Working Group on Radiography (SG-VM) (BPV V)

F. B. Kovacs, <i>Chair</i>	S. Johnson
S. J. Akrin	R. W. Kruzic
J. E. Batey	B. D. Laite
P. L. Brown	S. Mango
B. Caccamise	J. R. McGimpsey
N. Y. Faransso	R. J. Mills
A. F. Garbolevsky	A. B. Nagel
R. W. Hardy	T. L. Plasek
G. W. Hembree	

Subgroup on Welded Boilers (BPV IV)

J. Calland, <i>Chair</i>	P. A. Molvie
T. L. Bedeaux	R. E. Olson
B. G. French	M. Wadkinson
J. L. Kleiss	R. V. Wielgoszinski
M. R. Klosterman	J.-M. Andre, <i>Contributing Member</i>

Working Group on Ultrasonics (SG-VM) (BPV V)

N. A. Finney, <i>Chair</i>	R. W. Kruzic
J. F. Halley, <i>Vice Chair</i>	B. D. Laite
B. Caccamise	M. D. Moles
K. J. Chizen	L. E. Mullins
N. Y. Faransso	A. B. Nagel
O. F. Hedden	F. J. Sattler
S. Johnson	

Working Group on Design-By-Analysis (BPV III)

B. F. Hantz, <i>Chair</i>	A. Mann
T. W. Norton, <i>Secretary</i>	G. A. Miller
R. G. Brown	C. Nadarajah
R. D. Dixon	M. D. Rana
C. E. Hinnant	T. G. Seipp
M. H. Jawad	S. Terada
S. Krishnamurthy	

Working Group on Guided Wave Ultrasonic Testing (SG-VM) (BPV V)

N. Y. Faransso, <i>Chair</i>	G. M. Light
J. E. Batey, <i>Vice Chair</i>	M. D. Moles
D. Alleyne	P. Mudge
J. F. Halley	M. J. Quarry
S. Johnson	J. Vanvelsor

Subgroup on Fabrication and Inspection (BPV VIII)

C. D. Rodery, <i>Chair</i>	P. L. Sturgill
J. P. Swezy, Jr., <i>Vice Chair</i>	T. Tahara
B. R. Morelock, <i>Secretary</i>	E. A. Whittle
J. L. Arnold	K. Oyamada, <i>Delegate</i>
L. F. Campbell	R. Uebel, <i>Delegate</i>
H. E. Gordon	W. J. Bees, <i>Corresponding Member</i>
D. I. Morris	E. Uptis, <i>Corresponding Member</i>
M. J. Pischke	W. S. Jacobs, <i>Contributing Member</i>
M. J. Rice	J. Lee, <i>Contributing Member</i>
B. F. Shelley	

COMMITTEE ON PRESSURE VESSELS (VIII)

U. R. Miller, <i>Chair</i>	M. J. Pischke
R. J. Basile, <i>Vice Chair</i>	M. D. Rana
S. J. Rossi, <i>Staff Secretary</i>	G. B. Rawls, Jr.
T. Schellens, <i>Staff Secretary</i>	F. L. Richter
V. Bogosian	S. C. Roberts
J. Cameron	C. D. Rodery
A. Chaudouet	A. Selz
D. B. DeMichael	J. R. Sims, Jr.
J. P. Glaspie	E. Soltow
M. Gold	D. A. Swanson
J. F. Grubb	J. P. Swezy, Jr.
L. E. Hayden, Jr.	S. Terada
G. G. Karcher	E. Uptis
K. T. Lau	P. A. McGowan, <i>Delegate</i>
R. Mahadeen	H. Michael, <i>Delegate</i>
R. W. Mikitka	K. Oyamada, <i>Delegate</i>
K. Mokhtarian	M. E. Papponetti, <i>Delegate</i>
C. C. Neely	D. Rui, <i>Delegate</i>
T. W. Norton	T. Tahara, <i>Delegate</i>
T. P. Pastor	W. S. Jacobs, <i>Contributing Member</i>
D. T. Peters	

Subgroup on General Requirements (BPV VIII)

S. C. Roberts, <i>Chair</i>	C. C. Neely
D. B. DeMichael, <i>Vice Chair</i>	A. S. Olivares
F. L. Richter, <i>Secretary</i>	J. C. Sowinski
R. J. Basile	P. Speranza
V. Bogosian	D. B. Stewart
D. T. Davis	D. A. Swanson
J. P. Glaspie	R. Uebel
L. E. Hayden, Jr.	A. H. Gibbs, <i>Delegate</i>
K. T. Lau	K. Oyamada, <i>Delegate</i>
M. D. Lower	

Taskgroup on U-2(g) (BPV VIII)

S. R. Babka	R. F. Reedy, Sr.
R. J. Basile	S. C. Roberts
D. K. Chandiramani	J. R. Sims, Jr.
R. Mahadeen	D. Srnic
U. R. Miller	D. A. Swanson
T. W. Norton	R. Uebel
T. P. Pastor	K. K. Tam

Subgroup on Design (BPV VIII)

R. J. Basile, <i>Chair</i>	S. C. Roberts
J. C. Sowinski, <i>Vice Chair</i>	C. D. Rodery
M. D. Lower, <i>Secretary</i>	S. C. Shah
O. A. Barsky	D. A. Swanson
M. R. Breach	J. Vattappilly
F. L. Brown	R. A. Whipple
J. R. Farr	A. A. Gibbs, <i>Delegate</i>
B. F. Hantz	K. Oyamada, <i>Delegate</i>
C. E. Hinnant	M. E. Papponetti, <i>Delegate</i>
M. H. Jawad	M. Faulkner, <i>Corresponding Member</i>
D. L. Kurler	C. S. Hinson, <i>Corresponding Member</i>
R. W. Mikitka	W. S. Jacobs, <i>Corresponding Member</i>
U. R. Miller	A. Selz, <i>Corresponding Member</i>
K. Mokhtarian	K. K. Tam, <i>Corresponding Member</i>
T. P. Pastor	
M. D. Rana	
G. B. Rawls, Jr.	

Subgroup on Heat Transfer Equipment (BPV VIII)

R. Mahadeen, <i>Chair</i>	P. Matkovics
G. Auriolles, Sr., <i>Vice Chair</i>	S. Mayeux
F. E. Jehrio, <i>Secretary</i>	U. R. Miller
S. R. Babka	T. W. Norton
J. H. Barbee	K. Oyamada
O. A. Barsky	D. Srnic
I. G. Campbell	A. M. Voytko
A. Chaudouet	R. P. Wiberg
M. D. Clark	F. Osweiller, <i>Corresponding Member</i>
J. I. Gordon	S. Yokell, <i>Corresponding Member</i>
M. J. Holtz	R. Tiwari, <i>Contributing Member</i>
G. G. Karcher	S. M. Caldwell, <i>Honorary Member</i>
D. L. Kurler	
B. J. Lerch	

Subgroup on High Pressure Vessels (BPV VIII)

D. T. Peters, *Chair*
 R. T. Hallman, *Vice Chair*
 A. P. Maslowski, *Staff Secretary*
 L. P. Antalffy
 R. C. Biel
 P. N. Chaku
 R. Cordes
 R. D. Dixon
 L. Fridlund
 D. M. Fryer
 A. H. Honza
 M. M. James
 J. A. Kapp
 J. Keltjens
 A. K. Khare
 S. C. Mordre

G. T. Nelson
 E. A. Rodriguez
 E. D. Roll
 J. R. Sims, Jr.
 D. L. Stang
 F. W. Tatar
 S. Terada
 J. L. Traud
 R. Wink
 K. J. Young
 K. Oyamada, *Delegate*
 R. M. Hoshman, *Contributing Member*
 G. J. Mraz, *Contributing Member*
 D. J. Burns, *Honorary Member*
 E. H. Perez, *Honorary Member*

Task Group on Design (BPV VIII)

J. Keltjens, *Chair*
 R. C. Biel
 D. J. Burns
 R. Cordes
 R. D. Dixon
 L. Fridlund
 D. M. Fryer
 R. T. Hallman
 S. C. Mordre
 G. T. Nelson

E. H. Perez
 D. T. Peters
 E. D. Roll
 K. C. Simpson
 J. R. Sims, Jr.
 D. L. Stang
 S. Terada
 J. L. Traud
 R. Wink

Task Group on Materials (BPV VIII)

F. W. Tatar, *Chair*
 L. P. Antalffy
 P. N. Chaku

M. M. James
 J. A. Kapp
 A. K. Khare

Subgroup on Materials (BPV VIII)

J. F. Grubb, *Chair*
 J. Cameron, *Vice Chair*
 P. G. Wittenbach, *Secretary*
 A. Di Rienzo
 J. D. Fritz
 M. Gold
 M. Katcher
 W. M. Lundy
 D. W. Rahoi

R. C. Sutherlin
 E. Uptis
 K. Xu
 K. Oyamada, *Delegate*
 E. G. Nisbett, *Corresponding Member*
 G. S. Dixit, *Contributing Member*
 J. A. McMaster, *Contributing Member*

Task Group on Impulsively Loaded Vessels (BPV VIII)

E. A. Rodriguez, *Chair*
 P. O. Leslie, *Secretary*
 G. A. Antaki
 J. K. Asahina
 D. D. Barker
 D. W. Bowman
 A. M. Clayton
 J. E. Didlake, Jr.
 T. A. Duffey
 B. L. Haroldsen
 H. L. Heaton
 D. Hilding

K. W. King
 R. Kitamura
 R. A. Leishear
 R. E. Nickell
 F. Ohlson
 C. Romero
 N. Rushton
 J. E. Shepherd
 Q. Dong, *Corresponding Member*
 M. Yip, *Corresponding Member*
 C. R. Vaught, *Alternate*

Subgroup on Toughness (BPV II & BPV VIII)

D. A. Swanson, *Chair*
 J. P. Swezy, Jr., *Vice Chair*
 J. L. Arnold
 R. J. Basile
 J. Cameron
 H. E. Gordon
 W. S. Jacobs
 D. L. Kurlle

K. Mokhtarian
 C. C. Neely
 M. D. Rana
 F. L. Richter
 E. Uptis
 J. Vattappilly
 K. Xu
 K. Oyamada, *Delegate*

COMMITTEE ON WELDING, BRAZING, AND FUSING (BPV IX)

W. J. Sperko, *Chair*
 D. A. Bowers, *Vice Chair*
 S. J. Rossi, *Staff Secretary*
 M. Bernasek
 R. K. Brown, Jr.
 M. L. Carpenter
 J. G. Feldstein
 P. D. Flenner
 R. M. Jessee
 J. S. Lee
 W. M. Lundy
 T. Melfi
 W. F. Newell, Jr.
 B. R. Newmark

A. S. Olivares
 M. J. Pischke
 M. J. Rice
 M. B. Sims
 M. J. Stanko
 J. P. Swezy, Jr.
 P. L. Van Fosson
 R. R. Young
 A. Roza, *Delegate*
 M. Consonni, *Contributing Member*
 S. A. Jones, *Contributing Member*
 W. D. Doty, *Honorary Member*
 S. D. Reynolds, Jr., *Honorary Member*

Special Working Group on Graphite Pressure Equipment (BPV VIII)

E. Soltow, *Chair*
 G. C. Becherer
 T. F. Bonn
 F. L. Brown

R. W. Dickerson
 S. Malone
 M. R. Minick
 A. A. Stupica

Subgroup on Brazing (BPV IX)

M. J. Pischke, *Chair*
 E. W. Beckman
 L. F. Campbell

M. L. Carpenter
 A. F. Garbolevsky
 J. P. Swezy, Jr.

Special Working Group on Bolted Flanged Joints (BPV VIII)

R. W. Mikitka, *Chair*
 G. D. Bibel
 W. Brown
 W. J. Koves

M. Morishita
 J. R. Payne
 G. B. Rawls, Jr.
 M. S. Shelton

Subgroup on General Requirements (BPV IX)

B. R. Newmark, *Chair*
 E. W. Beckman
 G. Chandler
 P. R. Evans
 A. Howard
 R. M. Jessee
 A. S. Olivares

D. K. Peetz
 H. B. Porter
 P. L. Sturgill
 K. R. Willens
 E. W. Woelfel
 E. Molina, *Delegate*

Subgroup on Materials (BPV IX)

M. Bernasek, <i>Chair</i>	T. Melfi
T. Anderson	M. J. Pischke
J. L. Arnold	C. E. Sainz
M. L. Carpenter	W. J. Sperko
E. Cutlip	M. J. Stanko
S. S. Fiore	P. L. Sturgill
S. E. Gingrich	R. R. Young
R. M. Jessee	V. G. V. Giunto, <i>Delegate</i>
C. C. Kim	

Subgroup on Performance Qualification (BPV IX)

D. A. Bowers, <i>Chair</i>	K. L. Hayes
M. J. Rice, <i>Secretary</i>	J. S. Lee
V. A. Bell	W. M. Lundy
M. A. Boring	E. G. Reichelt
R. B. Corbit	M. B. Sims
P. D. Flenner	

Subgroup on Plastic Fusing (BPV IX)

M. L. Carpenter, <i>Chair</i>	J. E. O'Sullivan
D. Burwell	E. G. Reichelt
J. M. Craig	M. J. Rice
A. N. Haddad	P. L. Sturgill
K. L. Hayes	J. P. Swezy, Jr.
R. M. Jessee	E. W. Woelfel
E. Lever	J. C. Minichiello
E. W. McElroy	C. W. Rowley

Subgroup on Procedure Qualification (BPV IX)

D. A. Bowers, <i>Chair</i>	A. S. Olivares
M. J. Rice, <i>Secretary</i>	S. Raghunathan
M. Bernasek	M. B. Sims
M. A. Boring	W. J. Sperko
R. K. Brown, Jr.	S. A. Sprague
W. M. Lundy	J. P. Swezy, Jr.
J. R. McGimpsey	P. L. Van Fosson
W. F. Newell, Jr.	T. C. Wiesner

COMMITTEE ON FIBER-REINFORCED PLASTIC PRESSURE VESSELS (BPV X)

D. Eisberg, <i>Chair</i>	D. L. Keeler
P. D. Stumpf, <i>Staff Secretary</i>	B. M. Linnemann
F. L. Brown	N. L. Newhouse
J. L. Bustillos	D. J. Painter
T. W. Cowley	G. Ramirez
I. L. Dinovo	J. R. Richter
T. J. Fowler	B. F. Shelley
M. R. Gorman	F. W. Van Name
D. H. Hodgkinson	D. O. Yancey, Jr.
L. E. Hunt	P. H. Ziehl

COMMITTEE ON NUCLEAR INSERVICE INSPECTION (BPV XI)

G. C. Park, <i>Chair</i>	D. W. Lamond
R. W. Swayne, <i>Vice Chair</i>	G. A. Lofthus
R. A. Yonekawa, <i>Vice Chair</i>	J. E. O'Sullivan
R. L. Crane, <i>Staff Secretary</i>	R. K. Rhyne
J. M. Agold	D. A. Scarth
V. L. Armentrout	F. J. Schaaf, Jr.
W. H. Bamford	J. C. Spanner, Jr.
T. L. Chan	G. L. Stevens
R. C. Cipolla	D. E. Waskey
D. D. Davis	J. G. Weicks
G. H. DeBoo	C. J. Wirtz
R. L. Dyle	T. Yuhara
E. V. Farrell, Jr.	H. D. Chung, <i>Delegate</i>
E. L. Farrow	C. Ye, <i>Delegate</i>
E. B. Gerlach	R. A. West, <i>Contributing Member</i>
R. E. Gimple	J. Hakii, <i>Alternate</i>
T. J. Griesbach	J. T. Lindberg, <i>Alternate</i>
K. Hasegawa	W. E. Norris, <i>Alternate</i>
D. O. Henry	C. D. Cowfer, <i>Honorary Member</i>
R. D. Kerr	F. E. Gregor, <i>Honorary Member</i>
S. D. Kulat	O. F. Hedden, <i>Honorary Member</i>
G. L. Lagleder	P. C. Riccardella, <i>Honorary Member</i>

Executive Committee (BPV XI)

R. A. Yonekawa, <i>Chair</i>	S. D. Kulat
G. C. Park, <i>Vice Chair</i>	J. T. Lindberg
R. L. Crane, <i>Staff Secretary</i>	W. E. Norris
W. H. Bamford	R. K. Rhyne
R. L. Dyle	J. C. Spanner, Jr.
M. J. Ferlisi	G. L. Stevens
E. B. Gerlach	R. W. Swayne
R. E. Gimple	

Subgroup on Evaluation Standards (SG-ES) (BPV XI)

W. H. Bamford, <i>Chair</i>	D. R. Lee
G. L. Stevens, <i>Secretary</i>	R. O. McGill
H. D. Chung	H. S. Mehta
R. C. Cipolla	M. A. Mitchell
G. H. DeBoo	K. Miyazaki
R. L. Dyle	R. Pace
B. R. Ganta	S. Ranganath
T. J. Griesbach	D. A. Scarth
K. Hasegawa	T. V. Vo
K. Hojo	K. R. Wichman
D. N. Hopkins	S. X. Xu
K. Koyama	

Working Group on Flaw Evaluation (SG-ES) (BPV XI)

R. C. Cipolla, <i>Chair</i>	H. S. Mehta
S. X. Xu, <i>Secretary</i>	G. A. Miessi
W. H. Bamford	K. Miyazaki
B. Bezensek	R. K. Qashu
H. D. Chung	S. Ranganath
G. H. DeBoo	H. Rathbun
B. R. Ganta	P. J. Rush
R. G. Gilada	D. A. Scarth
H. L. Gustin	W. L. Server
F. D. Hayes	N. J. Shah
P. H. Hoang	T. V. Vo
K. Hojo	K. R. Wichman
D. N. Hopkins	G. M. Wilkowski
K. Koyama	D. L. Rudland, <i>Alternate</i>
D. R. Lee	

Working Group on Operating Plant Criteria (SG-ES) (BPV XI)

T. J. Griesbach, <i>Chair</i>	H. S. Mehta
D. V. Sommerville, <i>Secretary</i>	M. A. Mitchell
W. H. Bamford	R. Pace
H. Behnke	N. A. Palm
T. L. Dickson	S. Ranganath
R. L. Dyle	W. L. Server
S. R. Gosselin	D. P. Weakland
M. Hayashi	T. Hardin, <i>Alternate</i>

Working Group on Pipe Flaw Evaluation (SG-ES) (BPV XI)

D. A. Scarth, <i>Chair</i>	D. N. Hopkins
G. M. Wilkowski, <i>Secretary</i>	E. J. Houston
T. A. Bacon	K. Kashima
W. H. Bamford	R. O. McGill
B. Bezensek	H. S. Mehta
H. D. Chung	G. A. A. Miessi
R. C. Cipolla	K. Miyazaki
N. G. Cofie	D. L. Rudland
J. M. Davis	P. J. Rush
G. H. DeBoo	D.-J. Shim
B. R. Ganta	T. V. Vo
L. F. Goyette	B. Wasiluk
K. Hasegawa	S. X. Xu
P. H. Hoang	H. Rathbun, <i>Alternate</i>
K. Hojo	

Subgroup on Nondestructive Examination (SG-NDE) (BPV XI)

J. C. Spanner, Jr., <i>Chair</i>	J. T. Lindberg
G. A. Lofthus, <i>Secretary</i>	T. R. Lupold
T. L. Chan	G. R. Perkins
C. B. Cheezem	S. A. Sabo
D. R. Cordes	F. J. Schaaf, Jr.
F. E. Dohmen	R. V. Swain
M. E. Gothard	G. Tang
D. O. Henry	C. J. Wirtz

Working Group on Personnel Qualification and Surface Visual and Eddy Current Examination (SG-NDE) (BPV XI)

J. T. Lindberg, <i>Chair</i>	J. C. Spanner, Jr.
D. R. Cordes, <i>Secretary</i>	J. T. Timm
S. E. Cumblidge	M. C. Weatherly
N. Farenbaugh	M. L. Whytsell
D. O. Henry	C. J. Wirtz
J. W. Houf	

Working Group on Procedure Qualification and Volumetric Examination (SG-NDE) (BPV XI)

G. A. Lofthus, <i>Chair</i>	K. J. Hacker
G. R. Perkins, <i>Secretary</i>	D. B. King
M. T. Anderson	D. A. Kull
M. Briley	C. A. Nove
C. B. Cheezem	S. A. Sabo
A. D. Chockie	R. V. Swain
M. Dennis	B. A. Thigpen
S. R. Doctor	S. J. Todd
F. E. Dohmen	D. K. Zimmerman
M. E. Gothard	

Subgroup on Repair/Replacement Activities (SG-RRR) (BPV XI)

E. B. Gerlach, <i>Chair</i>	R. D. Kerr
E. V. Farrell, Jr., <i>Secretary</i>	S. L. McCracken
S. B. Brown	B. R. Newton
R. E. Cantrell	J. E. O'Sullivan
G. G. Elder	R. R. Stevenson
P. D. Fisher	R. W. Swayne
J. M. Gamber	D. L. Tilly
R. E. Gimple	D. E. Waskey
D. R. Graham	J. G. Weicks
R. A. Hermann	R. A. Yonekawa
K. J. Karwoski	E. G. Reichelt, <i>Alternate</i>

Working Group on Welding and Special Repair Processes (SG-RRR) (BPV XI)

D. E. Waskey, <i>Chair</i>	C. C. Kim
D. J. Tilly, <i>Secretary</i>	M. Lau
R. E. Cantrell	S. L. McCracken
S. J. Findlan	D. B. Meredith
P. D. Fisher	B. R. Newton
M. L. Hall	J. E. O'Sullivan
R. A. Hermann	R. E. Smith
K. J. Karwoski	J. G. Weicks

Working Group on Nonmetals Repair/Replacement Activities (SG-RRR) (BPV XI)

J. E. O'Sullivan, <i>Chair</i>	B. B. Raji
S. Schuessler, <i>Secretary</i>	E. G. Reichelt
E. W. McElroy	F. J. Schaaf, Jr.
T. M. Musto	Z. J. Zhou

Task Group on Repair by Carbon Fiber Composites (WGN-MRR) (BPV XI)

J. E. O'Sullivan, <i>Chair</i>	B. B. Raji
M. Golliet	F. J. Schaaf, Jr.
E. W. McElroy	

Working Group on Design and Programs (SG-RRR) (BPV XI)

G. G. Elder, <i>Chair</i>	E. B. Gerlach
S. B. Brown, <i>Secretary</i>	D. R. Graham
O. Bhatta	G. F. Harttraft
R. Clow	T. E. Hiss
J. W. Collins	H. Malinkowski
R. R. Croft	M. A. Pyne
E. V. Farrell, Jr.	R. R. Stevenson
S. K. Fisher	R. W. Swayne
J. M. Gamber	R. A. Yonekawa

Subgroup on Water-Cooled Systems (SG-WCS) (BPV XI)

S. D. Kulat, <i>Chair</i>	P. J. Hennessey
N. A. Palm, <i>Secretary</i>	D. W. Lamond
J. M. Agold	A. McNeill III
V. L. Armentrout	T. Nomura
J. M. Boughman	W. E. Norris
S. T. Chesworth	G. C. Park
D. D. Davis	J. E. Staffiera
H. Q. Do	H. M. Stephens, Jr.
E. L. Farrow	R. Turner
M. J. Ferlisi	H. L. Graves III, <i>Alternate</i>

Task Group on High Strength Nickel Alloys Issues (SG-WCS) (BPV XI)

V. L. Armentrout, <i>Chair</i>	K. Koyama
B. L. Montgomery, <i>Secretary</i>	M. Lashley
W. H. Bamford	G. C. Park
P. R. Donavin	J. M. Shuping
R. L. Dyle	J. C. Spanner, Jr.
G. G. Elder	K. B. Stuckey
R. E. Gimple	E. J. Sullivan, Jr.
R. Hardies	D. P. Weakland

Working Group on Containment (SG-WCS) (BPV XI)

J. E. Staffiera, <i>Chair</i>	D. J. Naus
H. M. Stephens, Jr., <i>Secretary</i>	F. Poteet III
P. S. Ghosal	A. A. Reyes-Cruz
D. H. Goche	E. A. Rodriguez
H. L. Graves III	G. Thomas
H. T. Hill	S. G. Brown, <i>Alternate</i>
R. D. Hough	W. E. Norris, <i>Alternate</i>
C. N. Krishnaswamy	

Working Group on Inspection of Systems and Components (SG-WCS) (BPV XI)

J. M. Agold, <i>Chair</i>	K. W. Hall
H. Q. Do, <i>Secretary</i>	K. M. Hoffman
V. L. Armentrout	S. D. Kulat
C. Cueto-Felgueroso	T. Nomura
R. E. Day	J. C. Nygaard
M. J. Ferlisi	R. Rishel
R. Fougereousse	C. M. Ross

Working Group on Pressure Testing (SG-WCS) (BPV XI)

D. W. Lamond, <i>Chair</i>	T. R. Lupold
J. M. Boughman, <i>Secretary</i>	J. K. McClanahan
Y.-K. Chung	B. L. Montgomery
T. Coste	S. A. Norman
J. A. Doughty	P. N. Passalugo
R. E. Hall	J. A. Stevenson

Task Group on Buried Components Inspection and Testing (WG-PT) (BPV XI)

D. W. Lamond, <i>Chair</i>	A. Lee
J. M. Boughman, <i>Secretary</i>	E. J. Maloney
C. Blackwelder	M. Moenssens
B. Clark III	J. Ossmann
G. C. Coker	P. N. Passalugo
R. E. Day	J. H. Riley
R. Hardies	D. M. Swann
T. Ivy	

Working Group on Risk-Informed Activities (SGW-CS) (BPV XI)

M. A. Pyne, <i>Chair</i>	K. W. Hall
S. T. Chesworth, <i>Secretary</i>	S. D. Kulat
J. M. Agold	D. W. Lamond
C. Cueto-Felgueroso	R. K. Mattu
H. Q. Do	A. McNeill III
R. Fougereousse	P. J. O'Regan
M. R. Graybeal	N. A. Palm
R. Haessler	D. Vetter
J. Hakii	J. C. Younger

Special Working Group on Editing and Review (BPV XI)

R. W. Swayne, <i>Chair</i>	J. E. Staffiera
C. E. Moyer	D. J. Tilly
K. R. Rao	C. J. Wirtz

Special Working Group on Nuclear Plant Aging Management (BPV XI)

T. A. Meyer, <i>Chair</i>	A. B. Meichler
B. R. Snyder, <i>Secretary</i>	R. E. Nickell
S. Asada	K. Sakamoto
D. V. Burgess	W. L. Server
Y.-K. Chung	R. L. Turner
D. D. Davis	G. G. Young
R. L. Dyle	Z. Zhong
A. L. Hiser, Jr.	C. E. Carpenter, <i>Alternate</i>

Working Group on General Requirements (BPV XI)

R. K. Rhyne, <i>Chair</i>	K. M. Herman
E. J. Maloney, <i>Secretary</i>	R. K. Mattu
T. L. Chan	C. E. Moyer
E. L. Farrow	D. J. Potter
R. Fox	R. L. Williams
P. J. Hennessey	

Special Working Group on Reliability and Integrity Management Program (BPV XI)

F. J. Schaaf, Jr., <i>Chair</i>	D. R. Lee
M. A. Lockwood, <i>Secretary</i>	R. K. Miller
N. Broom	P. M. Mills
S. R. Doctor	M. N. Mitchell
J. Fletcher	A. T. Roberts III
M. R. Graybeal	T. Roney
J. Grimm	R. W. Swayne
A. B. Hull	

COMMITTEE ON TRANSPORT TANKS (BPV XII)

M. D. Rana, <i>Chair</i>	J. R. McGimpsey
N. J. Paulick, <i>Vice Chair</i>	M. Pitts
T. Schellens, <i>Staff Secretary</i>	T. A. Rogers
A. N. Antoniou	A. Selz
J. A. Byers	S. Staniszewski
W. L. Garfield	A. P. Varghese
C. H. Hochman	M. R. Ward
G. G. Karcher	M. D. Pham, <i>Contributing Member</i>

Subgroup on Design and Materials (BPV XII)

A. P. Varghese, <i>Chair</i>	N. J. Paulick
R. C. Sallash, <i>Secretary</i>	M. D. Rana
D. K. Chandiramani	T. A. Rogers
P. Chilukuri	A. Selz
T. Hitchcock	M. R. Ward
G. G. Karcher	K. Xu
T. P. Lokey	J. Zheng, <i>Corresponding Member</i>
S. L. McWilliams	M. D. Pham, <i>Contributing Member</i>

**Subgroup on Fabrication, Inspection, and Continued Service
(BPV XII)**

M. Pitts, <i>Chair</i>	K. Mansker
P. Chilukuri, <i>Secretary</i>	J. R. McGimpsey
S. E. Benet	A. S. Olivares
J. A. Byers	R. C. Sallash
W. L. Garfield	S. Staniszewski
T. P. Lokey	L. H. Strouse, <i>Contributing Member</i>

Subgroup on General Requirements (BPV XII)

W. L. Garfield, <i>Chair</i>	M. Pitts
S. E. Benet, <i>Secretary</i>	T. Rummel
T. W. Alexander	R. C. Sallash
A. N. Antoniou	S. Staniszewski
J. L. Freiler	K. L. Gilmore, <i>Contributing Member</i>
C. H. Hochman	L. H. Strouse, <i>Contributing Member</i>
J. R. McGimpsey	

Subgroup on Nonmandatory Appendices (BPV XII)

T. A. Rogers, <i>Chair</i>	D. G. Shelton
S. Staniszewski, <i>Secretary</i>	M. R. Ward
S. E. Benet	D. D. Brusewitz, <i>Contributing Member</i>
P. Chilukuri	J. L. Conley, <i>Contributing Member</i>
R. Hayworth	T. Eubanks, <i>Contributing Member</i>
K. Mansker	T. Hitchcock, <i>Contributing Member</i>
S. L. McWilliams	A. Selz, <i>Contributing Member</i>
N. J. Paulick	A. P. Varghese, <i>Contributing Member</i>
M. Pitts	
R. C. Sallash	

**COMMITTEE ON BOILER AND PRESSURE VESSEL CONFORMITY
ASSESSMENT (CBPVCA)**

P. D. Edwards, <i>Chair</i>	R. V. Wielgoszinski
K. I. Baron, <i>Staff Secretary</i>	S. F. Harrison, Jr., <i>Contributing Member</i>
S. W. Cameron	V. Bogosian, <i>Alternate</i>
M. A. DeVries	D. C. Cook, <i>Alternate</i>
T. E. Hansen	D. W. King, <i>Alternate</i>
D. J. Jenkins	B. L. Krasium, <i>Alternate</i>
K. T. Lau	W. C. LaRochelle, <i>Alternate</i>
L. E. McDonald	P. F. Martin, <i>Alternate</i>
K. M. McTague	K. McPhie, <i>Alternate</i>
D. Miller	M. R. Minick, <i>Alternate</i>
B. R. Morelock	I. Powell, <i>Alternate</i>
J. D. O'Leary	R. Pulliam, <i>Alternate</i>
T. M. Parks	M. T. Roby, <i>Alternate</i>
B. C. Turczynski	J. A. West, <i>Alternate</i>
D. E. Tuttle	A. J. Spencer, <i>Honorary Member</i>
E. A. Whittle	

COMMITTEE ON NUCLEAR CERTIFICATION (CNC)

W. C. LaRochelle, <i>Chair</i>	M. F. Sullivan, <i>Contributing Member</i>
R. R. Stevenson, <i>Vice Chair</i>	S. Andrews, <i>Alternate</i>
E. Suarez, <i>Staff Secretary</i>	V. Bogosian, <i>Alternate</i>
J. DeKleine	P. D. Edwards, <i>Alternate</i>
G. Gobbi	D. P. Gobbi, <i>Alternate</i>
S. M. Goodwin	K. M. Hottle, <i>Alternate</i>
J. W. Highlands	K. A. Kavanagh, <i>Alternate</i>
K. A. Huber	B. G. Kovarik, <i>Alternate</i>
J. C. Krane	M. A. Lockwood, <i>Alternate</i>
R. P. McIntyre	R. J. Luymes, <i>Alternate</i>
M. R. Minick	J. Oyler, <i>Alternate</i>
L. M. Plante	M. Paris, <i>Alternate</i>
H. B. Prasse	D. W. Stepp, <i>Alternate</i>
T. E. Quaka	A. Torosyan, <i>Alternate</i>
C. T. Smith	E. A. Whittle, <i>Alternate</i>
D. M. Vickery	H. L. Wiger, <i>Alternate</i>
C. S. Withers	
S. Yang	

COMMITTEE ON SAFETY VALVE REQUIREMENTS (BPV-SVR)

J. A. West, <i>Chair</i>	R. J. Doelling
D. B. DeMichael, <i>Vice Chair</i>	J. P. Glaspie
C. E. O'Brien, <i>Staff Secretary</i>	S. F. Harrison, Jr.
J. F. Ball	W. F. Hart
S. Cammeresi	D. Miller
J. A. Cox	T. Patel
R. D. Danzy	Z. Wang

Subgroup on Design (BPV-SVR)

R. D. Danzy, <i>Chair</i>	D. Miller
C. E. Beair	T. Patel
J. A. Conley	J. A. West
R. J. Doelling	

Subgroup on General Requirements (BPV-SVR)

D. B. DeMichael, <i>Chair</i>	S. T. French
J. F. Ball	J. P. Glaspie
G. Brazier	J. W. Richardson
J. Burgess	D. E. Tuttle

Subgroup on Testing (BPV-SVR)

J. A. Cox, <i>Chair</i>	W. F. Hart
J. E. Britt	B. K. Nutter
S. Cammeresi	C. Sharpe
J. W. Dickson	Z. Wang
G. D. Goodson	A. Wilson

U.S. Technical Advisory Group ISO/TC 185 Safety Relief Valves

T. J. Bevilacqua, <i>Chair</i>	D. B. DeMichael
C. E. O'Brien, <i>Staff Secretary</i>	D. Miller
J. F. Ball	B. K. Nutter
G. Brazier	J. A. West

INTRODUCTION

The following is provided as a brief introduction to Section IX, and cannot be considered as a substitute for the actual review of the document. However, this introduction is intended to give the reader a better understanding of the purpose and organization of Section IX.

Section IX of the ASME Boiler and Pressure Vessel Code relates to the qualification of welders, welding operators, brazers, brazing operators, and fusing machine operators, and the procedures employed in welding, brazing, or plastic fusing in accordance with the ASME Boiler and Pressure Vessel Code and the ASME B31 Code for Pressure Piping. As such, this is an active document subject to constant review, interpretation, and improvement to recognize new developments and research data. Section IX is a document referenced for the qualification of material joining processes by various construction codes such as Section I, III, IV, VIII, XII, etc. These particular construction codes apply to specific types of fabrication and may impose additional requirements or exemptions to Section IX qualifications. Qualification in accordance with Section IX is not a guarantee that procedures and performance qualifications will be acceptable to a particular construction code.

Section IX does not contain rules for production joining, nor does it contain rules to cover all factors affecting production material joining properties under all circumstances. Where such factors are determined by the organization to affect material joining properties, the organization shall address those factors in the Procedure Specification to ensure that the required properties are achieved in the production material joining process.

The purpose of the Procedure Specification and the Procedure Qualification Record (PQR) is to ensure the material joining process proposed for construction is capable of producing joints having the required mechanical properties for the intended application. Personnel performing the material joining procedure qualification test shall be sufficiently skilled. The purpose of the procedure qualification test is to establish the mechanical properties of the joint produced by the material joining process and not the skill of the personnel using the material joining process. In addition, special consideration is given when toughness testing is required by other Sections of the Code. The toughness supplementary essential variables do not apply unless referenced by the construction codes.

The purpose of Performance Qualification is to determine the ability of the person using a material joining process to produce a sound joint. In Operator Performance Qualification, the basic criterion is to determine the ability of the operator to properly operate the equipment to produce a sound joint.

In developing Section IX, each material joining process that is included was reviewed with regard to those factors (called variables) which have an effect upon the material joining operations as applied to procedure or performance criteria.

The user of Section IX should be aware of how Section IX is organized. It is divided into four Parts: general requirements, welding, brazing, and plastic fusing. Each Part addressing a material joining process is then divided into Articles. The Articles for each material joining process deal with the following:

- (a) general requirements specifically applicable to the material joining process ([Article I](#) Welding, [Article XI](#) Brazing, and [Article XXI](#) Plastic Fusing)
- (b) procedure qualifications ([Article II](#) Welding, [Article XII](#) Brazing, and [Article XXII](#) Plastic Fusing)
- (c) performance qualifications ([Article III](#) Welding, [Article XIII](#) Brazing, and [Article XXIII](#) Plastic Fusing)
- (d) data ([Article IV](#) Welding, [Article XIV](#) Brazing, and [Article XXIV](#) Plastic Fusing)
- (e) standard welding procedure specifications ([Article V](#) Welding)

These articles contain general references and guides that apply to procedure and performance qualifications such as positions, type and purpose of various mechanical tests, acceptance criteria, and the applicability of Section IX, which previously appeared in the Preamble of the 1980 Edition of Section IX (the Preamble has since been deleted). The general requirement articles reference the data articles for specific details of the testing equipment and removal of the mechanical test specimens.

PROCEDURE QUALIFICATIONS

Each material joining process that has been evaluated and adopted by Section IX is listed separately with the essential and nonessential variables as they apply to that particular process. In general, the Procedure Specifications are required to list all essential and nonessential variables for each process that is included under that particular procedure specification. When an essential variable must be changed beyond the range qualified and the change is not an editorial revision to

correct an error, requalification of the procedure specification is required. If a change is made in a nonessential variable, the procedure need only be revised or amended to address the nonessential variable change. When toughness testing is required for Welding Procedure Specification (WPS) qualification by the construction code, the supplementary essential variables become additional essential variables, and a change in these variables requires requalification of the procedure specification.

In addition to covering various processes, there are also rules for procedure qualification of corrosion-resistant weld metal overlay and hard-facing weld metal overlay.

Beginning with the 2000 Addenda, the use of Standard Welding Procedure Specifications (SWPSs) was permitted. [Article V](#) provides the requirements and limitations that govern the use of these documents. The SWPSs approved for use are listed in [Mandatory Appendix E](#).

In the 2004 Edition, rules for temper bead welding were added.

With the incorporation of the new Creep-Strength Enhanced Ferritic (CSEF) alloys in the 1986 Edition, using the existing P-Number groupings to specify PWHT parameters can lead to variations in heat treatments that may significantly degrade the mechanical properties of these alloys. CSEF alloys are a family of ferritic steels whose creep strength is enhanced by the creation of a precise condition of microstructure, specifically martensite or bainite, which is stabilized during tempering by controlled precipitation of temper-resistant carbides, carbo-nitrides, or other stable phases.

In the 2007 Edition of the Code, only P-No. 5B, Group 2 base metals met this definition and were approved for Code construction. Looking forward, a number of CSEF alloys are already in use in Code Cases and drawing near to incorporation. To facilitate addressing their special requirements, P-No. 15A through P-No. 15F have been established for CSEF alloys.

In the 2013 Edition, [Part QG](#) General Requirements and [Part QF](#) Plastic Fusing were added.

PERFORMANCE QUALIFICATIONS

These articles list separately the various processes with the essential variables that apply to the performance qualifications of each process. The performance qualifications are limited by essential variables.

The performance qualification articles have numerous paragraphs describing general applicable variables for all processes. [QW-350](#), [QB-350](#), and [QF-360](#) list additional essential variables that are applicable for specific processes. The [QW-350](#) variables do not apply to welding operators. [QW-360](#) lists the additional essential variables for welding operators.

Generally, a welder or welding operator may be qualified by mechanical bending tests, or volumetric NDE of a test coupon, or the initial production weld. Brazers or brazing operators and fusing machine operators may not be qualified by volumetric NDE.

WELDING, BRAZING, AND FUSING DATA

The data articles include the variables grouped into categories such as joints, base materials and filler materials, positions, preheat/postweld heat treatment, gas, electrical characteristics, and technique. They are referenced from other articles as they apply to each process.

These articles are frequently misused by selecting variables that do not apply to a particular process. Variables only apply as referenced for the applicable process in [Article II](#) or [III](#) for welding, [Article XII](#) or [XIII](#) for brazing, and [Article XXII](#) or [XXIII](#) for plastic fusing. The user of Section IX should not apply any variable that is not referenced for that process.

These articles also include assignments of welding and brazing P-Numbers to particular base materials and F-Numbers to filler materials. [Article IV](#) also includes A-Number tables for reference by the Code user.

Beginning with the 1994 Addenda, welding P-Numbers, brazing P-Numbers, and nonmandatory S-Numbers were consolidated into one table identified as [QW/QB-422](#). Both the [QB-422](#) table (brazing P-Numbers) and Appendix C table (S-Numbers) were deleted. The new [Table QW/QB-422](#) was divided into ferrous and nonferrous sections. Metals were listed in numerical order by material specification number to aid users in locating the appropriate grouping number. An abbreviated listing of metals grouped by P-Numbers, [Nonmandatory Appendix D](#), has been included for users still wishing to locate groupings of metals by welding P-Number.

In the 2009 Addenda, S-Number base metals listed in the [QW/QB-422](#) table were reassigned as P-Numbers and the S-Number listings and references were deleted.

The [QW-451](#) and [QB-451](#) tables for procedure qualification thickness requirements and the [QW-452](#) and [QB-452](#) tables for performance qualification thickness are given and may be used only as referenced by other paragraphs. Generally, the appropriate essential variables reference these tables.

Revisions to the 1980 Edition of Section IX introduced new definitions for position and added a fillet-weld orientation sketch to complement the groove-weld orientation sketch. The new revision to position indicates that a welder qualifies in the 1G, 2G, 3G, etc., position and is then qualified to weld, in production, in the F, V, H, or O positions as appropriate. [QW-461.9](#) is a revised table that summarizes these new qualifications.

The data articles also give sketches of coupon orientations, removal of test specimens, and test jig dimensions. These are referenced by [Articles I, XI, and XXI](#).

[QW-470](#) describes etching processes and reagents.

Within [Part QG](#) is a list of general definitions applicable to Section IX-adopted material joining processes. These may differ slightly from other welding documents.

Nonmandatory Forms for documenting procedure and performance qualifications are provided for the aid of those who do not wish to design their own forms. Any form(s) that address all applicable requirements of Section IX may be used.

SUMMARY OF CHANGES

The 2013 Edition of this Code contains revisions in addition to the 2010 Edition with 2011 Addenda.

After publication of the 2013 Edition, Errata to the BPV Code may be posted on the ASME Web site to provide corrections to incorrectly published items, or to correct typographical or grammatical errors in the BPV Code. Such Errata shall be used on the date posted.

Information regarding Special Notices and Errata is published on the ASME Web site under the BPVC Resources page at <http://www.asme.org/kb/standards/publications/bpvc-resources>.

Changes given below are identified on the pages by a margin note, **(13)**, placed next to the affected area.

The Record Numbers listed below are explained in more detail in "List of Changes in Record Number Order" following this Summary of Changes.

<i>Page</i>	<i>Location</i>	<i>Change (Record Number)</i>
	Cover and Title Page	Section title and subtitle revised (12-1134)
x	List of Sections	Revised (12-749)
xii	Foreword	Revised in its entirety (09-760)
xv	Submittal of Technical Inquiries to the Boiler and Pressure Vessel Standards Committees	Revised (12-1641)
xvii	Personnel	Updated
xxxii	Introduction	Revised in its entirety (12-383)
xlii	Cross-Referencing and Stylistic Changes in the Boiler and Pressure Vessel Code	Added
1	Part QG	Added (12-383, 12-1956)
14	QW-100	Revised (12-159, 12-383)
20	QW-191.1.2.2	(1) Subparagraph (b)(3) revised (11-1697) (2) Figure QW-192.2.2.2(b)(4) added (formerly, in Appendix I)
21	QW-191.2.1	Subparagraph (b) revised (12-383)
22	QW-191.2.2	Subparagraph (a) revised (12-383)
23	QW-193.1	Revised (11-2142)
24	QW-194	Revised (11-1145)
26	Appendix I	Illustration designated as Figure QW-191.1.2.2(b)(4) and placed after QW-191.1.2.2(b)(3) (11-1697)
27	QW-200.1	First paragraph, second paragraph of subpara. (b), and subpara. (d) revised (12-383)
27	QW-200.2	Revised (12-383)
28	QW-201	Revised in its entirety (12-383)

<i>Page</i>	<i>Location</i>	<i>Change (Record Number)</i>
29	QW-202.1	Fifth paragraph revised (12-383)
31	QW-220	Added (09-298)
31	QW-221	Added (11-996)
54	Table QW-261	Rows for QW-403 revised (11-507)
57	Table QW-264	Revised (12-404, 11-2028)
58	Table QW-264.1	Revised (11-2028)
61	Table QW-267	Added (08-265)
62	Table QW-268	Added (09-298)
64	Table QW-269	Added (11-996)
66	Table QW-269.1	Added (11-996)
72	QW-290.5	Subparagraph (c) revised (10-33, 11-2062)
74	QW-300	(1) QW-300.2 and QW-300.3 redesignated as QG-106.2 and QG-106.3, respectively (12-383) (2) In QW-301.2, first sentence revised and last paragraph deleted (12-383) (3) QW-301.3 revised (12-383) (4) In QW-302.2, seventh line revised (11-1008) (5) In QW-303.3, first line revised (12-383) (6) QW-304.1(b) and QW-305.1(b) revised (11-1008)
76	QW-310	In QW-310.2 and QW-310.3, "manufacturer" revised to read "organization" (12-383, 12-1903)
77	QW-321.3	(1) Third line of subpara. (a) revised (11-1008) (2) In suparas. (b) and (c), "manufacturer" revised to read "organization" (12-383, 12-1903)
77	QW-322.1	Subparagraphs (a)(1) and (a)(2) revised (12-383, 12-1903)
78	Table QW-356	Entry for "Brief of Variables" revised for QW-404.23 and Legend added editorially (12-338)
79	Table QW-357	Entry for "Brief of Variables" revised for QW-404.23 (12-338)
79	QW-361	(1) QW-361.1(d) revised (09-298) (2) QW-361.2(h) revised (11-996)
79	QW-362	Title revised (09-298)
82	QW-402	QW-402.27 through QW-402.30 added (08-265, 09-298)
85	QW-403.30	Added (08-265)
85	QW-403.31	Added (09-298)
87	QW-404.23	Revised (10-1589)
87	QW-404.30	Revised (11-1469)
88	QW-404.54	Added (09-298)
88	QW-405.4	First line of subpara. (b) revised (12-383)
90	QW-408.13	Deleted (11-2028)
90	QW-408.26	Added (08-265)

<i>Page</i>	<i>Location</i>	<i>Change (Record Number)</i>
92	QW-410	(1) QW-410.69 deleted (11-2028) (2) QW-410.73 through QW-410.76 added (08-265) (3) QW-410.77 through QW-410.80 added (09-298) (4) QW-410.81 through QW-410.84 added (11-996)
95	Table QW-416	Entry under "Brief of Variables" revised for QW-404.23 (12-338)
96	QW-420	Seventh paragraph revised (12-1794)
	Table QW/QB-422	(1) Revised (09-237, 09-1775, 10-1926, 11-191, 11-622, 11-653, 11-677, 11-876, 11-998, 11-999, 11-1122, 11-1151, 11-1275, 11-1572, 11-1943, 11-2027, 12-481, 12-713, 12-740, 12-1367, 12-1393, 12-1774, 12-1954, 12-1955) (2) Corrected by errata (11-130, 11-729, 12-1305, 12-1506, 12-2090)
166	QW-423.1	In-text table revised (12-2167)
166	QW-424.2	Added (10-1463)
167	Table QW-432	(1) F-No. 23, SFA-5.10, rows for AWS Classification ER4943 UNS No. A94943 and AWS Classification R4943 UNS No. A94943 added (12-1352) (2) For F-No. 43, SFA-5.14, AWS Classification ERNiCrFe-14 UNS N06043 row added (12-152)
176	Table QW-442	Revised (10-1741)
177	Table QW-451.1	Note (6) added (11-1146)
178	Table QW-451.4	General Note added (12-65)
190	Figure QW-461.10	Added (08-265)
190	QW-462	First sentence revised (12-383)
192	Figure QW-462.1(d)	General Note (e) added (12-224)
208	Table QW-462.10(a)	Revised (10-1774)
209	Table QW-462.10(b)	Revised (10-1774)
210	Table QW-462.10(c)	Revised (10-1774)
222	Figure QW-466.1	For both Customary and SI Units tables, second row of Material column revised (10-2021)
228	QW-471	Revised (12-1569)
229	QW-490	(1) Redesignated as QG-109 (12-383) (2) Definitions for <i>control method (FSW)</i> ; <i>control method, force (FSW)</i> ; <i>control method, position (FSW)</i> ; <i>control method, travel (FSW)</i> ; <i>metal transfer mode (gas metal-arc welding)</i> ; <i>organization</i> ; <i>welding, hybrid</i> ; <i>welding, hybrid, process separation</i> ; and <i>welding, hybrid, process sequence</i> added (08-265, 09-298, 10-2104, 11-2031, 12-383) (3) Figures QW/QB-492.1 and QW/QB-492.2 redesignated as QG-109.2.1 and QG-109.2.2, respectively (12-383)
230	QW-510	Revised (12-383)
231	QW-540	Revised (12-383)
232	QB-100	Revised in its entirety (12-159, 12-383)
233	QB-141.4	Revised (11-1175)

<i>Page</i>	<i>Location</i>	<i>Change (Record Number)</i>
236	QB-200	(1) In QB-200.1 and QB-200.2, "manufacturer or contractor" revised to read "organization" (12-383) (2) First line of QB-200.2 revised (12-383) (3) QB-201 revised in its entirety (12-383) (4) In QB-202.1, last sentence of last paragraph revised (12-383)
242	QB-300	(1) QB-300.2 and QB-300.3 deleted (12-383) (2) QB-301.2, QB-301.3, and QB-303.4 revised (12-383)
245	QB-410.5	Revised (11-1537)
260	Figure QB-462.4	General Note revised (11-1175)
271	Part QF	Added (11-568, 11-569, 11-570, 11-571, 12-159, 12-383, 12-1904, 12-2292)
294	Mandatory Appendix A	Deleted (12-1643)
296	Form QW-482	Revised (12-383, 11-1469)
298	Form QW-483	Revised (12-383)
300	Form QW-484A	Revised (12-383)
301	Form QW-484B	Revised (12-383)
302	Form QW-485	Revised (12-383)
304	Form QB-483	Revised (12-383)
305	Form QB-484	Revised (12-383)
306	Nonmandatory Appendix D	(1) Revised (09-237, 09-1775, 10-1926, 11-191, 11-622, 11-677, 11-876, 11-998, 11-999, 11-1122, 11-1151, 11-1275, 11-1572, 11-1943, 11-2027, 12-481, 12-713, 12-1367, 12-1393, 12-1506, 12-1774, 12-1954) (2) Corrected by errata (11-2201, 12-1506)
324	Mandatory Appendix E	WPS replaced with SWPS throughout (11-1249)
332	H-500	First paragraph revised (12-383)
334	Nonmandatory Appendix K	Added (12-564)

NOTE: Volume 62 of the Interpretations to Section IX of the ASME Boiler and Pressure Vessel Code follows the last page of Section IX.

LIST OF CHANGES IN BC ORDER

Record Number	Change
08-265	Added new Table QW-266 and paras. QW-402.27, QW-402.28, QW-402.29, QW-403.30, QW-410.73, QW-410.74, QW-410.75, and QW-410.76; added new definitions for <i>control method (FSW)</i> , <i>control method, force (FSW)</i> , <i>control method, position (FSW)</i> , <i>control method, travel (FSW)</i> , and <i>welding, friction stir (FSW)</i> in QW-492.
09-237	Added SA-387 9Cr-1Mo plate as Grade 9 Cl. 1 and Grade 9 Cl. 2 to Table QW/QB 422 and Appendix D.
09-298	Added QW-220, QW-267, and QW-360 to incorporate hybrid laser welding.
09-760	Added an introductory subtitle clarifying the purpose and limitations of the Foreword. Revised history paragraph to recognize the realignment of the BPV into several BPV's. Deleted the paragraph on tolerances. Made editorial changes to recognize the new committee structure. Deleted words addressing governing code editions. Deleted paragraph concerning materials. Deleted the paragraph dealing with what the committee considers in the formulation of these rules.
09-1775	Revised QW/QB-422 and Nonmandatory Appendix D.
10-33	Revised QW-290.5 and figures in QW-462.12.
10-1463	Revised QW-424 to add a new para. QW-424.2 as shown in the proposal.
10-1589	Revised QW-404.23 to add clarification.
10-1741	Replaced ellipses with numeric values. Reduced significant figures to three for most elements, and to two for Si. Added Note (2) to clarify intent of nonlisted elements.
10-1774	Revised Tables QW-462.10(a), (b), and (c) to change the units from "kg" to "N."
10-1926	Revised SA/CSA-G40.21 Grades 44W and 50W material in QW/QB-422 and Appendix D.
10-2021	Revised Table QW-466.1 to update P-Numbers.
10-2104	Added the definition of "transfer mode" for GMAW to QW-492.
11-130	Errata correction. See Summary of Changes for details.
11-191	Assigned P-Numbers to SA-494 in QW/QB-422 and Appendix D.
11-507	Revised QW-409.8 and QW-409.10.
11-568	Incorporated new Article QF-100.
11-569	Incorporated new Article QF-200.
11-570	Incorporated new Article QF-300. Revised proposal includes QF-300 - Article redesignated from QX to QF, rewrote QF-300.2 to be the same as QW-300.2 (welding requirements), revised QF-302.2(a)(1) - changed QX-463 to QF-463(a), revised QF-302.2(a)(2) - changed QX-46X to QF-463(b), revised QF-302.2 - deleted QF-302.2(b) and removed FTT. Added QF-403.1 (2nd Column) and Ø Pipe Material (3rd Column) in Table QF-360.
11-571	Incorporated new Article QF-400.
11-622	Assigned welding and brazing P-Numbers (P-8, Grp. 4 and 102) along with ISO 15608 Group (8.2) (QW/QB-422 and Appendix D) to (10) of the specifications referenced by Table 3 of the Code Case. P-Numbers were not assigned for SA-193 (Bolting) and SA-194 (Nuts).
11-653	Deleted current reference to SA-240 UNS 31050 Type 310MoLN from QW/QB 422 as shown in the proposal file and added the dual reference for SA-240 UNS 31050 Type 310MoLN with ultimate tensile strengths of 78 and 84 ksi to QW/QB 422 as shown in the proposal file.
11-677	Assigned welding and brazing P-Numbers (P-10H, Grp. 1, and 102) along with ISO 15608 Group (10.1) (QW/QB-422 and Appendix D) to the (6) specifications referenced by the Code Case.
11-729	Errata correction. See Summary of Changes for details.
11-876	Deleted SA-695 from Table QW/QB-422 and Appendix D.
11-996	Added QW-221 and Table QW-468 to incorporate hybrid plasma GMAW. Revised text and tables to incorporate ballot comments and input from Nashville 2012 meetings. Observed that paragraph QW-251.1 should be revised (see Project Manager notes, below).
11-998	Revised QW/QB-422 and Nonmandatory Appendix D.
11-999	Assigned proposed Welding and brazing P-Numbers (P-10H, Grp. 1 and 102) along with ISO 15608 Group (10.1) (QW/QB-422 and Appendix D) to the (3) specifications referenced by the Code Case.

Record Number	Change
11-1008	Revised QW-302.2, QW-304.1, QW-305.1, and QW-321.3(a) to improve consistency and apply more logical requirements for volumetric examination when used for welder and welding operator performance qualification.
11-1122	Added GB 713 Grades Q370R and 15CrMoR to QW/QB-422 and Appendix D.
11-1145	Proposed additional acceptance criteria for visual examination of performance coupons.
11-1146	Revised QW-451.1.
11-1151	Revised A-213 and A-312 tube and pipe alloys P-numbers in Table QW/QB-422 and Appendix D.
11-1175	Revised QB-141.4 and Figure QB-462.4.
11-1249	Revised Appendix E to updated references.
11-1275	Modified Table QW/QB-422 and Nonmandatory Appendix D.
11-1469	Revised QW-404.30 and QW-482.
11-1537	Revised QB-410.5.
11-1572	Revised Table QW/QB-422 and Nonmandatory Appendix D.
11-1697	Errata correction. See Summary of Changes for details.
11-1943	Added ASTM A859 as SA-859 and assigned a P-No. to Table QW/QB-422 and Appendix D.
11-2027	Added SA/NF A 36-215 Grade P440 NJ4 to QW/QB-422 and Appendix D.
11-2028	Revised QW-264 and QW-264.1, and deleted QW-408.13 and QW-410.69.
11-2031	Added definitions to QW/QB-492.
11-2062	Added paragraph to QW-209.5(c).
11-2142	Revised QW-193.1.
11-2201	Errata correction. See Summary of Changes for details.
12-65	Added General Note to Table QW-451.4.
12-152	Added ERNiCrFe-14 to QW-432.
12-159	Revised Scope paragraphs QW-101, QB-101, and QF-101.
12-224	Added Note (e) to QW-462.1(d).
12-338	Revised QW-356, QW-357, and QW-416.
12-383	Added Part QG, General Requirements. Revised the Introduction, Part QW, and Part QB to eliminate redundancy with Part QG. Added a definition for the term <i>organization</i> . Globally revised Section IX to replace the terms <i>manufacturer</i> , <i>contractor</i> , <i>assembler</i> , <i>installer</i> , and <i>fabricator</i> with the term <i>organization</i> .
12-404	Errata correction. See Summary of Changes for details.
12-481	Added SA 533 Type E Cl 1 & 2 to Appendix D, and added SA 533 Type E Cl 1 & 2 to Table QW/QB-422.
12-564	Added Nonmandatory Appendix on Guidance on Invoking SC IX Requirements.
12-713	Revised Table QW/QB-422 and Appendix D to include a number of ASTM specifications. The changes to be voted on in the recirculation ballot are as follows: <ul style="list-style-type: none"> changed "N08637" to "N08367" on pages 10, 12, 16, 17, 23, 24, and 35 changed "pipe" to "tube" for A789 S32205 on page 21 deleted the addition of "10H...1...A182...S32205" on page 32 because it is already listed as F60
12-740	Added ISO 15608 Group numbers for SA/GB713 Q370R and SA/GB713 15CrMoR materials to Table QW/QB-422
12-1134	Added "Fusing" to title of Section IX Code Book.
12-1305	Errata correction. See Summary of Changes for details..
12-1352	Adopted AWS A5.10/A5.10M:2012 (ISO 18273:2004 MOD) in Modification to QW-432 to add alloys to the F-number table.
12-1367	Added and revised API 5L grades in QW/QB-422 and Appendix D.
12-1393	Revised entire Table QW/QB-422 and Appendix D. Replaced all "SA-" with "A/SA-" and all "SB-" with "B/SB-". Deleted redundant ASTM A and B spec no.'s. Replaced ASTM A and B spec no.'s with "A/SA-" and "B/SB-" for materials listed in Section II Part A and Part B.
12-1506	Errata correction. See Summary of Changes for details.
12-1569	Revised QW-471.
12-1643	Deleted Appendix A and added the requirements to the front matter.
12-1774	Added A/SA 350 LF6 Cl 2 material to Table QW/QB-422 and Appendix D as a P-No 1 Group 3 material.

Record Number	Change
12-1794	Revised 7th paragraph of QW-420.
12-1903	Revised QW-322.1(a)(1) and (a)(2).
12-1904	Revised Part QF to incorporate Part QG.
12-1954	Added UNS numbers in Table QW/QB 422 to SA-53 Type F, SA-134 (SA283GrA) and (SA283GrB), SA-135 A and B, A139 A, SA-178 D, SA-182 F3VCb and F92, SA-336 F3VCb, A351 CE20N, SA-369 FP92, A451 CPE20N, SA-508 3VCb, SA-541 3VCb, SA-542 E, Cl. 4a, B361 WP Alclad 3003, and B547 Alclad 3003. Deleted and replaced material grades with UNS numbers in Appendix D for B361 and B547.
12-1955	Revised Table QW/QB-422 by deleting tensile strengths from A519.
12-1956	Revise QG-106.3 and QG-106.3(f).
12-2090	Errata correction. See Summary of Changes for details.
12-2167	Errata correction. See Summary of Changes for details.
12-2292	Errata correction. See Summary of Changes for details.

(13) CROSS-REFERENCING AND STYLISTIC CHANGES IN THE BOILER AND PRESSURE VESSEL CODE

There have been structural and stylistic changes to BPVC, starting with the 2011 Addenda, that should be noted to aid navigating the contents. The following is an overview of the changes:

Subparagraph Breakdowns/Nested Lists Hierarchy

- First-level breakdowns are designated as (a), (b), (c), etc., as in the past.
- Second-level breakdowns are designated as (1), (2), (3), etc., as in the past.
- Third-level breakdowns are now designated as (-a), (-b), (-c), etc.
- Fourth-level breakdowns are now designated as (-1), (-2), (-3), etc.
- Fifth-level breakdowns are now designated as (+a), (+b), (+c), etc.
- Sixth-level breakdowns are now designated as (+1), (+2), etc.

Footnotes

With the exception of those included in the front matter (roman-numbered pages), all footnotes are treated as endnotes. The endnotes are referenced in numeric order and appear at the end of each BPVC section/subsection.

Submittal of Technical Inquiries to the Boiler and Pressure Vessel Standards Committees

Submittal of Technical Inquiries to the Boiler and Pressure Vessel Standards Committees has been moved to the front matter. This information now appears in all Boiler Code Sections (except for Code Case books).

Cross-References

It is our intention to establish cross-reference link functionality in the current edition and moving forward. To facilitate this, cross-reference style has changed. Cross-references within a subsection or subarticle will not include the designator/identifier of that subsection/subarticle. Examples follow:

- *(Sub-)Paragraph Cross-References.* The cross-references to subparagraph breakdowns will follow the hierarchy of the designators under which the breakdown appears.
 - If subparagraph (-a) appears in X.1(c)(1) and is referenced in X.1(c)(1), it will be referenced as (-a).
 - If subparagraph (-a) appears in X.1(c)(1) but is referenced in X.1(c)(2), it will be referenced as (1)(-a).
 - If subparagraph (-a) appears in X.1(c)(1) but is referenced in X.1(e)(1), it will be referenced as (c)(1)(-a).
 - If subparagraph (-a) appears in X.1(c)(1) but is referenced in X.2(c)(2), it will be referenced as X.1(c)(1)(-a).
- *Equation Cross-References.* The cross-references to equations will follow the same logic. For example, if eq. (1) appears in X.1(a)(1) but is referenced in X.1(b), it will be referenced as eq. (a)(1)(1). If eq. (1) appears in X.1(a)(1) but is referenced in a different subsection/subarticle/paragraph, it will be referenced as eq. X.1(a)(1)(1).

(13)

PART QG

GENERAL REQUIREMENTS

QG-100 SCOPE

(a) This Section contains requirements for the qualification of welders, welding operators, brazers, brazing operators, plastic fusing machine operators, and the material joining processes they use during welding, brazing, and fusing operations for the construction of components under the rules of the ASME Boiler and Pressure Vessel Code, the ASME B31 Codes for Pressure Piping, and other Codes, standards, and specifications that reference this Section. This Section is divided into four parts.

(1) **Part QG** contains general requirements for all material-joining processes.

(2) **Part QW** contains requirements for welding.

(3) **Part QB** contains requirements for brazing.

(4) **Part QF** contains requirements for plastic fusing.

(b) Whenever the referencing Code, standard, or specification imposes requirements different than those given in this Section, the requirements of the referencing Code, standard, or specification shall take precedence over the requirements of this Section.

(c) Some of the more common terms relating to material joining processes are defined in **QG-109**. Whenever the word “pipe” is used, “tube” shall also be applicable.

QG-101 PROCEDURE SPECIFICATION

A procedure specification is a written document providing direction to the person applying the material joining process. Details for the preparation and qualification of procedure specifications for welding (WPS), brazing (BPS), and fusing (FPS) are given in the respective Parts addressing those processes. Procedure specifications used by an *organization* (see **QG-109.2**) having responsibility for operational control of material joining processes shall have been qualified by that organization, or shall be a standard procedure specification acceptable under the rules of the applicable Part for the joining process to be used.

Procedure specifications address the conditions (including ranges, if any) under which the material joining process must be performed. These conditions are referred to in this Section as “variables.” When a procedure specification is prepared by the organization, it shall address, as a minimum, the specific essential and nonessential variables that are applicable to the material joining process to be used in production. When the referencing Code, standard, or specification requires toughness qualification of

the material joining procedure, the applicable supplementary essential variables shall also be addressed in the procedure specification.

Procedure specifications written and qualified in accordance with the rules of this Section and personnel whose performance has been qualified to use the procedure specification in accordance with these rules may be used to construct components that comply with the requirements of the ASME Boiler and Pressure Vessel Code or the ASME B31 Codes for Pressure Piping.

However, other Sections of the Code state the rules under which Section IX requirements are mandatory, in whole or in part, and may give additional requirements. The reader is advised to take these provisions into consideration when using this Section.

QG-102 PROCEDURE QUALIFICATION RECORD

The purpose of qualifying the procedure specification is to demonstrate that the joining process proposed for construction is capable of producing joints having the required mechanical properties for the intended application. Qualification of the procedure specification demonstrates the mechanical properties of the joint made using a joining process, and not the skill of the person using the joining process.

The procedure qualification record (PQR) documents what occurred during the production of a procedure qualification test coupon and the results of testing that coupon. As a minimum, the PQR shall document the essential procedure qualification test variables applied during production of the test joint, and the results of the required tests. When toughness testing is required for qualification of the procedure specification, the applicable supplementary essential variables shall be recorded for each process. The organization shall certify the PQR by a signature or other means as described in the organization's Quality Control System. The PQR shall be accessible to the Authorized Inspector. A procedure specification may be supported by one or more PQR(s), and one PQR may be used to support one or more procedure specification(s).

QG-103 PERFORMANCE QUALIFICATION

The purpose of qualifying the person who will use a joining process is to demonstrate that person's ability to produce a sound joint when using a procedure specification.

QG-104 PERFORMANCE QUALIFICATION RECORD

The performance qualification record documents what occurred during the production of a test coupon by a person using one or more joining processes following an organization's procedure specification. As a minimum, the record shall document the essential variables for each process used to produce the test coupon, the ranges of variables qualified, and the results of the required testing and/or nondestructive examinations. The organization shall certify a performance qualification record by a signature or other means as described in the organization's Quality Control System and shall make the performance qualification record accessible to the Authorized Inspector.

QG-105 VARIABLES

QG-105.1 Essential Variables. Essential variables are conditions in which a change, as described in the specific variables, is considered to affect the mechanical properties of the joint. Before using a procedure specification whose essential variables have been revised and fall outside their qualified range, the procedure specification must be requalified. Procedure qualification records may be changed when a procedure qualification test supporting the change has been completed, or when an editorial revision is necessary to correct an error, as permitted by the rules of the Part applicable to the material-joining process.

QG-105.2 Supplementary Essential Variables. Supplementary essential variables are conditions in which a change will affect the toughness properties of the joint, heat-affected zone, or base material. Supplementary essential variables become additional essential variables in situations where procedure qualifications require toughness testing. When procedure qualification does not require the addition of toughness testing, supplementary essential variables are not applicable. See [QW-401.3](#).

QG-105.3 Nonessential Variables. Nonessential variables are conditions in which a change, as described in the specific variables, is not considered to affect the mechanical properties of the joint. A procedure specification may be editorially revised to change a nonessential variable to fall outside of its previously listed range, but does not require requalification of the procedure specification.

QG-105.4 Special Process Variables. Special process variables are conditions that apply only to special processes that are described in the Part that addresses those processes. When these special processes are used,

only the applicable special process variables shall apply. A change in these process variables shall require requalification of the procedure specification.

QG-105.5 Applicability. The applicable essential, supplementary essential, nonessential, and special process variables for a specific joining process are given in the Part addressing that joining process.

QG-106 ORGANIZATIONAL RESPONSIBILITY

QG-106.1 Procedure Qualifications. Each organization is responsible for conducting the tests required by this Section to qualify the procedures that are used in the construction of components under the rules of the Codes, standards, and specifications that reference this Section.

(a) Each organization is responsible for the supervision and control of persons using material-joining processes for the production of test joints for procedure qualification. The persons producing test joints for the qualification of procedures shall be either direct employees or shall be personally engaged by contract for material-joining services.

(b) Production of qualification test joints under the supervision and control of another organization is not permitted. However, it is permitted to subcontract any or all of the work necessary for preparing the materials to be joined, the subsequent work for preparing test specimens from the completed test joint, and the performance of non-destructive examination and mechanical tests, provided the organization accepts full responsibility for any such work.

(c) If the effective operational control of procedure qualifications for two or more companies of different names exists under the same corporate ownership, the companies involved shall describe in their Quality Control System/Quality Assurance Program the operational control of procedure qualifications. In this case, separate procedure qualifications are not required, provided all other requirements of this Section are met.

QG-106.2 Performance Qualifications. Each organization is responsible for the supervision and control of material joining performed by persons for whom they have operational responsibility and control. The organization shall conduct the tests required by this Section to qualify the performance of those persons with each joining process they will use for the construction of components under the rules of the Codes, standards, and specifications that reference this Section. This responsibility cannot be delegated to another organization.

(a) Each organization is responsible for the supervision and control of persons using material-joining processes for the production of test joints for performance qualification.

(b) The performance qualification test shall be performed following either a qualified procedure specification or a standard procedure specification acceptable

under the rules of the applicable Part for the joining process. The Part addressing any specific joining process may exempt a portion of the procedure specification from being followed during production of the performance qualification test coupon.

(c) Production of test joints under the supervision and control of another organization is not permitted. It is permitted to subcontract any or all of the work necessary for preparing the materials to be joined in the test joint, and the subsequent work for preparing test specimens from the completed test joint, and the performance of nondestructive examination and mechanical tests, provided the organization accepts full responsibility for any such work.

(d) The performance qualification test may be terminated at any stage, whenever it becomes apparent to the supervisor conducting the tests that the person being tested does not have the required skill to produce satisfactory results.

(e) When a procedure qualification test coupon has been tested and found acceptable, the person who prepared the test coupon is also qualified for the joining process used, within the ranges specified for performance qualification for the applicable process(es).

(f) Persons who are successfully qualified shall be assigned an identifying number, letter, or symbol by the organization, which shall be used to identify their work.

(g) If effective operational control of performance qualifications for two or more companies of different names exists under the same corporate ownership, the companies involved shall describe in their Quality Control System/Quality Assurance Program, the operational control of performance qualifications. In this case, requalification of persons working within the companies of such an organization are not required, provided all other requirements of this Section are met.

QG-106.3 Simultaneous Performance Qualifications. Organizations may participate in an association to collectively qualify the performance of one or more persons for material-joining processes simultaneously. When simultaneous performance qualifications are conducted, each participating organization shall be represented during the preparation of the joint test by an employee with designated responsibility for performance qualifications.

(a) The procedure specifications to be followed during simultaneous performance qualifications shall be compared by the participating organizations, and shall be identical for all the essential variables, except as otherwise provided in the Part addressing the specific joining method. The qualified thickness ranges need not be identical but shall be adequate to permit the completion of the test.

(b) Alternatively, the participating organizations shall agree upon the use of a single procedure specification, for which each participating organization has a supporting PQR or has accepted responsibility for using a standard procedure specification in accordance with applicable Part

for the joining method, whose acceptable range of variables is consistent with those to be followed during the performance qualification. When a single procedure specification is to be followed, each participating organization shall review and accept that procedure specification.

(c) Each participating organization's representative shall positively identify the person whose performance is to be tested, and shall verify the markings on the test coupon correspond to the person's identification; and shall also verify that the positional orientation markings on the test coupon reflect the test position of the coupon as required to identify the location of test specimen removal.

(d) Each organization's representative shall perform a visual examination of each completed test coupon and each test specimen to determine its acceptability. Alternatively, after visual examination, when the test coupon(s) is prepared and tested by an independent laboratory, that laboratory's report may be used as the basis for accepting the test results. When the test coupon(s) is examined by volumetric examination, the examining organization's report may be used as the basis for acceptance of the test coupon.

(e) Each organizational representative shall prepare and certify a performance qualification record for each person qualified.

(f) When the person changes employers between participating organizations, the employing organization shall verify the continuity of the person's qualifications has been maintained by previous employers since his qualification date, as required by the applicable Part for the joining method. Evidence of activities supporting performance qualification continuity may be obtained from any member of the association, even if the member was not a participant in the simultaneous welder qualifications.

(g) If a person has had their performance qualification withdrawn for specific reasons, the employing organization shall notify all other participating organizations that the person's qualification(s) has been revoked. The remaining participating organizations shall determine whether or not they will uphold or withdraw the performance qualifications for that person in accordance with this Section.

(h) When a person's performance qualifications are renewed in accordance with the provisions of the applicable Part for the joining method, the testing procedures shall follow the rules of this paragraph. Each renewing organization shall be represented by an employee with designated responsibility for performance qualification.

QG-107 OWNERSHIP TRANSFERS

Organizations may maintain effective operational control of PQRs, procedure specifications, and performance qualification records under different ownership than existed during the original procedure qualification. When an organization or some part thereof is acquired by a new owner(s), the PQRs, procedure specifications, and

performance qualification records may remain valid for use by the new owner(s) without requalification; and the new owner(s) PQRs, procedure specifications, and performance qualification records become valid for use by the acquired organization, provided all of the following requirements have been met:

(a) The new owner(s) takes responsibility for the procedure specifications and performance qualification records.

(b) The procedure specifications and performance qualification records have been revised to reflect the name of the new owner(s).

(c) The Quality Control System/Quality Assurance Program documents the original source of the PQRs, procedure specifications, and performance qualification records as being from the original qualifying organization.

QG-108 QUALIFICATIONS MADE TO PREVIOUS EDITIONS

Joining procedures, procedure qualifications, and performance qualifications that were made in accordance with Editions and Addenda of this Section as far back as the 1962 Edition may be used in any construction for which the current Edition has been specified.

Joining procedures, procedure qualifications, and performance qualifications that were made in accordance with Editions and Addenda of this Section prior to the 1962 Edition may be used in any construction for which the current Edition has been specified provided the requirements of the 1962 Edition or any later edition have been met.

Procedure specifications, PQRs, and performance qualification records meeting the above requirements do not require amendment to include any variables required by later Editions and Addenda, except as specified in [QW-420](#). Qualification of new procedure specifications for joining processes, and performance qualifications for persons applying them, shall be in accordance with the current Edition of Section IX.

QG-109 DEFINITIONS

QG-109.1 GENERAL

Definitions of the more common terms relating to material-joining processes are defined in [QG-109.2](#). There are terms listed that are specific to ASME Section IX and are not presently defined in AWS A3.0. Several definitions have been modified slightly from AWS A3.0 so as to better define the context/intent as used in ASME Section IX.

QG-109.2 DEFINITIONS

arc seam weld: a seam weld made by an arc welding process.

arc spot weld: a spot weld made by an arc welding process.

arc strike: any inadvertent discontinuity resulting from an arc, consisting of any localized remelted metal, heat-affected metal, or change in the surface profile of any metal object. The arc may be caused by arc welding electrodes, magnetic inspection prods, or frayed electrical cable.

arc welding: a group of welding processes wherein coalescence is produced by heating with an arc or arcs, with or without the application of pressure, and with or without the use of filler metal.

as-brazed: adj. pertaining to the condition of brazements after brazing, prior to any subsequent thermal, mechanical, or chemical treatments.

as-welded: adj. pertaining to the condition of weld metal, welded joints, and weldments after welding but prior to any subsequent thermal, mechanical, or chemical treatments.

backgouging: the removal of weld metal and base metal from the weld root side of a welded joint to facilitate complete fusion and complete joint penetration upon subsequent welding from that side.

backhand welding: a welding technique in which the welding torch or gun is directed opposite to the progress of welding.

backing: a material placed at the root of a weld joint for the purpose of supporting molten weld metal so as to facilitate complete joint penetration. The material may or may not fuse into the joint. See also *retainer*.

backing gas: a gas, such as argon, helium, nitrogen, or reactive gas, which is employed to exclude oxygen from the root side (opposite from the welding side) of weld joints.

base metal: the metal or alloy that is welded, brazed, or cut.

bead-up cycle: part of the butt-fusing process to ensure complete contact between the heater surface and the pipe ends. The bead-up cycle begins when initial contact of the pipe ends to the heater is made at butt-fusing pressure until an indication of melt is observed around the pipe circumference.

bond line (brazing and thermal spraying): the cross section of the interface between a braze or thermal spray deposit and the substrate.

braze: a joint produced by heating an assembly to suitable temperatures and by using a filler metal having a liquidus above 840°F (450°C) and below the solidus of the base materials. The filler metal is distributed between the closely fitted surfaces of the joint by capillary action.

brazer: one who performs a manual or semiautomatic brazing operation.

brazing: a group of metal joining processes which produces coalescence of materials by heating them to a suitable temperature, and by using a filler metal having a liquidus above 840°F (450°C) and below the solidus of the base materials. The filler metal is distributed between the closely fitted surfaces of the joint by capillary action.

brazing operator: one who operates machine or automatic brazing equipment.

brazing temperature: the temperature to which the base metal(s) is heated to enable the filler metal to wet the base metal(s) and form a brazed joint.

brazing temperature range: the temperature range within which brazing can be conducted.

brazing, automatic: brazing with equipment which performs the brazing operation without constant observation and adjustment by a brazing operator. The equipment may or may not perform the loading and unloading of the work.

brazing, block (BB): a brazing process that uses heat from heated blocks applied to the joint. This is an obsolete or seldom used process.

brazing, dip (DB): a brazing process in which the heat required is furnished by a molten chemical or metal bath. When a molten chemical bath is used, the bath may act as a flux; when a molten metal bath is used, the bath provides the filler metal.

brazing, furnace (FB): a brazing process in which the workpieces are placed in a furnace and heated to the brazing temperature.

brazing, induction (IB): a brazing process that uses heat from the resistance of the workpieces to induced electric current.

brazing, machine: brazing with equipment which performs the brazing operation under the constant observation and control of a brazing operator. The equipment may or may not perform the loading and unloading of the work.

brazing, manual: a brazing operation performed and controlled completely by hand. See also *automatic brazing* and *machine brazing*.

brazing, resistance (RB): a brazing process that uses heat from the resistance to electric current flow in a circuit of which the workpieces are a part.

brazing, semiautomatic: brazing with equipment which controls only the brazing filler metal feed. The advance of the brazing is manually controlled.

brazing, torch (TB): a brazing process that uses heat from a fuel gas flame.

build-up of base metal/restoration of base metal thickness: this is the application of a weld material to a base metal so as to restore the design thickness and/or structural

integrity. This build-up may be with a chemistry different from the base metal chemistry which has been qualified via a standard butt welded test coupon. Also, may be called base metal repair or buildup.

butt joint: a joint between two members aligned approximately in the same plane.

butt-fusing cycle: pressure-time diagram for a defined fusing temperature, representing the entire butt-fusing operation.

butt-fusing pressure: the sum of the theoretical butt-fusing pressure plus the drag pressure. This is the gauge pressure used by the butt-fusing operator on the butt-fusing machine to join the pipe ends.

buttering: the addition of material, by welding, on one or both faces of a joint, prior to the preparation of the joint for final welding, for the purpose of providing a suitable transition weld deposit for the subsequent completion of the joint.

clad brazing sheet: a metal sheet on which one or both sides are clad with brazing filler metal.

coalescence: the growing together or growth into one body of the materials being joined.

complete fusion: fusion which has occurred over the entire base material surfaces intended for welding, and between all layers and beads.

composite: a material consisting of two or more discrete materials with each material retaining its physical identity.

consumable insert: filler metal that is placed at the joint root before welding, and is intended to be completely fused into the root to become part of the weld.

contact tube: a device which transfers current to a continuous electrode.

control method (FSW): the manner of monitoring and controlling the position of the rotating tool with respect to the weld joint during the friction stir welding process.

control method, force (FSW): a control method that uses a force set point, such as plunge force or travel force, to control the tool position. Under the force control method, the plunge depth or travel speed can vary, within a specified range, during welding.

control method, position (FSW): a control method that uses a set plunge position relative to the plate surface to control the tool position. Under the position control method, the plunge force can vary, within a specified range, during welding.

control method, travel (FSW): a control method that uses a set travel speed to control the tool position. Under the travel control method, the travel force can vary, within a specified range, during welding.

control specimen: a section from the base material tested to determine its tensile strength for the purpose of comparing to the tensile strength of the butt-fused joint.

cool time at butt-fusing pressure: the minimum time that the butt-fusing pressure shall be maintained between the pipe faces while the pipe joint cools. This is a function of the wall thickness.

corner joint: a joint between two members located approximately at right angles to each other in the form of an L.

coupon: see *test coupon*.

crack: a fracture-type discontinuity characterized by a sharp tip and high ratio of length and width to opening displacement.

creep strength enhanced ferritic alloys (CSEF's): a family of ferritic steels whose creep temperature strength is enhanced by the creation of a precise condition of microstructure, specifically martensite or bainite, which is stabilized during tempering by controlled precipitation of temper-resistant carbides, carbo-nitrides, or other stable and/or meta-stable phases.

data acquisition record: a detailed, permanent record of the times and pressures used in the fusing process along with the heater surface temperature, employee information, fusing machine information, pipe information, date, and time for each joint made.

defect: a discontinuity or discontinuities that by nature or accumulated effect (for example, total crack length) render a part or product unable to meet minimum applicable acceptance standards or specifications. This term designates rejectability. See also *discontinuity* and *flaw*.

direct current electrode negative (DCEN): the arrangement of direct current arc welding leads in which the electrode is the negative pole and the workpiece is the positive pole of the welding arc.

direct current electrode positive (DCEP): the arrangement of direct current arc welding leads in which the electrode is the positive pole and the workpiece is the negative pole of the welding arc.

discontinuity: an interruption of the typical structure of a material, such as a lack of homogeneity in its mechanical, metallurgical, or physical characteristics. A discontinuity is not necessarily a defect. See also *defect* and *flaw*.

double-welded joint: a joint that is welded from both sides.

double-welded lap joint: a lap joint in which the overlapped edges of the members to be joined are welded along the edges of both members.

drag pressure: the pressure required to overcome the drag resistance and frictional resistance in the butt-fusing machine and keep the carriage moving at its slowest speed.

drag resistance: force-opposing movement of the movable clamp due to the weight of the pipe.

dwell: the time during which the energy source pauses at any point in each oscillation.

electrode, arc welding: a component of the welding circuit through which current is conducted.

electrode, bare: a filler metal electrode that has been produced as a wire, strip, or bar with no coating or covering other than that incidental to its manufacture or preservation.

electrode, carbon: a nonfiller material electrode used in arc welding and cutting, consisting of a carbon or graphite rod, which may be coated with copper or other materials.

electrode, composite: a generic term of multicomponent filler metal electrodes in various physical forms, such as stranded wires, tubes, and covered electrodes.

electrode, covered: a composite filler metal electrode consisting of a core of a bare electrode or metal-cored electrode to which a covering sufficient to provide a slag layer on the weld metal has been applied. The covering may contain materials providing such functions as shielding from the atmosphere, deoxidation, and arc stabilization, and can serve as a source of metallic additions to the weld.

electrode, electroslog welding: a filler metal component of the welding circuit through which current is conducted between the electrode guiding member and the molten slag.

NOTE: Bare electrodes and composite electrodes as defined under arc welding electrode are used for electroslog welding. A consumable guide may also be used as part of the electroslog welding electrode system.

electrode, emissive: a filler metal electrode consisting of a core of a bare electrode or a composite electrode to which a very light coating has been applied to produce a stable arc.

electrode, flux-cored: a composite filler metal electrode consisting of a metal tube or other hollow configuration containing ingredients to provide such functions as shielding atmosphere, deoxidation, arc stabilization, and slag formation. Alloying materials may be included in the core. External shielding may or may not be used.

electrode, lightly coated: a filler metal electrode consisting of a metal wire with a light coating applied subsequent to the drawing operation, primarily for stabilizing the arc.

electrode, metal: a filler or nonfiller metal electrode used in arc welding and cutting that consists of a metal wire or rod that has been manufactured by any method and that is either bare or covered.

electrode, metal-cored: a composite filler metal electrode consisting of a metal tube or other hollow configuration containing alloying ingredients. Minor amounts of ingredients providing such functions as arc stabilization and fluxing of oxides may be included. External shielding gas may or may not be used.

electrode, resistance welding: the part of a resistance welding machine through which the welding current and, in most cases, force are applied directly to the workpiece. The electrode may be in the form of a rotating wheel, rotating roll, bar, cylinder, plate, clamp, chuck, or modification thereof.

electrode, stranded: a composite filler metal electrode consisting of stranded wires which may mechanically enclose materials to improve properties, stabilize the arc, or provide shielding.

electrode, tungsten: a nonfiller metal electrode used in arc welding, arc cutting, and plasma spraying, made principally of tungsten.

face feed: the application of filler metal to the face side of a joint.

ferrite number: an arbitrary, standardized value designating the ferrite content of an austenitic stainless steel weld metal. It should be used in place of percent ferrite or volume percent ferrite on a direct one-to-one replacement basis. See the latest edition of AWS A4.2, Standard Procedures for Calibrating Magnetic Instruments to Measure the Delta Ferrite Content of Austenitic Stainless Steel Weld Metal.

filler metal: the metal or alloy to be added in making a welded, brazed, or soldered joint.

filler metal, brazing: the metal or alloy used as a filler metal in brazing, which has a liquidus above 840°F (450°C) and below the solidus of the base metal.

filler metal, powder: filler metal in particle form.

filler metal, supplemental: in electroslag welding or in a welding process in which there is an arc between one or more consumable electrodes and the workpiece, a powder, solid, or composite material that is introduced into the weld other than the consumable electrode(s).

fillet weld: a weld of approximately triangular cross section joining two surfaces approximately at right angles to each other in a lap joint, tee joint, or corner joint.

flaw: an undesirable discontinuity. See also *defect*.

flux (welding/brazing): a material used to dissolve, prevent, or facilitate the removal of oxides or other undesirable surface substances. It may act to stabilize the arc, shield the molten pool, and may or may not evolve shielding gas by decomposition.

flux cover: metal bath dip brazing and dip soldering. A layer of molten flux over the molten filler metal bath.

flux, active (SAW): a flux from which the amount of elements deposited in the weld metal is dependent upon the welding parameters, primarily arc voltage.

flux, alloy (SAW): a flux which provides alloying elements in the weld metal deposit.

flux, neutral (SAW): a flux which will not cause a significant change in the weld metal composition when there is a large change in the arc voltage.

forehand welding: a welding technique in which the welding torch or gun is directed toward the progress of welding.

frequency: the completed number of cycles which the oscillating head makes in 1 min or other specified time increment.

frictional resistance in the butt-fusing machine: force-opposing movement due to friction in the mechanism of the fusing machine.

fuel gas: a gas such as acetylene, natural gas, hydrogen, propane, stabilized methylacetylene propadiene, and other fuels normally used with oxygen in one of the oxy-fuel processes and for heating.

fused spray deposit (thermal spraying): a self-fluxing thermal spray deposit which is subsequently heated to coalescence within itself and with the substrate.

fusing: the coalescence of two plastic members by the combination of controlled heating and the application of pressure approximately normal to the interface between them.

fusing gauge pressure: the hydraulic gauge pressure to be observed by the fusing machine operator when fusing PE pipe ends. This is the sum of the theoretical fusing pressure plus the drag pressure.

fusing machine operator: person trained and qualified to carry out fusing of polyethylene (PE) pipes and/or fittings using a fusing procedure.

fusing procedure: a document providing in detail the required variables for the butt-fusing process to assure repeatability in the butt-fusing procedure (FPS or SFPS).

fusion (fusion welding): the melting together of filler metal and base metal, or of base metal only, to produce a weld.

fusion face: a surface of the base metal that will be melted during welding.

fusion line: a non-standard term for weld interface.

gas backing: see *backing gas*.

globular transfer (arc welding): a type of metal transfer in which molten filler metal is transferred across the arc in large droplets.

groove weld: a weld made in a groove formed within a single member or in the groove between two members to be joined. The standard types of groove weld are as follows:

- (a) square groove weld
- (b) single-Vee groove weld
- (c) single-bevel groove weld
- (d) single-U groove weld
- (e) single-J groove weld
- (f) single-flare-bevel groove weld
- (g) single-flare-Vee groove weld
- (h) double-Vee groove weld
- (i) double-bevel groove weld
- (j) double-U groove weld
- (k) double-J groove weld
- (l) double-flare-bevel groove weld
- (m) double-flare-Vee groove weld

heat soak cycle: the portion of the procedure where heat is allowed to soak into the pipes or fittings after the bead-up cycle is complete. The heat soak cycle begins by reducing the pressure to that required to maintain contact with the heater surfaces without force. The pipe ends continue heating until the minimum heat soak time is completed for the pipe wall being joined and the minimum bead size is attained per the standard procedure.

heat soak time: the time required to complete the heat soak cycle.

heater removal (dwell) time: period of time from the separation of the pipe or fitting ends from the heater surface, removal of the heater, and closure of the carriage to bring the molten pipe or fitting ends together.

heater temperature: measured temperature on the surface of the heater where the pipe or fitting cross section makes contact.

heat-affected zone: that portion of the base metal which has not been melted, but whose mechanical properties or microstructures have been altered by the heat of welding or cutting.

Instantaneous power or energy: As used for waveform controlled welding, the determination of power or energy using the product of current and voltage measurements made at rapid intervals which capture brief changes in the welding waveform.

interfacial pressure: the amount of force per pipe joint area required to make an approved butt-fusing joint. This is used to calculate the fusing machine gauge pressure. The interfacial pressure is often expressed as a range

[example: 60 psi to 90 psi (400 kPa to 600 kPa)], and the common practice is to use the mid-range [example: 75 psi (505 kPa) when making these calculations.

interpass temperature: the highest temperature in the weld joint immediately prior to welding, or in the case of multiple pass welds, the highest temperature in the section of the previously deposited weld metal, immediately before the next pass is started.

joint: the junction of members or the edges of members which are to be joined or have been joined.

joint penetration: the distance the weld metal extends from the weld face into a joint, exclusive of weld reinforcement.

keyhole welding: a technique in which a concentrated heat source penetrates partially or completely through a workpiece, forming a hole (keyhole) at the leading edge of the weld pool. As the heat source progresses, the molten metal fills in behind the hole to form the weld bead.

lap joint: a joint between two overlapping members in parallel planes.

lap or overlap: the distance measured between the edges of two plates when overlapping to form the joint.

layer: a stratum of weld metal consisting of one or more beads. See [Figures QG-109.2.1](#) and [QG-109.2.2](#).

lower transformation temperature: the temperature at which austenite begins to form during heating.

macro-examination: the process of observing a specimen cross-section by the unaided eye, or at a specified low magnification, with or without the use of smoothing and etching.

melt bead size: the width of a bead formed at the interface between the pipe end and the heater surface during the heating cycle.

melt-in: a technique of welding in which the intensity of a concentrated heat source is so adjusted that a weld pass can be produced from filler metal added to the leading edge of the molten weld metal.

metal transfer mode (gas metal-arc welding): the manner in which molten metal travels from the end of a consumable electrode to the workpiece. See also *short-circuiting transfer (gas metal-arc welding)*; *pulsed power welding*; *globular transfer (arc welding)*; *pulsed spray welding*; and *spray transfer (arc welding)*.

nugget: the volume of weld metal formed in a spot, seam, or projection weld.

organization: as used in this Section, an organization is a manufacturer, contractor, assembler, installer, or some other single or combined entity having responsibility for operational control of the material-joining methods used

in the construction of components in accordance with the codes, standards, and specifications which reference this Section.

oscillation: for a machine or automatic process, an alternating motion relative to the direction of travel of welding, brazing, or thermal spray device. See also *weave bead*.

overlay: a non-standard term, used in Section IX, for surfacing. See also *hard-facing* and *corrosion-resistant overlay*.

overlay, corrosion-resistant weld metal: deposition of one or more layers of weld metal to the surface of a base material in an effort to improve the corrosion resistance properties of the surface. This would be applied at a level above the minimum design thickness as a nonstructural component of the overall wall thickness.

overlay, hard-facing weld metal: deposition of one or more layers of weld metal to the surface of a material in an effort to improve the wear resistance properties of the surface. This would be applied at a level above the minimum design thickness as a nonstructural component of the overall wall thickness.

pass: a single progression of a welding or surfacing operation along a joint, weld deposit, or substrate. The result of a pass is a weld bead or layer.

pass, cover: a final or cap pass(es) on the face of a weld.

pass, wash: pass to correct minor surface aberrations and/or prepare the surface for nondestructive testing.

peel test: a destructive method of testing that mechanically separates a lap joint by peeling.

peening: the mechanical working of metals using impact blows.

performance qualification: the demonstration of a welder's or welding operator's ability to produce welds meeting prescribed standards.

plastics:: those materials listed in [Table QF-422](#).

plug weld: a weld made in a circular, or other geometrically shaped hole (like a slot weld) in one member of a lap or tee joint, joining that member to the other. The walls of the hole may or may not be parallel, and the hole may be partially or completely filled with weld metal. (A fillet-welded hole or spot weld should not be construed as conforming to this definition.)

polarity, reverse: the arrangement of direct current arc welding leads with the work as the negative pole and the electrode as the positive pole of the welding arc; a synonym for direct current electrode positive.

polarity, straight: the arrangement of direct current arc welding leads in which the work is the positive pole and the electrode is the negative pole of the welding arc; a synonym for direct current electrode negative.

polyethylene (PE): a polyolefin composed of polymers of ethylene.

postbrazing heat treatment: any heat treatment subsequent to brazing.

postheating: the application of heat to an assembly after welding, brazing, soldering, thermal spraying, or thermal cutting.

postweld heat treatment: any heat treatment subsequent to welding.

postweld hydrogen bakeout: holding a completed or partially completed weld at elevated temperature below 800°F (425°C) for the purpose of allowing hydrogen diffusion from the weld.

powder: see *filler metal, powder*.

preheat current: an impulse or series of impulses that occurs prior to and is separated from the welding current.

preheat maintenance: practice of maintaining the minimum specified preheat temperature, or some specified higher temperature for some required time interval after welding or thermal spraying is finished or until post weld heat treatment is initiated.

preheat temperature: the minimum temperature in the weld joint preparation immediately prior to the welding; or in the case of multiple pass welds, the minimum temperature in the section of the previously deposited weld metal, immediately prior to welding.

preheating: the application of heat to the base metal immediately before a welding or cutting operation to achieve a specified minimum preheat temperature.

pulsed power welding: an arc welding process variation in which the welding power source is programmed to cycle between low and high power levels.

rabbit joint: typical design is indicated in [Figures QB-462.1\(c\), QB-462.4, QB-463.1\(c\), and QB-463.2\(a\)](#).

retainer: nonconsumable material, metallic or nonmetallic, which is used to contain or shape molten weld metal. See also *backing*.

seal weld: any weld designed primarily to provide a specific degree of tightness against leakage.

seam weld: a continuous weld made between or upon overlapping members in which coalescence may start and occur on the faying surfaces, or may have proceeded from the surface of one member. The continuous weld may consist of a single weld bead or a series of overlapping spot welds. See also *resistance welding*.

short-circuiting transfer (gas metal-arc welding): metal transfer in which molten metal from a consumable electrode is deposited during repeated short circuits. See also *globular transfer* and *spray transfer*.

single-welded joint: a joint welded from one side only.

single-welded lap joint: a lap joint in which the overlapped edges of the members to be joined are welded along the edge of one member only.

slag inclusion: nonmetallic solid material entrapped in weld metal or between weld metal and base metal.

specimen: see *test specimen*.

spot weld: a weld made between or upon overlapping members in which coalescence may start and occur on the faying surfaces or may proceed from the outer surface of one member. The weld cross section (plan view) is approximately circular.

spray transfer (arc welding): metal transfer in which molten metal from a consumable electrode is propelled axially across the arc in small droplets.

spray-fuse: a thermal spraying technique in which the deposit is reheated to fuse the particles and form a metallurgical bond with the substrate.

Standard Welding Procedure Specification (SWPS): a welding procedure specification, published by the American Welding Society, that is made available for production welding by companies or individuals without further qualification, and that may be used in Code applications in accordance with the restrictions and limitations of Article V.

stringer bead: a weld bead formed without appreciable weaving.

surface temper bead reinforcing layer: a subset of temper bead welding in which one or more layers of weld metal are applied on or above the surface layers of a component and are used to modify the properties of previously deposited weld metal or the heat-affected zone. Surface layer may cover a surface or only the perimeter of the weld.

surfacing: the application by welding, brazing, or thermal spraying of a layer(s) of material to a surface to obtain desired properties or dimensions, as opposed to making a joint.

tee joint (T): a joint between two members located approximately at right angles to each other in the form of a T.

temper bead welding: a weld bead placed at a specific location in or at the surface of a weld for the purpose of affecting the metallurgical properties of the heat-affected zone or previously deposited weld metal. The bead may be above, flush with, or below the surrounding base metal surface. If above the base metal surface, the beads may cover all or only part of the weld deposit and may or may not be removed following welding.

test coupon: a weld or braze assembly for procedure or performance qualification testing. The coupon may be any product from plate, pipe, tube, etc., and may be a fillet weld, overlay, deposited weld metal, etc.

test coupon, fusing: a butt-fused plastic test joint that is made to qualify a butt-fusing procedure or operator.

test specimen: a sample of a test coupon for specific test. The specimen may be a bend test, tension test, impact test, chemical analysis, macrotest, etc. A specimen may be a complete test coupon, for example, in radiographic testing or small diameter pipe tension testing.

theoretical fusing pressure: the pipe area multiplied by the interfacial pressure and divided by the total effective piston area of the butt-fusing machine.

thermal cutting (TC): a group of cutting processes that severs or removes metal by localized melting, burning, or vaporizing of the workpieces.

throat, actual (of fillet): the shortest distance from the root of a fillet weld to its face.

throat, effective (of fillet): the minimum distance from the fillet face, minus any convexity, to the weld root. In the case of fillet welds combined with a groove weld, the weld root of the groove weld shall be used.

throat, theoretical (of fillet): the distance from the beginning of the joint root perpendicular to the hypotenuse of the largest right triangle that can be inscribed within the cross-section of a fillet weld. This dimension is based on the assumption that the root opening is equal to zero.

undercut: a groove melted into the base metal adjacent to the weld toe or weld root and left unfilled by weld metal.

upper transformation temperature: the temperature at which transformation of the ferrite to austenite is completed during heating.

usability: a measure of the relative ease of application of a filler metal to make a sound weld or braze joint.

waveform controlled welding: A welding process modification of the voltage and/or current wave shape to control characteristics such as droplet shape, penetration, wetting, bead shape or transfer mode(s).

weave bead: for a manual or semiautomatic process, a weld bead formed using weaving. See also *oscillation*.

weaving: a welding technique in which the energy source is oscillated transversely as it progresses along the weld path.

weld: a localized coalescence of metals or nonmetals produced either by heating the materials to the welding temperature, with or without the application of pressure, or by the application of pressure alone and with or without the use of filler material.

weld bead: a weld deposit resulting from a pass. See also *stringer bead* and *weave bead*.

weld face: the exposed surface of a weld on the side from which welding was done.

weld interface: the interface between the weld metal and base metal in a fusion weld.

weld metal: metal in a fusion weld consisting of that portion of the base metal and filler metal melted during welding.

weld reinforcement: weld metal on the face or root of a groove weld in excess of the metal necessary for the specified weld size.

weld size: for equal leg fillet welds: the leg lengths of the largest isosceles right triangle which can be inscribed within the fillet weld cross section.

weld size: for unequal leg fillet welds: the leg lengths of the largest right triangle which can be inscribed within the fillet weld cross section.

weld size: groove welds: the depth of chamfering plus any penetration beyond the chamfering, resulting in the strength carrying dimension of the weld.

weld, autogenous: a fusion weld made without filler metal.

welder: one who performs manual or semiautomatic welding.

welding operator: one who operates machine or automatic welding equipment.

welding, arc stud (SW): an arc welding process that uses an arc between a metal stud, or similar part, and the other workpiece. The process is used without filler metal, with or without shielding gas or flux, with or without partial shielding from a ceramic or graphite ferrule surrounding the stud, and with the application of pressure after the faying surfaces are sufficiently heated.

welding, automatic: welding with equipment which performs the welding operation without adjustment of the controls by a welding operator. The equipment may or may not perform the loading and unloading of the work. See also *machine welding*.

welding, consumable guide electroslag: an electroslag welding process variation in which filler metal is supplied by an electrode and its guiding member.

welding, diffusion (DFW): a solid-state welding process producing a weld between multiple layers of sheet or plate by the application of mechanical pressure at elevated temperature with no macroscopic deformation or relative motion of the work pieces. A solid filler metal may be inserted between the faying surfaces.

welding, electrogas (EGW): an arc welding process that uses an arc between a continuous filler metal electrode and the weld pool, employing approximately vertical welding progression with retainers to confine the weld metal. The process is used with or without an externally supplied shielding gas and without the application of pressure. Shielding for use with solid or metal-cored electrodes is obtained from a gas or gas mixture. Shielding for use with flux-cored electrodes may or may not be obtained from an externally supplied gas or gas mixture.

welding, electron beam (EBW): a welding process that produces coalescence with a concentrated beam composed primarily of high velocity electrons, impinging on the joint. The process is used without shielding gas and without the application of pressure.

welding, electroslag (ESW): a welding process producing coalescence of metals with molten slag which melts the filler metal and the surfaces of the work to be welded. The molten weld pool is shielded by this slag which moves along the full cross section of the joint as welding progresses. The process is initiated by an arc which heats the slag. The arc is then extinguished and the conductive slag is maintained in a molten condition by its resistance to electric current passing between the electrode and the work. See electroslag welding electrode and consumable guide electroslag welding.

welding, flux-cored arc (FCAW): a gas metal-arc welding process that uses an arc between a continuous filler metal electrode and the weld pool. The process is used with shielding gas from a flux contained within the tubular electrode, with or without additional shielding from an externally supplied gas, and without the application of pressure.

welding, friction (FRW): a solid state welding process that produces a weld under compressive force contact of workpieces rotating or moving relative to one another to produce heat and plastically displace material from the faying surfaces.

welding, friction stir (FSW): a variation of friction welding producing a weld by the friction heating and plastic material displacement caused by a rapidly rotating tool traversing the weld joint.

welding, friction, inertia and continuous drive: processes and types of friction welding (solid state welding process) wherein coalescence is produced after heating is obtained from mechanically induced sliding motion between rubbing surfaces held together under pressure. Inertia welding utilizes all of the kinetic energy stored in a revolving flywheel spindle system. Continuous drive friction welding utilizes the energy provided by a continuous drive source such as an electric or hydraulic motor.

welding, gas metal-arc (GMAW): an arc welding process that uses an arc between a continuous filler metal electrode and the weld pool. The process is used with shielding from an externally supplied gas and without the application of pressure.

welding, gas metal-arc, pulsed spray (GMAW-P): a variation of the gas metal-arc welding process in which the power is pulsed resulting in transfer of the metal across the arc in spray mode. See also *pulsed power welding*.

welding, gas metal-arc, short-circuiting arc (GMAW-S): a variation of the gas metal-arc welding process in which the consumable electrode is deposited during repeated short circuits. See also *short-circuiting transfer*.

welding, gas tungsten-arc (GTAW): an arc welding process which produces coalescence of metals by heating them with an arc between a tungsten (nonconsumable) electrode and the work. Shielding is obtained from a gas or gas mixture. Pressure may or may not be used and filler metal may or may not be used. (This process has sometimes been called TIG welding, a nonpreferred term.)

welding, gas tungsten-arc, pulsed arc (GTAW-P): a variation of the gas tungsten-arc welding process in which the current is pulsed. See also *pulsed power welding*.

welding, hybrid: welding in which two or more welding processes are used in the same weld pool.

welding, hybrid, process separation: the distance between each welding process as specified in the WPS.

welding, hybrid, process sequence: the order of each welding process with respect to the direction of travel.

welding, induction (IW): a welding process that produces coalescence of metals by the heat obtained from resistance of the workpieces to the flow of induced high frequency welding current with or without the application of pressure. The effect of the high-frequency welding current is to concentrate the welding heat at the desired location.

welding, laser beam (LBW): a welding process which produces coalescence of materials with the heat obtained from the application of a concentrated coherent light beam impinging upon the members to be joined.

welding, machine: welding with equipment that has controls that can be adjusted by the welding operator, or adjusted under the welding operator's direction, in response to changes in the welding conditions. The torch, gun, or electrode holder is held by a mechanical device. See also *welding, automatic*.

welding, manual: welding wherein the entire welding operation is performed and controlled by hand.

welding, oxyfuel gas (OFW): a group of welding processes which produces coalescence by heating materials with an oxyfuel gas flame or flames, with or without the application of pressure, and with or without the use of filler metal.

welding, plasma-arc (PAW): an arc welding process which produces coalescence of metals by heating them with a constricted arc between an electrode and the workpiece (transferred arc), or the electrode and the constricting nozzle (nontransferred arc). Shielding is obtained from the hot, ionized gas issuing from the torch orifice which may be supplemented by an auxiliary source of shielding gas. Shielding gas may be an inert gas or a mixture of gases. Pressure may or may not be used, and filler metal may or may not be supplied.

welding, projection (PW): a resistance welding process that produces coalescence by the heat obtained from the resistance of the flow of welding current. The resulting welds are localized at predetermined points by projections, embossments, or intersections. The metals to be joined lap over each other.

welding, resistance (RW): a group of welding processes that produces coalescence of the faying surfaces with the heat obtained from resistance of the workpieces to the flow of the welding current in a circuit of which the workpieces are a part, and by the application of pressure.

welding, resistance seam (RSEW): a resistance welding process that produces a weld at the faying surfaces of overlapped parts progressively along a length of a joint. The weld may be made with overlapping weld nuggets, a continuous weld nugget, or by forging the joint as it is heated to the welding temperature by resistance to the flow of the welding current.

welding, resistance spot (RSW): a resistance welding process that produces a weld at the faying surfaces of a joint by the heat obtained from resistance to the flow of welding current through the workpieces from electrodes that serve to concentrate the welding current and pressure at the weld area.

welding, resistance stud: a resistance welding process wherein coalescence is produced by the heat obtained from resistance to electric current at the interface between the stud and the workpiece, until the surfaces to be joined are properly heated, when they are brought together under pressure.



welding, semiautomatic arc: arc welding with equipment which controls only the filler metal feed. The advance of the welding is manually controlled.

welding, shielded metal-arc (SMAW): an arc welding process with an arc between a covered electrode and the weld pool. The process is used with shielding from the decomposition of the electrode covering, without the application of pressure, and with filler metal from the electrode.

welding, stud: a general term for the joining of a metal stud or similar part to a workpiece. Welding may be accomplished by arc, resistance, friction, or other suitable process with or without external gas shielding.

welding, submerged-arc (SAW): an arc welding process that uses an arc or arcs between a bare metal electrode or electrodes and the weld pool. The arc and molten metal are shielded by a blanket of granular flux on the workpieces. The process is used without pressure and with filler metal from the electrode and sometimes from a supplemental source (welding rod, flux, or metal granules).

weldment: an assembly whose constituent parts are joined by welding, or parts which contain weld metal overlay.

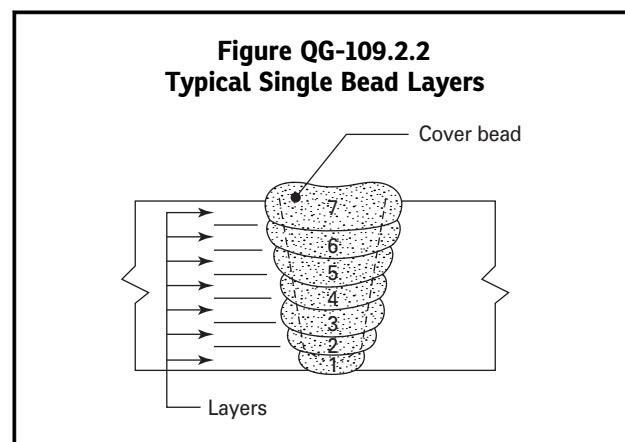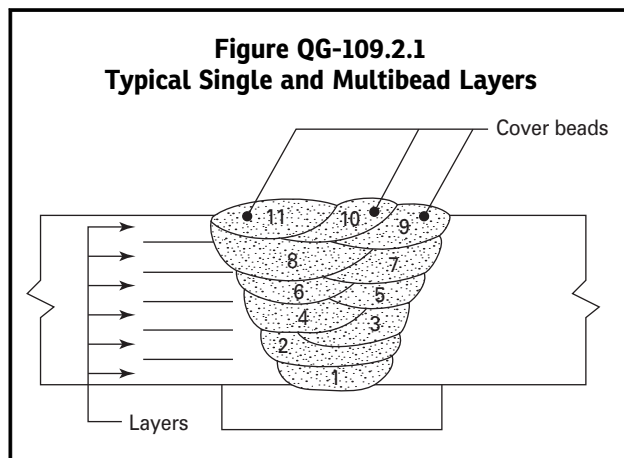

PART QW WELDING

ARTICLE I WELDING GENERAL REQUIREMENTS

(13) QW-100 SCOPE

The rules in this Part apply to the preparation of Welding Procedure Specifications (WPS) and the qualification of welding procedures, welders, and welding operators for all types of manual and machine welding processes permitted in this Part. These rules may also be applied, insofar as they are applicable, to other manual or machine welding processes permitted in other Sections.

QW-101

A WPS used by an organization that will have responsible operational control of production welding shall be a WPS that has been qualified by that organization in accordance with [Article II](#), or it shall be an AWS Standard Welding Procedure Specification (SWPS) listed in [Mandatory Appendix E](#) and adopted by that organization in accordance with [Article V](#).

Both WPSs and SWPSs specify the variables (including ranges, if any) under which welding must be performed. These conditions include the base metals that are permitted, the filler metals that must be used (if any), preheat and postweld heat treatment requirements, etc.

When a WPS is to be prepared by the organization, it must address, as a minimum, the specific variables, both essential and nonessential, as provided in [Article II](#) for each process to be used in production welding. In addition, when other Sections of the Code require notch toughness qualification of the WPS, the supplementary essential variables must be addressed in the WPS.

QW-102

In performance qualification, the basic criterion established for welder qualification is to determine the welder's ability to deposit sound weld metal. The purpose of the performance qualification test for the welding operator is to determine the welding operator's mechanical ability to operate the welding equipment.

QW-103 RESPONSIBILITY

QW-103.1 Welding. Each organization shall conduct the tests required in this Section to qualify the welding procedures used in the construction of the weldments built under this Code and the performance of welders and welding operators who apply these procedures.

QW-103.2 Records. Each organization shall maintain a record of the results obtained in welding procedure and welder and welding operator performance qualifications. Refer to recommended Forms in [Nonmandatory Appendix B](#).

QW-110 WELD ORIENTATION

The orientations of welds are illustrated in [Figure QW-461.1](#) or [Figure QW-461.2](#).

QW-120 TEST POSITIONS FOR GROOVE WELDS

Groove welds may be made in test coupons oriented in any of the positions in [Figure QW-461.3](#) or [Figure QW-461.4](#) and as described in the following paragraphs, except that an angular deviation of ± 15 deg from the specified horizontal and vertical planes, and an angular deviation of ± 5 deg from the specified inclined plane are permitted during welding.

QW-121 PLATE POSITIONS

QW-121.1 Flat Position 1G. Plate in a horizontal plane with the weld metal deposited from above. Refer to [Figure QW-461.3](#), illustration (a).

QW-121.2 Horizontal Position 2G. Plate in a vertical plane with the axis of the weld horizontal. Refer to [Figure QW-461.3](#), illustration (b).

QW-121.3 Vertical Position 3G. Plate in a vertical plane with the axis of the weld vertical. Refer to [Figure QW-461.3](#), illustration (c).

QW-121.4 Overhead Position 4G. Plate in a horizontal plane with the weld metal deposited from underneath. Refer to [Figure QW-461.3](#), illustration (d).

QW-122 PIPE POSITIONS

QW-122.1 Flat Position 1G. Pipe with its axis horizontal and rolled during welding so that the weld metal is deposited from above. Refer to [Figure QW-461.4](#), illustration (a).

QW-122.2 Horizontal Position 2G. Pipe with its axis vertical and the axis of the weld in a horizontal plane. Pipe shall not be rotated during welding. Refer to [Figure QW-461.4](#), illustration (b).

QW-122.3 Multiple Position 5G. Pipe with its axis horizontal and with the welding groove in a vertical plane. Welding shall be done without rotating the pipe. Refer to [Figure QW-461.4](#), illustration (c).

QW-122.4 Multiple Position 6G. Pipe with its axis inclined at 45 deg to horizontal. Welding shall be done without rotating the pipe. Refer to [Figure QW-461.4](#), illustration (d).

QW-123 TEST POSITIONS FOR STUD WELDS

QW-123.1 Stud Welding. Stud welds may be made in test coupons oriented in any of the positions as described in [QW-121](#) for plate and [QW-122](#) for pipe (excluding [QW-122.1](#)). In all cases, the stud shall be perpendicular to the surface of the plate or pipe. See [Figures QW-461.7](#) and [QW-461.8](#).

QW-130 TEST POSITIONS FOR FILLET WELDS

Fillet welds may be made in test coupons oriented in any of the positions of [Figure QW-461.5](#) or [Figure QW-461.6](#), and as described in the following paragraphs, except that an angular deviation of ± 15 deg from the specified horizontal and vertical planes is permitted during welding.

QW-131 PLATE POSITIONS

QW-131.1 Flat Position 1F. Plates so placed that the weld is deposited with its axis horizontal and its throat vertical. Refer to [Figure QW-461.5](#), illustration (a).

QW-131.2 Horizontal Position 2F. Plates so placed that the weld is deposited with its axis horizontal on the upper side of the horizontal surface and against the vertical surface. Refer to [Figure QW-461.5](#), illustration (b).

QW-131.3 Vertical Position 3F. Plates so placed that the weld is deposited with its axis vertical. Refer to [Figure QW-461.5](#), illustration (c).

QW-131.4 Overhead Position 4F. Plates so placed that the weld is deposited with its axis horizontal on the underside of the horizontal surface and against the vertical surface. Refer to [Figure QW-461.5](#), illustration (d).

QW-132 PIPE POSITIONS

QW-132.1 Flat Position 1F. Pipe with its axis inclined at 45 deg to horizontal and rotated during welding so that the weld metal is deposited from above and at the point of deposition the axis of the weld is horizontal and the throat vertical. Refer to [Figure QW-461.6](#), illustration (a).

QW-132.2 Horizontal Positions 2F and 2FR.

(a) *Position 2F.* Pipe with its axis vertical so that the weld is deposited on the upper side of the horizontal surface and against the vertical surface. The axis of the weld will be horizontal and the pipe is not to be rotated during welding. Refer to [Figure QW-461.6](#), illustration (b).

(b) *Position 2FR.* Pipe with its axis horizontal and the axis of the deposited weld in the vertical plane. The pipe is rotated during welding. Refer to [Figure QW-461.6](#), illustration (c).

QW-132.3 Overhead Position 4F. Pipe with its axis vertical so that the weld is deposited on the underside of the horizontal surface and against the vertical surface. The axis of the weld will be horizontal and the pipe is not to be rotated during welding. Refer to [Figure QW-461.6](#), illustration (d).

QW-132.4 Multiple Position 5F. Pipe with its axis horizontal and the axis of the deposited weld in the vertical plane. The pipe is not to be rotated during welding. Refer to [Figure QW-461.6](#), illustration (e).

QW-140 TYPES AND PURPOSES OF TESTS AND EXAMINATIONS

QW-141 MECHANICAL TESTS

Mechanical tests used in procedure or performance qualification are specified in [QW-141.1](#) through [QW-141.5](#).

QW-141.1 Tension Tests. Tension tests as described in [QW-150](#) are used to determine the ultimate strength of groove-weld joints.

QW-141.2 Guided-Bend Tests. Guided-bend tests as described in [QW-160](#) are used to determine the degree of soundness and ductility of groove-weld joints.

QW-141.3 Fillet-Weld Tests. Tests as described in [QW-180](#) are used to determine the size, contour, and degree of soundness of fillet welds.

QW-141.4 Notch-Toughness Tests. Tests as described in [QW-171](#) and [QW-172](#) are used to determine the notch toughness of the weldment.

QW-141.5 Stud-Weld Test. Deflection bend, hammering, torque, or tension tests as shown in Figures QW-466.4, QW-466.5, and QW-466.6, and a macro-examination performed in accordance with QW-202.5, respectively, are used to determine acceptability of stud welds.

QW-142 SPECIAL EXAMINATIONS FOR WELDERS

Radiographic or Ultrasonic examination per QW-191 may be substituted for mechanical testing of QW-141 for groove-weld performance qualification as permitted in QW-304 to prove the ability of welders to make sound welds.

QW-143 EXAMINATION FOR WELDING OPERATORS

Radiographic or Ultrasonic examination per QW-191 may be substituted for mechanical testing of QW-141 for groove weld performance qualification as permitted in QW-305 to prove the ability of welding operators to make sound welds.

QW-144 VISUAL EXAMINATION

Visual examination as described in QW-194 is used to determine that the final weld surfaces meet specified quality standards.

QW-150 TENSION TESTS

QW-151 SPECIMENS

Tension test specimens shall conform to one of the types illustrated in Figures QW-462.1(a) through QW-462.1(e) and shall meet the requirements of QW-153.

QW-151.1 Reduced Section — Plate. Reduced-section specimens conforming to the requirements given in Figure QW-462.1(a) may be used for tension tests on all thicknesses of plate.

(a) For thicknesses up to and including 1 in. (25 mm), a full thickness specimen shall be used for each required tension test.

(b) For plate thickness greater than 1 in. (25 mm), full thickness specimens or multiple specimens may be used, provided (c) and (d) are complied with.

(c) When multiple specimens are used, in lieu of full thickness specimens, each set shall represent a single tension test of the full plate thickness. Collectively, all of the specimens required to represent the full thickness of the weld at one location shall comprise a set.

(d) When multiple specimens are necessary, the entire thickness shall be mechanically cut into a minimum number of approximately equal strips of a size that can be tested in the available equipment. Each specimen of the set shall be tested and meet the requirements of QW-153.

QW-151.2 Reduced Section — Pipe. Reduced-section specimens conforming to the requirements given in Figure QW-462.1(b) may be used for tension tests on all thicknesses of pipe having an outside diameter greater than 3 in. (75 mm).

(a) For thicknesses up to and including 1 in. (25 mm), a full thickness specimen shall be used for each required tension test.

(b) For pipe thicknesses greater than 1 in. (25 mm), full thickness specimens or multiple specimens may be used, provided (c) and (d) are complied with.

(c) When multiple specimens are used, in lieu of full thickness specimens, each set shall represent a single tension test of the full pipe thickness. Collectively, all of the specimens required to represent the full thickness of the weld at one location shall comprise a set.

(d) When multiple specimens are necessary, the entire thickness shall be mechanically cut into a minimum number of approximately equal strips of a size that can be tested in the available equipment. Each specimen of the set shall be tested and meet the requirements of QW-153.

For pipe having an outside diameter of 3 in. (75 mm) or less, reduced-section specimens conforming to the requirements given in Figure QW-462.1(c) may be used for tension tests.

QW-151.3 Turned Specimens. Turned specimens conforming to the requirements given in Figure QW-462.1(d) may be used for tension tests.

(a) For thicknesses up to and including 1 in. (25 mm), a single turned specimen may be used for each required tension test, which shall be a specimen of the largest diameter D of Figure QW-462.1(d) possible for test coupon thickness [per Note (a) of Figure QW-462.1(d)].

(b) For thicknesses over 1 in. (25 mm), multiple specimens shall be cut through the full thickness of the weld with their centers parallel to the metal surface and not over 1 in. (25 mm) apart. The centers of the specimens adjacent to the metal surfaces shall not exceed $\frac{5}{8}$ in. (16 mm) from the surface.

(c) When multiple specimens are used, each set shall represent a single required tension test. Collectively, all the specimens required to represent the full thickness of the weld at one location shall comprise a set.

(d) Each specimen of the set shall be tested and meet the requirements of QW-153.

QW-151.4 Full-Section Specimens for Pipe. Tension specimens conforming to the dimensions given in Figure QW-462.1(e) may be used for testing pipe with an outside diameter of 3 in. (75 mm) or less.

QW-152 TENSION TEST PROCEDURE

The tension test specimen shall be ruptured under tensile load. The tensile strength shall be computed by dividing the ultimate total load by the least cross-sectional area of the specimen as calculated from actual measurements made before the load is applied.

QW-153 ACCEPTANCE CRITERIA — TENSION TESTS

QW-153.1 Tensile Strength. Minimum values for procedure qualification are provided under the column heading “Minimum Specified Tensile, ksi” of [Table QW/QB-422](#). In order to pass the tension test, the specimen shall have a tensile strength that is not less than

(a) the minimum specified tensile strength of the base metal; or

(b) the minimum specified tensile strength of the weaker of the two, if base metals of different minimum tensile strengths are used; or

(c) the minimum specified tensile strength of the weld metal when the applicable Section provides for the use of weld metal having lower room temperature strength than the base metal;

(d) if the specimen breaks in the base metal outside of the weld or weld interface, the test shall be accepted as meeting the requirements, provided the strength is not more than 5% below the minimum specified tensile strength of the base metal.

(e) the specified minimum tensile strength is for full thickness specimens including cladding for Aluminum Alclad materials (P-No. 21 through P-No. 23) less than $\frac{1}{2}$ in. (13 mm). For Aluminum Alclad materials $\frac{1}{2}$ in. (13 mm) and greater, the specified minimum tensile strength is for both full thickness specimens that include cladding and specimens taken from the core.

QW-160 GUIDED-BEND TESTS

QW-161 SPECIMENS

Guided-bend test specimens shall be prepared by cutting the test plate or pipe to form specimens of approximately rectangular cross section. The cut surfaces shall be designated the sides of the specimen. The other two surfaces shall be called the face and root surfaces, the face surface having the greater width of weld. The specimen thickness and bend radius are shown in [Figures QW-466.1](#), [QW-466.2](#), and [QW-466.3](#). Guided-bend specimens are of five types, depending on whether the axis of the weld is transverse or parallel to the longitudinal axis of the specimen, and which surface (side, face, or root) is on the convex (outer) side of bent specimen. The five types are defined as follows.

QW-161.1 Transverse Side Bend. The weld is transverse to the longitudinal axis of the specimen, which is bent so that one of the side surfaces becomes the convex surface of the bent specimen. Transverse side-bend test specimens shall conform to the dimensions shown in [Figure QW-462.2](#).

Specimens of base metal thickness equal to or greater than $1\frac{1}{2}$ in. (38 mm) may be cut into approximately equal strips between $\frac{3}{4}$ in. (19 mm) and $1\frac{1}{2}$ in. (38 mm) wide for testing, or the specimens may be bent at full width (see requirements on jig width in [QW-466](#)). When the

width of the weld is so large that a bend specimen cannot be bent so that the entire weld and heat affected zones are within the bent portion, multiple specimens across the entire weld and heat affected zones shall be used.

If multiple specimens are used in either situation above, one complete set shall be made for each required test. Each specimen shall be tested and meet the requirements in [QW-163](#).

QW-161.2 Transverse Face Bend. The weld is transverse to the longitudinal axis of the specimen, which is bent so that the face surface becomes the convex surface of the bent specimen. Transverse face-bend test specimens shall conform to the dimensions shown in [Figure QW-462.3\(a\)](#). For subsize transverse face bends, see [QW-161.4](#).

QW-161.3 Transverse Root Bend. The weld is transverse to the longitudinal axis of the specimen, which is bent so that the root surface becomes the convex surface of the bent specimen. Transverse root-bend test specimens shall conform to the dimensions shown in [Figure QW-462.3\(a\)](#). For subsize transverse root bends, see [QW-161.4](#).

QW-161.4 Subsize Transverse Face and Root Bends. Bend specimens taken from small diameter pipe coupons may be subsize in accordance with General Note (b) of [Figure QW-462.3\(a\)](#).

QW-161.5 Longitudinal-Bend Tests. Longitudinal-bend tests may be used in lieu of the transverse side-bend, face-bend, and root-bend tests for testing weld metal or base metal combinations, which differ markedly in bending properties between

(a) the two base metals, or

(b) the weld metal and the base metal

QW-161.6 Longitudinal Face Bend. The weld is parallel to the longitudinal axis of the specimen, which is bent so that the face surface becomes the convex surface of the bent specimen. Longitudinal face-bend test specimens shall conform to the dimensions shown in [Figure QW-462.3\(b\)](#).

QW-161.7 Longitudinal Root Bend. The weld is parallel to the longitudinal axis of the specimen, which is bent so that the root surface becomes the convex side of the bent specimen. Longitudinal root-bend test specimens shall conform to the dimensions shown in [Figure QW-462.3\(b\)](#).

QW-162 GUIDED-BEND TEST PROCEDURE

QW-162.1 Jigs. Guided-bend specimens shall be bent in test jigs that are in substantial accordance with [QW-466](#). When using the jigs illustrated in [Figure QW-466.1](#) or [Figure QW-466.2](#), the side of the specimen turned toward the gap of the jig shall be the face for face-bend specimens, the root for root-bend specimens, and the side with the greater discontinuities, if any, for side-bend specimens. The specimen shall be forced into the die by

applying load on the plunger until the curvature of the specimen is such that a $\frac{1}{8}$ in. (3 mm) diameter wire cannot be inserted between the specimen and the die of [Figure QW-466.1](#), or the specimen is bottom ejected if the roller type of jig ([Figure QW-466.2](#)) is used.

When using the wrap around jig ([Figure QW-466.3](#)), the side of the specimen turned toward the roller shall be the face for face-bend specimens, the root for root-bend specimens, and the side with the greater discontinuities, if any, for side-bend specimens.

When specimens wider than $1\frac{1}{2}$ in. (38 mm) are to be bent as permitted in [Figure QW-462.2](#), the test jig mandrel must be at least $\frac{1}{4}$ in. (6 mm) wider than the specimen width.

QW-163 ACCEPTANCE CRITERIA — BEND TESTS

The weld and heat-affected zone of a transverse weld-bend specimen shall be completely within the bent portion of the specimen after testing.

The guided-bend specimens shall have no open discontinuity in the weld or heat-affected zone exceeding $\frac{1}{8}$ in. (3 mm), measured in any direction on the convex surface of the specimen after bending. Open discontinuities occurring on the corners of the specimen during testing shall not be considered unless there is definite evidence that they result from lack of fusion, slag inclusions, or other internal discontinuities. For corrosion-resistant weld overlay cladding, no open discontinuity exceeding $\frac{1}{16}$ in. (1.5 mm), measured in any direction, shall be permitted in the cladding, and no open discontinuity exceeding $\frac{1}{8}$ in. (3 mm) shall be permitted along the approximate weld interface.

QW-170 NOTCH-TOUGHNESS TESTS

QW-171 NOTCH-TOUGHNESS TESTS — CHARPY V-NOTCH

QW-171.1 General. Charpy V-notch impact tests shall be made when required by other Sections.

Test procedures and apparatus shall conform to the requirements of SA-370.

QW-171.2 Acceptance. The acceptance criteria shall be in accordance with that Section specifying impact requirements.

QW-171.3 Location and Orientation of Test Specimen. The impact test specimen and notch location and orientation shall be as given in the Section requiring such tests.

When qualifying pipe in the 5G or 6G position, the notch-toughness specimens shall be removed from the shaded portion of [Figure QW-463.1\(f\)](#).

QW-172 NOTCH-TOUGHNESS TESTS — DROP WEIGHT

QW-172.1 General. Drop weight tests shall be made when required by other Sections.

Test procedures and apparatus shall conform to the requirements of ASTM Specification E208.

QW-172.2 Acceptance. The acceptance criteria shall be in accordance with that Section requiring drop weight tests.

QW-172.3 Location and Orientation of Test Specimen. The drop weight test specimen, the crack starter location, and the orientation shall be as given in the Section requiring such tests.

When qualifying pipe in the 5G or 6G position, the notch-toughness specimens shall be removed from the shaded portion of [Figure QW-463.1\(f\)](#).

QW-180 FILLET-WELD TESTS

QW-181 PROCEDURE AND PERFORMANCE QUALIFICATION SPECIMENS

QW-181.1 Procedure. The dimensions and preparation of the fillet-weld test coupon for procedure qualification as required in [QW-202](#) shall conform to the requirements in [Figure QW-462.4\(a\)](#) or [Figure QW-462.4\(d\)](#). The test coupon for plate-to-plate shall be cut transversely to provide five test specimen sections, each approximately 2 in. (50 mm) long. For pipe-to-plate or pipe-to-pipe, the test coupon shall be cut transversely to provide four approximately equal test specimen sections. The test specimens shall be macro-examined to the requirements of [QW-183](#).

QW-181.1.1 Production Assembly Mockups . Production assembly mockups may be used in lieu of [QW-181.1](#). The mockups for plate-to-plate shall be cut transversely to provide five approximately equal test specimens not to exceed approximately 2 in. (50 mm) in length. For pipe-to-plate mockups, the mockup shall be cut transversely to provide four approximately equal test specimens. For small mockups, multiple mockups may be required to obtain the required number of test specimens. The test specimens shall be macro-examined to the requirements of [QW-183](#).

QW-181.2 Performance. The dimensions and the preparation of the fillet-weld test coupon for performance qualification shall conform to the requirements in [Figure QW-462.4\(b\)](#) or [Figure QW-462.4\(c\)](#). The test coupon for plate-to-plate shall be cut transversely to provide a center section approximately 4 in. (100 mm) long and two end sections, each approximately 1 in. (25 mm) long. For pipe-to-plate or pipe-to-pipe, the test coupon shall be cut to provide two quarter sections test specimens opposite to each other. One of the test specimens shall be fracture tested in accordance with [QW-182](#) and the other macro-examined to the requirements of [QW-184](#). When

qualifying pipe-to-plate or pipe-to-pipe in the 5F position, the test specimens shall be removed as indicated in Figure QW-463.2(h).

QW-181.2.1 Production Assembly Mockups . Production assembly mockups may be used in lieu of the fillet-weld test coupon requirements of QW-181.2.

(a) Plate-to-Shape

(1) The mockup for plate-to-shape shall be cut transversely to provide three approximately equal test specimens not to exceed approximately 2 in. (50 mm) in length. The test specimen that contains the start and stop of the weld shall be fracture tested in accordance with QW-182. A cut end of one of the remaining test specimens shall be macro-examined in accordance with QW-184.

(b) Pipe-to-Shape

(1) The mockup for pipe-to-shape shall be cut transversely to provide two quarter sections approximately opposite to each other. The test specimen that contains the start and stop of the weld shall be fracture tested in accordance with QW-182. A cut end of the other quarter section shall be macro-examined in accordance with QW-184. When qualifying pipe-to-shape in the 5F position, the fracture specimen shall be removed from the lower 90 deg section of the mockup.

QW-182 FRACTURE TESTS

The stem of the 4 in. (100 mm) performance specimen center section in Figure QW-462.4(b) or the stem of the quarter section in Figure QW-462.4(c), as applicable, shall be loaded laterally in such a way that the root of the weld is in tension. The load shall be steadily increased until the specimen fractures or bends flat upon itself.

If the specimen fractures, the fractured surface shall show no evidence of cracks or incomplete root fusion, and the sum of the lengths of inclusions and porosity visible on the fractured surface shall not exceed $\frac{3}{8}$ in. (10 mm) in Figure QW-462.4(b) or 10% of the quarter section in Figure QW-462.4(c).

QW-183 MACRO-EXAMINATION — PROCEDURE SPECIMENS

One face of each cross section of the five test specimens in Figure QW-462.4(a) or four test specimens in Figure QW-462.4(d), as applicable shall be smoothed and etched with a suitable etchant (see QW-470) to give a clear definition to the weld metal and heat affected zone. The examination of the cross sections shall include only one side of the test specimen at the area where the plate or pipe is divided into sections i.e., adjacent faces at the cut shall not be used. In order to pass the test

(a) visual examination of the cross sections of the weld metal and heat-affected zone shall show complete fusion and freedom from cracks

(b) there shall be not more than $\frac{1}{8}$ in. (3 mm) difference in the length of the legs of the fillet

QW-184 MACRO-EXAMINATION — PERFORMANCE SPECIMENS

The cut end of one of the end plate sections, approximately 1 in. (25 mm) long, in Figure QW-462.4(b) or the cut end of one of the pipe quarter sections in Figure QW-462.4(c), as applicable, shall be smoothed and etched with a suitable etchant (see QW-470) to give a clear definition of the weld metal and heat affected zone. In order to pass the test

(a) visual examination of the cross section of the weld metal and heat-affected zone shall show complete fusion and freedom from cracks, except that linear indications at the root not exceeding $\frac{1}{32}$ in. (0.8 mm) shall be acceptable

(b) the weld shall not have a concavity or convexity greater than $\frac{1}{16}$ in. (1.5 mm)

(c) there shall be not more than $\frac{1}{8}$ in. (3 mm) difference in the lengths of the legs of the fillet

QW-185 DIFFUSION WELDING — PROCEDURE AND PERFORMANCE QUALIFICATION SPECIMENS

QW-185.1 The test block shall be a minimum of 8 in. x 8 in. (200 mm x 200 mm) and of a thickness such that there are at least 50 interface planes being welded.

QW-185.2 A minimum of three tension test specimens in accordance with the requirements of SA-370 shall be taken perpendicular to the interface planes and three parallel to the interface planes. The tension test results shall comply with QW-153.

QW-185.3 Microstructural evaluation shall be conducted in accordance with the requirements of ASTM E3 on a minimum of three cross-sections, one each from the top, center, and bottom one-third of the test coupon. The samples shall be polished, etched, and shall be free from cracks and shall show no incomplete bond or porosity on or adjacent to the bond lines. Size of each sample shall be that which can be mounted and polished to allow examination with an optical microscope at 50x to 100x magnification.

QW-190 OTHER TESTS AND EXAMINATIONS

QW-191 VOLUMETRIC NDE

QW-191.1 Radiographic Examination

QW-191.1.1 Method

The radiographic examination in QW-142 for welders and in QW-143 for welding operators shall meet the requirements of Article 2, Section V, except as follows:

(a) A written radiographic examination procedure is not required. Demonstration of density and image quality requirements on production or technique radiographs shall be considered satisfactory evidence of compliance with Article 2 of Section V.

(b) Final acceptance of radiographs shall be based on the ability to see the prescribed image and the specified hole of a hole-type image quality indicator (IQI) or the designated wire of a wire-type IQI. The acceptance standards of QW-191.1.2 shall be met.

QW-191.1.2 Acceptance Criteria.

QW-191.1.2.1 Terminology.

(a) *Linear Indications.* Cracks, incomplete fusion, inadequate penetration, and slag are represented on the radiograph as linear indications in which the length is more than three times the width.

(b) *Rounded Indications.* Porosity and inclusions such as slag or tungsten are represented on the radiograph as rounded indications with a length three times the width or less. These indications may be circular, elliptical, or irregular in shape; may have tails; and may vary in density.

(13) **QW-191.1.2.2 Qualification Test Welds.** Welder and welding operator performance tests by radiography of welds in test assemblies shall be judged unacceptable when the radiograph exhibits any imperfections in excess of the limits specified below

(a) *Linear Indications*

(1) any type of crack or zone of incomplete fusion or penetration

(2) any elongated slag inclusion which has a length greater than

(-a) $\frac{1}{8}$ in. (3 mm) for t up to $\frac{3}{8}$ in. (10 mm), inclusive

(-b) $\frac{1}{3}t$ for t over $\frac{3}{8}$ in. (10 mm) to $2\frac{1}{4}$ in. (57 mm), inclusive

(-c) $\frac{3}{4}$ in. (19 mm) for t over $2\frac{1}{4}$ in. (57 mm)

(3) any group of slag inclusions in line that have an aggregate length greater than t in a length of $12t$, except when the distance between the successive imperfections exceeds $6L$ where L is the length of the longest imperfection in the group


(b) *Rounded Indications*

(1) The maximum permissible dimension for rounded indications shall be 20% of t or $\frac{1}{8}$ in. (3 mm), whichever is smaller.


(2) For welds in material less than $\frac{1}{8}$ in. (3 mm) in thickness, the maximum number of acceptable rounded indications shall not exceed 12 in a 6 in. (150 mm) length of weld. A proportionately fewer number of rounded indications shall be permitted in welds less than 6 in. (150 mm) in length.

(3) For welds in material $\frac{1}{8}$ in. (3 mm) or greater in thickness, the charts in Figure QW-191.1.2.2(b)(4) represent the maximum acceptable types of rounded indications illustrated in typically clustered, assorted, and randomly dispersed configurations. Rounded indications less than $\frac{1}{32}$ in. (0.8 mm) in maximum diameter shall not be considered in the radiographic acceptance tests of welders and welding operators in these ranges of material thicknesses.

**Figure QW-191.1.2.2(b)(4)
Rounded Indication Charts**




Typical Quantity and Size Permitted
in 6 in. (150 mm) Length of Weld
 $\frac{1}{8}$ in. (3 mm) to $\frac{1}{4}$ in. (6 mm)
Thickness



Typical Quantity and Size Permitted
in 6 in. (150 mm) Length of Weld
Over $\frac{1}{4}$ in. (6 mm) to $\frac{1}{2}$ in. (13 mm)
Thickness



Typical Quantity and Size Permitted
in 6 in. (150 mm) Length of Weld
Over $\frac{1}{2}$ in. (13 mm) to 1 in. (25 mm)
Thickness

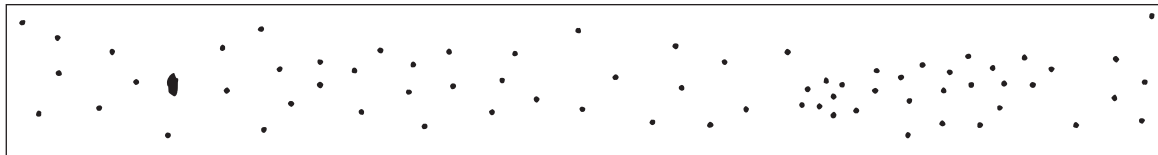

Typical Quantity and Size Permitted
in 6 in. (150 mm) Length of Weld
Over 1 in. (25 mm) Thickness

QW-191.1.2.3 Production Welds. The acceptance criteria for welders or welding operators who qualify on production welds by radiography as permitted in [QW-304.1](#) or [QW-305.1](#) shall be per [QW-191.1.2.2](#)

QW-191.2 Ultrasonic Examination

(13) QW-191.2.1 Method

(a) The ultrasonic examination in [QW-142](#) for welders and in [QW-143](#) for welding operators may be conducted on test welds in material $\frac{1}{2}$ in. (13 mm) thick or greater.

(b) Ultrasonic examinations shall be performed using a written procedure in compliance with paragraph T-150, Article 1, Section V and the requirements of Article 4, Section V for methods, procedures, and qualifications.

(c) Ultrasonic examination personnel shall meet the requirements of [QW-191.2.2](#).

(13) QW-191.2.2 Personnel Qualifications and Certifications.

(a) All personnel performing ultrasonic examinations for welder and welding operator qualifications shall be qualified and certified in accordance with their employer's written practice.

(b) The employer's written practice for qualification and certification of examination personnel shall meet all applicable requirements of SNT-TC-1A1 for the examination method and technique.

(c) Alternatively, the ASNT Central Certification Program (ACCP) or CP-1891 may be used to fulfill the examination and demonstration requirements of SNT-TC-1A and the employer's written practice.

(d) Provisions for the training, experience, qualification, and certification of NDE personnel shall be described in the Manufacturer's Quality Control System.

QW-191.2.3 Acceptance Criteria for Qualification Test Welds. Indications shall be sized using the applicable technique(s) provided in the written procedure for the examination method. Indications shall be evaluated for acceptance as follows:

(a) All indications characterized as cracks, lack of fusion, or incomplete penetration are unacceptable regardless of length.

(b) Indications exceeding $\frac{1}{8}$ in. (3 mm) in length are considered relevant, and are unacceptable when their lengths exceed

(1) $\frac{1}{8}$ in. (3 mm) for t up to $\frac{3}{8}$ in. (10 mm).

(2) $\frac{1}{3}t$ for t from $\frac{3}{8}$ in. to $2\frac{1}{4}$ in. (10 mm to 57 mm).

(3) $\frac{3}{4}$ in. (19 mm) for t over $2\frac{1}{4}$ in. (57 mm), where t is the thickness of the weld excluding any allowable reinforcement. For a butt weld joining two members having different thicknesses at the weld, t is the thinner of these two thicknesses. If a full penetration weld includes a fillet weld, the thickness of the throat of the fillet shall be included in t .

QW-191.2.4 Acceptance Criteria for Production Welds. The acceptance criteria for welders or welding operators who qualify on production welds by ultrasonic examination as permitted in QW-304.1 or QW-305.1 shall be per QW-191.2.3.

QW-191.3 Record of Tests. The results of welder and welding operator performance tests evaluated by volumetric NDE shall be recorded in accordance with QW-301.4.

QW-192 STUD-WELD TESTS**QW-192.1 Procedure Qualification Specimens.**

QW-192.1.1 Required Tests. Ten stud-weld tests are required to qualify each procedure. The equipment used for stud welding shall be completely automatic except for manual starting.

Every other welding stud (five joints) shall be tested either by hammering over until one-fourth of its length is flat on the test piece, or by bending the stud to an angle of at least 15 deg and returning it to its original position using a test jig and an adapter location dimension that are in accordance with Figure QW-466.4.

The remaining five welded stud joints shall be tested in torque using a torque testing arrangement that is substantially in accordance with Figure QW-466.5. Alternatively, where torquing is not feasible, tensile testing may be used, and the fixture for tensile testing shall be similar to that shown in Figure QW-466.6, except that studs without heads may be gripped on the unwelded end in the jaws of the tensile testing machine.

QW-192.1.2 Acceptance Criteria — Bend and Hammer Tests. In order to pass the test(s), each of the five stud welds and heat-affected zones shall be free of visible separation or fracture after bending and return bending or after hammering.

QW-192.1.3 Acceptance Criteria — Torque Tests. In order to pass the test(s), each of the five stud welds shall be subjected to the required torque shown in the following table before failure occurs.

Required Torque for Testing Threaded Carbon Steel Studs		
Nominal Diameter of Studs, in. (mm)	Threads/in. and Series Designated	Testing Torque, ft-lb (J)
$\frac{1}{4}$ (6.4)	28 UNF	5.0 (6.8)
$\frac{1}{4}$ (6.4)	20 UNC	4.2 (5.7)
$\frac{5}{16}$ (7.9)	24 UNF	9.5 (12.9)
$\frac{5}{16}$ (7.9)	18 UNC	8.6 (11.7)
$\frac{3}{8}$ (9.5)	24 UNF	17 (23.0)
$\frac{3}{8}$ (9.5)	16 UNC	15 (20.3)
$\frac{7}{16}$ (11.1)	20 UNF	27 (36.6)
$\frac{7}{16}$ (11.1)	14 UNC	24 (32.5)
$\frac{1}{2}$ (12.7)	20 UNF	42 (57.0)
$\frac{1}{2}$ (12.7)	13 UNC	37 (50.2)
$\frac{9}{16}$ (14.3)	18 UNF	60 (81.4)
$\frac{9}{16}$ (14.3)	12 UNC	54 (73.2)
$\frac{5}{8}$ (15.9)	18 UNF	84 (114.0)
$\frac{5}{8}$ (15.9)	11 UNC	74 (100.0)
$\frac{3}{4}$ (19.0)	16 UNF	147 (200.0)
$\frac{3}{4}$ (19.0)	10 UNC	132 (180.0)
$\frac{7}{8}$ (22.2)	14 UNF	234 (320.0)
$\frac{7}{8}$ (22.2)	9 UNC	212 (285.0)
1 (25.4)	12 UNF	348 (470.0)
1 (25.4)	8 UNC	318 (430.0)

Required Torque for Testing Threaded Austenitic Stainless Steel Studs		
Nominal Diameter of Studs, in. (mm)	Threads/in. and Series Designated	Testing Torque, ft-lb (J)
1/4 (6.4)	28 UNF	4.5 (6.1)
1/4 (6.4)	20 UNC	4.0 (5.4)
5/16 (7.9)	24 UNF	9.0 (12.2)
5/16 (7.9)	18 UNC	8.0 (10.8)
3/8 (9.5)	24 UNF	16.5 (22.4)
3/8 (9.5)	16 UNC	14.5 (19.7)
7/16 (11.1)	20 UNF	26.0 (35.3)
7/16 (11.1)	14 UNC	23.0 (31.2)
1/2 (12.7)	20 UNF	40.0 (54.2)
1/2 (12.7)	13 UNC	35.5 (48.1)
5/8 (15.9)	18 UNF	80.0 (108.5)
5/8 (15.9)	11 UNC	71.0 (96.3)
3/4 (19.0)	16 UNF	140.0 (189.8)
3/4 (19.0)	10 UNC	125.0 (169.5)
7/8 (22.2)	14 UNF	223.0 (302.3)
7/8 (22.2)	9 UNC	202.0 (273.9)
1 (25.4)	14 UNF	339.0 (459.6)
1 (25.4)	8 UNC	303.0 (410.8)

Alternatively, where torquing to destruction is not feasible, tensile testing may be used. For carbon and austenitic stainless steel studs, the failure strength shall be not less than 35,000 psi (240 MPa) and 30,000 psi (210 MPa), respectively. For other metals, the failure strength shall not be less than half of the minimum specified tensile strength of the stud material. The failure strength shall be based on the minor diameter of the threaded section of externally threaded studs, except where the shank diameter is less than the minor diameter, or on the original cross-sectional area where failure occurs in a nonthreaded, internally threaded, or reduced-diameter stud.

QW-192.1.4 Acceptance Criteria — Macro-Examination. In order to pass the macro-examination, each of five sectioned stud welds and the heat-affected zone shall be free of cracks when examined at 10X magnification, which is required by QW-202.5 when studs are welded to metals other than P-No. 1.

QW-192.2 Performance Qualification Specimens.

QW-192.2.1 Required Tests. Five stud-weld tests are required to qualify each stud-welding operator. The equipment used for stud welding shall be completely automatic except for manual starting. The performance test shall be welded in accordance with a qualified WPS per QW-301.2.

Each stud (five joints) shall be tested either by hammering over until one-fourth of its length is flat on the test piece or by bending the stud to an angle of at least

15 deg and returning it to its original position using a test jig and an adapter location dimension that are in accordance with Figure QW-466.4.

QW-192.2.2 Acceptance Criteria — Bend and Hammer Tests. In order to pass the test(s), each of the five stud welds and heat affected zones shall be free of visible separation or fracture after bending and return bending or after hammering.

QW-193 TUBE-TO-TUBESHEET TESTS

When the applicable Code Section requires the use of this paragraph for tube-to-tubesheet demonstration mockup qualification, QW-193.1 through QW-193.1.3 shall apply.

QW-193.1 Procedure Qualification Specimens. Ten (13) mockup welds are required to qualify each procedure. The mockup assembly shall essentially duplicate the tube hole configuration and tube-to-tubesheet joint design within the limits of the essential variables of QW-288. The thickness of the tubesheet in the mockup test assembly shall be at least as thick as the production tubesheet, except it is not required to be thicker than 2 in. (50 mm). The cladding may be represented by the base material of essentially equivalent chemical composition to the cladding composition. The mockup welds shall be submitted to the following tests sequentially and must meet the applicable acceptance criteria.

QW-193.1.1 Acceptance Criteria — Visual Examination. The accessible surfaces of the welds shall be examined visually with no magnification required. The welds shall show complete fusion and no evidence of burning through the tube wall, and shall be free from cracking or porosity.

QW-193.1.2 Acceptance Criteria — Liquid Penetrant. The liquid penetrant examination shall meet the requirements of Section V, Article 6. The weld surfaces shall meet the requirements of QW-195.2.

QW-193.1.3 Acceptance Criteria — Macro-Examination. The mockup welds shall be sectioned through the center of the tube for macro-examination. The four exposed surfaces shall be smoothed and etched with a suitable etchant (see QW-470) to give a clear definition of the weld and heat-affected zone. Using a magnification of 10X to 20X, the exposed cross sections of the weld shall confirm

(a) minimum leak path dimension required by the design

(b) no cracking

(c) complete fusion of the weld deposit into the tube-sheet and tube wall face

(d) complete penetration of the weld deposit to within 1/64 in. (0.4 mm) of the root of the joint

(e) porosity shall not reduce the weld throat below the required minimum leak path thickness

QW-193.2 Performance Qualification Specimens.

Five mockup welds are required to qualify each welder or welding operator. The same rules as that for procedure qualification ([QW-193.1](#)) shall be followed. Only one mockup weld is required to renew a welder's or welding operator's qualification when that qualification has expired or been revoked per the requirements of [QW-322.1](#).

(13) QW-194 VISUAL EXAMINATION — PERFORMANCE

Performance test coupons shall show no cracks and complete joint penetration with complete fusion of weld metal and base metal.

QW-195 LIQUID PENETRANT EXAMINATION

QW-195.1 The liquid penetrant examination in [QW-214](#) for corrosion-resistant weld metal overlay shall meet the requirements of Section V, Article 6. The acceptance standards of [QW-195.2](#) shall be met.

QW-195.2 Liquid Penetrant Acceptance Criteria.**QW-195.2.1 Terminology.**

relevant indications: indications with major dimensions greater than $\frac{1}{16}$ in. (1.5 mm)

linear indications: an indication having a length greater than three times the width.

rounded indications: an indication of circular or elliptical shape with the length equal to or less than three times the width.

QW-195.2.2 Acceptance Standards. Procedure and performance tests examined by liquid penetrant techniques shall be judged unacceptable when the examination exhibits any indication in excess of the limits specified in the following:

- (a) relevant linear indications
- (b) relevant rounded indications greater than $\frac{3}{16}$ in. (5 mm)
- (c) four or more relevant rounded indications in a line separated by $\frac{1}{16}$ in. (1.5 mm) or less (edge-to-edge)

QW-196 RESISTANCE WELD TESTING**QW-196.1 Macro-Examination.**

QW-196.1.1 Welds shall be cross-sectioned, polished, and etched to reveal the weld metal. The section shall be examined at 10X magnification. Seam welding specimens shall be prepared as shown in [Figure QW-462.7.3](#). The sectioned weldment shall be free of cracks, incomplete penetration, expulsions, and inclusions. Porosity shall not exceed one void in the transverse cross section or three voids in the longitudinal cross section of a specimen. The maximum dimension of any void shall not exceed 10% of the thickness of the weld bead.

QW-196.1.2 For spot and seam welds, the minimum width of the weld nugget shall be as follows in relation to thickness, t , of the thinner member.

Material Thickness, in. (mm)	Weld Nugget Width
< 0.010 (0.25)	6t
≥ 0.010 (0.25) and < 0.020 (0.50)	5t
≥ 0.020 (0.50) and < 0.040 (1.00)	4t
≥ 0.040 (1.00) and < 0.069 (1.75)	3t
≥ 0.069 (1.75) and < 0.100 (2.54)	2.50t
≥ 0.100 (2.54) and < 0.118 (3.00)	2.25t
≥ 0.118 (3.00) and < 0.157 (4.00)	2t
≥ 0.157 (4.00)	1.80t

The weld depth (extent of fusion) shall be a minimum of 20% of the thickness of the thinner ply (in each member) and a maximum of 80% of the total thickness of all plies.

QW-196.1.3 For projection welds, the width of the nugget shall be not less than 80% of the width of the projection.

QW-196.2 Mechanical Testing.

QW-196.2.1 Shear test specimens shall be prepared as shown on [Figure QW-462.9](#). For spot and projection welds, each test specimen shall equal or exceed the minimum strength, and the average strength specified in [Tables QW-462.10\(a\)](#) through [QW-462.10\(c\)](#) for the appropriate material. Further, for each set, 90% shall have shear strength values between 0.9 and 1.1 times the set average value. The remaining 10% shall lie between 0.8 and 1.2 times the set average value.

QW-196.2.2 Peel test specimens shall be prepared as shown in [Figure QW-462.8.1](#) for spot and projection welding and per [Figure QW-462.8.2](#) for seam welding. The specimens shall be peeled or separated mechanically, and fracture shall occur in the base metal by tearing out of the weld in order for the specimen to be acceptable.

QW-197 LASER BEAM WELDING (LBW) LAP JOINT TESTS**QW-197.1 Procedure Qualification Specimens.**

QW-197.1.1 Required Tests. Six tension shear specimens and eight macro specimens are required to qualify each procedure. The qualification test coupon shall be prepared in accordance with [Figure QW-464.1](#). The tension shear specimens shall conform to the dimensions indicated in the table of [Figure QW-464.1](#). The longitudinal and transverse sections indicated in [Figure QW-464.1](#) shall be cross-sectioned as closely as possible through the centerline of the weld. A minimum of 1 in. (25 mm) shall be provided for examination of each longitudinal specimen. The transverse specimens shall be of sufficient length to include weld, the heat-affected zone, and portions of the unaffected base material. Cross-sections shall be smoothed and etched with a suitable etchant (see [QW-470](#)), and examined at a minimum magnification of 25X. The dimensions of the fusion zone and penetration of each weld of the transverse specimens shall be measured to the nearest hundredth of an inch and recorded.

QW-197.1.2 Acceptance Criteria — Tension Shear Tests. In order to pass the tension shear test(s), the requirements of [QW-153](#) shall apply.

QW-197.1.3 Acceptance Criteria — Macro-Examination. In order to pass the macro-examination, each of the eight specimens shall meet the following criteria:

(a) The outline of the fusion zone shall be generally consistent in size and regular in shape and uniformity of penetration.

(b) The examination of the weld area shall reveal sound weld metal, complete fusion along the bond line, and complete freedom from cracks in the weld metal and heat-affected zone.

QW-197.2 Performance Qualification Specimens.

QW-197.2.1 Required Tests. A peel test specimen at least 6 in. (150 mm) long shall be prepared as shown in [Figure QW-464.2](#) illustration (a) and macro specimens as shown in [Figure QW-464.2](#) illustration (b). The peel test specimens shall be peeled apart to destruction and the fusion zone and penetration measured to the nearest hundredth of an inch. The end of each strip of the macro coupon shall be polished and etched to clearly reveal the weld metal. The width and depth of penetration of each weld shall be measured to the nearest hundredth of an inch. Each specimen shall be examined in accordance with [QW-197.1](#).

QW-197.2.2 Acceptance Criteria — Peel Test and Macro-Examination. In order to pass the peel test and macro-examination, the dimensions of the fusion zone (averaged) and the penetration (averaged) shall be within the range of dimensions of those specified on the WPS that was used to make the test coupon.

QW-199 FLASH WELDING

QW-199.1 Procedure Qualification Test Coupons and Testing.

QW-199.1.1 Test Coupon Preparation. For coupons NPS 1 (DN 25) and smaller, four test welds shall be made, and for pipes over NPS 1 (DN 25), three test coupons shall be made using one set of welding parameters (i.e., the same equipment, base metals, joint preparation, and other essential variables to be utilized for production welding.) These variables shall be recorded on the qualification record.

QW-199.1.2 Tensile Tests. For pipes NPS 1 (DN 25) and smaller, and nontubular cross sections, two full-section tensile specimens shall be prepared in accordance with [Figure QW-462.1\(e\)](#). For pipes greater than NPS 1 (DN 25), two reduced section tension specimens shall be prepared in accordance with

[Figure QW-462.1\(b\)](#) or [Figure QW-462.1\(c\)](#) from one coupon. For nontubular cross sections, two reduced section tension specimens shall be prepared in accordance with [Figure QW-462.1\(a\)](#) or [Figure QW-462.1\(d\)](#) from two of the coupons. The specimens shall be tested in accordance with [QW-150](#).

QW-199.1.3 Section and Bend Testing. The entire circumference of each remaining pipe coupon shall be cut along the axis of the pipe into an even number of strips of a length sufficient to perform bend tests. The maximum width of each strip shall be $1\frac{1}{2}$ in. (38 mm) and the minimum width

$$w = t + D / 4 \text{ for pipes NPS 2 (DN 50) and smaller}$$

$$w = t + D / 8 \text{ for pipes greater than NPS 2 (DN 50)}$$

where

D = OD of the tube

t = nominal wall thickness

w = width of the specimen

One edge of one strip from each coupon shall be polished to a 600 grit finish with the final grinding parallel to the long axis of the strip. The polished surface shall be examined at 5X magnification. No incomplete fusion or other open flaws on the polished surface are acceptable. Defects occurring in the base metal not associated with the weld may be disregarded. For nontubular cross sections, four side-bend specimens shall be prepared from the two remaining coupons as specified in [Figure QW-462.2](#) and polished for examination.

All flash shall be removed from the strips and the welds shall be visually examined per [QW-194](#). Half of the strips from each pipe specimen shall then be prepared as root bend specimens and the remaining strips shall be prepared as face bend specimens in accordance with [QW-160](#). The specimens shall be tested in accordance with [QW-160](#), except for the following:

(a) For P-No. 1, Groups 2 through 4 materials, the minimum bend radius (dimension B in [Figure QW-466.1](#)) shall be three times the thickness of the specimen.

(b) In lieu of [QW-163](#), the sum of lengths of individual open flaws on the convex surface of all the bend test specimens taken from each pipe individually shall not exceed 5% of the outside circumference of that test pipe.

QW-199.2 Flash Welding — Performance Qualification Test Coupons and Testing. One test coupon shall be welded, cut into strips, visually examined, and bend tested in accordance with [QW-199.1.3](#). Polishing and examination of a cross-section is not required.

(13)

APPENDIX I ROUNDED INDICATION CHARTS

Illustration that appeared in this Appendix in the previous edition and addenda has been designated as [QW-191.1.2.2\(b\)\(4\)](#) and follows [QW-191.1.2.2\(b\)\(3\)](#).

ARTICLE II

WELDING PROCEDURE QUALIFICATIONS

QW-200 GENERAL

- (13) **QW-200.1** Each organization shall prepare written Welding Procedure Specifications that are defined as follows:

(a) *Welding Procedure Specification (WPS)*. A WPS is a written qualified welding procedure prepared to provide direction for making production welds to Code requirements. The WPS or other documents may be used to provide direction to the welder or welding operator to assure compliance with the Code requirements.

(b) *Contents of the WPS*. The completed WPS shall describe all of the essential, nonessential, and, when required, supplementary essential variables for each welding process used in the WPS. These variables are listed in [QW-250](#) through QW-280 and are defined in [Article IV](#), Welding Data.

The WPS shall reference the supporting Procedure Qualification Record(s) (PQR) described in [QW-200.2](#). The organization may include any other information in the WPS that may be helpful in making a Code weldment.

(c) *Changes to the WPS*. Changes may be made in the nonessential variables of a WPS to suit production requirements without requalification provided such changes are documented with respect to the essential, nonessential, and, when required, supplementary essential variables for each process. This may be by amendment to the WPS or by use of a new WPS.

Changes in essential or supplementary essential (when required) variables require requalification of the WPS (new or additional PQRs to support the change in essential or supplementary essential variables).

(d) *Format of the WPS*. The information required to be in the WPS may be in any format, written or tabular, to fit the needs of each organization, as long as every essential, nonessential, and, when required, supplementary essential variables outlined in [QW-250](#) through QW-280 is included or referenced.

Form QW-482 (see [Nonmandatory Appendix B](#)) has been provided as a guide for the WPS. This Form includes the required data for the SMAW, SAW, GMAW, and GTAW processes. It is only a guide and does not list all required data for other processes. It also lists some variables that do not apply to all processes (e.g., listing shielding gas which is not required for SAW). The guide does not easily lend itself to multiple process procedure specification (e.g., GTAW root with SMAW fill).

(e) *Availability of the WPS*. A WPS used for Code production welding shall be available for reference and review by the Authorized Inspector (AI) at the fabrication site.

- QW-200.2** Each organization shall be required to prepare a procedure qualification record which is defined as follows: (13)

(a) *Procedure Qualification Record (PQR)*. The PQR is a record of variables recorded during the welding of the test coupons. It also contains the test results of the tested specimens. Recorded variables normally fall within a small range of the actual variables that will be used in production welding.

(b) *Contents of the PQR*. The completed PQR shall document all essential and, when required, supplementary essential variables of [QW-250](#) through QW-280 for each welding process used during the welding of the test coupon. Nonessential or other variables used during the welding of the test coupon may be recorded at the organization's option. All variables, if recorded, shall be the actual variables (including ranges) used during the welding of the test coupon. If variables are not monitored during welding, they shall not be recorded. It is not intended that the full range or the extreme of a given range of variables to be used in production be used during qualification unless required due to a specific essential or, when required, supplementary essential variable.

The PQR shall be certified accurate by the organization. The organization may not subcontract the certification function. This certification is intended to be the organization's verification that the information in the PQR is a true record of the variables that were used during the welding of the test coupon and that the resulting tensile, bend, or macro (as required) test results are in compliance with Section IX.

One or more combinations of welding processes, filler metal, and other variables may be used when welding a test coupon. The approximate thickness of weld metal deposited shall be recorded for each set of essential and, when required, supplementary essential variables. Weld metal deposited using each set of variables shall be included in the tension, bend, notch toughness, and other mechanical test specimens that are required.

(c) *Changes to the PQR*. Changes to the PQR are not permitted except as described below. Editorial corrections or addenda to the PQR are permitted. An example of an editorial correction is an incorrect P-Number, F-Number, or A-Number that was assigned to a particular base metal

or filler metal. An example of an addendum would be a change resulting from a Code change. For example, Section IX may assign a new F-Number to a filler metal or adopt a new filler metal under an established F-Number. This may permit, depending on the particular construction Code requirements, an organization to use other filler metals that fall within that particular F-Number where, prior to the Code revision, the organization was limited to the particular electrode classification that was used during qualification. Additional information can be incorporated into a PQR at a later date provided the information is substantiated as having been part of the original qualification condition by lab record or similar data.

All changes to a PQR require recertification (including date) by the organization.

(d) *Format of the PQR.* Form QW-483 (see Nonmandatory Appendix B) has been provided as a guide for the PQR. The information required to be in the PQR may be in any format to fit the needs of each organization, as long as every essential and, when required, supplementary essential variable, required by QW-250 through QW-280, is included. Also the type of tests, number of tests, and test results shall be listed in the PQR.

Form QW-483 does not easily lend itself to cover combinations of welding processes or more than one F-Number filler metal in one test coupon. Additional sketches or information may be attached or referenced to record the required variables.

(e) *Availability of the PQR.* PQRs used to support WPSs shall be available, upon request, for review by the Authorized Inspector (AI). The PQR need not be available to the welder or welding operator.

(f) *Multiple WPSs With One PQR/Multiple PQRs With One WPS.* Several WPSs may be prepared from the data on a single PQR (e.g., a 1G plate PQR may support WPSs for the F, V, H, and O positions on plate or pipe within all other essential variables). A single WPS may cover several sets of essential variable ranges as long as a supporting PQR exists for each essential and, when required, supplementary essential variable [e.g., a single WPS may cover a thickness range from $\frac{1}{16}$ in. (1.5 mm) through $1\frac{1}{4}$ in. (32 mm) if PQRs exist for both the $\frac{1}{16}$ in. (1.5 mm) through $\frac{3}{16}$ in. (5 mm) and $\frac{3}{16}$ in. (5 mm) through $1\frac{1}{4}$ in. (32 mm) thickness ranges].

QW-200.3 To reduce the number of welding procedure qualifications required, P-Numbers are assigned to base metals dependent on characteristics such as composition, weldability, and mechanical properties, where this can logically be done; and for steel and steel alloys (Table QW/QB-422) Group Numbers are assigned additionally to P-Numbers. These Group Numbers classify the metals within P-Numbers for the purpose of procedure qualification where notch-toughness requirements are specified. The assignments do not imply that base metals may be indiscriminately substituted for a base metal which was used in the qualification test without

consideration of the compatibility from the standpoint of metallurgical properties, postweld heat treatment, design, mechanical properties, and service requirements. Where notch toughness is a consideration, it is presupposed that the base metals meet the specific requirements.

In general, notch-toughness requirements are mandatory for all P-No. 11 quenched and tempered metals, for low temperature applications of other metals as applied to Section VIII, and for various classes of construction required by Section III. Acceptance criteria for the notch-toughness tests are as established in the other Sections of the Code.

QW-200.4 Combination of Welding Procedures.

(a) More than one WPS having different essential, supplementary essential, or nonessential variables may be used in a single production joint. Each WPS may include one or a combination of processes, filler metals, or other variables.

Where more than one WPS specifying different processes, filler metals, or other essential or supplementary essential variables is used in a joint, QW-451 shall be used to determine the range of base metal thickness and maximum weld metal thickness qualified for each process, filler metal, or set of variables, and those limits shall be observed. Alternatively, qualification of WPSs for root deposits only may be made in accordance with (b).

When following a WPS that has more than one welding process, filler metal, or set of variables, each process, filler metal, or set of variables may be used individually or in different combinations, provided

(1) the essential, nonessential, and required supplementary essential variables associated with the process, filler metal, or set of variables are applied

(2) the base metal and deposited weld metal thickness limits of QW-451 for each process, filler metal, or set of variables are applied

(b) For GTAW, SMAW, GMAW, PAW, and SAW, or combinations of these processes, a PQR for a process recording a test coupon that was at least $\frac{1}{2}$ in. (13 mm) thick may be combined with one or more other PQRs recording another welding process and any greater base metal thickness. In this case, the process recorded on the first PQR may be used to deposit the root layers using the process(es) recorded on that PQR up to $2t$ (for short-circuiting type of GMAW, see QW-404.32) in thickness on base metal of the maximum thickness qualified by the other PQR(s) used to support the WPS. The requirements of Note (1) of Tables QW-451.1 and QW-451.2 shall apply.

QW-201 Organizational Responsibility

(13)

The organization shall certify that they have qualified each Welding Procedure Specification, performed the procedure qualification test, and documented it with the necessary Procedure Qualification Record (PQR).

QW-202 TYPE OF TESTS REQUIRED

- (13) **QW-202.1 Mechanical Tests.** The type and number of test specimens that shall be tested to qualify a groove weld procedure are given in [QW-451](#), and shall be removed in a manner similar to that shown in QW-463. If any test specimen required by [QW-451](#) fails to meet the applicable acceptance criteria, the test coupon shall be considered as failed.

When it can be determined that the cause of failure is not related to welding parameters, another test coupon may be welded using identical welding parameters.

Alternatively, if adequate material of the original test coupon exists, additional test specimens may be removed as close as practicable to the original specimen location to replace the failed test specimens.

When it has been determined that the test failure was caused by an essential or supplementary essential variable, a new test coupon may be welded with appropriate changes to the variable(s) that was determined to cause the test failure. If the new test passes, the essential and supplementary variables shall be documented on the PQR.

When it is determined that the test failure was caused by one or more welding related factors other than essential or supplementary essential variables, a new test coupon may be welded with the appropriate changes to the welding related factors that were determined to cause the test failure. If the new test passes, the welding related factors that were determined to cause the previous test failure shall be addressed by the organization to ensure that the required properties are achieved in the production weldment.

Where qualification is for fillet welds only, the requirements are given in [QW-202.2\(c\)](#); and where qualification is for stud welds only, the requirements are given in [QW-202.5](#).

QW-202.2 Groove and Fillet Welds

(a) *Qualification for Groove Full Penetration Welds.* Groove-weld test coupons shall qualify the thickness ranges of both base metal and deposited weld metal to be used in production. Limits of qualification shall be in accordance with [QW-451](#). WPS qualification for groove welds shall be made on groove welds using tension and guided-bend specimens. Notch-toughness tests shall be made when required by other Section(s) of the Code. The WPS shall be qualified for use with groove welds within the range of essential variables listed.

(b) *Qualification for Partial Penetration Groove Welds.* Partial penetration groove welds shall be qualified in accordance with the requirements of [QW-451](#) for both base metal and deposited weld metal thickness, except there need be no upper limit on the base metal thickness provided qualification was made on base metal having a thickness of $1\frac{1}{2}$ in. (38 mm) or more.

(c) *Qualification for Fillet Welds.* WPS qualification for fillet welds may be made on groove-weld test coupons using test specimens specified in (a) or (b). Fillet-weld procedures so qualified may be used for welding all thicknesses of base metal for all sizes of fillet welds, and all diameters of pipe or tube in accordance with [Table QW-451.4](#). Nonpressure-retaining fillet welds, as defined in other Sections of the Code, may as an alternate be qualified with fillet welds only. Tests shall be made in accordance with [QW-180](#). Limits of qualification shall be in accordance with [Table QW-451.3](#).

QW-202.3 Weld Repair and Buildup. WPS qualified on groove welds shall be applicable for weld repairs to groove and fillet welds and for weld buildup under the following provisions:

(a) There is no limitation on the thickness of base metal or deposited weld metal for fillet welds.

(b) For other than fillet welds, the thickness range for base metal and deposited weld metal for each welding process shall be in accordance with [QW-451](#), except there need be no upper limit on the base metal thickness provided qualification was made on base metal having a thickness of $1\frac{1}{2}$ in. (38 mm) or more.

QW-202.4 Dissimilar Base Metal Thicknesses. WPS qualified on groove welds shall be applicable for production welds between dissimilar base metal thicknesses provided:

(a) the thickness of the thinner member shall be within the range permitted by [QW-451](#)

(b) the thickness of the thicker member shall be as follows:

(1) For P-No. 8, P-No. 41, P-No. 42, P-No. 43, P-No. 44, P-No. 45, P-No. 46, P-No. 49, P-No. 51, P-No. 52, P-No. 53, P-No. 61, and P-No. 62 metal, there shall be no limitation on the maximum thickness of the thicker production member in joints of similar P-Number materials provided qualification was made on base metal having a thickness of $\frac{1}{4}$ in. (6 mm) or greater.

(2) For all other metal, the thickness of the thicker member shall be within the range permitted by [QW-451](#), except there need be no limitation on the maximum thickness of the thicker production member provided qualification was made on base metal having a thickness of $1\frac{1}{2}$ in. (38 mm) or more.

More than one procedure qualification may be required to qualify for some dissimilar thickness combinations.

QW-202.5 Stud Welding. Procedure qualification tests for stud welds shall be made in accordance with [QW-192](#). The procedure qualification tests shall qualify the welding procedures for use within the range of the essential variables of QW-261. For studs welded to other than P-No. 1 metals, five additional welds shall be made and subjected to a macro-test, except that this is not required for studs used for extended heating surfaces.

QW-202.6 Tube-to-Tubesheet Qualification. When the applicable Code Section requires the use of [QW-193](#) for tube-to-tubesheet demonstration mockup qualification tests, [QW-193.1](#) shall apply. If specific qualification test requirements are not specified by the applicable Code Section, tube-to-tubesheet welds shall be qualified with one of the following methods:

(a) groove welds per the requirements of [QW-202.2](#) and [QW-202.4](#)

(b) a demonstration mockup per the requirements of [QW-193.1](#)

(c) fillet welds per the requirements of [QW-202.2\(c\)](#) (for nonpressure retaining tube-to-tubesheet welds only)

QW-203 LIMITS OF QUALIFIED POSITIONS FOR PROCEDURES

Unless specifically required otherwise by the welding variables ([QW-250](#)), a qualification in any position qualifies the procedure for all positions. The welding process and electrodes must be suitable for use in the positions permitted by the WPS. A welder or welding operator making and passing the WPS qualification test is qualified for the position tested. see [QW-301.2](#).

QW-210 PREPARATION OF TEST COUPON

QW-211 BASE METAL

The base metals may consist of either plate, pipe, or other product forms. Qualification in plate also qualifies for pipe welding and vice versa. The dimensions of the test coupon shall be sufficient to provide the required test specimens.

QW-212 TYPE AND DIMENSIONS OF GROOVE WELDS

Except as otherwise provided in [QW-250](#), the type and dimensions of the welding groove are not essential variables.

QW-214 CORROSION-RESISTANT WELD METAL OVERLAY

QW-214.1 The size of test coupons, limits of qualification, required examinations and tests, and test specimens shall be as specified in [Table QW-453](#).

QW-214.2 Essential variables shall be as specified in [QW-250](#) for the applicable welding process.

QW-215 ELECTRON BEAM WELDING AND LASER BEAM WELDING

QW-215.1 The WPS qualification test coupon shall be prepared with the joint geometry duplicating that to be used in production. If the production weld is to include a lap-over (completing the weld by rewelding over the starting area of the weld, as for a girth weld), such lap-over shall be included in the WPS qualification test coupon.

QW-215.2 The mechanical testing requirements of [QW-451](#) shall apply.

QW-215.3 Essential variables shall be as specified in [Tables QW-260](#) and [QW-264](#) for the applicable welding process.

QW-216 HARD-FACING WELD METAL OVERLAY

Hard-Facing Weld Metal Overlay refers to weld deposits made, using a variety of processes, to deter the effects of wear and/or abrasion. The requirements specified in [QW-216.1](#) through [QW-216.4](#) apply regardless of which hard-facing process is used.

QW-216.1 The size of test coupons, limits of qualification, required examinations and tests, and test specimens shall be as specified in [Table QW-453](#).

QW-216.2 Welding variables shall be as specified in [QW-250](#) for the applicable process.

QW-216.3 Where Spray Fuse methods of hard-facing (e.g., Oxyfuel and Plasma Arc) are to be used, the coupons for these methods shall be prepared and welding variables applied in accordance with [QW-216.1](#) and [QW-216.2](#), respectively.

QW-216.4 If a weld deposit is to be used under a hard-facing weld metal overlay, a base metal with an assigned P-Number and a chemical analysis nominally matching the weld deposit chemical analysis may be substituted to qualify the PQR.

QW-217 JOINING OF COMPOSITE (CLAD METALS)

The WPS for groove welds in clad metal shall be qualified as provided in (a) when any part of the cladding thickness, as permitted by the referencing Code Section, is included in the design calculations. Either (a) or (b) may be used when the cladding thickness is not included in the design calculations.

(a) The essential and nonessential variables of [QW-250](#) shall apply for each welding process used in production. The procedure qualification test coupon shall be made using the same P-Number base metal, cladding, and welding process, and filler metal combination to be used in production welding. For metal not included in [Table QW/QB-422](#), the metal used in the composite test plate shall be within the range of chemical composition of that to be used in production. The qualified thickness range for the base metal and filler metal(s) shall be based on the actual test coupon thickness for each as applied to [QW-451](#), except that the minimum thickness of filler metal joining the cladding portion of the weldment shall be based on a chemical analysis performed in accordance with [Table QW-453](#). Tensile and bend tests required in [QW-451](#) for groove welds shall be made, and they shall contain the full thickness of cladding through the reduced section of the specimen. The bond line between the

original cladding and the base metal may be disregarded when evaluating side-bend tests if the cladding was applied by a process other than fusion welding.

(b) The essential and nonessential variables of QW-250 shall apply for each welding process used in production for joining the base metal portion of the weldment. The PQRs that support this portion of the WPS need not be based on test coupons made with clad metal. For the corrosion-resistant overlay portion of the weld, the essential variables of QW-251.4 shall apply and the test coupon and testing shall be in accordance with Table QW-453. The WPS shall limit the depth of the groove, which will receive the corrosion-resistant overlay in order to ensure development of the full strength of the underlying weld in the base metal.

QW-218 APPLIED LININGS

QW-218.1 WPSs for attaching applied linings shall be qualified in accordance with QW-202.2(a), QW-202.2(b), or QW-202.2(c).

QW-218.2 As an alternative to the above, each process to be used in attaching applied linings to base metal shall be qualified on a test coupon welded into the form and arrangement to be used in construction using materials that are within the range of chemical composition of the metal to be used for the base plate, the lining, and the weld metal. The welding variables of QW-250 shall apply except for those regarding base metal or weld metal thickness. Qualification tests shall be made for each position to be used in production welding in accordance with Table QW-461.9, except that qualification in the vertical position, uphill progression shall qualify for all positions. One cross-section for each position tested shall be sectioned, polished, and etched to clearly show the demarcation between the base metal and the weld metal. In order to be acceptable, each specimen shall exhibit complete fusion of the weld metal with the base metal and freedom from cracks.

QW-218.3 When chemical analysis of the weld deposit for any elements is required, a chemical analysis shall be performed per Table QW-453, Note 9 for those elements.

QW-219 FLASH WELDING

Flash welding shall be limited to automatic electrical resistance flash welding. Procedure qualification tests shall be conducted in accordance with QW-199.1.

QW-219.1 Tolerances on Variables . Flash welding variables that may require adjustment during production welding are synergistically related. Accordingly, even though the variables shown in Table QW-265 provide tolerances on many welding variables, the WPS shall specify the same specific variables shown on the PQR with tolerance shown for no more than one variable (e.g., if it is desired to provide a tolerance on the upset current, all other variables shown on the WPS must be the same as they are shown on the PQR). If it is desired to provide tolerances in

the WPS for two variables, the first variable with a tolerance shall be set at the midpoint of its tolerance and two test coupons shall be welded with each of the upper and lower extremes of the tolerance for the second variable (i.e., four coupons must be welded). These coupons shall be examined and tested in accordance with QW-199.1.3.

If it is desired to provide tolerance for a third variable, the first two variables shall be set at the midpoint of their tolerance, and two test coupons shall be welded with each of the upper and lower extremes of the new tolerances for the third variable (i.e., four coupons must be welded). These coupons shall be examined and tested in accordance with QW-199.1.3.

No more than three essential variables on a WPS may show tolerances.

Production tests conducted in accordance with the requirements of other Sections may be used to satisfy this requirement.

QW-220 HYBRID LASER-GMAW WELDING (13)

Hybrid laser-GMAW is limited to the combination of automatic LBW and automatic GMAW. The GMAW process shall not be applied using the short-circuiting arc transfer mode.

All hybrid laser-GMAW procedures for welding groove and fillet welds shall be qualified in accordance with the rules in QW-202. Table QW-268 lists the essential, supplementary essential, and nonessential variables that apply for hybrid laser-GMAW qualification.

QW-221 HYBRID PLASMA-GMAW (13)

When the applicable Code Section specifies the use of this paragraph for utilizing the hybrid plasma-GMAW process, QW-221.1 through QW-221.3 shall apply.

QW-221.1 Qualification. All hybrid plasma-GMAW procedures for groove and fillet welds shall be qualified in accordance with the rules outlined in QW-202. All hybrid plasma-GMAW procedures for corrosion-resistant overlay shall be qualified in accordance with the rules outlined in QW-214. All hybrid plasma-GMAW procedures for hard-facing overlay shall be qualified in accordance with the rules outlined in QW-216.

QW-221.2 Welding Process Restriction. Hybrid plasma-GMAW is limited to the combination of PAW and GMAW. The hybrid process is limited to machine welding only.

QW-221.3 Variables for Hybrid Plasma-GMAW. Table QW-269 lists the essential, supplementary essential, and nonessential variables that apply when hybrid plasma-GMAW qualification is required for groove and fillet welds. Table QW-269.1 lists the special process essential and nonessential variables associated with hardfacing and corrosion resistant overlay (CRO).

QW-250 WELDING VARIABLES**QW-251 GENERAL**

QW-251.1 Types of Variables for Welding Procedure Specifications (WPS). These variables (listed for each welding process in [Tables QW-252](#) through [QW-266](#)) are subdivided into essential variables, supplementary essential variables, and nonessential variables ([QW-401](#)). The "Brief of Variables" listed in the tables are for reference *only*. See the complete variable in Welding Data of [Article IV](#).

QW-251.2 Essential Variables. Essential variables are those in which a change, as described in the specific variables, is considered to affect the mechanical properties of the weldment, and shall require requalification of the WPS.

Supplementary essential variables are required for metals for which other Sections specify notch-toughness tests and are in addition to the essential variables for each welding process.

QW-251.3 Nonessential Variables. Nonessential variables are those in which a change, as described in the specific variables, may be made in the WPS without requalification.

QW-251.4 Special Processes.

(a) The special process essential variables for corrosion-resistant and hard-surfacing weld metal overlays are as indicated in the following tables for the specified process. Only the variables specified for special processes shall apply. A change in the corrosion-resistant or hard-surfacing welding process shall require requalification.

(b) WPS qualified for corrosion-resistant and hard-surfacing overlay welding, in accordance with other Sections when such qualification rules were included in those Sections, may be used with the same provisions as provided in [QG-101](#).

Table QW-252
Welding Variables Procedure Specifications (WPS) — Oxyfuel Gas Welding (OFW)

Paragraph		Brief of Variables	Essential	Supplementary Essential	Nonessential
QW-402 Joints	.1	ϕ Groove design			X
	.2	\pm Backing			X
	.3	ϕ Backing comp.			X
	.10	ϕ Root spacing			X
QW-403 Base Metals	.1	ϕ P-Number	X		
	.2	Max. T Qualified	X		
QW-404 Filler Metals	.3	ϕ Size			X
	.4	ϕ F-Number	X		
	.5	ϕ A-Number	X		
	.12	ϕ Classification	X		
QW-405 Positions	.1	+ Position			X
QW-406 Preheat	.1	Decrease > 100°F (55°C)			X
QW-407 PWHT	.1	ϕ PWHT	X		
QW-408 Gas	.7	ϕ Type fuel gas	X		
QW-410 Technique	.1	ϕ String/weave			X
	.2	ϕ Flame characteristics			X
	.4	ϕ $\leftarrow \rightarrow$ Technique			X
	.5	ϕ Method cleaning			X
	.26	\pm Peening			X
	.64	Use of thermal processes	X		

Legend:

+ Addition
 - Deletion

> Increase/greater than
 < Decrease/less than

↑ Uphill
 ↓ Downhill

← Forehand
 → Backhand

 ϕ Change

Table QW-252.1
Welding Variables Procedure Specifications (WPS) — Oxyfuel Gas Welding (OFW)

Paragraph		Special Process Essential Variables		Hard-Facing Spray Fuse (QW-216)
		Hard-Facing Overlay (QW-216)	Corrosion-Resistant Overlay (QW-214)	
QW-402 Joint	.16	< Finished <i>t</i>		
	.17			> Finished <i>t</i>
QW-403 Base Metals	.20	ϕ P-Number		ϕ P-Number
	.23	ϕ <i>T</i> Qualified	ϕ <i>T</i> Qualified	ϕ <i>T</i> Qualified
QW-404 Filler Metals	.12	ϕ Classification		ϕ Classification
	.42			> 5% Particle size range
	.46			ϕ Powder feed rate
QW-405 Positions	.4	+ Position		+ Position
QW-406 Preheat	.4	Dec. > 100°F (55°C) preheat > Interpass		Dec. > 100°F (55°C) preheat > Interpass
	.5			ϕ Preheat maint.
QW-407 PWHT	.6	ϕ PWHT		ϕ PWHT
	.7			ϕ PWHT after fusing
QW-408 Gas	.7	ϕ Type of fuel gas		
	.14	ϕ Oxyfuel gas pressure		
	.16			ϕ > 5% Gas feed rate
	.19			ϕ Plasma/feed gas comp.
QW-410 Technique	.38	ϕ Multiple to single layer		ϕ Multiple to single layer
	.39	ϕ Torch type, tip sizer		
	.44			ϕ > 15% Torch to workpiece
	.45			ϕ Surface prep.
	.46			ϕ Spray torch
	.47			ϕ > 10% Fusing temp. or method

Legend:

+ Addition
- Deletion

> Increase/greater than
< Decrease/less than

↑ Uphill
↓ Downhill

← Forehand
→ Backhand

ϕ Change

Table QW-253
Welding Variables Procedure Specifications (WPS) — Shielded Metal-Arc Welding (SMAW)

Paragraph		Brief of Variables	Essential	Supplementary Essential	Nonessential
QW-402 Joints	.1	ϕ Groove design			X
	.4	- Backing			X
	.10	ϕ Root spacing			X
	.11	\pm Retainers			X
QW-403 Base Metals	.5	ϕ Group Number		X	
	.6	T Limits impact		X	
	.8	ϕ T Qualified	X		
	.9	t Pass > $\frac{1}{2}$ in. (13 mm)	X		
	.11	ϕ P-No. qualified	X		
QW-404 Filler Metals	.4	ϕ F-Number	X		
	.5	ϕ A-Number	X		
	.6	ϕ Diameter			X
	.7	ϕ Diameter > $\frac{1}{4}$ in. (6 mm)		X	
	.12	ϕ Classification		X	
	.30	ϕ t	X		
	.33	ϕ Classification			X
QW-405 Positions	.1	+ Position			X
	.2	ϕ Position		X	
	.3	ϕ \updownarrow Vertical welding			X
QW-406 Preheat	.1	Decrease > 100°F (55°C)	X		
	.2	ϕ Preheat maint.			X
	.3	Increase > 100°F (55°C) (IP)		X	
QW-407 PWHT	.1	ϕ PWHT	X		
	.2	ϕ PWHT (T & T range)		X	
	.4	T Limits	X		
QW-409 Electrical Characteristics	.1	> Heat input		X	
	.4	ϕ Current or polarity		X	X
	.8	ϕ I & E range			X
QW-410 Technique	.1	ϕ String/weave			X
	.5	ϕ Method cleaning			X
	.6	ϕ Method back gouge			X
	.9	ϕ Multiple to single pass/side		X	X
	.25	ϕ Manual or automatic			X
	.26	\pm Peening			X
	.64	Use of thermal processes	X		

Legend:

+ Addition
 - Deletion

> Increase/greater than
 < Decrease/less than

\uparrow Uphill
 \downarrow Downhill

\leftarrow Forehand
 \rightarrow Backhand

ϕ Change

Table QW-253.1
Welding Variables Procedure Specifications (WPS) — Shielded Metal-Arc Welding (SMAW)

Special Process Variables				
Paragraph		Essential Variables		Nonessential Variables for HFO and CRO
		Hard-Facing Overlay (HFO) (QW-216)	Corrosion-Resistant Overlay (CRO) (QW-214)	
QW-402 Joints	.16	< Finished <i>t</i>	< Finished <i>t</i>	
QW-403 Base Metals	.20	ϕ P-Number	ϕ P-Number	
	.23	ϕ <i>T</i> Qualified	ϕ <i>T</i> Qualified	
QW-404 Filler Metals	.12	ϕ Classification		
	.37		ϕ A-Number	
	.38			ϕ Diameter (1st layer)
QW-405 Positions	.4	+ Position	+ Position	
QW-406 Preheat	.4	Dec. > 100°F (55°C) preheat > Interpass	Dec. > 100°F (55°C) preheat > Interpass	
QW-407 PWHT	.6	ϕ PWHT		
	.9		ϕ PWHT	
QW-409 Electrical Characteristics	.4	ϕ Current or polarity	ϕ Current or polarity	
	.22	Inc. > 10% 1st layer	Inc. > 10% 1st layer	
QW-410 Technique	.1			ϕ String/weave
	.5			ϕ Method of cleaning
	.26			± Peening
	.38	ϕ Multiple to single layer	ϕ Multiple to single layer	

Legend:

+ Addition
 - Deletion

> Increase/greater than
 < Decrease/less than

↑ Uphill
 ↓ Downhill

← Forehand
 → Backhand

ϕ Change

Table QW-254
Welding Variables Procedure Specifications (WPS) — Submerged-Arc Welding (SAW)

Paragraph		Brief of Variables	Essential	Supplementary Essential	Nonessential
QW-402 Joints	.1	ϕ Groove design			X
	.4	– Backing			X
	.10	ϕ Root spacing			X
	.11	\pm Retainers			X
QW-403 Base Metals	.5	ϕ Group Number		X	
	.6	T Limits		X	
	.8	ϕ T Qualified	X		
	.9	t Pass $\frac{1}{2}$ in. (13 mm)	X		
	.11	ϕ P-No. qualified	X		
QW-404 Filler Metals	.4	ϕ F-Number	X		
	.5	ϕ A-Number	X		
	.6	ϕ Diameter			X
	.9	ϕ Flux/wire class.	X		
	.10	ϕ Alloy flux	X		
	.24	\pm Supplemental ϕ	X		
	.27	ϕ Alloy elements	X		
	.29	ϕ Flux designation			X
	.30	ϕ t	X		
	.33	ϕ Classification			X
	.34	ϕ Flux type	X		
	.35	ϕ Flux/wire class.		X	X
	.36	Recrushed slag	X		
QW-405 Positions	.1	+ Position			X
QW-406 Preheat	.1	Decrease > 100°F (55°C)	X		
	.2	ϕ Preheat maint.			X
	.3	Increase > 100°F (55°C) (IP)		X	
QW-407 PWHT	.1	ϕ PWHT	X		
	.2	ϕ PWHT (T & T range)		X	
	.4	T Limits	X		
QW-409 Electrical Characteris- tics	.1	> Heat input		X	
	.4	ϕ Current or polarity		X	X
	.8	ϕ I & E range			X

Table QW-254
Welding Variables Procedure Specifications (WPS) — Submerged-Arc Welding (SAW) (Cont'd)

Paragraph		Brief of Variables	Essential	Supplementary Essential	Nonessential
QW-410 Technique	.1	ϕ String/weave			X
	.5	ϕ Method cleaning			X
	.6	ϕ Method back gouge			X
	.7	ϕ Oscillation			X
	.8	ϕ Tube-work distance			X
	.9	ϕ Multi to single pass/side		X	X
	.10	ϕ Single to multi electrodes		X	X
	.15	ϕ Electrode spacing			X
	.25	ϕ Manual or automatic			X
	.26	\pm Peening			X
	.64	Use of thermal processes	X		

Legend:

+ Addition

- Deletion

> Increase/greater than

< Decrease/less than

↑ Uphill

↓ Downhill

← Forehand

→ Backhand

 ϕ Change

Table QW-254.1
Welding Variables Procedure Specifications (WPS) — Submerged-Arc Welding (SAW)

Special Process Variables				
Paragraph		Essential Variables		Nonessential Variables for HFO and CRO
		Hard-Facing Overlay (HFO) (QW-216)	Corrosion-Resistant Overlay (CRO) (QW-214)	
QW-402 Joints	.16	< Finished <i>t</i>	< Finished <i>t</i>	
QW-403 Base Metals	.20	ϕ P-Number	ϕ P-Number	
	.23	ϕ T Qualified	ϕ T Qualified	
QW-404 Filler Metals	.6			ϕ Nominal size of electrode
	.12	ϕ Classification		
	.24	± or ϕ > 10% in supplemental filler metal	± or ϕ > 10% in supplemental filler metal	
	.27	ϕ Alloy elements		
	.37		ϕ A-Number	
	.39	ϕ Nominal flux comp.	ϕ Nominal flux comp.	
QW-405 Positions	.4	+ Position	+ Position	
QW-406 Preheat	.4	Dec. > 100°F (55°C) preheat > Interpass	Dec. > 100°F (55°C) preheat > Interpass	
QW-407 PWHT	.6	ϕ PWHT		
	.9		ϕ PWHT	
QW-409 Electrical Characteristics	.4	ϕ Current or polarity	ϕ Current or polarity	
	.26	1st layer — Heat input > 10%	1st layer — Heat input > 10%	
QW-410 Technique	.1			ϕ String/weave
	.5			ϕ Method of cleaning
	.7			ϕ Oscillation
	.8			ϕ Tube to work distance
	.15			ϕ Electrode spacing
	.25			ϕ Manual or automatic
	.26			± Peening
	.38	ϕ Multiple to single layer	ϕ Multiple to single layer	
	.40		- Supplemental device	
	.50	ϕ No. of electrodes	ϕ No. of electrodes	

Legend:

+ Addition
- Deletion

> Increase/greater than
< Decrease/less than

↑ Uphill
↓ Downhill

← Forehand
→ Backhand

ϕ Change

Table QW-255
Welding Variables Procedure Specifications (WPS) — Gas Metal-Arc Welding (GMAW and FCAW)

Paragraph		Brief of Variables	Essential	Supplementary Essential	Nonessential
QW-402 Joints	.1	ϕ Groove design			X
	.4	– Backing			X
	.10	ϕ Root spacing			X
	.11	\pm Retainers			X
QW-403 Base Metals	.5	ϕ Group Number		X	
	.6	T Limits		X	
	.8	ϕ T Qualified	X		
	.9	t Pass > $\frac{1}{2}$ in. (13 mm)	X		
	.10	T limits (S. cir. arc)	X		
	.11	ϕ P-No. qualified	X		
QW-404 Filler Metals	.4	ϕ F-Number	X		
	.5	ϕ A-Number	X		
	.6	ϕ Diameter			X
	.12	ϕ Classification		X	
	.23	ϕ Filler metal product form	X		
	.24	\pm or ϕ Supplemental	X		
	.27	ϕ Alloy elements	X		
	.30	ϕ t	X		
	.32	t Limits (S. cir. arc)	X		
	.33	ϕ Classification			X
QW-405 Positions	.1	+ Position			X
	.2	ϕ Position		X	
	.3	ϕ $\uparrow \downarrow$ Vertical welding			X
QW-406 Preheat	.1	Decrease > 100°F (55°C)	X		
	.2	ϕ Preheat maint.			X
	.3	Increase > 100°F (55°C) (IP)		X	
QW-407 PWHT	.1	ϕ PWHT	X		
	.2	ϕ PWHT (T & T range)		X	
	.4	T Limits	X		
QW-408 Gas	.1	\pm Trail or ϕ comp.			X
	.2	ϕ Single, mixture, or %	X		
	.3	ϕ Flow rate			X
	.5	\pm or ϕ Backing flow			X
	.9	– Backing or ϕ comp.	X		
	.10	ϕ Shielding or trailing	X		
QW-409 Electrical Characteristics	.1	> Heat input		X	
	.2	ϕ Transfer mode	X		
	.4	ϕ Current or polarity		X	X
	.8	ϕ I & E range			X

Table QW-255
Welding Variables Procedure Specifications (WPS) — Gas Metal-Arc Welding (GMAW and FCAW)
(Cont'd)

Paragraph		Brief of Variables	Essential	Supplementary Essential	Nonessential
QW-410 Technique	.1	ϕ String/weave			X
	.3	ϕ Orifice, cup, or nozzle size			X
	.5	ϕ Method cleaning			X
	.6	ϕ Method back gouge			X
	.7	ϕ Oscillation			X
	.8	ϕ Tube-work distance			X
	.9	ϕ Multiple to single pass/side		X	X
	.10	ϕ Single to multiple electrodes		X	X
	.15	ϕ Electrode spacing			X
	.25	ϕ Manual or automatic			X
	.26	± Peening			X
	.64	Use of thermal processes	X		

Legend:

+ Addition
 - Deletion

> Increase/greater than
 < Decrease/less than

↑ Uphill
 ↓ Downhill

← Forehand
 → Backhand

ϕ Change

Table QW-255.1
Welding Variables Procedure Specifications (WPS) — Gas Metal-Arc Welding (GMAW and FCAW)

Special Process Variables				
Paragraph		Essential Variables		Nonessential Variables for HFO and CRO
		Hard-Facing Overlay (HFO) (QW-216)	Corrosion-Resistant Overlay (CRO) (QW-214)	
QW-402 Joints	.16	< Finished t	< Finished t	
QW-403 Base Metals	.20	ϕ P-Number	ϕ P-Number	
	.23	ϕ T Qualified	ϕ T Qualified	
QW-404 Filler Metals	.6			ϕ Nominal size of electrode
	.12	ϕ Classification		
	.23	ϕ Filler metal product form	ϕ Filler metal product form	
	.24	\pm or ϕ > 10% in supplemental filler metal	\pm or ϕ > 10% in supplemental filler metal	
	.27	ϕ Alloy elements		
	.37		ϕ A-Number	
QW-405 Positions	.4	+ Position	+ Position	
QW-406 Preheat	.4	Dec. > 100°F (55°C) preheat > Interpass	Dec. > 100°F (55°C) preheat > Interpass	
QW-407 PWHT	.6	ϕ PWHT		
	.9		ϕ PWHT	
QW-408 Gas	.2	ϕ Single, mixture, or %	ϕ Single, mixture, or %	
	.3			ϕ Flow rate
QW-409 Electrical Characteristics	.4	ϕ Current or polarity	ϕ Current or polarity	
	.26	1st layer — Heat input > 10%	1st layer — Heat input > 10%	
QW-410 Technique	.1			ϕ String/weave
	.3			ϕ Orifice/cup or nozzle size
	.5			ϕ Method of cleaning
	.7			ϕ Oscillation
	.8			ϕ Tube to work distance
	.25			ϕ Manual or automatic
	.26			\pm Peening
	.38	ϕ Multiple to single layer	ϕ Multiple to single layer	
	.50	ϕ No. of electrodes	ϕ No. of electrodes	

Legend:

+ Addition
 - Deletion

> Increase/greater than
 < Decrease/less than

↑ Uphill
 ↓ Downhill

← Forehand
 → Backhand

 ϕ Change

Table QW-256
Welding Variables Procedure Specifications (WPS) — Gas Tungsten-Arc Welding (GTAW)

Paragraph		Brief of Variables	Essential	Supplementary Essential	Nonessential
QW-402 Joints	.1	ϕ Groove design			X
	.5	+ Backing			X
	.10	ϕ Root spacing			X
	.11	\pm Retainers			X
QW-403 Base Metals	.5	ϕ Group Number		X	
	.6	T Limits		X	
	.8	T Qualified	X		
	.11	ϕ P-No. qualified	X		
QW-404 Filler Metals	.3	ϕ Size			X
	.4	ϕ F-Number	X		
	.5	ϕ A-Number	X		
	.12	ϕ Classification		X	
	.14	\pm Filler	X		
	.22	\pm Consum. insert			X
	.23	ϕ Filler metal product form	X		
	.30	ϕ t	X		
	.33	ϕ Classification			X
	.50	\pm Flux			X
QW-405 Positions	.1	+ Position			X
	.2	ϕ Position		X	
	.3	ϕ \updownarrow Vertical welding			X
QW-406 Preheat	.1	Decrease > 100°F (55°C)	X		
	.3	Increase > 100°F (55°C) (IP)		X	
QW-407 PWHT	.1	ϕ PWHT	X		
	.2	ϕ PWHT (T & T range)		X	
	.4	T Limits	X		
QW-408 Gas	.1	\pm Trail or ϕ comp.			X
	.2	ϕ Single, mixture, or %	X		
	.3	ϕ Flow rate			X
	.5	\pm or ϕ Backing flow			X
	.9	- Backing or ϕ comp.	X		
	.10	ϕ Shielding or trailing	X		
QW-409 Electrical Characteris- tics	.1	> Heat input		X	
	.3	\pm Pulsing I			X
	.4	ϕ Current or polarity		X	X
	.8	ϕ I & E range			X
	.12	ϕ Tungsten electrode			X

Table QW-256
Welding Variables Procedure Specifications (WPS) — Gas Tungsten-Arc Welding (GTAW) (Cont'd)

Paragraph	Brief of Variables	Essential	Supplementary Essential	Nonessential
QW-410 Technique	.1 ϕ String/weave			X
	.3 ϕ Orifice, cup, or nozzle size			X
	.5 ϕ Method cleaning			X
	.6 ϕ Method back gouge			X
	.7 ϕ Oscillation			X
	.9 ϕ Multi to single pass/side		X	X
	.10 ϕ Single to multi electrodes		X	X
	.11 ϕ Closed to out chamber	X		
	.15 ϕ Electrode spacing			X
	.25 ϕ Manual or automatic			X
	.26 \pm Peening			X
	.64 Use of thermal processes	X		

Legend:

+ Addition

- Deletion

> Increase/greater than

< Decrease/less than

↑ Uphill

↓ Downhill

← Forehand

→ Backhand

 ϕ Change

Table QW-256.1
Welding Variables Procedure Specifications (WPS) — Gas Tungsten-Arc Welding (GTAW)

Special Process Variables				
Paragraph		Essential Variables		Nonessential Variables for HFO and CRO
		Hard-Facing Overlay (HFO) (QW-216)	Corrosion-Resistant Overlay (CRO) (QW-214)	
QW-402 Joints	.16	< Finished <i>t</i>	< Finished <i>t</i>	
QW-403 Base Metals	.20	ϕ P-Number	ϕ P-Number	
	.23	ϕ <i>T</i> Qualified	ϕ <i>T</i> Qualified	
QW-404 Filler Metals	.3			ϕ Wire size
	.12	ϕ Classification		
	.14	± Filler metal	± Filler metal	
	.23	ϕ Filler metal product form	ϕ Filler metal product form	
	.37		ϕ A-Number	
QW-405 Positions	.4	+ Position	+ Position	
QW-406 Preheat	.4	Dec. > 100°F (55°C) preheat > Interpass	Dec. > 100°F (55°C) preheat > Interpass	
QW-407 PWHT	.6	ϕ PWHT		
	.9		ϕ PWHT	
QW-408 Gas	.2	ϕ Single, mixture, or %	ϕ Single, mixture, or %	
	.3			ϕ Flow rate
QW-409 Electrical Characteris- tics	.4	ϕ Current or polarity	ϕ Current or polarity	
	.12			ϕ Tungsten electrode
	.26	1st layer — Heat input > 10%	1st layer — Heat input > 10%	
QW-410 Technique	.1			ϕ String/weave
	.3			ϕ Orifice/cup or nozzle size
	.5			ϕ Method of cleaning
	.7			ϕ Oscillation
	.15			ϕ Electrode spacing
	.25			ϕ Manual or automatic
	.26			± Peening
	.38	ϕ Multiple to single layer	ϕ Multiple to single layer	
	.50	ϕ No. of electrodes	ϕ No. of electrodes	
	.52			ϕ Filler metal delivery

Legend:

+ Addition
 - Deletion

> Increase/greater than
 < Decrease/less than

↑ Uphill
 ↓ Downhill

← Forehand
 → Backhand

ϕ Change

Table QW-257
Welding Variables Procedure Specifications (WPS) — Plasma-Arc Welding (PAW)

Paragraph	Brief of Variables	Essential	Supplementary Essential	Nonessential
QW-402 Joints	.1 ϕ Groove design		X	
	.5 + Backing			X
	.10 ϕ Root spacing			X
	.11 \pm Retainers			X
QW-403 Base Metals	.5 ϕ Group Number		X	
	.6 T Limits		X	
	.8 ϕ T Qualified	X		
	.12 ϕ P-Number/melt-in	X		
QW-404 Filler Metals	.3 ϕ Size			X
	.4 ϕ F-Number	X		
	.5 ϕ A-Number	X		
	.12 ϕ Classification		X	
	.14 \pm Filler metal	X		
	.22 \pm Consum. insert			X
	.23 ϕ Filler metal product form	X		
	.27 ϕ Alloy elements	X		
	.30 ϕ t	X		
	.33 ϕ Classification			X
QW-405 Positions	.1 + Position			X
	.2 ϕ Position		X	
	.3 ϕ \updownarrow Vertical welding			X
QW-406 Preheat	.1 Decrease > 100°F (55°C)	X		
	.3 Increase > 100°F (55°C) (IP)		X	
QW-407 PWHT	.1 ϕ PWHT	X		
	.2 ϕ PWHT (T & T range)		X	
	.4 ϕ Limits	X		
QW-408 Gas	.1 \pm Trail or ϕ comp.			X
	.4 ϕ Composition	X		
	.5 \pm Or ϕ backing flow			X
	.9 – Backing or ϕ comp.	X		
	.10 ϕ Shielding or trailing	X		
	.21 ϕ Flow rate			X
QW-409 Electrical Characteristics	.1 > Heat input		X	
	.4 ϕ Current or polarity		X	X
	.8 ϕ I & E range			X
	.12 ϕ Tungsten electrode			X

Table QW-257
Welding Variables Procedure Specifications (WPS) — Plasma-Arc Welding (PAW) (Cont'd)

Paragraph	Brief of Variables	Essential	Supplementary Essential	Nonessential
QW-410 Technique	.1 ϕ String/weave			X
	.3 ϕ Orifice, cup, or nozzle size			X
	.5 ϕ Method cleaning			X
	.6 ϕ Method back gouge			X
	.7 ϕ Oscillation			X
	.9 ϕ Multiple to single pass/side		X	X
	.10 ϕ Single to multiple electrodes		X	X
	.11 ϕ Closed to out chamber	X		
	.12 ϕ Melt-in to keyhole		X	
	.15 ϕ Electrode spacing			X
	.26 \pm Peening			X
	.64 Use of thermal processes	X		

Legend:

+ Addition
 - Deletion

> Increase/greater than
 < Decrease/less than

↑ Uphill
 ↓ Downhill

← Forehand
 → Backhand

ϕ Change

Table QW-257.1
Welding Variables Procedure Specifications (WPS) — Plasma-Arc Welding (PAW)

Special Process Variables					
Paragraph		Essential Variables			Nonessential Variables for HFO, CRO, and HFSF
		Hard-Facing Overlay (HFO) (QW-216)	Corrosion-Resistant Overlay (CRO) (QW-214)	Hard-Facing Spray Fuse (HFSF) (QW-216)	
QW-402 Joints	.16	< Finished t	< Finished t		
	.17			> Finished t	
QW-403 Base Metals	.20	ϕ P-Number	ϕ P-Number	ϕ P-Number	
	.23	ϕ T Qualified	ϕ T Qualified		
QW-404 Filler Metals	.12	ϕ Classification		ϕ Classification	
	.14	\pm Filler metal	\pm Filler metal		
	.37		ϕ A-Number		
	.41	ϕ > 10% Powder feed rate	ϕ > 10% Powder feed rate		
	.42			ϕ > 5% Particle size	
	.43	ϕ Particle size	ϕ Particle size		
	.44	ϕ Powder type	ϕ Powder type		
	.45	ϕ Filler metal form	ϕ Filler metal form		
	.46			ϕ Powder feed rate	
QW-405 Positions	.4	+ Position	+ Position	+ Position	
QW-406 Preheat	.4	Dec. > 100°F (55°C) preheat > Interpass	Dec. > 100°F (55°C) preheat > Interpass	Dec. > 100°F (55°C) preheat > Interpass	
	.5			ϕ Preheat maintenance	
QW-407 PWHT	.6	ϕ PWHT		ϕ PWHT	
	.7			ϕ PWHT after fusing	
	.9		ϕ PWHT		
QW-408 Gas	.1				\pm Trail or π comp.
	.16	ϕ > 5% Arc or metal feed gas	ϕ > 5% Arc or metal feed gas	ϕ > 5% Arc or metal feed gas	
	.17	ϕ Type or mixture	ϕ Type or mixture		
	.18	ϕ > 10% Mix. comp.	ϕ > 10% Mix. comp.		
	.19			ϕ Plasma/feed gas comp.	
	.20			ϕ Plasma gas flow-rate range	
QW-409 Electrical Characteris- tics	.4	ϕ Current or polarity	ϕ Current or polarity		
	.12			ϕ Type or size of electrode	
	.23			ϕ > 10% I & E	
	.24	ϕ > 10% Filler wire watt.	ϕ > 10% Filler wire watt.		
	.25	ϕ > 10% I & E	ϕ > 10% I & E		

Table QW-257.1
Welding Variables Procedure Specifications (WPS) — Plasma-Arc Welding (PAW) (Cont'd)

Special Process Variables				
Paragraph	Essential Variables			Nonessential Variables for HFO, CRO, and HFSF
	Hard-Facing Overlay (HFO) (QW-216)	Corrosion-Resistant Overlay (CRO) (QW-214)	Hard-Facing Spray Fuse (HFSF) (QW-216)	
QW-410 Technique	.1			ϕ String/weave (HFO and CRO only)
	.3			ϕ Orifice/cup or nozzle size
	.5			ϕ Method of cleaning
	.7			ϕ Oscillation
	.25			ϕ Manual or automatic
	.26			± Peening
	.38 ϕ Multiple to single layer	ϕ Multiple to single layer	ϕ Multiple to single layer	
	.41 ϕ > 15% Travel speed	ϕ > 15% Travel speed		
	.43		ϕ > 10% Travel speed range	
	.44		ϕ > 15% Torch to workplace	
	.45		ϕ Surface preparation	
	.46		ϕ Spray torch	
	.47		ϕ > 10% Fusing temp. or method	
	.48 ϕ Transfer mode	ϕ Transfer mode	ϕ Transfer mode	
	.49 ϕ Torch orifice diameter	ϕ Torch orifice diameter		
	.52 ϕ Filler metal del.	ϕ Filler metal del.		
Legend: + Addition > Increase/greater than ↑ Uphill ← Forehand ϕ Change - Deletion < Decrease/less than ↓ Downhill → Backhand				

Table QW-258
Welding Variables Procedure Specifications (WPS) — Electroslag Welding (ESW)

Paragraph		Brief of Variables	Essential	Supplementary Essential	Nonessential
QW-402 Joints	.1	ϕ Groove design			X
	.10	ϕ Root spacing			X
	.11	± Retainers	X		
QW-403 Base Metals	.1	ϕ P-Number	X		
	.4	ϕ Group Number		X	
	.9	t Pass > 1/2 in. (13 mm)	X		
QW-404 Filler Metals	.4	ϕ F-Number	X		
	.5	ϕ A-Number	X		
	.6	ϕ Diameter			X
	.12	ϕ Classification		X	
	.17	ϕ Flux type or comp.	X		
	.18	ϕ Wire to plate	X		
	.19	ϕ Consum. guide	X		
	.33	ϕ Classification			X
QW-407 PWHT	.1	ϕ PWHT	X		
	.2	ϕ PWHT (T & T range)		X	
	.4	T Limits	X		
QW-409 Electrical Characteristics	.5	ϕ ± 15% I & E range	X		
QW-410 Technique	.5	ϕ Method cleaning			X
	.7	ϕ Oscillation	X		
	.10	ϕ Single to multiple electrodes	X		
	.15	ϕ Electrode spacing			X
	.26	± Peening			X
	.64	Use of thermal processes	X		

Legend:

+ Addition
 - Deletion

> Increase/greater than
 < Decrease/less than

↑ Uphill
 ↓ Downhill

← Forehand
 → Backhand

ϕ Change

Table QW-258.1
Welding Variables Procedure Specifications (WPS) — Electroslag Welding (ESW)

Special Process Variables				
Paragraph		Essential Variables		Nonessential Variables for HFO and CRO
		Hard-Facing Overlay (HFO) (QW-216)	Corrosion-Resistant Overlay (CRO) (QW-214)	
QW-402 Joints	.16	< Finished t	< Finished t	
QW-403 Base Metals	.20	ϕ P-Number	ϕ P-Number	
	.23	ϕ T Qualified	ϕ T Qualified	
QW-404 Filler Metals	.6			ϕ Nominal size of electrode
	.12	ϕ Classification		
	.24	\pm or ϕ > 10% in supplemental filler metal	\pm or ϕ > 10% in supplemental filler metal	
	.37		ϕ A-Number	
	.39	ϕ Nominal flux comp.	ϕ Nominal flux comp.	
QW-406 Preheat	.4	Dec. > 100°F (55°C) preheat > Interpass	Dec. > 100°F (55°C) preheat > Interpass	
QW-407 PWHT	.6	ϕ PWHT		
	.9		ϕ PWHT	
QW-409 Electrical Characteristics	.4	ϕ Current or polarity	ϕ Current or polarity	
	.26	1st layer — Heat input > 10%	1st layer — Heat input > 10%	
QW-410 Technique	.5			ϕ Method of cleaning
	.7			ϕ Oscillation (CRO only)
	.38	ϕ Multiple to single layer	ϕ Multiple to single layer	
	.40	– Supplemental device	– Supplemental device	
	.50	ϕ No. of electrodes	ϕ No. of electrodes	

Legend:

+ Addition	> Increase/greater than	↑ Uphill	← Forehand	ϕ Change
– Deletion	< Decrease/less than	↓ Downhill	→ Backhand	

Table QW-259
Welding Variables Procedure Specifications (WPS) — Electrogas Welding (EGW)

Paragraph		Brief of Variables	Essential	Supplementary Essential	Nonessential
QW-402 Joints	.1	ϕ Groove design			X
	.10	ϕ Root spacing			X
	.11	± Retainers	X		
QW-403 Base Metals	.1	ϕ P-Number	X		
	.5	ϕ Group Number		X	
	.6	T Limits		X	
	.8	ϕ T Qualified	X		
	.9	t Pass > 1/2 in. (13 mm)	X		
QW-404 Filler Metals	.4	ϕ F-Number	X		
	.5	ϕ A-Number	X		
	.6	ϕ Diameter			X
	.12	ϕ Classification		X	
	.23	ϕ Filler metal product form	X		
	.33	ϕ Classification			X
QW-406 Preheat	.1	Decrease > 100°F (55°C)			X
QW-407 PWHT	.1	ϕ PWHT	X		
	.2	ϕ PWHT (T & T range)		X	
	.4	T Limits	X		
QW-408 Gas	.2	ϕ Single, mixture, or %	X		
	.3	ϕ Flow rate			X
QW-409 Electrical Characteris- tics	.1	> Heat input		X	
	.4	ϕ Current or polarity		X	X
	.8	ϕ I & E range			X
QW-410 Technique	.5	ϕ Method cleaning			X
	.7	ϕ Oscillation			X
	.8	ϕ Tube-work distance			X
	.9	ϕ Multiple to single pass/side		X	X
	.10	ϕ Single to multiple electrodes	X		
	.15	ϕ Electrode spacing			X
	.26	± Peening			X
	.64	Use of thermal processes	X		

Legend:

+ Addition
 - Deletion

> Increase/greater than
 < Decrease/less than

↑ Uphill
 ↓ Downhill

← Forehand
 → Backhand

ϕ Change

GENERAL NOTE: Automated vertical gas metal-arc welding for vertical position only.

Table QW-260
Welding Variables Procedure Specifications (WPS) — Electron Beam Welding (EBW)

Paragraph		Brief of Variables	Essential	Supplementary Essential	Nonessential
QW-402 Joints	.1	ϕ Groove design	X		
	.2	- Backing	X		
	.6	> Fit-up gap	X		
QW-403 Base Metals	.1	ϕ P-Number	X		
	.3	ϕ Penetration	X		
	.15	ϕ P-Number	X		
QW-404 Filler Metals	.1	ϕ Cross section or speed	X		
	.2	< t or ϕ comp.	X		
	.8	\pm or ϕ Chem. comp.	X		
	.14	\pm Filler	X		
	.20	ϕ Method of addition	X		
	.21	ϕ Analysis	X		
	.33	ϕ Classification			X
QW-406 Preheat	.1	Decrease > 100°F (55°C)	X		
QW-407 PWHT	.1	ϕ PWHT	X		
QW-408 Gas	.6	ϕ Environment	X		
QW-409 Electrical Characteristics	.6	ϕ I, E, speed, distance, osc.	X		
	.7	ϕ Pulsing frequency	X		
QW-410 Technique	.5	ϕ Method cleansing			X
	.7	ϕ Oscillation	X		
	.14	ϕ Angle of beam axis	X		
	.17	ϕ Type equip.	X		
	.18	> Pressure of vacuum	X		
	.19	ϕ Filament type, size, etc.	X		
	.20	+ Wash pass	X		
	.21	1 vs. 2 side welding	X		
	.64	Use of thermal processes	X		

Legend:

+ Addition
- Deletion

> Increase/greater than
< Decrease/less than

↑ Uphill
↓ Downhill

← Forehand
→ Backhand

ϕ Change

(13)

Table QW-261
Welding Variables Procedure Specifications (WPS) — Stud Welding

Paragraph		Brief of Variables	Essential	Supplementary Essential	Nonessential
QW-402 Joints	.8	ϕ Stud shape size	X		
	.9	– Flux or ferrule	X		
QW-403 Base Metal	.17	ϕ Base metal or stud metal P-No.	X		
QW-405 Positions	.1	+ Position	X		
QW-406 Preheat	.1	Decrease > 100°F (55°C)	X		
QW-407 PWHT	.1	ϕ PWHT	X		
QW-408 Gas	.2	ϕ Single, mixture, or %	X		
QW-409 Electrical Characteristics	.4	ϕ Current or polarity	X		
	.9	ϕ Arc timing	X		
	.10	ϕ Amperage	X		
	.11	ϕ Power source	X		
QW-410 Technique	.22	ϕ Gun model or lift	X		
	.64	Use of thermal processes	X		

Legend:

+ Addition
 – Deletion

> Increase/greater than
 < Decrease/less than

↑ Uphill
 ↓ Downhill

← Forehand
 → Backhand

ϕ Change

Table QW-262
Welding Variables Procedure Specifications (WPS) — Inertia and Continuous Drive Friction Welding

Paragraph		Brief of Variables	Essential	Supplementary Essential	Nonessential
QW-402 Joints	.12	ϕ \pm 10 deg	X		
		ϕ Cross section > 10%	X		
		ϕ O.D. > \pm 10%	X		
		ϕ Solid-to-tube	X		
QW-403 Base Metals	.19	ϕ Base metal	X		
QW-406 Preheat	.1	ϕ Decrease > 100°F (55°C)	X		
QW-407 PWHT	.1	ϕ PWHT	X		
QW-408 Gas	.6	ϕ Environment	X		
QW-410 Technique	.27	ϕ Spp. > \pm 10%	X		
	.28	ϕ Load > \pm 10%	X		
	.29	ϕ Energy > \pm 10%	X		
	.30	ϕ Upset > \pm 10%	X		
	.64	Use of thermal processes	X		

Legend:

+ Addition
 - Deletion

> Increase/greater than
 < Decrease/less than

↑ Uphill
 ↓ Downhill

← Forehand
 → Backhand

ϕ Change

Table QW-263
Welding Variables Procedure Specifications (WPS) — Resistance Welding

Paragraph		Brief of Variables	Essential	Nonessential
QW-402 Joints	.13	ϕ Spot, projection, seam	X	
	.14	ϕ Overlap, spacing	X	
	.15	ϕ Projection, shape, size	X	
QW-403 Base Metals	.1	ϕ P-No.	X	
	.21	\pm Coating, plating	X	
	.22	\pm T	X	
QW-407 PWHT	.1	ϕ PWHT	X	
QW-408 Gas	.23	- Gases	X	
QW-409 Electrical	.13	ϕ RWMA class	X	
	.14	\pm ϕ Slope	X	
	.15	ϕ Pressure, current, time	X	
	.17	ϕ Power supply		X
	.18	Tip cleaning		X
QW-410 Technique	.31	ϕ Cleaning method	X	
	.32	ϕ Pressure, time	X	
	.33	ϕ Equipment	X	
	.34	ϕ Cooling medium		X
	.35	ϕ Throat		X
	.64	Use of thermal processes	X	

Legend:

+ Addition
 - Deletion

> Increase/greater than
 < Decrease/less than

↑ Uphill
 ↓ Downhill

← Forehand
 → Backhand

ϕ Change

Table QW-264
Welding Variables Procedure Specifications (WPS) — Laser Beam Welding (LBW)

Paragraph	Brief of Variables	Essential	Supplementary Essential	Nonessential
QW-402 Joints	.2 ± Backing	X		
	.6 > Fit-up gap	X		
	.18 ϕ Lap joint config.	X		
	.25 ϕ Lap to groove	X		
	.26 < Bevel angle > 5 deg	X		
QW-403 Base Metals	.1 ϕ P-Number	X		
	.3 ϕ Penetration	X		
QW-404 Filler Metals	.1 ϕ Cross section or speed	X		
	.2 < t or ϕ comp.	X		
	.4 ϕ F-No.	X		
	.5 ϕ A-No.	X		
	.8 ± or ϕ chem. comp.	X		
	.14 ± Filler metal	X		
	.20 ϕ Method of addition	X		
QW-406 Preheat	.1 Decrease > 100°F (55°C)	X		
QW-407 PWHT	.1 ϕ PWHT	X		
QW-408 Gas	.2 ϕ Single, mixture, or %	X		
	.6 ϕ Environment	X		
	.11 ± Gases	X		
	.12 Decrease > 10% flow rate	X		
QW-409 Electrical Characteristics	.19 ϕ Pulse	X		
	.20 ϕ Mode, energy	X		
	.21 Decrease > 10% power	X		
QW-410 Technique	.5 ϕ Method cleaning			X
	.7 ϕ Oscillation	X		
	.14 ϕ Angle of beam axis	X		
	.20 + Wash pass	X		
	.21 1 vs. 2 side welding	X		
	.37 ϕ Single to multiple pass	X		
	.64 Use of thermal processes	X		
	.66 ϕ Travel, Beam factors	X		
	.67 ϕ Optical technique	X		
	.68 ϕ Type of equipment	X		
	.77 ϕ Wavelength	X		
	.80 ϕ Spot size	X		

Legend:

+ Addition
- Deletion

> Increase/greater than
< Decrease/less than

↑ Uphill
↓ Downhill

← Forehand
→ Backhand

ϕ Change

(13)

Table QW-264.1
Welding Variables Procedure Specifications (WPS) — Laser Beam Welding (LBW)

Special Process Variables				
Paragraph		Essential Variables		Nonessential Variables for HFO and CRO
		Hard-Facing Overlay (HFO) (QW-216)	Corrosion-Resistant Overlay (CRO) (QW-214)	
QW-402 Joints	.16	< Finished <i>t</i>	< Finished <i>t</i>	
QW-403 Base Metals	.20	ϕ P-Number	ϕ P-Number	
QW-404 Filler Metals	.12	ϕ Classification	ϕ Classification	
	.27	ϕ Alloy elements	ϕ Alloy elements	
	.44	ϕ Particle type	ϕ Particle type	
	.47	ϕ Filler/powder metal size	ϕ Filler/powder metal size	
	.48	ϕ Powder metal density	ϕ Powder metal density	
	.49	ϕ Filler metal powder feed rate	ϕ Filler metal powder feed rate	
QW-405 Positions	.1	+ Position	+ Position	
QW-406 Preheat	.4	Dec. > 100°F (55°C) preheat > Interpass	Dec. > 100°F (55°C) preheat > Interpass	
QW-407 PWHT	.6	ϕ PWHT		
	.9		ϕ PWHT	
QW-408 Gas	.2	ϕ Single, mixture, or %	ϕ Single, mixture, or %	
	.6	ϕ Environment	ϕ Environment	
	.11	± Gases	± Gases	
	.12	Decrease > 10% flow rate	Decrease > 10% flow rate	
QW-409 Electrical Characteristics	.19	ϕ Pulse	ϕ Pulse	
	.20	ϕ Mode, energy	ϕ Mode, energy	
	.21	Decrease > 10% power	Decrease > 10% power	
QW-410 Technique	.5			ϕ Method of cleaning
	.7	ϕ Oscillation	ϕ Oscillation	
	.14	ϕ Angle of beam axis	ϕ Angle of beam axis	
	.17	ϕ Type/model of equipment	ϕ Type/model of equipment	
	.38	ϕ Multiple to single layer	ϕ Multiple to single layer	
	.45	ϕ Method of surface prep.	ϕ Method of surface prep.	
	.52	ϕ Filler metal delivery	ϕ Filler metal delivery	
	.53	ϕ Overlap, spacing	ϕ Overlap, spacing	
	.77	ϕ Wavelength	ϕ Wavelength	
	.80	ϕ Spot size	ϕ Spot size	

Legend:

+ Addition
 - Deletion

> Increase/greater than
 < Decrease/less than

↑ Uphill
 ↓ Downhill

← Forehand
 → Backhand

ϕ Change

Table QW-265
Welding Variables Procedure Specifications (WPS) — Flash Welding

Paragraph		Brief of Variables	Essential	Supplementary Essential	Nonessential
QW-402 Joints	.19	ϕ Diameter or thickness	X		
	.20	ϕ Joint configuration	X		
	.21	ϕ Method or equip. used to minimize ID flash	X		
	.22	ϕ End preparation method	X		
QW-403 Base Metals	.24	ϕ Spec., type, or grade	X		
QW-406 Preheat	.7	ϕ > 10% Amperage or number of preheat cycles, or method, or > 25°F temperature	X		
QW-407 PWHT	.8	ϕ PWHT, PWHT cycles, or separate PWHT time or temperature	X		
QW-408 Gas	.22	ϕ Shielding gas composition, pressure, or purge time	X		
QW-409 Electrical Characteristics	.27	ϕ > 10% Flashing time	X		
	.28	ϕ > 10% Upset current time	X		
QW-410 Technique	.17	ϕ Type/model of equipment	X		
	.54	ϕ > 10% Upset length or force	X		
	.55	ϕ > 10% Distance between clamping dies or preparation of clamping area	X		
	.56	ϕ Clamping force	X		
	.57	ϕ 10% Forward or reverse speed	X		
	.64	Use of thermal processes	X		

Legend:

+ Addition
 - Deletion

> Increase/greater than
 < Decrease/less than

↑ Uphill
 ↓ Downhill

← Forehand
 → Backhand

ϕ Change

Table QW-266
Welding Variables Procedure Specifications (WPS) — Diffusion Welding (DFW)

Paragraph		Brief of Variables	Essential	Supplementary Essential	Nonessential
QW-403 Base Metals	.28	Base metal grade	X		
	.29	ϕ Surface finish	X		
QW-404 Filler Metal	.53	\pm Filler metal and composition	X		
QW-407 PWHT	.10	\pm PWHT temperature, time, cooling rate	X		
QW-408 Gas	.25	ϕ Furnace Atmosphere	X		
QW-410 Technique	.70	ϕ Preassembly Cleaning	X		
	.71	< Block Compression	X		
	.72	< Welding time or temperature	X		

Legend:

+ Addition
 - Deletion

> Increase/greater than
 < Decrease/less than

↑ Uphill
 ↓ Downhill

← Forehand
 → Backhand

ϕ Change

Table QW-267
Welding Variables Procedure Specifications — Friction Stir Welding (FSW)

Paragraph		Brief of Variables	Essential	Supplementary Essential	Nonessential
QW-402 Joints	.27	ϕ Fixed backing	X		
	.28	ϕ Joint design	X		
	.29	ϕ Joint spacing > 10%	X		
QW-403 Base Metals	.19	ϕ Type/grade	X		
	.30	ϕ T qualified > 20%	X		
QW-407 PWHT	.1	ϕ PWHT	X		
QW-408 Gas	.26	ϕ Shielding gas	X		
QW-410 Technique	.21	1-side vs. 2-side welding	X		
	.73	ϕ Joint restraint	X		
	.74	ϕ Control method	X		
	.75	ϕ Tool design	X		
	.76	ϕ Tool operation	X		

Legend:

+ Addition
 - Deletion

> Increase/greater than
 < Decrease/less than

↑ Uphill
 ↓ Downhill

← Forehand
 → Backhand

ϕ Change

(13)

Table QW-268
Welding Variables Procedure Specifications (WPS) — Hybrid Laser-GMAW

Paragraph		Brief of Variables	GMAW			LBW		
			Essential	Supple- mentary Essential	Nonessential	Essential	Supple- mentary Essential	Nonessential
QW-402 Joints	.30	ϕ Weld joint design	X			X		
QW-403 Base Materials	.1	ϕ P-No.	X			X		
	.5	ϕ Group number		X		X		
	.31	ϕ T	X			X		
QW-404 Filler Metals	.4	ϕ F-Number	X					
	.5	ϕ A-Number	X					
	.6	ϕ Diameter	X					
	.33	ϕ Classification	X					
	.54	$> t$	X			X		
QW-405 Positions	.1	+ Position	X					
	.3	ϕ \updownarrow Vertical welding	X					
QW-406 Preheat	.1	Decrease $> 100^{\circ}\text{F}$	X			X		
	.2	ϕ Preheat maintenance			X			
	.3	Increase $> 100^{\circ}\text{F}$ (IP)		X		X		
QW-407 PWHT	.1	ϕ PWHT	X			X		
	.2	ϕ PWHT (T & T range)		X		X		
QW-408 Gas	.2	ϕ Single, mixture, or %	X			X		
	.3	ϕ Flow rate			X			
	.9	- Backing or ϕ composition	X			X		
	.10	ϕ Shielding or trailing	X			X		
	.12	ϕ $> 5\%$ gases				X		
QW-409 Electrical Characteris- tics	.1	$>$ Heat input		X				
	.2	ϕ Transfer mode			X			
	.4	ϕ Current or polarity		X				
	.8	ϕ I & E range			X			
	.19	ϕ Pulse				X		
	.20	ϕ Mode, energy				X		
	.21	ϕ Power, speed, d/fl, distance				X		

Table QW-268
Welding Variables Procedure Specifications (WPS) — Hybrid Laser-GMAW (Cont'd)

Paragraph	Brief of Variables	GMAW			LBW		
		Essential	Supple- mentary	Nonessential	Essential	Supple- mentary	Nonessential
QW-410 Technique	.3 ϕ Orifice, cup, or nozzle size			X			
	.5 ϕ Method of cleaning			X			X
	.6 ϕ Method of back gouging			X			
	.7 ϕ Oscillation	X			X		
	.8 ϕ Tube-to-work distance			X			
	.10 ϕ Single or multiple electrodes		X				
	.14 ϕ Angle or beam axis				X		
	.15 ϕ Electrode spacing		X				
	.21 1-side vs. 2-side welding	X			X		
	.26 \pm Peening			X			
	.37 ϕ Single to multiple pass	X			X		
	.64 Use of thermal processes	X			X		
	.66 ϕ Travel, beam factors				X		
	.67 ϕ Optical technique				X		
	.68 ϕ Type/model of equipment				X		
	.77 ϕ Wavelength				X		
	.78 ϕ Process sequence	X			X		
	.79 ϕ Process separation	X			X		
	.80 ϕ Spot size				X		

Legend:

+ Addition
- Deletion

> Increase/greater than
< Decrease/less than

↑ Uphill
↓ Downhill

← Forehand
→ Backhand

ϕ Change

(13)

Table QW-269
Welding Variables Procedure Specifications (WPS) — Hybrid Plasma-GMAW

Paragraph	Brief of Variables	PAW			GMAW		
		Essential	Supple- mentary	Nonessential	Essential	Supple- mentary Essential	Nonessential
QW-402 Joints	.1 Groove design		X			X	
	.5 + Backing			X			X
	.10 Root spacing			X			X
	.11 ± Retainers			X			X
QW-403 Base Metals	.5 Group number		X				
	.6 <i>T</i> limits		X				
	.8 <i>T</i> qualified	X			X		
	.9 <i>T</i> pass > 1/2 in. (13 mm)	X			X		
	.11 P-No. qualified				X		
	.12 P-Number/melt-in	X					
QW-404 Filler Metals	.3 Size			X			
	.4 F-Number	X			X		
	.5 A-Number	X			X		
	.6 Diameter			X			X
	.12 Classification		X			X	
	.14 ± Filler metal	X					
	.22 ± Consum. insert			X			
	.23 Filler metal form	X			X		
	.24 ± Supplemental				X		
	.27 Alloy elements	X					
	.30 <i>t</i>			X	X		
	.33 Classification				X		
QW-405 Positions	.1 + Position			X			X
	.2 Position		X			X	
	.3 Vertical welding			X			X
QW-406 Preheat	.1 Decrease > 100°F (55°C)	X			X		
	.2 Preheat maint.			X			X
	.3 Increase > 100°F (55°C)		X			X	
QW-407 PWHT	.1 PWHT	X			X		
	.2 PWHT (<i>T</i> & <i>T</i> range)		X			X	
	.4 <i>T</i> limits	X			X		
QW-408 Gas	.1 + Trail or comp.			X			X
	.2 Single, mixture, or %				X		
	.3 Flow rate						X
	.4 Composition	X					
	.5 + Or backing flow			X			X
	.9 - Backing or comp.	X					X
	.10 Shielding or trailing	X			X		
	.21 Flow rate			X			
QW-409 Electrical Characteris- tics	.1 > Heat input	X			X		
	.4 Current or polarity	X			X		
	.8 I & E		X				X
	.12 Tungsten electrode		X				

Table QW-269
Welding Variables Procedure Specifications (WPS) — Hybrid Plasma-GMAW (Cont'd)

Paragraph	Brief of Variables	PAW			GMAW		
		Essential	Supple- mentary	Nonessential	Essential	Supple- mentary Essential	Nonessential
QW-410 Technique	.1 Stinger/weave			X			X
	.3 Orifice, cup, or nozzle size			X			X
	.5 Method of cleaning			X			X
	.6 Method of backgouge			X			X
	.7 Oscillation			X			X
	.8 Tube-to-work distance						X
	.9 Single to multiple pass/side		X	X		X	X
	.10 Single to multiple electrodes		X	X		X	X
	.11 Closed to out chamber	X					
	.12 Melt-in to keyhole		X				
	.15 Electrode spacing			X			X
	.26 Peening			X			X
	.64 Use of thermal processes	X			X		
	.77 ϕ Orientation or #	X			X		
	.78 ϕ Process spacing	X			X		
	.79 ϕ Height differential	X			X		
	.80 ϕ Angle of plasma	X			X		

Legend:

+ Addition
- Deletion

> Increase/greater than
< Decrease/less than

↑ Uphill
↓ Downhill

← Forehand
→ Backhand

ϕ Change

(13)

Table QW-269.1
Welding Variables Procedure Specifications (WPS) — Hybrid Plasma-GMAW

Special Process Variables						
Paragraph		Brief of Variables	Hardfacing		Corrosion Resistant Overlay (CRO)	
			Essential	Nonessential	Essential	Nonessential
QW-402 Joints	.16	< Finished <i>t</i>	X		X	
QW-403 Base Metals	.20	P Number	X		X	
	.23	<i>T</i> qualified	X		X	
QW-404 Filler Metals	.6	Nominal size of electrode		X		X
	.12	Classification	X			X
	.14	± Filler metal	X		X	
	.23	Product form	X		X	
	.24	Supplemental filler	X		X	
	.27	Alloy elements	X			
	.37	A Number			X	
	.41	Powder feed rate	X		X	
	.43	Particle size	X		X	
	.44	Powder type	X		X	
QW-405 Positions	.4	+ Position	X		X	
QW-406 Preheat	.4	Decrease > 100°F (55°C) in preheat/ increase of interpass	X		X	
QW-407 PWHT	.6	Change in PWHT	X			
	.9	Change in PWHT			X	
QW-408 Gas	.2	Single, mixture, or %	X		X	
	.3	Flow rate		X		X
	.16	> 5% arc or metal feed gas	X		X	
	.17	Type or mixture	X		X	
	.18	> 10% mix comp.	X			
QW-409 Electrical Characteris- tics	.4	Current or polarity	X		X	
	.24	> 10% change in filler wire watts	X		X	
	.25	> 10% I & E	X		X	
	.26	1st layer heat input > 10%	X		X	

Table QW-269.1
Welding Variables Procedure Specifications (WPS) — Hybrid Plasma-GMAW (Cont'd)

Special Process Variables					
Paragraph	Brief of Variables	Hardfacing		Corrosion Resistant Overlay (CRO)	
		Essential	Nonessential	Essential	Nonessential
QW-410 Technique	.1 Stinger/weave		X		X
	.3 Orifice/cup or nozzle size		X		X
	.5 Method of cleaning		X		X
	.7 Oscillation		X		X
	.8 Contact tip to work dist.		X		X
	.15 Electrode spacing	X		X	
	.26 Peening		X		X
	.38 Multiple or single layer	X		X	
	.41 > 15% travel speed	X		X	
	.48 Transfer mode	X		X	
	.49 Torch orifice diameter	X		X	
	.50 No. of electrodes	X		X	
	.52 Method of filler delivery	X		X	
	.77 ϕ Orientation or #	X		X	
	.78 ϕ Process spacing	X		X	
	.79 ϕ Height differential	X		X	
	.80 ϕ Angle of plasma	X		X	

Legend:

+ Addition
 - Deletion

> Increase/greater than
 < Decrease/less than

↑ Uphill
 ↓ Downhill

← Forehand
 → Backhand

ϕ Change

QW-283 WELDS WITH BUTTERING

QW-283.1 Scope. This paragraph only applies when the essential variables for the buttering process are different than the essential variables for the process used for subsequent completion of the joint. Common examples are

(a) the buttered member is heat treated and the completed weld is not heat treated after welding

(b) the filler metal used for buttering has a different F-Number from that used for the subsequent completion of the weld

QW-283.2 Tests Required. The procedure shall be qualified by buttering the test coupon (including heat treating of the buttered member when this will be done in production welding) and then making the subsequent weld joining the members. The variables for the buttering and for the subsequent weld shall be in accordance with [QW-250](#), except that [QW-409.1](#) shall be an essential variable for the welding process(es) used to complete the weld when the minimum buttering thickness is less than $\frac{3}{16}$ in. (5 mm). Mechanical testing of the completed weldment shall be in accordance with [QW-202.2\(a\)](#).

If the buttering is done with filler metal of the same composition as the filler metal used to complete the weld, one weld test coupon may be used to qualify the dissimilar metal joint by welding the first member directly to the second member in accordance with Section IX.

QW-283.3 Buttering Thickness. The thickness of buttering which shall remain on the production buttered member after all machining and grinding is completed and before subsequent completion of the joint shall be required by the WPS. When this thickness is less than $\frac{3}{16}$ in. (5 mm), the thickness of buttering on the test coupon shall be measured before the buttered member is welded to the second member. This thickness shall become the minimum qualified thickness of buttering.

QW-283.4 Qualification Alternative. When an essential variable is changed in the portion of the weld to be made after buttering or when a different organization is performing the portion of the weld to be made after buttering, a new qualification shall be performed in accordance with one of the following methods:

(a) Qualify in accordance with [QW-283.2](#) and [QW-283.3](#). When the original qualification buttering thickness is less than $\frac{3}{16}$ in. (5 mm), the buttering thickness shall not be greater, nor the heat input higher than was used on the original qualification.

(b) When the original qualification buttering thickness is $\frac{3}{16}$ in. (5 mm) or greater, qualify the portion of the weld to be made after buttering using any P-Number material that nominally matches the chemical analysis of the buttering weld metal for the buttered base metal of the test coupon.

QW-284 RESISTANCE WELDING MACHINE QUALIFICATION

Each resistance welding machine shall be tested to determine its ability to make welds consistently and reproducibly. A machine shall be requalified whenever it is rebuilt, moved to a new location requiring a change in power supply, when the power supply is changed, or any other significant change is made to the equipment. Spot and projection welding machine qualification testing shall consist of making a set of 100 consecutive welds. Every fifth of these welds shall be subjected to mechanical shear tests. Five welds, which shall include one of the first five and one of the last five of the set shall be metallographically examined. Seam welding machine qualification testing shall be the same as procedure qualification testing required per [QW-286](#). Maintenance or adjustment of the welding machine shall not be permitted during welding of a set of test welds. Qualification testing on any P-No. 21 through P-No. 26 aluminum alloy shall qualify the machine for all materials. Qualification on P-No. 1 through P-No. 15F iron-base alloys and any P-No. 41 through P-No. 49 nickel-base alloys shall qualify the machine for all P-No. 1 through P-No. 15F and P-No. 41 through P-No. 49 metals. Qualification testing of the machine using base metals assigned to P-No. 51 through P-No. 53, P-No. 61, or P-No. 62 qualifies the welding machine to weld all base metals assigned to P-No. 51 through P-No. 53, P-No. 61, and P-No. 62. Testing and acceptance criteria shall be in accordance with [QW-196](#).

QW-285 RESISTANCE SPOT AND PROJECTION WELD PROCEDURE QUALIFICATION

Procedure qualification testing for spot or projection welds shall be done following a Welding Procedure Specification, and it shall consist of making a set of ten consecutive welds. Five of these welds shall be subjected to mechanical shear tests and five to metallographic examination. Examination, testing, and acceptance criteria shall be in accordance with [QW-196](#).

QW-286 RESISTANCE SEAM WELD PROCEDURE QUALIFICATION

QW-286.1 Test coupons described below shall consist of the same number of members, orientation, material grades/types, and thicknesses to be used in production welding.

QW-286.2 A test coupon as shown in [Figure QW-462.7.1](#) shall be prepared by drilling a hole in the center of one of the outer coupon members. In the case of a test coupon containing more than two members, a hole shall be drilled in each member except for one of the outer members. A pipe nipple shall be welded or brazed to the outer member at the hole. The test coupon shall then be welded around the edges, sealing the space between the members as shown in [Figure QW-462.7.1](#). The coupon

shall be pressurized hydrostatically until failure occurs. The procedure qualification is acceptable if failure occurs in the base metal.

QW-286.3 A test coupon at least 10 in. (250 mm) long shall be made per [Figure QW-462.7.2](#). This test coupon shall be cut transverse to the length of the weld into ten pieces, each approximately 1 in. (25 mm) long. Four transverse weld specimens and four longitudinal weld cross section specimens shall be cut and prepared as detailed in [Figure QW-462.7.2](#). The specimens shall be metallographically examined for compliance with the requirements of [QW-196](#).

QW-287 VARIATION OF SETTINGS FOR ELECTRIC RESISTANCE WELDING

Settings for preheating cycles, electrode pressure, welding current, welding time cycle, or postheating cycles may be varied by $\pm 5\%$ from the values recorded on the PQR, or by $\pm 10\%$ when only one of the above settings is changed.

QW-288 TUBE-TO-TUBESHEET QUALIFICATION ESSENTIAL VARIABLES

The following shall be considered essential variables for tube-to-tubesheet welding qualifications in accordance with [QW-193](#).

QW-288.1 All Processes.

- (a) A change in the welding process used.
- (b) A change in the weld joint configuration (beyond the manufacturing tolerance) such as the addition or deletion of preplaced filler metal, an increase in the depth of the groove, a decrease in the groove angle, or a change in the groove type.
- (c) For tubes of specified wall thickness of 0.100 in. (2.5 mm) or less, an increase or decrease of 10% of the specified wall thickness. For tubes of specified wall thickness greater than 0.100 in. (2.5 mm), only one qualification test is required.
- (d) For tubes of specified diameter of 2 in. (50 mm) or less and a specified wall thickness of 0.100 in. (2.5 mm) or less, a decrease greater than 10% of the specified tube diameter. For tubes of specified diameter greater than 2 in. (50 mm), the minimum diameter qualified is 2 in. (50 mm). For tubes of specified wall thickness greater than 0.100 in. (2.5 mm), diameter is not an essential variable.
- (e) A decrease of 10% or more in the specified width of the ligament between tube holes when the specified width of the ligament is less than the greater of $\frac{3}{8}$ in. (10 mm) or 3 times the specified tube wall thickness.
- (f) A change from multiple passes to a single pass or vice versa.
- (g) A change in the welding position of the tube-to-tubesheet joint from that qualified (see [QW-461.1](#)).
- (h) A change in the progression of a vertical position weld from that qualified.

(i) A change in the P-No. of the tube or tubesheet material (if the tubesheet material is part of the weld), a change in the P-No. or A-No. of the tubesheet cladding material (if the cladding material is part of the weld), or a change in a material not assigned a P-No. or A-No.

(j) If filler metal is added, a change in the A-No. of the weld deposit or a change in the nominal composition of the weld deposit if there is no A-No.

(k) A decrease of more than 100°F (55°C) in the pre-heat temperature or an increase of more than 100°F (55°C) in the interpass temperature from that qualified.

(l) The addition or deletion of PWHT.

(m) A change of more than 10% in the current level from that qualified.

(n) A change in the polarity or current type (AC or DC) from that qualified.

(o) A change between manual, semiautomatic, machine, or automatic methods of application.

(p) The addition of tube expansion prior to welding.

(q) A change in the method of cleaning prior to welding.

QW-288.2 Shielded Metal Arc Welding.

(a) An increase in the electrode diameter.

(b) A change in the F-No. of the electrode.

QW-288.3 Gas Tungsten Arc, Plasma Arc, and Gas Metal Arc Welding.

(a) A change in the size or shape of preplaced metal inserts.

(b) A change from one shielding gas to another shielding gas or to a mixture of shielding gases.

(c) When using a mixed shielding gas, a change of $\pm 25\%$ or 5 ft³/hr (2.5 L/min), whichever is the larger, in the rate of flow of the minor gas constituent.

(d) For GTAW or PAW, the addition or deletion of filler metal.

(e) For GTAW or PAW, a change in the nominal diameter of the filler metal or electrode.

(f) The elimination of an auxiliary gas shield system if used during qualification.

(g) A change in the F-No. of the electrode or filler metal.

QW-288.4 Explosion Welding.

(a) A 10% change in the specified tube wall thickness or diameter for all diameters and wall thicknesses.

(b) A change in the method of pressure application.

(c) A change in the type of explosive or a change in the energy content of $\pm 10\%$.

(d) A change of $\pm 10\%$ in the distance between the charge and the tubesheet face.

(e) A change of $\pm 10\%$ in the specified clearance between the tube and the tubesheet.

NOTE: [QW-288.1](#) (f), (h), (j), (k), (m), (n), and (o) do not apply for this process.

QW-290 TEMPER BEAD WELDING

When the applicable Code Section specifies the use of this paragraph for temper bead welding, [QW-290.1](#) through [QW-290.6](#) shall apply.

QW-290.1 Basic Qualification and Upgrading Existing WPSs. All WPSs for temper bead welding of groove and fillet weld shall be qualified for groove welding in accordance with the rules in [QW-202](#) for qualification by groove welding or the rules in [QW-283](#) for welds with buttering. WPSs for overlay shall be qualified in accordance with [QW-214](#) or [QW-216](#). Once these requirements and any additional qualification requirements of the applicable construction code have been satisfied, then it is necessary only to prepare an additional test coupon using the same procedure with the same essential and, if applicable, the supplementary essential variables with the coupon long enough to obtain the required temper bead test specimens. Qualification for groove welding, welding with buttering or cladding, and temper bead welding may also be done in a single test coupon.

When a procedure has been previously qualified to satisfy all requirements including temper bead welding, but one or more temper bead welding variables is changed, then it is necessary only to prepare an additional test coupon using the same procedure with the same essential and, if applicable, the supplementary essential variables and the new temper bead welding essential variable(s) with the coupon long enough to obtain the required test specimens.

QW-290.2 Welding Process Restrictions. Temper bead welding is limited to SMAW, GTAW, SAW, GMAW (including FCAW), and PAW. Manual and semiautomatic GTAW and PAW are prohibited, except for the root pass of groove welds made from one side and as described for making repairs to temper bead welds in [QW-290.6](#). The essential variables listed in [Table QW-290.4](#) apply in addition to the variables applicable for the process(es) qualified as given in [QW-250](#). When impact testing is the basis for acceptance, the supplementary essential variables of [QW-250](#) applicable to the process being qualified shall apply. When these variables conflict with or provide more stringent limitations than those of [QW-250](#), these variables shall govern.

QW-290.3 Variables for Temper Bead Welding Qualifications. [Table QW-290.4](#) lists the essential and nonessential variables that apply when temper bead qualification is required. The column "Hardness Test Essential Variables" shall apply, except that when the applicable Construction Code or Design Specification specifies acceptance based on impact testing, the column "Impact Test Essential Variables" shall apply. The column "Nonessential Variables" applies in all cases.

Table QW-290.4
Welding Variables for Temper Bead Procedure Qualification

Paragraph	Brief of Variables	Hardness Test Essential Variables	Impact Test Essential Variables	Nonessential Variables
QW-402	.23 + Fluid backing	X		
	.24 + Fluid backing		X	
QW-403	.25 ϕ P-No. or Gr. No.		X	
	.26 > Carbon equivalent	X		
	.27 > T	X		
QW-404	.51 Storage			X
	.52 Diffusible hydrogen			X
QW-406	.8 > Interpass temperature		X	
	.9 < Preheat temperature	X		
	.10 Preheat soak time			X
	.11 Postweld bakeout			X
QW-408	.24 Gas moisture			X
QW-409	.29 ϕ Heat input ratio	X	X	
QW-410	.10 ϕ Single to multiple electrode	X	X	
	.58 – Surface temper beads	X	X	
	.59 ϕ Type of welding	X	X	
	.60 + Thermal preparation	X	X	
	.61 Surface bead placement	X	X	
	.62 Surface bead removal method			X
	.63 Bead overlap	X	X	
	.65 \pm Grinding	X	X	

Legend:

+ Addition

> Increase/greater than

 ϕ Change

– Deletion

< Decrease/less than

(13) QW-290.5 Test Coupon Preparation and Testing.

(a) The test coupon may be any geometry that is suitable for removal of the required specimens. It shall consist of a groove weld, a cavity in a plate, overlay, or other suitable geometry. The distance from each edge of the weld preparation to the edge of the test coupon shall be at least 3 in. measured transverse to the direction of welding. The depth of preparation shall be such that at least two layers of weld metal are deposited, one of which may be the surface temper bead layer and deep enough to remove the required test specimens.

(b) The test coupon shall be bend-tested in accordance with [QW-451](#).

(c) When hardness testing is specified by a Construction Code or Design Specification or no specific testing is required, measurements shall be taken across the weld metal, heat-affected zone, and base metal using the Vickers method with a 10-kg load. Increments between measurements shall be as specified in ASTM E384. As an alternative to the Vickers method, Instrumented Indentation Testing in accordance with ASTM E2546 may be used with test forces in the macro range of 2.2 lbf to 265 lbf (1 kgf to 120 kgf) and increments between measurements as determined in accordance with ASTM E2546.

(1) Measurements shall be taken along a line at approximately mid-plane of the thickness of the test coupon weld metal. Along this line, there shall be

(-a) a minimum of two measurements in the weld metal fill layers.

(-b) at least one measurement on each: the weld beads against base metal, first-layer tempering beads, and the second-layer tempering beads.

(-c) a minimum of three measurements in the heat-affected zone. These measurements may be taken in a line approximately parallel to the HAZ when spacing between impressions does not allow for three measurements to be taken in a single line transverse to the HAZ.

(-d) a minimum of two measurements in the unaffected base metal.

(2) Additional measurements shall be taken along a line approximately 0.04 in. (1 mm) below the original base metal surface. Along this line, there shall be

(-a) a minimum of two measurements in the weld metal fill layers

(-b) at least one measurement on each: the weld beads against base metal, first-layer tempering beads, and the second-layer tempering beads

(-c) one measurement located immediately below the toe of the weld bead and at least one measurement on each side of that impression

(3) When the coupon is a full-penetration groove weld made from one side, additional measurements shall be taken along a line approximately 0.04 in. (1 mm) above the root side surface. Along this line, there shall be a minimum of two measurements in the weld metal, two in the heat-affected zone, and two in the unaffected base metal.

Full-penetration groove weld test coupons qualify full and partial penetration groove welds, fillet welds, and weld build-up. Partial penetration groove weld test coupons only qualify partial penetration groove welds, fillet welds, and build-up. Overlay test coupons only qualify overlay welds.

Hardness readings shall not exceed the hardness limits specified by the Construction Code or Design Specification. Where hardness is not specified, the data shall be reported.

(d) When specified by the applicable Construction Code or Design Specification, the test coupon shall be Charpy V-notch impact tested. The extent of testing (i.e., weld metal, HAZ, unaffected base metal), the testing temperature, and the acceptance criteria shall be as provided in the applicable Construction Code or Design Specification. Impact test specimens shall be removed from the coupon in the weld metal and HAZ as near as practical to a depth of one-half the thickness of the weld metal for each process. For HAZ specimens, the specimen shall be oriented so as to include as much of the HAZ as possible at the notch. The impact specimens and testing shall be in accordance with SA-370 using the largest size specimen that can be removed from the test coupon with the notch cut approximately normal to the test coupon surface. More than one set of impact test specimens shall be removed and tested when weld metal and heat-affected zone material from each process or set of variables cannot be included in a single set of test specimens.

QW-290.6 In-Process Repair Welding.

(a) In-process repairs to welds made using temper bead welding are permitted. In-process repairs are defined as repairs in which a flaw is mechanically removed and a repair weld is made before welding of a joint is presented for final visual inspection. Examples of such repairs are areas of removal of porosity, incomplete fusion, etc., where sufficient metal has been mechanically removed that localized addition of weld metal is necessary in order to make the surface geometry suitable for continuation of normal welding.

(b) Surfaces to be repaired shall be prepared by mechanical removal of flaws and preparation of the surface to a suitable geometry.

(c) For processes other than manual and semiautomatic GTAW and PAW, repairs shall be made using the parameters given in the WPS for production temper bead welding. The approximate location of beads to be deposited relative to the original base metal surface shall be identified, and the applicable parameters shall be used for the layers to be deposited as specified by the WPS.

(d) When it is necessary to make repairs using manual or semiautomatic GTAW or PAW, a WPS shall be prepared based on PQRs developed for temper bead welding using machine or automatic GTAW or PAW, respectively. This WPS shall describe the size of the beads to be deposited and the volts, amps, and travel speed to be used for the

beads against the base metal, for each temper bead layer and for the fill and surface temper bead layers corresponding to the locations where repair welding is to be done. These shall be within the equivalent power ratio for machine or automatic welding for the respective layers given in [QW-409.29](#).

(e) Welders who will use manual and semiautomatic GTAW or PAW shall be qualified to use these welding processes as required by [QW-300](#). In addition, each welder shall complete a proficiency demonstration. For this demonstration, each welder shall deposit two or more weld beads using WPS parameters for each deposit layer. The test coupon size shall be sufficiently large to make the required weld bead passes. The minimum pass length

shall be 4 in. (100 mm). The heat input used by the welder shall be measured for each pass, and the size of each weld bead shall be measured for each pass, and they shall be as required by the WPS. The following essential variables shall apply for this demonstration:

- (1) a change from one welding procedure to another
- (2) a change from manual to semiautomatic welding and vice versa
- (3) a change in position based on a groove weld in either plate or pipe as shown in [Table QW-461.9](#)
- (4) continuity of qualification in accordance with [QW-322](#) shall be based on following the WPS that was demonstrated in addition to using the process as required by [QW-322](#)

ARTICLE III

WELDING PERFORMANCE QUALIFICATIONS

(13) QW-300 GENERAL

QW-300.1 This Article lists the welding processes separately, with the essential variables that apply to welder and welding operator performance qualifications.

The welder qualification is limited by the essential variables given for each welding process. These variables are listed in [QW-350](#), and are defined in [Article IV](#) Welding Data. The welding operator qualification is limited by the essential variables given in [QW-360](#) for each type of weld.

A welder or welding operator may be qualified by volumetric NDE of a test coupon or their initial production welding within the limitations of [QW-304](#) and [QW-305](#) or by bend tests taken from a test coupon.

QW-301 TESTS

QW-301.1 Intent of Tests. The performance qualification tests are intended to determine the ability of welders and welding operators to make sound welds.

QW-301.2 Qualification Tests. Each organization shall qualify each welder or welding operator for each welding process to be used in production welding. The performance qualification test shall be welded in accordance with qualified Welding Procedure Specifications (WPS), or Standard Welding Procedure Specifications (SWPS) listed in [Mandatory Appendix E](#), except that when performance qualification is done in accordance with a WPS or SWPS that requires a preheat or postweld heat treatment, these may be omitted. Changes beyond which requalification is required are given in [QW-350](#) for welders and in [QW-360](#) for welding operators. Allowable visual, mechanical, and radiographic examination requirements are described in [QW-304](#) and [QW-305](#). Retests and renewal of qualification are given in [QW-320](#).

The welder or welding operator who prepares the WPS qualification test coupons meeting the requirements of [QW-200](#) is also qualified within the limits of the performance qualifications, listed in [QW-304](#) for welders and in [QW-305](#) for welding operators. He is qualified only within the limits for positions specified in [QW-303](#).

QW-301.3 Identification of Welders and Welding Operators. Each qualified welder and welding operator shall be assigned an identifying number, letter, or symbol by the organization, which shall be used to identify the work of that welder or welding operator.

QW-301.4 Record of Tests. The record of Welder/Welding Operator Performance Qualification (WPQ) tests shall include the essential variables ([QW-350](#) or [QW-360](#)), the type of test and test results, and the ranges qualified in accordance with [QW-452](#) for each welder and welding operator. Suggested forms for these records are given in [Forms QW-484A/QW-484B](#) (see [Nonmandatory Appendix B](#)).

QW-302 TYPE OF TEST REQUIRED

QW-302.1 Mechanical Tests. Except as may be specified for special processes ([QW-380](#)), the type and number of test specimens required for mechanical testing shall be in accordance with [QW-452](#). Groove weld test specimens shall be removed in a manner similar to that shown in [Figures QW-463.2\(a\) through QW-463.2\(g\)](#). Fillet weld test specimens shall be removed in a manner similar to that shown in [Figures QW-462.4\(a\) through QW-462.4\(d\)](#) and [Figure QW-463.2\(h\)](#).

All mechanical tests shall meet the requirements prescribed in [QW-160](#) or [QW-180](#), as applicable.

QW-302.2 Volumetric NDE. When the welder or welding operator is qualified by volumetric NDE, as permitted in [QW-304](#) for welders and [QW-305](#) for welding operators, the minimum length of coupon(s) to be examined shall be 6 in. (150 mm) and shall include the entire weld circumference for pipe(s), except that for small diameter pipe, multiple coupons of the same diameter pipe may be required, but the number need not exceed four consecutively made test coupons. The examination technique and acceptance criteria shall be in accordance with [QW-191](#).

QW-302.3 Test Coupons in Pipe. For test coupons made on pipe in position 1G or 2G of [Figure QW-461.4](#), two specimens shall be removed as shown for bend specimens in [Figure QW-463.2\(d\)](#) or [Figure QW-463.2\(e\)](#), omitting the specimens in the upper-right and lower-left quadrants, and replacing the root-bend specimen in the upper-left quadrant of [Figure QW-463.2\(d\)](#) with a face-bend specimen. For test coupons made on pipe in position 5G or 6G of [Figure QW-461.4](#), specimens shall be removed in accordance with [Figure QW-463.2\(d\)](#) or [Figure QW-463.2\(e\)](#) and all four specimens shall pass the test. For test coupons made in both positions 2G and 5G on a single pipe test coupon, specimens shall be removed in accordance with [Figure QW-463.2\(f\)](#) or [Figure QW-463.2\(g\)](#).

QW-302.4 Visual Examination. For plate coupons all surfaces (except areas designated “discard”) shall be examined visually per [QW-194](#) before cutting of bend specimens. Pipe coupons shall be visually examined per [QW-194](#) over the entire circumference, inside and outside.

QW-303 LIMITS OF QUALIFIED POSITIONS AND DIAMETERS (SEE [QW-461](#))

QW-303.1 Groove Welds — General. Welders and welding operators who pass the required tests for groove welds in the test positions of [Table QW-461.9](#) shall be qualified for the positions of groove welds and fillet welds shown in [Table QW-461.9](#). In addition, welders and welding operators who pass the required tests for groove welds shall also be qualified to make fillet welds in all thicknesses and pipe diameters of any size within the limits of the welding variables of [QW-350](#) or [QW-360](#), as applicable.

QW-303.2 Fillet Welds — General. Welders and welding operators who pass the required tests for fillet welds in the test positions of [Table QW-461.9](#) shall be qualified for the positions of fillet welds shown in [Table QW-461.9](#). Welders and welding operators who pass the tests for fillet welds shall be qualified to make fillet welds only in the thicknesses of material, sizes of fillet welds, and diameters of pipe and tube $2\frac{7}{8}$ in. (73 mm) O.D. and over, as shown in [Table QW-452.5](#), within the applicable essential variables. Welders and welding operators who make fillet welds on pipe or tube less than $2\frac{7}{8}$ in. (73 mm) O.D. must pass the pipe fillet weld test per [Table QW-452.4](#) or the required mechanical tests in [QW-304](#) and [QW-305](#) as applicable.

QW-303.3 Special Positions. An organization who does production welding in a special orientation may make the tests for performance qualification in this specific orientation. Such qualifications are valid only for the flat position and for the special positions actually tested, except that an angular deviation of ± 15 deg is permitted in the inclination of the weld axis and the rotation of the weld face, as defined in [Figures QW-461.1](#) and [QW-461.2](#).

QW-303.4 Stud-Weld Positions. Qualification in the 4S position also qualifies for the 1S position. Qualification in the 4S and 2S positions qualifies for all positions.

QW-303.5 Tube-to-Tubesheet Welder and Welding Operator Qualification. When the applicable Code Section requires the use of [QW-193](#) for tube-to-tubesheet demonstration mockup qualification tests, [QW-193.2](#) shall apply. If specific qualification test requirements are not specified by the applicable Code Section, welders and welding operators shall be qualified with one of the following methods:

- (a) groove welds per the requirements of [QW-303.1](#)
- (b) a demonstration mockup per the requirements of [QW-193.2](#)

QW-304 WELDERS

Except for the special requirements of [QW-380](#), each welder who welds under the rules of the Code shall have passed the mechanical and visual examinations prescribed in [QW-302.1](#) and [QW-302.4](#) respectively. Alternatively, welders may be qualified by volumetric NDE per [QW-191](#) When making a groove weld using SMAW, SAW, GTAW, PAW, and GMAW (except short-circuiting mode for radiographic examination) or a combination of these processes, except for P-No. 21 through P-No. 26, P-No. 51 through P-No. 53, and P-No. 61 through P-No. 62 metals. Welders making groove welds in P-No. 21 through P-No. 26 and P-No. 51 through P-No. 53 metals with the GTAW process may also be qualified by volumetric NDE per [QW-191](#). The Volumetric NDE shall be in accordance with [QW-302.2](#).

A welder qualified to weld in accordance with one qualified WPS is also qualified to weld in accordance with other qualified WPSs, using the same welding process, within the limits of the essential variables of [QW-350](#).

QW-304.1 Examination. Welds made in test coupons for performance qualification may be examined by visual and mechanical examinations ([QW-302.1](#), [QW-302.4](#)) or by volumetric NDE ([QW-302.2](#)) for the process(es) and mode of arc transfer specified in [QW-304](#). Alternatively, a minimum 6 in. (150 mm) length of the first production weld(s) made by a welder using the process(es) and/or mode of arc transfer specified in [QW-304](#) may be examined by volumetric NDE.

(a) For pipe(s) welded in the 5G, 6G, or special positions, the entire production weld circumference made by the welder shall be examined.

(b) For small diameter pipe where the required minimum length of weld cannot be obtained from a single production pipe circumference, additional consecutive circumferences of the same pipe diameter made by the welder shall be examined, except that the total number of circumferences need not exceed four.

(c) The examination technique and acceptance criteria for production welds shall be in accordance with [QW-191](#).

QW-304.2 Failure to Meet Examination Standards. If a production weld is selected for welder performance qualification and it does not meet the examination standards, the welder has failed the test. In this event, the entire production weld made by this welder shall be examined and repaired by a qualified welder or welding operator. Alternatively, retests may be made as permitted in [QW-320](#).

QW-305 WELDING OPERATORS

Except for the special requirements of [QW-380](#), each welding operator who welds under the rules of this Code shall have passed the mechanical and visual examinations prescribed in [QW-302.1](#) and [QW-302.4](#), respectively. Alternatively, welding operators may be qualified by volumetric NDE per [QW-191](#) when making a groove weld

using SMAW, SAW, GTAW, PAW, EGW, and GMAW (except short-circuiting mode for radiographic examination) or a combination of these processes, except for P-No. 21 through P-No. 26, P-No. 51 through P-No. 53, and P-No. 61 through P-No. 62 metals. Welding operators making groove welds in P-No. 21 through P-No. 26 and P-No. 51 through P-No. 53 metals with the GTAW process may also be qualified by volumetric NDE. The volumetric NDE shall be in accordance with [QW-302.2](#).

A welding operator qualified to weld in accordance with one qualified WPS is also qualified to weld in accordance with other qualified WPSs within the limits of the essential variables of [QW-360](#).

QW-305.1 Examination. Welds made in test coupons may be examined by volumetric NDE ([QW-302.2](#)) or by visual and mechanical examinations ([QW-302.1](#), [QW-302.4](#)). Alternatively, a minimum 3 ft (1 m) length of the first production weld(s) made entirely by the welding operator in accordance with a qualified WPS may be examined by volumetric NDE.

(a) For pipe(s) welded in the 5G, 6G, or special positions, the entire production weld circumference made by the welding operator shall be examined.

(b) For small diameter pipe where the required minimum length of weld cannot be obtained from a single production pipe circumference, additional consecutive circumferences of the same pipe diameter made by the welding operator shall be examined except that the total number of circumferences need not exceed four.

(c) The examination technique and acceptance criteria for production welds shall be in accordance with [QW-191](#).

QW-305.2 Failure to Meet Examination Standards. If a portion of a production weld is selected for welding operator performance qualification, and it does not meet the examination standards, the welding operator has failed the test. In this event, the entire production weld made by this welding operator shall be examined completely and repaired by a qualified welder or welding operator. Alternatively, retests may be made as permitted in [QW-320](#).

QW-306 COMBINATION OF WELDING PROCESSES

Each welder or welding operator shall be qualified within the limits given in [QW-301](#) for the specific welding process(es) he will be required to use in production welding. A welder or welding operator may be qualified by making tests with each individual welding process in separate test coupons, or with a combination of welding processes in a single test coupon. Two or more welders or welding operators, each using the same or a different welding process, may be qualified in combination in a single test coupon. For combination qualifications in a single test coupon, the limits for thicknesses of deposited weld metal, and bend and fillet testing are given in [QW-452](#) and shall be considered individually for each welder or welding

operator for each welding process or whenever there is a change in an essential variable. A welder or welding operator qualified in combination on a single test coupon is qualified to weld in production using any of his processes individually or in different combinations, provided he welds within his limits of qualification with each specific process.

Failure of any portion of a combination test in a single test coupon constitutes failure of the entire combination.

QW-310 QUALIFICATION TEST COUPONS

(13)

QW-310.1 Test Coupons. The test coupons may be plate, pipe, or other product forms. When all position qualifications for pipe are accomplished by welding one pipe assembly in both the 2G and 5G positions ([Figure QW-461.4](#)), NPS 6 (DN 150), NPS 8 (DN 200), NPS 10 (DN 250), or larger diameter pipe shall be employed to make up the test coupon as shown in [Figure QW-463.2\(f\)](#) for NPS 10 (DN 250) or larger pipe and in [Figure QW-463.2\(g\)](#) for NPS 6 (DN 150) or NPS 8 (DN 200) diameter pipe.

QW-310.2 Welding Groove With Backing. The dimensions of the welding groove on the test coupon used in making qualification tests for double-welded groove welds or single-welded groove welds with backing shall be the same as those for any Welding Procedure Specification (WPS) qualified by the organization, or shall be as shown in [Figure QW-469.1](#).

A single-welded groove-weld test coupon with backing or a double-welded groove-weld test coupon shall be considered welding with backing. Partial penetration groove welds and fillet welds are considered welding with backing.

QW-310.3 Welding Groove Without Backing. The dimensions of the welding groove of the test coupon used in making qualification tests for single-welded groove welds without backing shall be the same as those for any WPS qualified by the organization, or as shown in [Figure QW-469.2](#).

QW-320 RETESTS AND RENEWAL OF QUALIFICATION

QW-321 RETESTS

A welder or welding operator who fails one or more of the tests prescribed in [QW-304](#) or [QW-305](#), as applicable, may be retested under the following provisions.

QW-321.1 Immediate Retest Using Visual Examination. When the qualification coupon has failed the visual examination of [QW-302.4](#), retesting shall be by visual examination before conducting the mechanical testing.

When an immediate retest is made, the welder or welding operator shall make two consecutive test coupons for each position which he has failed, all of which shall pass the visual examination requirements.

The examiner may select one of the successful test coupons from each set of retest coupons which pass the visual examination for conducting the mechanical testing.

QW-321.2 Immediate Retest Using Mechanical Testing. When the qualification coupon has failed the mechanical testing of [QW-302.1](#), retesting shall be by mechanical testing.

When an immediate retest is made, the welder or welding operator shall make two consecutive test coupons for each position which he has failed, all of which shall pass the test requirements.

(13) **QW-321.3 Immediate Retest Using Volumetric NDE.**

When the qualification coupon has failed the volumetric NDE of [QW-302.2](#), the immediate retest shall be by the same examination method.

(a) For welders and welding operators the retest shall be to examine two 6 in. (150 mm) plate coupons; for pipe, to examine two or more pipe coupons of the same diameter for a total of 12 in. (300 mm) of weld, which shall include the entire weld circumference for pipe or pipes (for small diameter pipe the total number of consecutively made test coupons need not exceed eight).

(b) At the option of the organization, the welder who has failed the production weld alternative test may be retested by examining additional weld areas equal to twice the required length or number of pipe circumferences of the same or consecutively made production weld(s) specified in [QW-304.1](#). If this length of weld passes the test, the welder is qualified and the area of weld on which he had previously failed the test shall be repaired by him or another qualified welder. If this length does not meet the examination standards, the welder has failed the retest and all of the production welds made by this welder shall be examined completely and repaired by a qualified welder or welding operator.

(c) At the option of the organization, the welding operator who has failed the production weld alternative test may be retested by examining additional weld areas equal to twice the required length or number of pipe circumferences of the same or consecutively made production weld(s) specified in [QW-305.1](#). If this length of weld passes the test, the welding operator is qualified and the area of weld on which he had previously failed the test shall be repaired by him or another qualified welder or welding operator. If this length does not meet the examination standards, the welding operator has failed the retest and all of the production welds made by this welding operator shall be examined completely and repaired by a qualified welder or welding operator.

QW-321.4 Further Training. When the welder or the welding operator has had further training or practice, a new test shall be made for each position on which he failed to meet the requirements.

QW-322 EXPIRATION AND RENEWAL OF QUALIFICATION

QW-322.1 Expiration of Qualification. The performance qualification of a welder or welding operator shall be affected when one of the following occurs: (13)

(a) When he has not welded with a process during a period of 6 months or more, his qualifications for that process shall expire; unless, within the 6 month period, prior to his expiration of qualification

(1) the welder has welded with that process using manual or semiautomatic welding, under the supervision and control of the qualifying organization(s) that will extend his qualification for an additional 6 months

(2) the welding operator has welded with that process using machine or automatic welding, under the supervision and control of the qualifying organization(s) that will extend his qualification for an additional 6 months

(b) When there is a specific reason to question his ability to make welds that meet the specification, the qualifications that support the welding he is doing shall be revoked. All other qualifications not questioned remain in effect.

QW-322.2 Renewal of Qualification.

(a) Renewal of qualification expired under [QW-322.1\(a\)](#) may be made for any process by welding a single test coupon of either plate or pipe, of any material, thickness or diameter, in any position, and by testing of that coupon as required by [QW-301](#) and [QW-302](#). A successful test renews the welder or welding operator's previous qualifications for that process for those materials, thicknesses, diameters, positions, and other variables for which he was previously qualified.

Providing the requirements of [QW-304](#) and [QW-305](#) are satisfied, renewal of qualification under [QW-322.1\(a\)](#) may be done on production work.

(b) Welders and welding operators whose qualifications have been revoked under [QW-322.1\(b\)](#) above shall requalify. Qualification shall utilize a test coupon appropriate to the planned production work. The coupon shall be welded and tested as required by [QW-301](#) and [QW-302](#). Successful test restores the qualification.

QW-350 WELDING VARIABLES FOR WELDERS

QW-351 GENERAL

A welder shall be requalified whenever a change is made in one or more of the essential variables listed for each welding process.

Where a combination of welding processes is required to make a weldment, each welder shall be qualified for the particular welding process or processes he will be required to use in production welding. A welder may be qualified by making tests with each individual welding process, or with a combination of welding processes in a single test coupon.

The limits of weld metal thickness for which he will be qualified are dependent upon the approximate thickness of the weld metal he deposits with each welding process, exclusive of any weld reinforcement, this thickness shall be considered the test coupon thickness as given in QW-452.

In any given production weldment, welders may not deposit a thickness greater than that permitted by QW-452 for each welding process in which they are qualified.

Table QW-352
Oxyfuel Gas Welding (OFW)

Essential Variables

Paragraph		Brief of Variables
QW-402 Joints	.7	+ Backing
QW-403 Base Metals	.2	Maximum qualified
	.18	ϕ P-Number
QW-404 Filler Metals	.14	\pm Filler
	.15	ϕ F-Number
	.31	ϕ t Weld deposit
QW-405 Positions	.1	+ Position
QW-408 Gas	.7	ϕ Type fuel gas

Table QW-353
Shielded Metal-Arc Welding (SMAW)

Essential Variables

Paragraph		Brief of Variables
QW-402 Joints	.4	- Backing
QW-403 Base Metals	.16	ϕ Pipe diameter
	.18	ϕ P-Number
QW-404 Filler Metals	.15	ϕ F-Number
	.30	ϕ t Weld deposit
QW-405 Positions	.1	+ Position
	.3	ϕ \updownarrow Vertical welding

Table QW-354
Semiautomatic Submerged-Arc Welding (SAW)

Essential Variables

Paragraph		Brief of Variables
QW-403 Base Metals	.16	ϕ Pipe diameter
	.18	ϕ P-Number
QW-404 Filler Metals	.15	ϕ F-Number
	.30	t Weld deposit
QW-405 Positions	.1	+ Position

Table QW-355
Semiautomatic Gas Metal-Arc Welding (GMAW)

[This Includes Flux-Cored Arc Welding (FCAW)] Essential Variables

Paragraph		Brief of Variables
QW-402 Joints	.4	- Backing
QW-403 Base Metals	.16	ϕ Pipe diameter
	.18	ϕ P-Number
QW-404 Filler Metals	.15	ϕ F-Number
	.30	ϕ t Weld deposit
	.32	t Limit (S. Cir. Arc.)
QW-405 Positions	.1	+ Position
	.3	ϕ \updownarrow Vertical welding
QW-408 Gas	.8	- Inert backing
QW-409 Electrical	.2	ϕ Transfer mode

Table QW-356
Manual and Semiautomatic Gas Tungsten-Arc Welding (GTAW)

Essential Variables

Paragraph		Brief of Variables
QW-402 Joints	.4	- Backing
QW-403 Base Metals	.16	ϕ Pipe diameter
	.18	ϕ P-Number
QW-404 Filler Metals	.14	\pm Filler
	.15	ϕ F-Number
	.22	\pm Inserts
	.23	ϕ Filler metal product form
	.30	ϕ t Weld deposit

(13)

Table QW-356
Manual and Semiautomatic Gas
Tungsten-Arc Welding (GTAW)
Essential Variables (Cont'd)

Paragraph		Brief of Variables
QW-405 Positions	.1	+ Position
	.3	ϕ \updownarrow Vertical welding
QW-408 Gas	.8	- Inert backing
QW-409 Electrical	.4	ϕ Current or polarity

Legend:

ϕ Change	\uparrow Uphill
+ Addition	\downarrow Downhill
- Deletion	

Table QW-357
Manual and Semiautomatic Plasma-Arc
Welding (PAW)
Essential Variables

Paragraph		Brief of Variables
QW-402 Joints	.4	- Backing
QW-403 Base Metals	.16	ϕ Pipe diameter
	.18	ϕ P-Number
QW-404 Filler Metals	.14	\pm Filler
	.15	ϕ F-Number
	.22	\pm Inserts
	.23	ϕ Filler metal product form
	.30	ϕ t Weld deposit
QW-405 Positions	.1	+ Position
	.3	ϕ $\uparrow\downarrow$ Vertical welding
QW-408 Gas	.8	- Inert backing

Legend:

ϕ Change	\uparrow Uphill
+ Addition	\downarrow Downhill
- Deletion	

QW-360 WELDING VARIABLES FOR WELDING OPERATORS

(13) QW-361 GENERAL

A welding operator shall be requalfied whenever a change is made in one of the following essential variables (QW-361.1 and QW-361.2). There may be exceptions or additional requirements for the processes of QW-362, QW-363, and the special processes of QW-380.

QW-361.1 Essential Variables — Automatic Welding.

- (a) A change from automatic to machine welding.
- (b) A change in the welding process.
- (c) For electron beam and laser welding, the addition or deletion of filler metal.
- (d) For laser welding and hybrid laser-GMAW, a change in laser type (e.g., a change from CO₂ to YAG).
- (e) For friction welding, a change from continuous drive to inertia welding or vice versa.
- (f) For electron beam welding, a change from vacuum to out-of-vacuum equipment, and vice versa.

QW-361.2 Essential Variables — Machine Welding.

- (a) A change in the welding process.
- (b) A change from direct visual control to remote visual control and vice-versa.
- (c) The deletion of an automatic arc voltage control system for GTAW.
- (d) The deletion of automatic joint tracking.
- (e) The addition of welding positions other than those already qualified (see [QW-120](#), [QW-130](#), and [QW-303](#)).
- (f) The deletion of consumable inserts, except that qualification with consumable inserts shall also qualify for fillet welds and welds with backing.
- (g) The deletion of backing. Double-welded groove welds are considered welding with backing.
- (h) A change from single pass per side to multiple passes per side but not the reverse.
- (i) For hybrid plasma-GMAW welding, the essential variable for welding operator qualification shall be in accordance with [Table QW-357](#).

QW-362 ELECTRON BEAM WELDING (EBW), LASER BEAM WELDING (LBW), HYBRID WELDING, AND FRICTION WELDING (FRW)

The performance qualification test coupon shall be production parts or test coupons that have joint designs permitted by any qualified WPS. The coupon shall be mechanically tested in accordance with [QW-452](#). Alternatively, when the part or coupon does not readily lend itself to the preparation of bend test specimens, the part may be cut so that at least two full-thickness weld cross sections are exposed. Those cross sections shall be smoothed and etched with a suitable etchant (see [QW-470](#)) to give a clear definition of the weld metal and heat affected zone. The weld metal and heat affected zone shall exhibit complete fusion and freedom from cracks. The essential variables for welding operator qualification shall be in accordance with [QW-361](#).

QW-363 STUD WELDING

Stud welding operators shall be performance qualified in accordance with the test requirements of [QW-192.2](#) and the position requirements of [QW-303.4](#).

QW-380 SPECIAL PROCESSES**QW-381 CORROSION-RESISTANT WELD METAL OVERLAY****QW-381.1 Qualification Test.**

(a) The size of test coupons, limits of base metal thickness qualification, required examinations and tests, and test specimens shall be as specified in [Table QW-453](#).

(b) Welders or welding operators who pass the tests for corrosion-resistant weld metal overlay cladding shall only be qualified to apply corrosion-resistant weld metal overlay portion of a groove weld joining composite clad or lined materials.

(c) The essential variables of [QW-350](#) and [QW-360](#) shall apply for welders and welding operators, respectively, except there is no limit on the maximum thickness of corrosion-resistant overlay that may be applied in production. When specified as essential variables, the limitations of position and diameter qualified for groove welds shall apply to overlay welds, except the limitations on diameter qualified shall apply only to welds deposited in the circumferential direction.

QW-381.2 Qualification on Composite Welds. A welder or welding operator who has qualified on composite welds in clad or lined material, as provided in [QW-383.1\(b\)](#) is also qualified to deposit corrosion-resistant weld metal overlay.

QW-381.3 Alternative Qualification With Groove Weld Tests. When a chemical composition is not specified in the WPS, welders or welding operators who successfully complete a groove weld performance qualification test meeting the corrosion-resistant overlay bend test requirements of [QW-163](#) may be considered qualified for corrosion-resistant overlay welding within the ranges defined in [QW-350](#) or [QW-360](#).

QW-382 HARD-FACING WELD METAL OVERLAY (WEAR RESISTANT)

(a) The size of the test coupons, limits of base metal thickness qualification, required examinations and tests, and test specimens shall be as specified in [Table QW-453](#). Base material test coupons may be as permitted in [QW-423](#).

(b) Welders and welding operators who pass the tests for hard-facing weld metal overlay are qualified for hard-facing overlay only.

(c) The essential variable, of [QW-350](#) and [QW-360](#), shall apply for welders and welding operators, respectively, except there is no limit on the maximum thickness of hard-facing overlay that may be applied in production. When specified as essential variables, the limitations of position and diameter qualified for groove welds shall apply to overlay welds except the limitations on diameter qualified shall apply only to welds deposited in the circumferential direction.

(d) Qualification with one AWS classification within an SFA specification qualifies for all other AWS classifications in that SFA specification.

(e) A change in welding process shall require welder and welding operator requalification.

QW-383 JOINING OF CLAD MATERIALS AND APPLIED LININGS**QW-383.1 Clad Materials.**

(a) Welders and welding operators who will join the base material portion of clad materials shall be qualified for groove welding in accordance with [QW-301](#). Welders and welding operators who will apply the cladding portion of a weld between clad materials shall be qualified in accordance with [QW-381](#). Welders and welding operators need only be qualified for the portions of composite welds that they will make in production.

(b) As an alternative to (a), welders and welding operators may be qualified using composite test coupons. The test coupon shall be at least $\frac{3}{8}$ in. (10 mm) thick and of dimensions such that a groove weld can be made to join the base materials and the corrosion-resistant weld metal overlay can be applied to the completed groove weld. Four side bend test specimens shall be removed from the completed test coupon and tested. The groove weld portion and the corrosion-resistant weld metal overlay portion of the test coupon shall be evaluated using the respective criteria in [QW-163](#). Welders and welding operators qualified using composite test coupons are qualified to join base materials as provided by [QW-301](#), and they are qualified to apply corrosion-resistant weld metal overlay as provided by [QW-381](#).

QW-383.2 Applied Linings.

(a) Welders and welding operators shall be qualified following the rules for making groove or fillet welds in accordance with [QW-301](#). Plug welds for attaching applied linings shall be considered equivalent to fillet welds for the purpose of performance qualification.

(b) An alternate test coupon shall consist of the geometry to be welded, except the base material need not exceed 1 in. (25 mm) in thickness. The welded test coupon shall be sectioned and etched to reveal the weld and heat-affected zone. The weld shall show penetration into the base metal.

QW-384 RESISTANCE WELDING OPERATOR QUALIFICATION

Each welding operator shall be tested on each machine type which he will use. Qualification testing on any P-No. 21 through P-No. 26 metal shall qualify the operator for all metals. Qualification on any P-No. 1 through P-No. 15F or any P-No. 41 through P-No. 49 metals shall qualify the operator for all P-No. 1 through P-No. 15F and P-No. 41 through P-No. 49 metals. Qualification testing on any

P-No. 51 through P-No. 53, P-No. 61, or P-No. 62 metal shall qualify the operator for all P-No. 51 through P-No. 53, P-No. 61, and P-No. 62 metals.

(a) Qualification for spot and projection welding shall consist of making a set of ten consecutive welds, five of which shall be subjected to mechanical shear tests or peel tests, and five to macro-examination. Examination, testing, and acceptance criteria shall be in accordance with [QW-196](#).

(b) Qualification for seam welding shall consist of that testing specified in [QW-286.3](#), except that only one transverse cross section and one longitudinal cross section are required.

QW-385 FLASH WELDING OPERATOR QUALIFICATION

Each welding operator shall be tested by welding a test coupon following any WPS. The test coupon shall be welded and tested in accordance with [QW-199](#). Qualification following any flash welding WPS qualifies the operator to follow all flash welding WPSs.

Production weld sampling tests required by other Sections may be used to qualify welding operators. The test method, extent of tests, and acceptance criteria of the other Sections and [QW-199.2](#) shall be met when this is done.

QW-386 DIFFUSION WELDING OPERATOR QUALIFICATION

Each welding operator shall be tested by welding a procedure qualification test coupon in accordance with [QW-185.1](#). The coupon shall be metallographically examined in accordance with [QW-185.3](#).

ARTICLE IV WELDING DATA

QW-400 VARIABLES

QW-401 GENERAL

Each welding variable described in this Article is applicable as an essential, supplementary essential, or nonessential variable for procedure qualification when referenced in [QW-250](#) for each specific welding process. Essential variables for performance qualification are referenced in [QW-350](#) for each specific welding process. A change from one welding process to another welding process is an essential variable and requires requalification.

QW-401.1 Essential Variable (Procedure). A change in a welding condition which will affect the mechanical properties (other than notch toughness) of the weldment (e.g., change in P-Number, welding process, filler metal, electrode, preheat or postweld heat treatment).

QW-401.2 Essential Variable (Performance). A change in a welding condition which will affect the ability of a welder to deposit sound weld metal (such as a change in welding process, deletion of backing, electrode, F-Number, technique, etc.).

QW-401.3 Supplementary Essential Variable (Procedure). A change in a welding condition which will affect the notch-toughness properties of a weldment (for example, change in welding process, uphill or down vertical welding, heat input, preheat or PWHT, etc.). Supplementary essential variables are in addition to the essential variables for each welding process.

When a procedure has been previously qualified to satisfy all requirements other than notch toughness, it is then necessary only to prepare an additional test coupon using the same procedure with the same essential variables, but additionally with all of the required supplementary essential variables, with the coupon long enough to provide the necessary notch-toughness specimens.

When a procedure has been previously qualified to satisfy all requirements including notch toughness, but one or more supplementary essential variable is changed, then it is only necessary to prepare an additional test coupon using the same welding procedure and the new supplementary essential variable(s), with the coupon long enough to provide the necessary notch-toughness specimens. If a previously qualified weld procedure has satisfactory notch-toughness values in the weld metal, then it is necessary only to test notch-toughness specimens from the heat affected zone when such are required.

When essential variables are qualified by one or more PQRs and supplementary essential variables are qualified by other PQRs, the ranges of essential variables established by the former PQRs are only affected by the latter to the extent specified in the applicable supplementary essential variable (e.g., essential variable [QW-403.8](#) governs the minimum and maximum thickness of base metal qualified. When supplementary essential variable [QW-403.6](#) applies, it modifies only the minimum thickness qualified, not the maximum).

QW-401.4 Nonessential Variable (Procedure). A change in a welding condition which will *not* affect the mechanical properties of a weldment (such as joint design, method of back gouging or cleaning, etc.).

QW-401.5 The welding data includes the welding variables grouped as joints, base metals, filler metals, position, preheat, postweld heat treatment, gas, electrical characteristics, and technique. For convenience, variables for each welding process are summarized in [Table QW-416](#) for performance qualification.

QW-402 JOINTS

(13)

QW-402.1 A change in the type of groove (Vee-groove, U-groove, single-bevel, double-bevel, etc.).

QW-402.2 The addition or deletion of a backing.

QW-402.3 A change in the nominal composition of the backing.

QW-402.4 The deletion of the backing in single-welded groove welds. Double-welded groove welds are considered welding with backing.

QW-402.5 The addition of a backing or a change in its nominal composition.

QW-402.6 An increase in the fit-up gap, beyond that initially qualified.

QW-402.7 The addition of backing.

QW-402.8 A change in nominal size or shape of the stud at the section to be welded.

QW-402.9 In stud welding, a change in shielding as a result of ferrule or flux type.

QW-402.10 A change in the specified root spacing.

QW-402.11 The addition or deletion of nonmetallic retainers or nonfusing metal retainers.

QW-402.12 The welding procedure qualification test shall duplicate the joint configuration to be used in production within the limits listed, except that pipe or tube to pipe or tube may be used for qualification of a pipe or tube to other shapes, and solid round to solid round may be used for qualification of a solid round to other shapes

(a) any change exceeding ± 10 deg in the angle measured for the plane of either face to be joined, to the axis of rotation

(b) a change in cross-sectional area of the weld joint greater than 10%

(c) a change in the outside diameter of the cylindrical weld interface of the assembly greater than $\pm 10\%$

(d) a change from solid to tubular cross section at the joint or vice versa regardless of (b)

QW-402.13 A change in the method of joining from spot to projection to seam or vice versa.

QW-402.14 An increase or decrease of more than 10% in the spacing of the welds when they are within two diameters of each other.

QW-402.15 A change in the size or shape of the projection in projection welding.

QW-402.16 A decrease in the distance between the approximate weld interface and the final surface of the production corrosion-resistant or hard-facing weld metal overlay below the minimum thickness qualified as shown in [Figures QW-462.5\(a\) through QW-462.5\(e\)](#). There is no limit on the maximum thickness for corrosion-resistant or hard-facing weld metal overlay that may be used in production.

QW-402.17 An increase in the thickness of the production spray fuse hard-facing deposit above the thickness deposited on the procedure qualification test coupon.

QW-402.18 For lap joints,

(a) a decrease of more than 10% in the distance to the edge of the material

(b) an increase in the number of layers of material

(c) a change in surface preparation or finish from that qualified

QW-402.19 A change in the nominal diameter or nominal thickness for tubular cross sections, or an increase in the total cross section area beyond that qualified for all nontubular cross sections.

QW-402.20 A change in the joint configuration.

QW-402.21 A change in the method or equipment used to minimize internal flash.

QW-402.22 A change in the end preparation method.

QW-402.23 For test coupons less than $1\frac{1}{2}$ in. (38 mm) thick, the addition of a cooling medium (water, flowing gas, etc.) to the back side of the weld. Qualification on test coupons less than $1\frac{1}{2}$ in. (38 mm) thick with a

cooling medium on the back side of the weld qualifies base metal thickness equal to or greater than the test coupon thickness with and without coolant.

QW-402.24 Qualification with a cooling medium (water, flowing gas, etc.) on the root side of a test coupon weld that is welded from one side qualifies all thicknesses of base metal with cooling medium down to the thickness of the test coupon at the root or $\frac{1}{2}$ in. (13 mm), whichever is less.

QW-402.25 A change from lap joint to groove welding, and vice versa.

QW-402.26 A reduction of more than 5 deg in the edge preparation bevel angle for groove welds.

QW-402.27 A change in material of fixed backing anvils (when used). A change in backing anvil design that affects the weld cooling rate (e.g., a change from air-cooled to water-cooled, and vice versa). This variable is not applicable to tube-to-tubesheet or double-sided welds with overlapping fusion zones, or welds completed using self-reacting pins.

QW-402.28 A change in joint design from that qualified, including edge preparation geometry (e.g., a change from square butt edge to beveled edge), reductions in the smallest joint path radius to less than the shoulder radius, or joint paths crossing themselves or another HAZ.

QW-402.29 A change in joint spacing greater than $\pm 10\%$ of the qualification test coupon thickness. For WPSs qualified using intimate edge contact, the maximum allowable joint spacing is $\frac{1}{16}$ in. (1.5 mm).

QW-402.30 A change from a groove weld to a fillet weld, or vice versa, from that qualified. For groove welds, a change in any of the following variables:

(a) backing to no backing, or vice versa

(b) a change of $\pm 10\%$ in the root face thickness

(c) a change of $\pm 10\%$ in the root gap

(d) a change in bevel angle $> 5^\circ$

QW-403 BASE METALS

QW-403.1 A change from a base metal listed under one P-Number in [Table QW/QB-422](#) to a metal listed under another P-Number or to any other base metal. When joints are made between two base metals that have different P-Numbers, a procedure qualification shall be made for the applicable combination of P-Numbers, even though qualification tests have been made for each of the two base metals welded to itself.

QW-403.2 The maximum thickness qualified is the thickness of the test coupon.

QW-403.3 For full penetration single-sided welds without backing, where the measurement of penetration can be made by visual or mechanical means, requalification is required when the base metal thickness is more than 20% thicker than that qualified when the test coupon thickness is 1 in. (25 mm) and under, and more than 10%

thicker when the test coupon thickness is over 1 in. (25 mm). Where the measurement of penetration cannot be made, requalification is required when the base metal thickness is more than 10% thicker than that qualified when the test coupon thickness is 1 in. (25 mm) and under, and more than 5% thicker when the test coupon thickness is over 1 in. (25 mm).

QW-403.4 Welding procedure qualifications shall be made using a base metal of the same type or grade or another base metal listed in the same group (see [Table QW/QB-422](#)) as the base metal to be used in production welding. When joints are to be made between base metals from two different groups, a procedure qualification must be made for the applicable combination of base metals, even though procedure qualification tests have been made for each of the two base metals welded to itself.

QW-403.5 Welding procedure specifications shall be qualified using one of the following:

(a) the same base metal (including type or grade) to be used in production welding

(b) for ferrous materials, a base metal listed in the same P-Number Group Number in [Table QW/QB-422](#) as the base metal to be used in production welding

(c) for nonferrous materials, a base metal listed with the same P-Number UNS Number in [Table QW/QB-422](#) as the base metal to be used in production welding

For ferrous materials in [Table QW/QB-422](#), a procedure qualification shall be made for each P-Number Group Number combination of base metals, even though procedure qualification tests have been made for each of the two base metals welded to itself. If, however, two or more qualification records have the same essential and supplementary essential variables, except that the base metals are assigned to different Group Numbers within the same P-Number, then the combination of base metals is also qualified. In addition, when base metals of two different P-Number Group Number combinations are qualified using a single test coupon, that coupon qualifies the welding of those two P-Number Group Numbers to themselves as well as to each other using the variables qualified.

This variable does not apply when impact testing of the heat-affected zone is not required by other Sections.

QW-403.6 The minimum base metal thickness qualified is the thickness of the test coupon T or $\frac{5}{8}$ in. (16 mm), whichever is less. However, where T is less than $\frac{1}{4}$ in. (6 mm), the minimum thickness qualified is $\frac{1}{2}T$. This variable does not apply when a WPS is qualified with a PWHT above the upper transformation temperature or when an austenitic or P-No. 10H material is solution annealed after welding.

QW-403.8 A change in base metal thickness beyond the range qualified in [QW-451](#), except as otherwise permitted by [QW-202.4\(b\)](#).

QW-403.9 For single-pass or multipass welding in which any pass is greater than $\frac{1}{2}$ in. (13 mm) thick, an increase in base metal thickness beyond 1.1 times that of the qualification test coupon.

QW-403.10 For the short-circuiting transfer mode of the gas metal-arc process, when the qualification test coupon thickness is less than $\frac{1}{2}$ in. (13 mm), an increase in thickness beyond 1.1 times that of the qualification test coupon. For thicknesses of $\frac{1}{2}$ in. (13 mm) and greater, use [Table QW-451.1](#) or [Table QW-451.2](#), as applicable.

QW-403.11 Base metals specified in the WPS shall be qualified by a procedure qualification test that was made using base metals in accordance with [QW-424](#).

QW-403.12 A change from a base metal listed under one P-Number of [Table QW/QB-422](#) to a base metal listed under another P-Number. When joints are made between two base metals that have different P-Numbers, requalification is required even though the two base metals have been independently qualified using the same procedure. When the melt-in technique is used for joining P-No. 1, P-No. 3, P-No. 4, and P-No. 5A, a procedure qualification test with one P-Number metal shall also qualify for that P-Number metal welded to each of the lower P-Number metals, but not vice versa.

QW-403.15 Welding procedure qualifications for electron beam welding shall be made using a base metal of the same type or grade or another base metal listed in the same P-Number (and the same group where given — see [Table QW/QB-422](#)) as the base metal to be used in production welding. When joints are to be made between base metals from two different P-Numbers (or two different groups), a procedure qualification must be made for the applicable combination of base metals even though procedure qualification tests have been made for each of the two base metals welded to itself.

QW-403.16 A change in the pipe diameter beyond the range qualified in [QW-452](#), except as otherwise permitted in [QW-303.1](#), [QW-303.2](#), [QW-381.1\(c\)](#), or [QW-382\(c\)](#).

QW-403.17 In stud welding, a change in combination of base metal listed under one P-Number in [Table QW/QB-422](#) and stud metal P-Number (as defined in the following Note), or to any other base metal/stud metal combination.

NOTE: Stud metal shall be classified by nominal chemical composition and can be assigned a P-Number when it meets the nominal composition of any one of the P-Number metals.

QW-403.18 A change from one P-Number to any other P-Number or to a base metal not listed in [Table QW/QB-422](#), except as permitted in [QW-423](#), and in [QW-420](#).

QW-403.19 A change to another base material type or grade (type or grade are materials of the same nominal chemical analysis and mechanical property range, even though of different product form), or to any other base

material type or grade. When joints are made between two different types or grades of base material, a procedure qualification must be made for the applicable combinations of materials, even though procedure qualification tests have been made for each of the two base materials welded to itself.

QW-403.20 A change from a base metal, listed under one P-Number in [Table QW/QB-422](#), to a metal listed under another P-Number or to any other base metal; from a base metal of one subgroup to any other grouping in P-No. 10 or 11.

QW-403.21 The addition or deletion of a coating, plating or cladding, or a change in the nominal chemical analysis or thickness range of the plating or cladding, or a change in type of coating as specified in the WPS.

QW-403.22 A change in the base metal thickness exceeding 10% of the thickness of the total joint from that qualified.

QW-403.23 A change in base metal thickness beyond the range qualified in [Table QW-453](#).

QW-403.24 A change in the specification, type, or grade of the base metal. When joints are to be made between two different base metals, a procedure qualification must be made for the applicable combination even though procedure qualifications have been made for each of the two base metals welded to themselves.

QW-403.25 Welding procedure qualifications shall be made using a base metal of the same P-Number and Group Number as the base metal to be temper bead welded. When joints are to be made between base metals from two different P-Number/Group Number combinations, a temper bead procedure qualification must be made for each base metal P-Number/Group Number to be used in production; this may be done in separate test coupons or in combination on a single test coupon. When base metals of different P-Number/Group Numbers are tested in the same coupon, the welding variables utilized and test results on each side of the coupon shall be documented independently but may be reported on the same qualification record. Where temper bead welding is to be applied to only one side of a joint (e.g., on the P-No. 1 side of a joint between P-No. 1 and P-No. 8 metals) or where cladding is being applied or repaired using temper bead techniques, qualification in accordance with [QW-290](#) is required only for the portion of the WPS that applies to welding on the material to be temper bead welded.

QW-403.26 An increase in the base metal carbon equivalent using the following equation:

$$CE = C + \frac{Mn}{6} + \frac{Cr + Mo + V}{5} + \frac{Ni + Cu}{15}$$

QW-403.27 The maximum thickness qualified is the thickness of the test coupon, T , or it is unlimited if the test coupon is $1\frac{1}{2}$ in. (38 mm) thick or thicker. However,

where T is $\frac{1}{4}$ in. (6 mm) or less, the maximum thickness qualified is $2T$. This limitation applies to fillet welds as well as to groove welds.

QW-403.28 A change to another base metal type, grade, or UNS number.

QW-403.29 A change in the surface finish as defined by the material specification or established surface roughness range as measured in accordance with ASME B46.1-2006.

QW-403.30 A change in base metal thickness greater than 20% (13)

(a) of the test coupon thickness for fixed-pin and retracting-pin rotating tools

(b) beyond the minimum and maximum thickness or thickness transition slopes of the test coupon for self-reacting rotating tools

QW-403.31 (13)

(a) For full penetration groove welds made without backing, the base metal thickness qualified is $\pm 10\%$ from that of the test coupon when the test coupon thickness is less than or equal to 1 in. (25 mm) and $\pm 5\%$ when the test coupon thickness is greater than 1 in. (25 mm).

(b) For full penetration groove welds made with backing, partial penetration groove welds, and fillet welds, the minimum base metal thickness qualified shall be equal to that used for the PQR test coupon and the maximum thickness is unlimited.

QW-404 FILLER METALS

QW-404.1 An increase of greater than 10% in the cross-sectional area of the filler metal added (excluding buttering) or in the wire-feed speed beyond that qualified.

QW-404.2 A decrease in the thickness or change in nominal specified chemical analysis of weld metal buttering beyond that qualified. (Buttering or surfacing is the deposition of weld metal on one or both faces of the joint prior to preparation of the joint for final electron beam welding.)

QW-404.3 A change in the size of the filler metal.

QW-404.4 A change from one F-Number in [Table QW-432](#) to any other F-Number or to any other filler metal not listed in [Table QW-432](#).

QW-404.5 (Applicable only to ferrous metals.) A change in the chemical composition of the weld deposit from one A-Number to any other A-Number in [Table QW-442](#). Qualification with A-No. 1 shall qualify for A-No. 2 and vice versa.

The weld metal chemical composition may be determined by any of the following:

(a) For all welding processes — from the chemical analysis of the weld deposit taken from the procedure qualification test coupon.

(b) For SMAW, GTAW, LBW, and PAW — from the chemical analysis of the weld deposit prepared according to the filler metal specification, or from the chemical composition as reported either in the filler metal specification or the manufacturer's or supplier's certificate of compliance.

(c) For GMAW and EGW — from the chemical analysis of the weld deposit prepared according to the filler metal specification or the manufacturer's or supplier's certificate of compliance when the shielding gas used was the same as that used to weld the procedure qualification test coupon.

(d) For SAW — from the chemical analysis of the weld deposit prepared according to the filler metal specification or the manufacturer's or supplier's certificate of compliance when the flux used was the same as that used to weld the procedure qualification test coupon.

In lieu of an A-Number designation, the nominal chemical composition of the weld deposit shall be indicated on the WPS and on the PQR. Designation of nominal chemical composition may also be by reference to the AWS classification except for the "G" suffix classification, the manufacturer's trade designation, or other established procurement documents.

QW-404.6 A change in the nominal size of the electrode or electrodes specified in the WPS.

QW-404.7 A change in the nominal diameter of the electrode to over $\frac{1}{4}$ in. (6 mm). This variable does not apply when a WPS is qualified with a PWHT above the upper transformation temperature or when an austenitic material is solution annealed after welding.

QW-404.8 Addition or deletion, or a change of more than 10% in the nominal amount or composition of supplementary deoxidation material (in addition to filler metal) beyond that qualified.

QW-404.9

(a) A change in the indicator for minimum tensile strength (e.g., the 7 in F7A2-EM12K) when the flux wire combination is classified in Section II, Part C.

(b) A change in either the flux trade name or wire trade name when neither the flux nor the wire is classified in Section II, Part C.

(c) A change in the flux trade name when the wire is classified in Section II, Part C but the flux is not classified. A change in the wire classification within the requirements of [QW-404.5](#) does not require requalification.

(d) A change in the flux trade name for A-No. 8 deposits.

QW-404.10 Where the alloy content of the weld metal is largely dependent upon the composition of the flux used, any change in any part of the welding procedure which would result in the important alloying elements in the weld metal being outside of the specification range of chemistry given in the Welding Procedure Specification. If there is evidence that the production welds are not being made in accordance with the procedure

specification, the authorized inspector may require that a check be made on the chemical composition of the weld metal. Such a check shall preferably be made on a production weld.

QW-404.12 A change in the filler metal classification within an SFA specification, or for a filler metal not covered by an SFA specification or a filler metal with a "G" suffix within an SFA specification, a change in the trade designation of the filler metal.

When a filler metal conforms to a filler metal classification, within an SFA specification, except for the "G" suffix classification, requalification is not required if a change is made in any of the following:

(a) from a filler metal that is designated as moisture-resistant to one that is not designated as moisture-resistant and vice versa (i.e., from E7018R to E7018)

(b) from one diffusible hydrogen level to another (i.e., from E7018-H8 to E7018-H16)

(c) for carbon, low alloy, and stainless steel filler metals having the same minimum tensile strength and the same nominal chemical composition, a change from one low hydrogen coating type to another low hydrogen coating type (i.e., a change among EXX15, 16, or 18 or EXXX15, 16, or 17 classifications)

(d) from one position-usability designation to another for flux-cored electrodes (i.e., a change from E70T-1 to E71T-1 or vice versa)

(e) from a classification that requires impact testing to the same classification which has a suffix which indicates that impact testing was performed at a lower temperature or exhibited greater toughness at the required temperature or both, as compared to the classification which was used during procedure qualification (i.e., a change from E7018 to E7018-1)

(f) from the classification qualified to another filler metal within the same SFA specification when the weld metal is exempt from Impact Testing by other Sections

This exemption does not apply to hard-facing and corrosion-resistant overlays

QW-404.14 The deletion or addition of filler metal.

QW-404.15 A change from one F-Number in [Table QW-432](#) to any other F-Number or to any other filler metal, except as permitted in [QW-433](#).

QW-404.17 A change in the type of flux or composition of the flux.

QW-404.18 A change from wire to plate electrodes, and vice versa.

QW-404.19 A change from consumable guide to nonconsumable guide, and vice versa.

QW-404.20 Any change in the method by which filler metal is added, such as preplaced shim, top strip, wire, wire feed, or prior weld metal buttering of one or both joint faces.

QW-404.21 For filler metal additions, any change from the nominal specified analysis of the filler metal qualified.

QW-404.22 The omission or addition of consumable inserts. Qualification in a single-welded butt joint, with or without consumable inserts, qualifies for fillet welds and single-welded butt joints with backing or double-welded butt joints. Consumable inserts that conform to SFA-5.30, except that the chemical analysis of the insert conforms to an analysis for any bare wire given in any SFA specification or AWS Classification, shall be considered as having the same F-Number as that bare wire as given in [Table QW-432](#).

(13) **QW-404.23** A change from one of the following filler metal product forms to another:

- (a) bare (solid or metal cored)
- (b) flux cored
- (c) flux coated (solid or metal cored)
- (d) powder

QW-404.24 The addition, deletion, or change of more than 10% in the volume of supplemental filler metal.

QW-404.27 Where the alloy content of the weld metal is largely dependent upon the composition of the supplemental filler metal (including powder filler metal for PAW), any change in any part of the welding procedure that would result in the important alloying elements in the weld metal being outside of the specification range of chemistry given in the Welding Procedure Specification.

QW-404.29 A change in the flux trade name and designation.

(13) **QW-404.30** A change in deposited weld metal thickness beyond that qualified in accordance with [QW-451](#) for procedure qualification or [QW-452](#) for performance qualification, except as otherwise permitted in [QW-303.1](#) and [QW-303.2](#). When a welder is qualified using volumetric examination, the maximum thickness stated in [Table QW-452.1\(b\)](#) applies.

QW-404.31 The maximum thickness qualified is the thickness of the test coupon.

QW-404.32 For the low voltage short-circuiting type of gas metal-arc process when the deposited weld metal thickness is less than $\frac{1}{2}$ in. (13 mm), an increase in deposited weld metal thickness beyond 1.1 times that of the qualification test deposited weld metal thickness. For weld metal thicknesses of $\frac{1}{2}$ in. (13 mm) and greater, use [Table QW-451.1](#), [Table QW-451.2](#), or [Tables QW-452.1\(a\)](#) and [QW-452.1\(b\)](#), as applicable.

QW-404.33 A change in the filler metal classification within an SFA specification, or, if not conforming to a filler metal classification within an SFA specification, a change in the manufacturer's trade name for the filler metal. When optional supplemental designators, such as those which indicate moisture resistance (i.e., XXXXR), diffusible hydrogen (i.e., XXXX H16, H8, etc.), and supplemental

impact testing (i.e., XXXX-1 or EXXXXM), are specified on the WPS, only filler metals which conform to the classification with the optional supplemental designator(s) specified on the WPS shall be used.

QW-404.34 A change in flux type (i.e., neutral to active or vice versa) for multilayer deposits in P-No. 1 materials.

QW-404.35 A change in the flux/wire classification or a change in either the electrode or flux trade name when not classified in an SFA specification. Requalification is not required when a wire/flux combination conforms to an SFA specification and a change is made from one diffusible hydrogen level to another (i.e., a change from F7A2-EA1-A1H4 to F7A2-EA1-A1H16). This variable does not apply when the weld metal is exempt from impact testing by other Sections. This exemption does not apply to hard facing and corrosion-resistant overlays.

QW-404.36 When flux from recrushed slag is used, each batch or blend, as defined in SFA-5.01, shall be tested in accordance with Section II, Part C by either the manufacturer or user, or qualified as an unclassified flux in accordance with [QW-404.9](#).

QW-404.37 A change in the composition of the deposited weld metal from one A-Number in [Table QW-442](#) to any other A-Number, or to an analysis not listed in the table. A change in the UNS number for each AWS classification of A-No. 8 or A-No. 9 analysis of [Table QW-442](#), or each nonferrous alloy in [Table QW-432](#), shall require separate WPS qualification. A-Numbers may be determined in accordance with [QW-404.5](#).

QW-404.38 A change in the nominal electrode diameter used for the first layer of deposit.

QW-404.39 For submerged-arc welding and electroslag welding, a change in the nominal composition or type of flux used. Requalification is not required for a change in flux particle size.

QW-404.41 A change of more than 10% in the powdered metal feed rate recorded on the PQR.

QW-404.42 A change of more than 5% in the particle size range of the powder.

QW-404.43 A change in the powdered metal particle size range recorded on the PQR.

QW-404.44 A change from a homogeneous powdered metal to a mechanical mixed powdered metal or vice versa.

QW-404.45 A change in the form of filler metal from solid to fabricated wire, flux-cored wire, powdered metal, or vice versa.

QW-404.46 A change in the powder feed rate range qualified.

QW-404.47 A change of more than 10% in the filler metal size and/or powder metal particle size.

QW-404.48 A change of more than 10% in the powder metal density.

QW-404.49 A change of more than 10% in the filler metal or powder metal feed rate.

QW-404.50 The addition or deletion of flux to the face of a weld joint for the purpose of affecting weld penetration.

QW-404.51 The method of control of moisture pickup during storage and distribution for SMAW and GMAW-FC electrodes and flux for SAW (e.g., purchasing in hermetically sealed containers and storage in heated ovens, controlled distribution time, high-temperature baking prior to use).

QW-404.52 A change in the diffusible hydrogen level (e.g., from E7018-H8 to E7018-H16 or to no controlled diffusible hydrogen).

QW-404.53 The addition or deletion of filler metal and, when used, a change in the filler metal nominal composition.

- (13) **QW-404.54** An increase in the deposited weld metal thickness qualified.

QW-405 POSITIONS

QW-405.1 The addition of other welding positions than those already qualified. see [QW-120](#), [QW-130](#), [QW-203](#), and [QW-303](#).

QW-405.2 A change from any position to the vertical position uphill progression. Vertical-uphill progression (e.g., 3G, 5G, or 6G position) qualifies for all positions. In uphill progression, a change from stringer bead to weave bead. This variable does not apply when a WPS is qualified with a PWHT above the upper transformation temperature or when an austenitic material is solution annealed after welding.

QW-405.3 A change from upward to downward, or from downward to upward, in the progression specified for any pass of a vertical weld, except that the cover or wash pass may be up or down. The root pass may also be run either up or down when the root pass is removed to sound weld metal in the preparation for welding the second side.

- (13) **QW-405.4** Except as specified below, the addition of other welding positions than already qualified.

(a) Qualification in the horizontal, vertical, or overhead position shall also qualify for the flat position. Qualification in the horizontal fixed position, 5G, shall qualify for the flat, vertical, and overhead positions. Qualification in the horizontal, vertical, and overhead positions shall qualify for all positions. Qualification in the inclined fixed position, 6G, shall qualify for all positions.

(b) An organization who does production welding in a particular orientation may make the tests for procedure qualification in this particular orientation. Such qualifications are valid only for the positions actually tested, except

that an angular deviation of ± 15 deg is permitted in the inclination of the weld axis and the rotation of the weld face as defined in [Figure QW-461.1](#). A test specimen shall be taken from the test coupon in each special orientation.

(c) For hard-facing and corrosion-resistant weld metal overlay, qualification in the 3G, 5G, or 6G positions, where 5G or 6G pipe coupons include at least one vertical segment completed utilizing the up-hill progression or a 3G plate coupon is completed utilizing the up-hill progression, shall qualify for all positions. Chemical analysis, hardness, macro-etch, and at least two of the bend tests, as required in [Table QW-453](#), shall be removed from the vertical uphill overlaid segment as shown in [Figure QW-462.5\(b\)](#).

(d) A change from the vertical down to vertical up-hill progression shall require requalification.

QW-406 PREHEAT

QW-406.1 A decrease of more than 100°F (55°C) in the preheat temperature qualified. The minimum temperature for welding shall be specified in the WPS.

QW-406.2 A change in the maintenance or reduction of preheat upon completion of welding prior to any required postweld heat treatment.

QW-406.3 An increase of more than 100°F (55°C) in the maximum interpass temperature recorded on the PQR. This variable does not apply when a WPS is qualified with a PWHT above the upper transformation temperature or when an austenitic or P-No. 10H material is solution annealed after welding.

QW-406.4 A decrease of more than 100°F (55°C) in the preheat temperature qualified or an increase in the maximum interpass temperature recorded on the PQR. The minimum temperature for welding shall be specified in the WPS.

QW-406.5 A change in the maintenance or reduction of preheat upon completion of spraying and prior to fusing.

QW-406.7 A change of more than 10% in the amplitude or number of preheating cycles from that qualified, or if other preheating methods are employed, a change in the preheating temperature of more than 25°F (15°C).

QW-406.8 An increase in the maximum interpass temperature of more than 100°F (56°C) from that achieved on the test coupon and recorded on the PQR. The interpass temperature shall be measured and recorded separately for each tempering weld bead layer and, if any, for the surface weld bead layer(s). The WPS shall specify the maximum interpass temperature limits for each tempering bead layer separately and for the surfacing weld bead layer(s), if any.

QW-406.9 A decrease in the preheat temperature from that achieved on the test coupon and recorded on the PQR. The preheat temperature shall be measured

and recorded separately for each tempering weld bead layer and, if any, for the surface weld bead layer(s). The WPS shall specify the minimum preheat temperature limits for each tempering bead layer separately and for the surfacing weld bead layer(s), if any.

QW-406.10 The minimum preheating soaking time prior to the start of welding.

QW-406.11 The addition or deletion of a postweld hydrogen bakeout. When specified, the minimum soaking temperature and time shall be specified.

QW-407 POSTWELD HEAT TREATMENT

QW-407.1 A separate procedure qualification is required for each of the following:

(a) For P-Numbers 1 through 6 and 9 through 15F materials, the following postweld heat treatment conditions apply:

- (1) no PWHT
- (2) PWHT below the lower transformation temperature
- (3) PWHT above the upper transformation temperature (e.g., normalizing)
- (4) PWHT above the upper transformation temperature followed by heat treatment below the lower transformation temperature (e.g., normalizing or quenching followed by tempering)
- (5) PWHT between the upper and lower transformation temperatures
- (b) For all other materials, the following postweld heat treatment conditions apply:
 - (1) no PWHT
 - (2) PWHT within a specified temperature range

QW-407.2 A change in the postweld heat treatment (see [QW-407.1](#)) temperature and time range

The procedure qualification test shall be subjected to PWHT essentially equivalent to that encountered in the fabrication of production welds, including at least 80% of the aggregate times at temperature(s). The PWHT total time(s) at temperature(s) may be applied in one heating cycle.

QW-407.4 For ferrous base metals other than P-No. 7, P-No. 8, and P-No. 45, when a procedure qualification test coupon receives a postweld heat treatment exceeding the upper transformation temperature or a solution heat treatment for P-No. 10H materials, the maximum qualified base metal thickness, T , shall not exceed 1.1 times the thickness of the test coupon.

QW-407.6 A change in postweld heat treatment condition in [QW-407.1](#) or an increase of 25% or more in total time at postweld heat treating temperature.

QW-407.7 A change in the heat treatment temperature range qualified if heat treatment is applied after fusing.

QW-407.8 A separate PQR is required for each of the following:

- (a) no PWHT
- (b) a change of more than 10% in the number of PWHT heating current cycles following the welding cycle
- (c) PWHT within a specified temperature and time range if heat treatment is performed separately from the welding operation

QW-407.9 A separate procedure qualification is required for each of the following:

- (a) For weld corrosion-resistant overlay of A-No. 8 on all base materials, a change in postweld heat treatment condition in [QW-407.1](#), or when the total time at postweld heat treatment encountered in fabrication exceeds 20 hr, an increase of 25% or more in total time at postweld heat treating temperature.
- (b) For weld corrosion-resistant overlay of A-No. 9 on all base materials, a change in postweld heat treatment condition in [QW-407.1](#), or an increase of 25% or more in total time at postweld heat treating temperature.
- (c) For all other weld corrosion-resistant overlays on all base materials, a change in postweld heat treatment condition in [QW-407.1](#).

QW-407.10 The addition or deletion of PWHT, or a change of $\pm 45^\circ\text{F}$ ($\pm 25^\circ\text{C}$) in PWHT temperature or an increase in the holding time by more than 25% or change in the method of cooling (e.g., furnace, air, quench).

QW-408 GAS

QW-408.1 The addition or deletion of trailing shielding gas and/or a change in its composition.

QW-408.2 A separate procedure qualification is required for each of the following:

- (a) a change from a single shielding gas to any other single shielding gas
- (b) a change from a single shielding gas to a mixture of shielding gasses, and vice versa
- (c) a change in the specified percentage composition of a shielding gas mixture
- (d) the addition or omission of shielding gas

The AWS classification of SFA-5.32 may be used to specify the shielding gas composition.

QW-408.3 A change in the specified flow rate range of the shielding gas or mixture of gases.

QW-408.4 A change in the composition of the orifice or shielding gas.

QW-408.5 The addition or deletion of gas backing, a change in backing gas composition, or a change in the specified flow rate range of the backing gas.

QW-408.6 A change of environment shielding such as from vacuum to an inert gas, or vice versa.

QW-408.7 A change in the type of fuel gas.

QW-408.8 The omission of inert gas backing except that requalification is not required when welding a single-welded butt joint with a backing strip or a double-welded butt joint or a fillet weld. This exception does not apply to P-No. 51 through P-No. 53, P-No. 61 through P-No. 62, and P-No. 10I metals.

QW-408.9 For groove welds in P-No. 41 through P-No. 49 and all welds of P-No. 10I, P-No. 10J, P-No. 10K, P-No. 51 through P-No. 53, and P-No. 61 through P-No. 62 metals, the deletion of backing gas or a change in the nominal composition of the backing gas from an inert gas to a mixture including non-inert gas(es).

QW-408.10 For P-No. 10I, P-No. 10J, P-No. 10K, P-No. 51 through P-No. 53, and P-No. 61 through P-No. 62 metals, the deletion of trailing shielding gas, or a change in the nominal composition of the trailing gas from an inert gas to a mixture including non-inert gas(es), or a decrease of 10% or more in the trailing gas flow rate.

QW-408.11 The addition or deletion of one or more of the following:

- (a) shielding gas
- (b) trailing shielding gas
- (c) backing gas
- (d) plasma-removing gas

QW-408.12 A decrease of more than 10% in the flow rate of one or more of the following: shielding gas, trailing shielding gas, backing gas, and plasma-removing gas.

(13) **QW-408.13**

DELETED

QW-408.14 A change in the oxygen or fuel gas pressure beyond the range qualified.

QW-408.16 A change of more than 5% in the flow rate of the plasma-arc gas or powdered metal feed gas recorded on the PQR.

QW-408.17 A change in the plasma-arc gas, shielding gas, or powdered metal feed gas from a single gas to any other single gas, or to a mixture of gases, or vice versa.

QW-408.18 A change of more than 10% in the gas mixture composition of the plasma-arc gas, shielding gas, or powdered metal feed gas recorded on the PQR.

QW-408.19 A change in the nominal composition of the powder feed gas or (plasma-arc spray) plasma gas qualified.

QW-408.20 A change of more than 5% in the plasma gas flow rate range qualified.

QW-408.21 A change in the flow rate of the orifice or shielding gas.

QW-408.22 A change in the shielding gas type, gas pressure, or purging time.

QW-408.23 For titanium, zirconium, and their alloys, the deletion of one or more of the following:

- (a) shielding gas
- (b) trailing shielding gas
- (c) backing gas

QW-408.24 For gas-shielded processes, the maximum moisture content (dew point) of the shielding gas. Moisture control may be by specification of shielding gas classifications in SFA-5.32.

QW-408.25 A change in the furnace atmosphere from that qualified.

QW-408.26 For friction stir welding of P-No. 6, P-No. 7, P-No. 8, P-No. 10H, P-No. 10I, P-No. 41 through P-No. 47, P-No. 51 through P-No. 53, and P-No. 61 through P-No. 62, the addition or deletion of trailing or tool shielding gas, or a change in gas composition or flow rate. (13)

QW-409 ELECTRICAL CHARACTERISTICS

QW-409.1 An increase in heat input, or an increase in volume of weld metal deposited per unit length of weld, over that qualified. The increase shall be determined by (a), (b), or (c) for nonwaveform controlled welding, or by (b) or (c) for waveform controlled welding. See [Nonmandatory Appendix H](#).

(a) Heat input [J/in. (J/mm)]

$$= \frac{\text{Voltage} \times \text{Amperage} \times 60}{\text{Travel Speed} [\text{in./min} (\text{mm/min})]}$$

(b) Volume of weld metal measured by

(1) an increase in bead size (width × thickness), or

(2) a decrease in length of weld bead per unit length of electrode

(c) Heat input determined using instantaneous energy or power by

(1) for instantaneous energy measurements in joules (J) Heat input [J/in. (J/mm)]

$$= \frac{\text{Energy (J)}}{\text{Weld Bead Length [in. (mm)]}}$$

(2) for instantaneous power measurements in joules per second (J/s) or Watts (W) Heat input [J/in. (J/mm)]

$$= \frac{\text{Power (J/s or W)} \times \text{arc time (s)}}{\text{Weld Bead Length [in. (mm)]}}$$

The requirement for measuring the heat input or volume of deposited weld metal does not apply when the WPS is qualified with a PWHT above the upper transformation temperature or when an austenitic or P-No. 10H material is solution annealed after welding.

QW-409.2 A change from globular, spray or pulsed spray transfer welding to short circuiting transfer welding or vice versa.

QW-409.3 The addition or deletion of pulsing current to dc power source.

QW-409.4 A change from AC to DC, or vice versa; and in DC welding, a change from electrode negative (straight polarity) to electrode positive (reverse polarity), or vice versa.

QW-409.5 A change of $\pm 15\%$ from the amperage or voltage ranges in the qualified WPS.

QW-409.6 A change in the beam current of more than $\pm 5\%$, voltage of more than $\pm 2\%$, welding speed of more than $\pm 2\%$, beam focus current of more than $\pm 5\%$, gun-to-work distance of more than $\pm 5\%$, or a change in oscillation length or width of more than $\pm 20\%$ from those previously qualified.

QW-409.7 Any change in the beam pulsing frequency duration from that qualified.

QW-409.8 A change in the range of amperage, or except for SMAW, GTAW, or waveform controlled welding, a change in the range of voltage. A change in the range of electrode wire feed speed may be used as an alternative to amperage. See [Nonmandatory Appendix H](#):

QW-409.9 A change in the arc timing of more than $\pm \frac{1}{10}$ sec.

QW-409.10 A change in amperage of more than $\pm 10\%$.

QW-409.11 A change in the power source from one model to another.

QW-409.12 A change in type or size of tungsten electrode.

QW-409.13 A change from one Resistance Welding Manufacturer's Association (RWMA) electrode class to another. In addition, a change in the following:

(a) for spot and projection welding, a change in the nominal shape or more than 10% of the contact area of the welding electrode

(b) for seam welding, a change of thickness, profile, orientation, or diameter of electrodes exceeding 10%

QW-409.14 Addition or deletion of upslope or downslope current control, or a change of more than 10% in the slope current time or amplitude.

QW-409.15

(a) A change of more than 5% in any of the following from that qualified:

- (1) preheating current
- (2) preheating current amplitude
- (3) preheating current time duration
- (4) electrode pressure
- (5) welding current
- (6) welding current time duration

(b) A change from AC to DC or vice versa.

(c) The addition or deletion of pulsing current to a DC power source.

(d) When using pulsing DC current, a change of more than 5% in the pulse amplitude, frequency, or number of pulses per cycle from that qualified.

(e) A change of more than 5% in the post-heating current time duration from that qualified.

QW-409.17 A change in the power supply primary voltage or frequency, or in the transformer turns ratio, tap setting, choke position, secondary open circuit voltage or phase control setting.

QW-409.18 A change in the procedure or frequency of tip cleaning.

QW-409.19 Any change of more than $\pm 10\%$ in the beam pulsing frequency and pulse duration from that qualified.

QW-409.20 Any change in the following variables: mode of operation (from pulsed to continuous and vice versa), energy distribution across the beam (i.e., multi-mode or gaussian).

QW-409.21 A decrease of more than 10% in the power delivered to the work surface as measured by calorimeter or other suitable methods.

QW-409.22 An increase of more than 10% in the amperage used in application for the first layer.

QW-409.23 A change of more than 10% in the ranges of amperage or voltage qualified.

QW-409.24 A change of more than 10% in the filler wire wattage recorded on the PQR. Wattage is a function of current voltage, and stickout dimension.

QW-409.25 A change of more than 10% in the plasma-arc current or voltage recorded on the PQR.

QW-409.26 For the first layer only, an increase in heat input of more than 10% or an increase in volume of weld metal deposited per unit length of weld of more than 10% over that qualified. The increase shall be determined by the methods of [QW-409.1](#).

QW-409.27 A change in the flashing time of more than 10%.

QW-409.28 A change in the upset current time by more than 10%.

QW-409.29

(a) A change in heat input beyond the following (see [Figure QW-462.12](#)):

(1) An increase or decrease in the ratio of heat input between the first tempering bead layer and the weld beads deposited against the base metal of more than 20% for P-No. 1 and P-No. 3 metals and 10% for all other P-Number metals.

(2) An increase or decrease in the ratio of heat input between the second tempering bead layer and the first tempering bead layer of more than 20% for P-No. 1 and P-No. 3 metals and 10% for all other P-Number metals.

(3) The ratio of heat input between subsequent layers shall be maintained until a minimum of $\frac{3}{16}$ in. (5 mm) of weld metal has been deposited over the base metal.

(4) For qualifications where the basis for acceptance is impact testing and the filler metal is exempt from temper bead qualification, the heat input may not exceed 50% above the heat input qualified for the remaining fill passes.

(5) For qualifications where the basis for acceptance is hardness testing, a decrease of more than 20% in heat input for the remainder of the fill passes.

(b) Heat input shall be determined using the following methods:

(1) For machine or automatic GTAW or PAW, an increase or decrease of 10% in the power ratio measured as:

$$\text{Power Ratio} = \frac{\text{Amperage} \times \text{Voltage}}{[(WFS / TS) \times A_f]}$$

where

A_f = the cross-section area of the filler metal wire

TS = the welding travel speed

WFS = the filler metal wire feed speed

(2) For processes other than machine or automatic GTAW or PAW, heat input shall be determined by the method of [QW-409.1](#).

(3) If manual GTAW or PAW is used for making in-process repairs in accordance with [QW-290.5](#), a record of bead size shall be made.

(13) QW-410 TECHNIQUE

QW-410.1 For manual or semiautomatic welding, a change from the stringer bead technique to the weave bead technique, or vice versa.

QW-410.2 A change in the nature of the flame, oxidizing to reducing, or vice versa.

QW-410.3 A change in the orifice, cup, or nozzle size.

QW-410.4 A change in the welding technique, forehand to backhand, or vice versa.

QW-410.5 A change in the method of initial and inter-pass cleaning (brushing, grinding, etc.).

QW-410.6 A change in the method of back gouging.

QW-410.7 For the machine or automatic welding process, a change of more than $\pm 10\%$ in width, frequency, or dwell time of oscillation technique.

QW-410.8 A change in the contact tube to work distance.

QW-410.9 A change from multipass per side to single pass per side. This variable does not apply when a WPS is qualified with a PWHT above the upper transformation temperature or when an austenitic or P-No. 10H material is solution annealed after welding.

QW-410.10 A change from single electrode to multiple electrode, or vice versa, for machine or automatic welding only. This variable does not apply when a WPS is qualified with a PWHT above the upper transformation temperature or when an austenitic or P-No. 10H material is solution annealed after welding.

QW-410.11 A change from closed chamber to out-of-chamber conventional torch welding in P-No. 51 through P-No. 53 metals, but not vice versa.

QW-410.12 A change from the melt-in technique to the keyhole technique of welding, or vice versa, or the inclusion of both techniques though each has been individually qualified.

QW-410.14 For full penetration groove welds, a change of more than ± 10 deg in the relative angle between the axis of the beam and the workpiece.

QW-410.15 A change in the spacing of multiple electrodes for machine or automatic welding.

QW-410.17 A change in the type or model of the welding equipment.

QW-410.18 An increase in the absolute pressure of the vacuum welding environment beyond that qualified.

QW-410.19 Any change in filament type, size, or shape.

QW-410.20 The addition of a wash pass.

QW-410.21 For full penetration groove welds, a change of welding from both sides to welding from one side only, but not vice versa.

QW-410.22 A change in either of the following stud welding parameters: a change of stud gun model; a change in the lift more than $\pm \frac{1}{32}$ in. (0.8 mm).

QW-410.25 A change from manual or semiautomatic to machine or automatic welding and vice versa.

QW-410.26 The addition or deletion of peening.

QW-410.27 A change in the rotational speed producing a change in the outside surface velocity [ft/min (m/min)] greater than $\pm 10\%$ of the outside surface velocity qualified.

QW-410.28 A change in the thrust load greater than $\pm 10\%$ of the thrust load qualified.

QW-410.29 A change in the rotational energy greater than $\pm 10\%$ of the rotational energy qualified.

QW-410.30 Any change in upset dimension (overall loss in length of parts being joined) greater than $\pm 10\%$ of the upset qualified.

QW-410.31 A change in the method of preparing the base metal prior to welding (e.g., changing from mechanical cleaning to chemical cleaning or to abrasive cleaning, or vice versa).

QW-410.32 A change of more than 10% in the holding (forging) pressure prior to or after welding. A change of more than 10% in the electrode holding time (electrode duration sequence).

QW-410.33 A change from one welding type to another, or modification of equipment, including Manufacturer, control panel, model number, electrical rating or capacity, type of electrical energy source, or method of applying pressure.

QW-410.34 Addition or deletion of an electrode cooling medium and where it is used.

QW-410.35 A change in the distance between arms or a change in the throat depth.

QW-410.37 A change from single to multiple pass or vice versa.

QW-410.38 A change from multiple-layer to single layer cladding/hardsurfacing, or vice versa.

QW-410.39 A change in the torch type or tip size.

QW-410.40 For submerged-arc welding and electroslag welding, the deletion of a supplementary device for controlling the magnetic field acting on the weld puddle.

QW-410.41 A change of more than 15% in the travel speed range recorded on the PQR.

QW-410.43 For the torch or workpiece, a change of more than 10% in the travel speed range qualified.

QW-410.44 A change of more than 15% in the spray-torch to workpiece distance qualified.

QW-410.45 A change in the method of surface preparation of the base metal to be hard-faced (example: sandblasting versus chemical cleaning).

QW-410.46 A change in the spray-torch model or tip orifice size.

QW-410.47 A change of more than 10% in the fusing temperature range qualified. A change in the rate of cooling from the fusing temperature of more than 50°F/hr (28°C/hr), a change in the fusing method (e.g., torch, furnace, induction).

QW-410.48 A change in the constricted arc from transferable to nontransferable or vice versa.

QW-410.49 A change in the diameter of the plasma torch-arc constricting orifice.

QW-410.50 A change in the number of electrodes acting on the same welding puddle.

QW-410.52 A change in the method of delivering the filler metal to the molten pool, such as from the leading or trailing edge of the torch, the sides of the torch, or through the torch.

QW-410.53 A change of more than 20% in the center-to-center weld bead distance.

QW-410.54 A change in the upset length or force of more than 10%.

QW-410.55 A change in the distance between the clamping dies of more than 10% or a change in the surface preparation of the clamping area.

QW-410.56 A change in the clamping force by more than 10%.

QW-410.57 A change in more than 10% of the forward or reverse speed.

QW-410.58 The deletion of surface temper beads (see [Figure QW-462.12](#)) or a change from surface temper beads that cover the weld surface to beads that are only deposited along the toes of the weld.

QW-410.59 A change from machine or automatic welding to manual or semiautomatic welding.

QW-410.60 The addition of thermal methods to prepare the surface to be welded unless the WPS requires that the metal be ground to bright metal before welding.

QW-410.61 The distance, S , from the toe of the weld to the edge of any tempering bead shall be limited to the distance measured on the test coupon $\pm 1/16$ in. (± 1.5 mm) (see [Figure QW-462.12](#)). Alternatively, a range for S may be established by locating temper beads at various distances from the toe of the weld followed by hardness traverses or impact testing, as applicable. Temper reinforcing beads shall not be permitted to touch the toe of the weld. In addition, the ratios of heat input described in [QW-409.29](#) shall apply to temper beads.

QW-410.62 The method of removal of surface temper bead reinforcing layer when it will be removed, including provisions to prevent overheating of the weld surface.

QW-410.63 For weld beads against the base metal and for each tempering bead layer, the range of bead width, b , relative to overlap of the previous bead width, a , as shown in [Figure QW-462.13](#), shall be specified on the WPS. Overlap between 25% and 75% does not require qualification.

(a) Overlap greater than 75% shall be qualified by welding a test coupon using the desired overlap. The overlap qualified shall be the maximum overlap permitted and the minimum overlap shall be 50%.

(b) Overlap less than 25% shall be qualified by welding a test coupon using the desired overlap. The overlap qualified shall be the minimum overlap permitted and the maximum overlap shall be 50%.

QW-410.64 For vessels or parts of vessels constructed with P-No. 11A and P-No. 11B base metals, weld grooves for thickness less than $5/8$ in. (16 mm) shall be prepared by thermal processes when such processes are to be employed during fabrication. This groove

preparation shall also include back gouging, back grooving, or removal of unsound weld metal by thermal processes when these processes are to be employed during fabrication.

QW-410.65 The addition or deletion of grinding beyond that required to clean the surface or remove minor surface flaws (i.e., use or nonuse of half-bead technique or similar technique).

QW-410.66 A change of more than $\pm 10\%$ in the travel speed, the ratio of the beam diameter to focal length, or the lens to work distance.

QW-410.67 A change in the optical technique used to focus the welding energy from that qualified.

QW-410.68 A change in welding equipment type (e.g., YAG, TAG, etc.).

QW-410.70 A change in the method of preparing the base metal surface prior to insertion into the furnace.

QW-410.71 A decrease in the percentage of block compression (original stack height compared to height after welding) from that of the test coupon.

QW-410.72 A decrease in the welding temperature or time from that used on the procedure qualification test coupon.

QW-410.73 A change in joint restraint fixtures from that qualified (e.g., fixed anvil to self-reacting, and vice versa) or from single-sided to two-sided welding, and vice versa.

QW-410.74 A change in the welding control method from that qualified (e.g., force control method to position control method, or vice versa, in the plunge direction; and force control method to travel control method, or vice versa, in the travel direction).

QW-410.75 A change in the rotating tool
(a) type or design from the qualified "family" to another (i.e., threaded pin, smooth pin, fluted, self-reacting, retracting-pin, or other tool types)

(b) configuration or dimensions from that qualified beyond the following limits (as applicable):

(1) shoulder diameter greater than 10%

(2) shoulder scroll pitch greater than 10%

(3) shoulder profile (e.g., addition or deletion of shoulder feature)

(4) pin diameter greater than 5%

(5) pin length greater than the lesser of 5% of qualified pin length or 1% of base metal thickness (not minimum pin length for retracting-pin tools, and not applicable for self-reacting rotating tools)

(6) pin taper angle greater than 5 deg

(7) flute pitch greater than 5%

(8) pin tip geometry/shape

(9) thread pitch greater than 10% (as applicable)

(10) flat design resulting in a change of the total flat surface area greater than 20%

(11) number of flats

(12) cooling characteristics of the rotating pin (e.g., change from water-cooled to air-cooled, and vice versa)

(c) pin material specification, nominal chemical composition, and minimum hardness

QW-410.76 A change in the rotating tool operation from that qualified beyond the following limits (as applicable):

(a) decrease in rotation speed, or increase greater than 10%

(b) direction of rotation

(c) plunge force greater than 10% or plunge position set point greater than 5% when controlling the plunge direction (except during ramp-up and ramp-down when starting and stopping)

(d) angular tilt greater than 1 deg in any direction

(e) travel force or travel speed greater than 10% when controlling travel direction (except during ramp-up and ramp-down when starting and stopping)

(f) range of relative motion between tool components when using self-reacting or retractable-pin tools

(g) reduction in the smallest radius of travel path curvature that results in reversing the travel direction of the pin or the shoulder

(h) manner or angle of intersection, or number of coincident intersections, within the same weld or between the weld and the HAZ of other welds

QW-410.77 A change in the laser wavelength (e.g., CO₂, Nd:YAG, fiber, disk, diode) from that qualified.

QW-410.78 A change in the process sequence from that qualified.

QW-410.79 A change in the distance between the laser beam and the welding arc of more than 10%.

QW-410.80 A change of $\pm 5\%$ in the diameter of the focused spot size.

QW-410.81 A change in the alignment of the plasma torch and GMAW torch with respect to travel direction by more than 10 deg, or a change from a leading or lagging plasma or the addition/deletion of a leading or lagging plasma.

QW-410.82 A change in the distance between the plasma and the GMAW torches by more than 10%.

QW-410.83 A change in the height differential of the plasma contact tip to the GMAW contact tip by more than 10%.

QW-410.84 A change in the angle between the leading and/or trailing plasma and GMAW torches by more than 10 deg.

Table QW-416
Welding Variables
Welder Performance

			Essential						
			OFW QW-352	SMAW QW-353	SAW QW-354	GMAW [Note (2)] QW-355	GTAW QW-356	PAW QW-357	
Paragraph [Note (1)]	Brief of Variables								
QW-402 Joints	.4	– Backing		X		X	X	X	
	.7	+ Backing	X						
QW-403 Base Metal	.2	Maximum qualified	X						
	.16	ϕ Pipe diameter		X	X	X	X	X	
	.18	ϕ P-Number	X	X	X	X	X	X	
QW-404 Filler Metals	.14	\pm Filler	X				X	X	
	.15	ϕ F-Number	X	X	X	X	X	X	
	.22	\pm Inserts					X	X	
	.23	ϕ Filler metal product form					X	X	
	.30	ϕ t Weld deposit		X	X	X	X	X	
	.31	ϕ t Weld deposit	X						
	.32	t Limit (s. cir. arc)				X			
	QW-405 Positions	.1	+ Position	X	X	X	X	X	X
		.3	ϕ \updownarrow Vert. welding		X		X	X	X
QW-408 Gas	.7	ϕ Type fuel gas	X						
	.8	– Inert backing				X	X	X	
QW-409 Electrical	.2	ϕ Transfer mode				X			
	.4	ϕ Current or polarity					X		
Welding Processes:									
OFW		Oxyfuel gas welding							
SMAW		Shielded metal-arc welding							
SAW		Submerged-arc welding							
GMAW		Gas metal-arc welding							
GTAW		Gas tungsten-arc welding							
PAW		Plasma-arc welding							
Legend:									
ϕ Change		t Thickness							
+ Addition		\uparrow Uphill							
– Deletion		\downarrow Downhill							
NOTES:									
(1) For description, see Section IV.									
(2) Flux-cored arc welding as shown in QW-355, with or without additional shielding from an externally supplied gas or gas mixture, included.									

(13) QW-420 BASE METAL GROUPINGS

P-Numbers are assigned to base metals for the purpose of reducing the number of welding and brazing procedure qualifications required.

P-Numbers are alphanumeric designations: accordingly, each P-Number shall be considered a separate P-Number (e.g., base metals assigned P-No. 5A are considered a separate P-Number from those assigned P-No. 5B or P-No. 5C).

In addition, ferrous base metals have been assigned Group Numbers creating subsets of P-Numbers that are used when WPSs are required to be qualified by impact testing by other Sections or Codes. These assignments are based essentially on comparable base metal characteristics, such as composition, weldability, brazeability, and mechanical properties, where this can logically be done. These assignments do not imply that base metals may be indiscriminately substituted for a base metal that was used in the qualification test without consideration of compatibility from the standpoint of metallurgical properties, postweld heat treatment, design, mechanical properties, and service requirements. The following table shows the assignment groups for various alloy systems:

Base Metal	Welding	Brazing
Steel and steel alloys	P-No. 1 through P-No. 15F	P-No. 101 through P-No. 103
Aluminum and aluminum-base alloys	P-No. 21 through P-No. 26	P-No. 104 and P-No. 105
Copper and copper- base alloys	P-No. 31 through P-No. 35	P-No. 107 and P-No. 108
Nickel and nickel- base alloys	P-No. 41 through P-No. 49	P-No. 110 through P-No. 112
Titanium and titanium- base alloys	P-No. 51 through P-No. 53	P-No. 115
Zirconium and zirconium-base alloys	P-No. 61 and P-No. 62	P-No. 117

The values given in the column heading "Minimum Specified Tensile" of [Table QW/QB-422](#) are the acceptance values for the tensile tests of the welding or brazing procedure qualification, except as otherwise allowed in [QW-153](#) or [QB-153](#). Only base metals listed in [Table QW/QB-422](#) with minimum tensile strength values may be used for procedure qualification except as modified by the following paragraph.

If an unlisted base metal has the same UNS number designation as a base metal listed in [Table QW/QB-422](#), that base metal is also assigned that P-Number or P-Number plus Group Number. If the unlisted base metal is used

for procedure qualification, the minimum tensile value of the listed base metal shall apply for the tension test specimens.

Materials listed in [Table QW/QB-422](#) without a minimum specified tensile value shall not be used for the purpose of groove weld procedure qualification.

Material produced under an ASTM specification shall have the same P-Number or P-Number plus Group Number and minimum specified tensile strength value as that of the corresponding ASME specification listed in [Table QW/QB-422](#) with prefix A/SA- or B/SB- (e.g., listed under A/SA-240, SA-240 Type 304 is assigned P-No. 8, Group No. 1; and A240 Type 304 is also P-No. 8, Group No. 1).

The column "ISO/TR 15608 Group" in [Table QW/QB-422](#) is a listing of the assignments of materials in accordance with the grouping criteria of ISO/TR 15608:2005, *Welding — Guidelines for a metallic materials grouping system*, and it is consistent with the assignments found in ISO/TR 20173:2008, *Grouping systems for materials — American materials*. While this listing is provided as a convenience to users worldwide, it is provided for information only. Section IX does not refer to this grouping as a basis for establishing the range of base metals qualified for either procedure or performance qualification.

In 2009, S-Numbers were removed from [Table QW/QB-422](#). S-Numbers were assigned to materials that were acceptable for use by the ASME B31 Code for Pressure Piping, or by selected Boiler and Pressure Vessel Code Cases, but which were not included within ASME Boiler and Pressure Vessel Code Material Specifications (Section II). Base metals previously assigned S-Numbers were reassigned the corresponding P-Numbers or P-Numbers plus Group Numbers.

There are instances where materials assigned to one P- or S-Number or Group Number have been reassigned to a different P- or S-Number or Group Number in later editions. Procedure and performance qualifications that were qualified under the previous P- or S-Numbers or Group Number assignment may continue to be used under the new P-Number or Group Number assignment, see [QW-200.2\(c\)](#), provided the WPS is revised to limit the materials qualified for welding to those assigned to the new P- or S-number(s) and Group number(s) for the specific material(s) originally used for the procedure qualification test coupon. Other materials from the original P- or S-Number and Group Number must be reassigned to the same P- or S-Number or Group Number to be considered qualified for welding under the revised WPS.

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification

Spec. No.	Type or Grade	UNS No.	Minimum Specified Tensile, ksi (MPa)	Welding		Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	Group No.	P-No.			
Ferrous									
A/SA-36	...	K02600	58 (400)	1	1	101	11.1	C-Mn-Si	Plate, bar & shapes
A/SA-53	Type F	K03005	48 (330)	1	1	101	11.1	C	Furnace welded pipe
A/SA-53	Type S, Gr. A	K02504	48 (330)	1	1	101	1.1	C	Smls. pipe
A/SA-53	Type E, Gr. A	K02504	48 (330)	1	1	101	1.1	C	Resistance welded pipe
A/SA-53	Type E, Gr. B	K03005	60 (415)	1	1	101	11.1	C-Mn	Resistance welded pipe
A/SA-53	Type S, Gr. B	K03005	60 (415)	1	1	101	11.1	C-Mn	Smls. pipe
A/SA-105	...	K03504	70 (485)	1	2	101	11.1	C	Flanges & fittings
A/SA-106	A	K02501	48 (330)	1	1	101	1.1	C-Si	Smls. pipe
A/SA-106	B	K03006	60 (415)	1	1	101	11.1	C-Mn-Si	Smls. pipe
A/SA-106	C	K03501	70 (485)	1	2	101	11.1	C-Mn-Si	Smls. pipe
A108	1015 CW	G10150	...	1	1	101	1.1	C	Bar
A108	1018 CW	G10180	...	1	1	101	1.1	C	Bar
A108	1020 CW	G10200	...	1	1	101	1.1	C	Bar
A108	8620 CW	G86200	...	3	3	102	4.1	0.5Ni-0.5Cr-Mo	Bar
A/SA-134	SA283 Gr. A	K01400	45 (310)	1	1	101	1.1	C	Welded pipe
A/SA-134	SA283 Gr. B	K01702	50 (345)	1	1	101	1.1	C	Welded pipe
A/SA-134	SA283 Gr. C	K02401	55 (380)	1	1	101	1.1	C	Welded pipe
A/SA-134	SA283 Gr. D	K02702	60 (415)	1	1	101	11.1	C	Welded pipe
A/SA-134	SA285 Gr. A	K01700	45 (310)	1	1	101	1.1	C	Welded pipe
A/SA-134	SA285 Gr. B	K02200	50 (345)	1	1	101	1.1	C	Welded pipe
A/SA-134	SA285 Gr. C	K02801	55 (380)	1	1	101	11.1	C	Welded pipe
A/SA-135	A	K02509	48 (330)	1	1	101	1.1	C	E.R.W. pipe
A/SA-135	B	K03018	60 (415)	1	1	101	11.1	C	E.R.W. pipe
A139	A	K02508	48 (330)	1	1	101	1.1	C	Welded pipe
A139	B	K03003	60 (415)	1	1	101	11.1	C	Welded pipe
A139	C	K03004	60 (415)	1	1	101	11.1	C	Welded pipe
A139	D	K03010	60 (415)	1	1	101	11.1	C	Welded pipe
A139	E	K03012	66 (455)	1	1	101	11.1	C	Welded pipe
A167	Type 302B	S30215	75 (515)	8	1	102	8.1	18Cr-8Ni-2Si	Plate, sheet & strip
A167	Type 308	S30800	75 (515)	8	2	102	8.2	20Cr-10Ni	Plate, sheet & strip
A167	Type 309	S30900	75 (515)	8	2	102	8.2	23Cr-12Ni	Plate, sheet & strip

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	Type or Grade	UNS No.	Minimum Specified Tensile, ksi (MPa)	Welding		Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	Group No.	P-No.			
Ferrous (Cont'd)									
A167	Type 310	S31000	75 (515)	8	2	102	8.2	25Cr-20Ni	Plate, sheet & strip
A/SA-178	A	K01200	47 (325)	1	1	101	1.1	C	E.R.W. tube
A/SA-178	C	K03503	60 (415)	1	1	101	11.1	C	E.R.W. tube
A/SA-178	D	K02709	70 (485)	1	2	101	11.1	C-Mn-Si	E.R.W. tube
A/SA-179	...	K01200	47 (325)	1	1	101	1.1	C	Smls. tube
A/SA-181	Cl. 60	K03502	60 (415)	1	1	101	11.1	C-Si	Pipe flange & fittings
A/SA-181	Cl. 70	K03502	70 (485)	1	2	101	11.1	C-Si	Pipe flange & fittings
A/SA-182	F12, Cl. 1	K11562	60 (415)	4	1	102	5.1	1Cr-0.5Mo	Forgings
A/SA-182	F12, Cl. 2	K11564	70 (485)	4	1	102	5.1	1Cr-0.5Mo	Forgings
A/SA-182	F11, Cl. 2	K11572	70 (485)	4	1	102	5.1	1.25Cr-0.5Mo-Si	Forgings
A/SA-182	F11, Cl. 3	K11572	75 (515)	4	1	102	5.1	1.25Cr-0.5Mo-Si	Forgings
A/SA-182	F11, Cl. 1	K11597	60 (415)	4	1	102	5.1	1.25Cr-0.5Mo-Si	Forgings
A/SA-182	F2	K12122	70 (485)	3	2	101	4.2	0.5Cr-0.5Mo	Forgings
A/SA-182	F1	K12822	70 (485)	3	2	101	1.1	C-0.5Mo	Forgings
A/SA-182	F22, Cl. 1	K21590	60 (415)	5A	1	102	5.2	2.25Cr-1Mo	Forgings
A/SA-182	F22, Cl. 3	K21590	75 (515)	5A	1	102	5.2	2.25Cr-1Mo	Forgings
A/SA-182	FR	K22035	63 (435)	9A	1	101	9.1	2Ni-1Cu	Forgings
A/SA-182	F21	K31545	75 (515)	5A	1	102	5.2	3Cr-1Mo	Forgings
A/SA-182	F3V	K31830	85 (585)	5C	1	102	6.2	3Cr-1Mo-V-Ti-B	Forgings
A/SA-182	F3VCb	K31390	85 (585)	5C	1	102	6.2	3Cr-1Mo-0.25V-Cb-Ca	Forgings
A/SA-182	F22V	K31835	85 (585)	5C	1	102	6.2	2.25Cr-1Mo-V	Forgings
A/SA-182	F5	K41545	70 (485)	5B	1	102	5.3	5Cr-0.5Mo	Forgings
A/SA-182	F5a	K42544	90 (620)	5B	1	102	5.3	5Cr-0.5Mo	Forgings
A/SA-182	F9	K90941	85 (585)	5B	1	102	5.4	9Cr-1Mo	Forgings
A/SA-182	F91	K90901	85 (585)	15E	1	102	6.4	9Cr-1Mo-V	Forgings
A/SA-182	F92	K92460	90 (620)	15E	1	102	6.4	9Cr-2W	Forgings
A/SA-182	F904L	N08904	71 (490)	45	...	111	8.2	44Fe-25Ni-21Cr-Mo	Forgings
A/SA-182	F6a, Cl. 1	S41000	70 (485)	6	1	102	7.2	13Cr	Forgings
A/SA-182	F6a, Cl. 2	S41000	85 (585)	6	3	102	7.2	13Cr	Forgings
A/SA-182	FXM-19	S20910	100 (690)	8	3	102	8.3	22Cr-13Ni-5Mn	Forgings
A/SA-182	FXM-11	S21904	90 (620)	8	3	102	8.3	21Cr-6Ni-9Mn	Forgings
A/SA-182	F304	S30400	70 (485)	8	1	102	8.1	18Cr-8Ni	Forgings > 5 in. (127 mm)

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	Type or Grade	UNS No.	Minimum Specified Tensile, ksi (MPa)	Welding		Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	Group No.	P-No.			
Ferrous (Cont'd)									
A/SA-182	F304	S30400	75 (515)	8	1	102	8.1	18Cr-8Ni	Forgings
A/SA-182	F304L	S30403	65 (450)	8	1	102	8.1	18Cr-8Ni	Forgings > 5 in. (127 mm)
A/SA-182	F304L	S30403	70 (485)	8	1	102	8.1	18Cr-8Ni	Forgings
A/SA-182	F304H	S30409	70 (485)	8	1	102	8.1	18Cr-8Ni	Forgings > 5 in. (127 mm)
A/SA-182	F304H	S30409	75 (515)	8	1	102	8.1	18Cr-8Ni	Forgings
A/SA-182	F304N	S30451	80 (550)	8	1	102	8.1	18Cr-8Ni-N	Forgings
A/SA-182	F304LN	S30453	70 (485)	8	1	102	8.1	18Cr-8Ni-N	Forgings > 5 in. (127 mm)
A/SA-182	F304LN	S30453	75 (515)	8	1	102	8.1	18Cr-8Ni-N	Forgings
A/SA-182	F46	S30600	78 (540)	8	1	102	8.1	18Cr-15Ni-4Si	Forgings
A/SA-182	F45	S30815	87 (600)	8	2	102	8.2	21Cr-11Ni-N	Forgings
A/SA-182	F310	S31000	70 (485)	8	2	102	8.2	25Cr-20Ni	Forgings > 5 in. (127 mm)
A/SA-182	F310	S31000	75 (515)	8	2	102	8.2	25Cr-20Ni	Forgings
A/SA-182	F310MoLN	S31050	78 (540)	8	2	102	8.2	25Cr-22Ni-2Mo-N	Forgings
A/SA-182	F50	S31200	100 (690)	10H	1	102	10.2	25Cr-6Ni-Mo-N	Forgings
A/SA-182	F44	S31254	94 (650)	8	4	102	8.2	20Cr-18Ni-6Mo	Forgings
A/SA-182	F316	S31600	70 (485)	8	1	102	8.1	16Cr-12Ni-2Mo	Forgings > 5 in. (127 mm)
A/SA-182	F316	S31600	75 (515)	8	1	102	8.1	16Cr-12Ni-2Mo	Forgings
A/SA-182	F316L	S31603	65 (450)	8	1	102	8.1	16Cr-12Ni-2Mo	Forgings > 5 in. (127 mm)
A/SA-182	F316L	S31603	70 (485)	8	1	102	8.1	16Cr-12Ni-2Mo	Forgings
A/SA-182	F316H	S31609	70 (485)	8	1	102	8.1	16Cr-12Ni-2Mo	Forgings > 5 in. (127 mm)
A/SA-182	F316H	S31609	75 (515)	8	1	102	8.1	16Cr-12Ni-2Mo	Forgings
A/SA-182	F316N	S31651	80 (550)	8	1	102	8.1	16Cr-12Ni-2Mo-N	Forgings
A/SA-182	F316LN	S31653	70 (485)	8	1	102	8.1	16Cr-12Ni-2Mo-N	Forgings > 5 in. (127 mm)
A/SA-182	F316LN	S31653	75 (515)	8	1	102	8.1	16Cr-12Ni-2Mo-N	Forgings
A/SA-182	F317	S31700	70 (485)	8	1	102	8.1	18Cr-13Ni-3Mo	Forgings > 5 in. (127 mm)
A/SA-182	F317	S31700	75 (515)	8	1	102	8.1	18Cr-13Ni-3Mo	Forgings
A/SA-182	F317L	S31703	65 (450)	8	1	102	8.1	18Cr-13Ni-3Mo	Forgings > 5 in. (127 mm)
A/SA-182	F317L	S31703	70 (485)	8	1	102	8.1	18Cr-13Ni-3Mo	Forgings
A/SA-182	F51	S31803	90 (620)	10H	1	102	10.1	22Cr-5Ni-3Mo-N	Forgings
A/SA-182	...	S32053	93 (640)	8	4	102	8.2	23Cr-25Ni-5.5Mo-N	Forgings
A/SA-182	...	S32202	94 (650)	10H	1	102	10.1	22Cr-2Ni-Mo-N	Forgings
A/SA-182	F321	S32100	70 (485)	8	1	102	8.1	18Cr-10Ni-Ti	Forgings > 5 in. (127 mm)
A/SA-182	F321	S32100	75 (515)	8	1	102	8.1	18Cr-10Ni-Ti	Forgings

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	Type or Grade	UNS No.	Minimum Specified Tensile, ksi (MPa)	Welding		Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	Group No.	P-No.			
Ferrous (Cont'd)									
A/SA-182	F321H	S32109	70 (485)	8	1	102	8.1	18Cr-10Ni-Ti	Forgings > 5 in. (127 mm)
A/SA-182	F321H	S32109	75 (515)	8	1	102	8.1	18Cr-10Ni-Ti	Forgings
A/SA-182	F55	S32760	109 (750)	10H	1	102	10.1	25Cr-8Ni-3Mo-W-Cu-N	Forgings
A/SA-182	F10	S33100	80 (550)	8	2	102	8.1	20Ni-8Cr	Forgings
A/SA-182	F49	S34565	115 (795)	8	4	102	8.3	24Cr-17Ni-6Mn-4.5Mo-N	Forgings
A/SA-182	F347	S34700	70 (485)	8	1	102	8.1	18Cr-10Ni-Cb	Forgings > 5 in. (127 mm)
A/SA-182	F347	S34700	75 (515)	8	1	102	8.1	18Cr-10Ni-Cb	Forgings
A/SA-182	F347H	S34709	70 (485)	8	1	102	8.1	18Cr-10Ni-Cb	Forgings > 5 in. (127 mm)
A/SA-182	F347H	S34709	75 (515)	8	1	102	8.1	18Cr-10Ni-Cb	Forgings
A/SA-182	F348	S34800	70 (485)	8	1	102	8.1	18Cr-10Ni-Cb	Forgings > 5 in. (127 mm)
A/SA-182	F348	S34800	75 (515)	8	1	102	8.1	18Cr-10Ni-Cb	Forgings
A/SA-182	F348H	S34809	70 (485)	8	1	102	8.1	18Cr-10Ni-Cb	Forgings > 5 in. (127 mm)
A/SA-182	F348H	S34809	75 (515)	8	1	102	8.1	18Cr-10Ni-Cb	Forgings
A/SA-182	F6b	S41026	110 (760)	6	3	102	7.2	13Cr-0.5Mo	Forgings
A/SA-182	F6NM	S41500	115 (795)	6	4	102	7.2	13Cr-4.5Ni-Mo	Forgings
A/SA-182	F429	S42900	60 (415)	6	2	102	7.2	15Cr	Forgings
A/SA-182	F430	S43000	60 (415)	7	2	102	7.1	17Cr	Forgings
A/SA-182	FXM-27Cb	S44627	60 (415)	10I	1	102	7.1	27Cr-1Mo	Forgings
A/SA-182	F53	S32750	116 (800)	10H	1	102	10.2	25Cr-7Ni-4Mo-N	Forgings
A/SA-182	F54	S39274	116 (800)	10H	1	102	10.2	25Cr-7Ni-3Mo-2W-Cu-N	Forgings
A/SA-182	F60	S32205	95 (655)	10H	1	102	10.1	22Cr-5Ni-3Mo-N	Forgings
A/SA-182	F6a, Cl. 3	S41000	110 (760)	6	3	102	7.2	13Cr	Forgings
A/SA-182	F6a, Cl. 4	S41000	130 (895)	6	3	102	7.2	13Cr	Forgings
A/SA-192	...	K01201	47 (325)	1	1	101	1.1	C-Si	Smls. tube
A199	T11	K11597	60 (415)	4	1	102	5.1	1.25Cr-0.5Mo-Si	Smls. tube
A199	T22	K21590	60 (415)	5A	1	102	5.2	2.25Cr-1Mo	Smls. tube
A199	T21	K31545	60 (415)	5A	1	102	...	3Cr-1Mo	Smls. tube
A199	T5	K41545	60 (415)	5B	1	102	5.3	5Cr-0.5Mo	Smls. tube
A199	T9	K81590	60 (415)	5B	1	102	5.4	9Cr-1Mo	Smls. tube
A/SA-202	A	K11742	75 (515)	4	1	101	4.2	0.5Cr-1.25Mn-Si	Plate
A/SA-202	B	K12542	85 (585)	4	1	101	4.2	0.5Cr-1.25Mn-Si	Plate
A/SA-203	A	K21703	65 (450)	9A	1	101	9.1	2.5Ni	Plate
A/SA-203	B	K22103	70 (485)	9A	1	101	9.1	2.5Ni	Plate

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	Type or Grade	UNS No.	Minimum Specified Tensile, ksi (MPa)	Welding		Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	Group No.	P-No.			
Ferrous (Cont'd)									
A/SA-203	D	K31718	65 (450)	9B	1	101	9.2	3.5Ni	Plate
A/SA-203	E	K32018	70 (485)	9B	1	101	9.2	3.5Ni	Plate
A/SA-203	F	...	75 (515)	9B	1	101	9.2	3.5Ni	Plate > 2 in. (51 mm)
A/SA-203	F	...	80 (550)	9B	1	101	9.2	3.5Ni	Plate, 2 in. (51 mm) & under
A/SA-204	A	K11820	65 (450)	3	1	101	1.1	C-0.5Mo	Plate
A/SA-204	B	K12020	70 (485)	3	2	101	1.1	C-0.5Mo	Plate
A/SA-204	C	K12320	75 (515)	3	2	101	1.2	C-0.5Mo	Plate
A/SA-209	T1b	K11422	53 (365)	3	1	101	1.1	C-0.5Mo	Smls. tube
A/SA-209	T1	K11522	55 (380)	3	1	101	1.1	C-0.5Mo	Smls. tube
A/SA-209	T1a	K12023	60 (415)	3	1	101	1.1	C-0.5Mo	Smls. tube
A/SA-210	A-1	K02707	60 (415)	1	1	101	11.1	C-Si	Smls. tube
A/SA-210	C	K03501	70 (485)	1	2	101	11.1	C-Mn-Si	Smls. tube
A211	A570-30	K02502	49 (340)	1	1	101	1.1	C	Welded pipe
A211	A570-33	K02502	52 (360)	1	1	101	1.1	C	Welded pipe
A211	A570-40	K02502	55 (380)	1	1	101	1.1	C	Welded pipe
A/SA-213	T2	K11547	60 (415)	3	1	101	4.2	0.5Cr-0.5Mo	Smls. tube
A/SA-213	T12	K11562	60 (415)	4	1	102	5.1	1Cr-0.5Mo	Smls. tube
A/SA-213	T11	K11597	60 (415)	4	1	102	5.1	1.25Cr-0.5Mo-Si	Smls. tube
A/SA-213	T17	K12047	60 (415)	10B	1	102	4.1	1Cr-V	Smls. tube
A/SA-213	T22	K21590	60 (415)	5A	1	102	5.2	2.25Cr-1Mo	Smls. tube
A/SA-213	T21	K31545	60 (415)	5A	1	102	5.2	3Cr-1Mo	Smls. tube
A/SA-213	T5c	K41245	60 (415)	5B	1	102	5.3	5Cr-0.5Mo-Ti	Smls. tube
A/SA-213	T5	K41545	60 (415)	5B	1	102	5.3	5Cr-0.5Mo	Smls. tube
A/SA-213	T5b	K51545	60 (415)	5B	1	102	5.3	5Cr-0.5Mo-Si	Smls. tube
A/SA-213	T9	K90941	60 (415)	5B	1	102	5.4	9Cr-1Mo	Smls. tube
A/SA-213	T91	K90901	85 (585)	15E	1	102	6.4	9Cr-1Mo-V	Smls. tube
A/SA-213	T92	K92460	90 (620)	15E	1	102	6.4	9Cr-2W	Smls. tube
A/SA-213	TP201	S20100	95 (655)	8	3	102	8.3	17Cr-4Ni-6Mn	Smls. tube
A/SA-213	TP202	S20200	90 (620)	8	3	102	8.3	18Cr-5Ni-9Mn	Smls. tube
A/SA-213	XM-19	S20910	100 (690)	8	3	102	8.3	22Cr-13Ni-5Mn	Smls. tube
A/SA-213	TP304	S30400	75 (515)	8	1	102	8.1	18Cr-8Ni	Smls. tube
A/SA-213	TP304L	S30403	70 (485)	8	1	102	8.1	18Cr-8Ni	Smls. tube
A/SA-213	TP304H	S30409	75 (515)	8	1	102	8.1	18Cr-8Ni	Smls. tube

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	Type or Grade	UNS No.	Minimum Specified Tensile, ksi (MPa)	Welding		Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	Group No.	P-No.			
Ferrous (Cont'd)									
A/SA-213	TP304N	S30451	80 (550)	8	1	102	8.1	18Cr-8Ni-N	Smls. tube
A/SA-213	TP304LN	S30453	75 (515)	8	1	102	8.1	18Cr-8Ni-N	Smls. tube
A/SA-213	S30815	S30815	87 (600)	8	2	102	8.2	21Cr-11Ni-N	Smls. tube
A/SA-213	TP309S	S30908	75 (515)	8	2	102	8.2	23Cr-12Ni	Smls. tube
A/SA-213	TP309H	S30909	75 (515)	8	2	102	8.2	23Cr-12Ni	Smls. tube
A/SA-213	TP309Cb	S30940	75 (515)	8	2	102	8.2	23Cr-12Ni-Cb	Smls. tube
A/SA-213	TP309HCb	S30941	75 (515)	8	2	102	8.2	23Cr-12Ni-Cb	Smls. tube
A/SA-213	TP310S	S31008	75 (515)	8	2	102	8.2	25Cr-20Ni	Smls. tube
A/SA-213	TP310H	S31009	75 (515)	8	2	102	8.2	25Cr-20Ni	Smls. tube
A/SA-213	TP310Cb	S31040	75 (515)	8	2	102	8.2	25Cr-20Ni-Cb	Smls. tube
A/SA-213	TP310HCb	S31041	75 (515)	8	2	102	8.2	25Cr-20Ni-Cb	Smls. tube
A/SA-213	TP310HCbN	S31042	95 (655)	8	3	102	8.2	25Cr-20Ni-Cb-N	Smls. tube
A/SA-213	TP310MoLN	S31050	78 (540)	8	2	102	8.2	25Cr-22Ni-2Mo-N	Smls. tube, $t > \frac{1}{4}$ in. (6 mm)
A/SA-213	TP310MoLN	S31050	84 (580)	8	2	102	8.2	25Cr-22Ni-2Mo-N	Smls. tube, $t \leq \frac{1}{4}$ in. (6 mm)
A/SA-213	TP316	S31600	75 (515)	8	1	102	8.1	16Cr-12Ni-2Mo	Smls. tube
A/SA-213	TP316L	S31603	70 (485)	8	1	102	8.1	16Cr-12Ni-2Mo	Smls. tube
A/SA-213	TP316H	S31609	75 (515)	8	1	102	8.1	16Cr-12Ni-2Mo	Smls. tube
A/SA-213	TP316Ti	S31635	75 (515)	8	1	102	8.1	16Cr-12Ni-2Mo-Ti	Smls. tube
A/SA-213	TP316N	S31651	80 (550)	8	1	102	8.1	16Cr-12Ni-2Mo-N	Smls. tube
A/SA-213	TP316LN	S31653	75 (515)	8	1	102	8.1	16Cr-12Ni-2Mo-N	Smls. tube
A/SA-213	TP317	S31700	75 (515)	8	1	102	8.1	18Cr-13Ni-3Mo	Smls. tube
A/SA-213	TP317L	S31703	75 (515)	8	1	102	8.1	18Cr-13Ni-3Mo	Smls. tube
A/SA-213	TP317LM	S31725	75 (515)	8	4	102	8.1	19Cr-15Ni-4Mo	Smls. tube
A/SA-213	TP317LMN	S31726	80 (550)	8	4	102	8.1	19Cr-15.5Ni-4Mo	Smls. tube
A/SA-213	TP321	S32100	75 (515)	8	1	102	8.1	18Cr-10Ni-Ti	Smls. tube
A/SA-213	TP321H	S32109	75 (515)	8	1	102	8.1	18Cr-10Ni-Ti	Smls. tube
A/SA-213	S34565	S34565	115 (795)	8	4	102	8.3	24Cr-17Ni-6Mn-4.5Mo-N	Smls. tube
A/SA-213	TP347	S34700	75 (515)	8	1	102	8.1	18Cr-10Ni-Cb	Smls. tube
A/SA-213	TP347H	S34709	75 (515)	8	1	102	8.1	18Cr-10Ni-Cb	Smls. tube
A/SA-213	TP347HFG	S34710	80 (550)	8	1	102	8.1	18Cr-10Ni-Cb	Smls. tube
A/SA-213	TP347LN	S34751	75 (515)	8	1	102	8.1	18Cr-10Ni-Cb-N	Smls. tube
A/SA-213	TP348	S34800	75 (515)	8	1	102	8.1	18Cr-10Ni-Cb	Smls. tube
A/SA-213	TP348H	S34809	75 (515)	8	1	102	8.1	18Cr-10Ni-Cb	Smls. tube

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	Type or Grade	UNS No.	Minimum Specified Tensile, ksi (MPa)	Welding		Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	Group No.	P-No.			
Ferrous (Cont'd)									
A/SA-213	XM-15	S38100	75 (515)	8	1	102	8.1	18Cr-18Ni-2Si	Smls. tube
A/SA-213	S32615	S32615	80 (550)	8	1	102	8.1	18Cr-20Ni-5.5Si	Smls. tube
A/SA-214	...	K01807	47 (325)	1	1	101	1.1	C	E.R.W. tube
A/SA-216	WCA	J02502	60 (415)	1	1	101	1.1	C-Si	Castings
A/SA-216	WCC	J02503	70 (485)	1	2	101	1.1	C-Mn-Si	Castings
A/SA-216	WCB	J03002	70 (485)	1	2	101	1.1	C-Si	Castings
A/SA-217	WC6	J12072	70 (485)	4	1	102	5.1	1.25Cr-0.5Mo	Castings
A/SA-217	WC4	J12082	70 (485)	4	1	101	9.1	1Ni-0.5Cr-0.5Mo	Castings
A/SA-217	WC1	J12524	65 (450)	3	1	101	1.1	C-0.5Mo	Castings
A/SA-217	WC9	J21890	70 (485)	5A	1	102	5.2	2.25Cr-1Mo	Castings
A/SA-217	WC5	J22000	70 (485)	4	1	101	4.2	0.75Ni-1Mo-0.75Cr	Castings
A/SA-217	C5	J42045	90 (620)	5B	1	102	5.3	5Cr-0.5Mo	Castings
A/SA-217	C12	J82090	90 (620)	5B	1	102	5.4	9Cr-1Mo	Castings
A/SA-217	CA15	J91150	90 (620)	6	3	102	7.2	13Cr	Castings
A/SA-217	C12A	J84090	85 (585)	15E	1	102	6.4	9Cr-1Mo-V	Castings
A/SA-225	D	K12004	75 (515)	10A	1	101	2.1	Mn-0.5Ni-V	Plate > 3 in. (76 mm)
A/SA-225	D	K12004	80 (550)	10A	1	101	2.1	Mn-0.5Ni-V	Plate, 3 in. (76 mm) & under
A/SA-225	C	K12524	105 (725)	10A	1	101	4.1	Mn-0.5Ni-V	Plate
A/SA-234	WPB	K03006	60 (415)	1	1	101	11.1	C-Mn-Si	Piping fittings
A/SA-234	WPC	K03501	70 (485)	1	2	101	11.1	C-Mn-Si	Piping fittings
A/SA-234	WP11, Cl. 1	...	60 (415)	4	1	102	5.1	1.25Cr-0.5Mo-Si	Piping fittings
A/SA-234	WP12, Cl. 1	K12062	60 (415)	4	1	101	5.1	1Cr-0.5Mo	Piping fittings
A/SA-234	WP1	K12821	55 (380)	3	1	101	11.2	C-0.5Mo	Piping fittings
A/SA-234	WP22, Cl. 1	K21590	60 (415)	5A	1	102	5.2	2.25Cr-1Mo	Piping fittings
A/SA-234	WPR	K22035	63 (435)	9A	1	101	9.1	2Ni-1Cu	Piping fittings
A/SA-234	WP5, Cl. 1	K41545	60 (415)	5B	1	102	5.3	5Cr-0.5Mo	Piping fittings
A/SA-234	WP9, Cl. 1	K90941	60 (415)	5B	1	102	5.4	9Cr-1Mo	Piping fittings
A/SA-234	WP91	K90901	85 (585)	15E	1	102	6.4	9Cr-1Mo-V	Piping fittings
A/SA-234	WP11, Cl.3	...	75 (515)	4	1	102	5.1	1.25Cr-0.5Mo-Si	Piping fittings
A/SA-234	WP12, Cl.2	K12062	70 (485)	4	1	101	5.1	1Cr-0.5Mo	Piping fittings
A/SA-234	WP22, Cl.3	K21590	75 (515)	5A	1	102	5.2	2.25Cr-1Mo	Piping fittings
A/SA-234	WP5, Cl.3	K41545	75 (515)	5B	1	102	5.3	5Cr-0.5Mo	Piping fittings

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	Type or Grade	UNS No.	Minimum Specified Tensile, ksi (MPa)	Welding		Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	Group No.	P-No.			
Ferrous (Cont'd)									
A/SA-234	WP9, CL3	K90941	75 (515)	5B	1	102	5.4	9Cr-1Mo	Piping fittings
A/SA-240	...	N08367	95 (655)	45	...	111	8.2	46Fe-24Ni-21Cr-6Mo-Cu-N	Plate ≥ 0.1875 in. (5 mm)
A/SA-240	...	N08367	100 (690)	45	...	111	8.2	46Fe-24Ni-21Cr-6Mo-Cu-N	Sheet & strip < 0.1875 in. (5 mm)
A/SA-240	Type 904L	N08904	71 (490)	45	...	111	8.2	44Fe-25Ni-21Cr-Mo	Plate, sheet & strip
A/SA-240	Type 201-1	S20100	75 (515)	8	3	102	8.3	17Cr-4Ni-6Mn	Plate, sheet & strip
A/SA-240	Type 201-2	S20100	95 (655)	8	3	102	8.3	17Cr-4Ni-6Mn	Plate, sheet & strip
A/SA-240	Type 201LN	S20153	95 (655)	8	3	...	8.3	16Cr-4Ni-6Mn	Plate, sheet & strip
A/SA-240	Type 202	S20200	90 (620)	8	3	102	8.3	18Cr-5Ni-9Mn	Plate, sheet & strip
A/SA-240	...	S20400	95 (655)	8	3	102	8.3	16Cr-9Mn-2Ni-N	Plate, sheet & strip
A/SA-240	Type XM-19	S20910	100 (690)	8	3	102	8.3	22Cr-13Ni-5Mn	Plate
A/SA-240	Type XM-19	S20910	105 (725)	8	3	102	8.3	22Cr-13Ni-5Mn	Sheet & strip
A/SA-240	Type XM-17	S21600	90 (620)	8	3	102	8.3	19Cr-8Mn-6Ni-Mo-N	Plate
A/SA-240	Type XM-17	S21600	100 (690)	8	3	102	8.3	19Cr-8Mn-6Ni-Mo-N	Sheet & strip
A/SA-240	Type XM-18	S21603	90 (620)	8	3	102	8.3	19Cr-8Mn-6Ni-Mo-N	Plate
A/SA-240	Type XM-18	S21603	100 (690)	8	3	102	8.3	19Cr-8Mn-6Ni-Mo-N	Sheet & strip
A/SA-240	S21800	S21800	95 (655)	8	3	102	8.1	18Cr-8Ni-4Si-N	Plate, sheet & strip
A/SA-240	Type XM-29	S24000	100 (690)	8	3	102	8.3	18Cr-3Ni-12Mn	Plate, sheet & strip
A/SA-240	Type 301	S30100	75 (515)	8	1	102	8.1	17Cr-7Ni	Plate, sheet & strip
A/SA-240	Type 302	S30200	75 (515)	8	1	102	8.1	18Cr-8Ni	Plate, sheet & strip
A/SA-240	Type 304	S30400	75 (515)	8	1	102	8.1	18Cr-8Ni	Plate, sheet & strip
A/SA-240	Type 304L	S30403	70 (485)	8	1	102	8.1	18Cr-8Ni	Plate, sheet & strip
A/SA-240	Type 304H	S30409	75 (515)	8	1	102	8.1	18Cr-8Ni	Plate, sheet & strip
A/SA-240	Type 304N	S30451	80 (550)	8	1	102	8.1	18Cr-8Ni-N	Plate, sheet & strip
A/SA-240	Type XM-21	S30452	85 (585)	8	1	102	8.1	18Cr-8Ni-N	Plate
A/SA-240	Type XM-21	S30452	90 (620)	8	1	102	8.1	18Cr-8Ni-N	Sheet & strip
A/SA-240	Type 304LN	S30453	75 (515)	8	1	102	8.1	18Cr-8Ni-N	Plate, sheet & strip
A/SA-240	Type 305	S30500	70 (485)	8	1	102	8.1	18Cr-11Ni	Plate, sheet & strip
A/SA-240	S30600	S30600	78 (540)	8	1	102	8.1	18Cr-15Ni-4Si	Plate, sheet & strip
A/SA-240	S30601	S30601	78 (540)	8	1	102	8.1	17.5Cr-17.5Ni-5.3Si	Plate, sheet & strip
A/SA-240	S30815	S30815	87 (600)	8	2	102	8.2	21Cr-11Ni-N	Plate, sheet & strip
A/SA-240	S32615	S32615	80 (550)	8	1	102	8.1	18Cr-20Ni-5.5Si	Plate, sheet & strip
A/SA-240	Type 309S	S30908	75 (515)	8	2	102	8.2	23Cr-12Ni	Plate, sheet & strip
A/SA-240	Type 309H	S30909	75 (515)	8	2	102	8.2	23Cr-12Ni	Plate, sheet & strip

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	Type or Grade	UNS No.	Minimum Specified Tensile, ksi (MPa)	Welding		Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	Group No.	P-No.			
Ferrous (Cont'd)									
A/SA-240	Type 309Cb	S30940	75 (515)	8	2	102	8.2	23Cr-12Ni-Cb	Plate, sheet & strip
A/SA-240	Type 309HCb	S30941	75 (515)	8	2	102	8.2	23Cr-12Ni-Cb	Plate, sheet & strip
A/SA-240	Type 310S	S31008	75 (515)	8	2	102	8.2	25Cr-20Ni	Plate, sheet & strip
A/SA-240	Type 310H	S31009	75 (515)	8	2	102	8.2	25Cr-20Ni	Plate, sheet & strip
A/SA-240	Type 310Cb	S31040	75 (515)	8	2	102	8.2	25Cr-20Ni-Cb	Plate, sheet & strip
A/SA-240	Type 310HCb	S31041	75 (515)	8	2	102	8.2	25Cr-20Ni-Cb	Plate, sheet & strip
A/SA-240	TP310MoLN	S31050	78 (540)	8	2	102	8.2	25Cr-22Ni-2Mo-N	Plate, sheet & strip, $t > \frac{1}{4}$ in. (6 mm)
A/SA-240	TP310MoLN	S31050	84 (580)	8	2	102	8.2	25Cr-22Ni-2Mo-N	Plate, sheet & strip, $t \leq \frac{1}{4}$ in. (6 mm)
A/SA-240	S31200	S31200	100 (690)	10H	1	102	10.2	25Cr-6Ni-Mo-N	Plate, sheet & strip
A/SA-240	S31254	S31254	95 (655)	8	4	102	8.2	20Cr-18Ni-6Mo	Plate
A/SA-240	S31254	S31254	100 (690)	8	4	102	8.2	20Cr-18Ni-6Mo	Sheet & strip
A/SA-240	S31260	S31260	100 (690)	10H	1	102	10.2	25Cr-6.5Ni-3Mo-N	Plate, sheet & strip
A/SA-240	S31277	S31277	112 (770)	45	...	111	8.2	27Ni-22Cr-7Mo-Mn-Cu	Plate, sheet & strip
A/SA-240	Type 316	S31600	75 (515)	8	1	102	8.1	16Cr-12Ni-2Mo	Plate, sheet & strip
A/SA-240	Type 316L	S31603	70 (485)	8	1	102	8.1	16Cr-12Ni-2Mo	Plate, sheet & strip
A/SA-240	Type 316H	S31609	75 (515)	8	1	102	8.1	16Cr-12Ni-2Mo	Plate, sheet & strip
A/SA-240	Type 316Ti	S31635	75 (515)	8	1	102	8.1	16Cr-12Ni-2Mo-Ti	Plate, sheet & strip
A/SA-240	Type 316Cb	S31640	75 (515)	8	1	102	8.1	16Cr-12Ni-2Mo-Cb	Plate, sheet & strip
A/SA-240	Type 316N	S31651	80 (550)	8	1	102	8.1	16Cr-12Ni-2Mo-N	Plate, sheet & strip
A/SA-240	Type 316LN	S31653	75 (515)	8	1	102	8.1	16Cr-12Ni-2Mo-N	Plate, sheet & strip
A/SA-240	Type 317	S31700	75 (515)	8	1	102	8.1	18Cr-13Ni-3Mo	Plate, sheet & strip
A/SA-240	Type 317L	S31703	75 (515)	8	1	102	8.1	18Cr-13Ni-3Mo	Plate, sheet & strip
A/SA-240	S31725	S31725	75 (515)	8	4	102	8.1	19Cr-15Ni-4Mo	Plate, sheet & strip
A/SA-240	S31726	S31726	80 (550)	8	4	102	8.1	19Cr-15.5Ni-4Mo	Plate, sheet & strip
A/SA-240	S31753	S31753	80 (550)	8	1	102	8.1	18Cr-13Ni-3Mo-N	Plate, sheet & strip
A/SA-240	S31803	S31803	90 (620)	10H	1	102	10.1	22Cr-5Ni-3Mo-N	Plate, sheet & strip
A/SA-240	...	S32003	90 (620)	10H	1	102	10.1	21Cr-3.5Ni-Mo-N	Plate, sheet & strip
A/SA-240	...	S32053	93 (640)	8	4	102	8.2	23Cr-25Ni-5.5Mo-N	Plate, sheet & strip
A/SA-240	...	S32202	94 (650)	10H	1	102	10.1	22Cr-2Ni-Mo-N	Plate, sheet & strip
A/SA-240	Type 321	S32100	75 (515)	8	1	102	8.1	18Cr-10Ni-Ti	Plate, sheet & strip
A/SA-240	...	S32101	95 (655)	10H	1	102	10.1	21Cr-5Mn-1.5Ni-Cu-N	Plate, sheet & strip > 0.25 in. (6 mm)
A/SA-240	...	S32101	101 (700)	10H	1	102	10.1	21Cr-5Mn-1.5Ni-Cu-N	Plate, sheet & strip ≤ 0.25 in. (6 mm)
A/SA-240	Type 321H	S32109	75 (515)	8	1	102	8.1	18Cr-10Ni-Ti	Plate, sheet & strip
A/SA-240	2205	S32205	95 (655)	10H	1	102	10.1	22Cr-5Ni-3Mo-N	Plate, sheet & strip

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	Type or Grade	UNS No.	Minimum Specified Tensile, ksi (MPa)	Welding		Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	Group No.	P-No.			
Ferrous (Cont'd)									
A/SA-240	S32550	S32550	110 (760)	10H	1	102	10.2	25Cr-5Ni-3Mo-2Cu	Plate, sheet & strip
A/SA-240	S32750	S32750	116 (800)	10H	1	102	10.2	25Cr-7Ni-4Mo-N	Plate, sheet & strip
A/SA-240	S32760	S32760	108 (745)	10H	1	102	10.2	25Cr-8Ni-3Mo-W-Cu-N	Plate, sheet & strip
A/SA-240	Type 329	S32900	90 (620)	10H	1	102	10.2	26Cr-4Ni-Mo	Plate, sheet & strip
A/SA-240	S32906	S32906	109 (750)	10H	1	102	10.2	29Cr-6.5Ni-2Mo-N	Plate, sheet & strip ≥ 0.40 in. (10 mm)
A/SA-240	S32906	S32906	116 (800)	10H	1	102	10.2	29Cr-6.5Ni-2Mo-N	Plate, sheet & strip < 0.40 in. (10 mm)
A/SA-240	S32950	S32950	100 (690)	10H	1	102	10.2	26Cr-4Ni-Mo-N	Plate, sheet & strip
A/SA-240	S34565	S34565	115 (795)	8	4	102	8.3	24Cr-17Ni-6Mn-4.5Mo-N	Plate, sheet & strip
A/SA-240	Type 347	S34700	75 (515)	8	1	102	8.1	18Cr-10Ni-Cb	Plate, sheet & strip
A/SA-240	Type 347H	S34709	75 (515)	8	1	102	8.1	18Cr-10Ni-Cb	Plate, sheet & strip
A/SA-240	Type 348	S34800	75 (515)	8	1	102	8.1	18Cr-10Ni-Cb	Plate, sheet & strip
A/SA-240	Type 348H	S34809	75 (515)	8	1	102	8.1	18Cr-10Ni-Cb	Plate, sheet & strip
A/SA-240	Type XM-15	S38100	75 (515)	8	1	102	8.1	18Cr-18Ni-2Si	Plate, sheet & strip
A/SA-240	Type 405	S40500	60 (415)	7	1	102	7.1	12Cr-1Al	Plate, sheet & strip
A/SA-240	Type 409	S40910	55 (380)	7	1	102	7.1	11Cr-Ti	Plate, sheet & strip
A/SA-240	Type 409	S40920	55 (380)	7	1	102	7.1	11Cr-Ti	Plate, sheet & strip
A/SA-240	Type 409	S40930	55 (380)	7	1	102	7.1	11Cr-Ti	Plate, sheet & strip
A/SA-240	Type 410	S41000	65 (450)	6	1	102	7.2	13Cr	Plate, sheet & strip
A/SA-240	Type 410S	S41008	60 (415)	7	1	102	7.2	13Cr	Plate, sheet & strip
A/SA-240	S41500	S41500	115 (795)	6	4	102	7.2	13Cr-4.5Ni-Mo	Plate, sheet & strip
A/SA-240	Type 429	S42900	65 (450)	6	2	102	7.2	15Cr	Plate, sheet & strip
A/SA-240	Type 430	S43000	65 (450)	7	2	102	7.1	17Cr	Plate, sheet & strip
A/SA-240	Type 439	S43035	60 (415)	7	2	102	7.1	18Cr-Ti	Plate, sheet & strip
A/SA-240	S44400	S44400	60 (415)	7	2	102	7.1	18Cr-2Mo	Plate, sheet & strip
A/SA-240	Type XM-33	S44626	68 (470)	10I	1	102	7.1	27Cr-1Mo-Ti	Plate, sheet & strip
A/SA-240	Type XM-27	S44627	65 (450)	10I	1	102	7.1	27Cr-1Mo	Plate, sheet & strip
A/SA-240	S43932	S43932	60 (415)	7	2	102	...	18Cr-Ti-Cb	Plate, sheet & strip
A/SA-240	S44635	S44635	90 (620)	10I	1	102	7.1	25Cr-4Ni-4Mo-Ti	Plate, sheet & strip
A/SA-240	S44660	S44660	85 (585)	10K	1	102	7.1	26Cr-3Ni-3Mo	Plate, sheet & strip
A/SA-240	S44700	S44700	80 (550)	10J	1	102	7.1	29Cr-4Mo	Plate, sheet & strip
A/SA-240	S44800	S44800	80 (550)	10K	1	102	7.1	29Cr-4Mo-2Ni	Plate, sheet & strip
A/SA-249	...	N08367	95 (655)	45	...	111	8.2	46Fe-24Ni-21Cr-6Mo-Cu-N	Welded tube > 0.1875 in. (5 mm)
A/SA-249	...	N08367	100 (690)	45	...	111	8.2	46Fe-24Ni-21Cr-6Mo-Cu-N	Welded tube ≤ 0.1875 in. (5 mm)

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	Type or Grade	UNS No.	Minimum Specified Tensile, ksi (MPa)	Welding		Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	Group No.	P-No.			
Ferrous (Cont'd)									
A/SA-249	...	N08904	71 (490)	45	...	111	8.2	44Fe-25Ni-21Cr-Mo	Welded tube
A/SA-249	TP201	S20100	95 (655)	8	3	102	8.3	17Cr-4Ni-6Mn	Welded tube
A/SA-249	TP202	S20200	90 (620)	8	3	102	8.3	18Cr-5Ni-9Mn	Welded tube
A/SA-249	TPXM-19	S20910	100 (690)	8	3	102	8.3	22Cr-13Ni-5Mn	Welded tube
A/SA-249	TPXM-29	S24000	100 (690)	8	3	102	8.3	18Cr-3Ni-12Mn	Welded tube
A/SA-249	TP304	S30400	75 (515)	8	1	102	8.1	18Cr-8Ni	Welded tube
A/SA-249	TP304L	S30403	70 (485)	8	1	102	8.1	18Cr-8Ni	Welded tube
A/SA-249	TP304H	S30409	75 (515)	8	1	102	8.1	18Cr-8Ni	Welded tube
A/SA-249	TP304N	S30451	80 (550)	8	1	102	8.1	18Cr-8Ni-N	Welded tube
A/SA-249	TP304LN	S30453	75 (515)	8	1	102	8.1	18Cr-8Ni-N	Welded tube
A/SA-249	S30815	S30815	87 (600)	8	2	102	8.2	21Cr-11Ni-N	Welded tube
A/SA-249	TP309S	S30908	75 (515)	8	2	102	8.2	23Cr-12Ni	Welded tube
A/SA-249	TP309H	S30909	75 (515)	8	2	102	8.2	23Cr-12Ni	Welded tube
A/SA-249	TP309Cb	S30940	75 (515)	8	2	102	8.2	23Cr-12Ni-Cb	Welded tube
A/SA-249	TP309HCb	S30941	75 (515)	8	2	102	8.2	23Cr-12Ni-Cb	Welded tube
A/SA-249	TP310S	S31008	75 (515)	8	2	102	8.2	25Cr-20Ni	Welded tube
A/SA-249	TP310H	S31009	75 (515)	8	2	102	8.2	25Cr-20Ni	Welded tube
A/SA-249	TP310Cb	S31040	75 (515)	8	2	102	8.2	25Cr-20Ni-Cb	Welded tube
A/SA-249	TP310HCb	S31041	75 (515)	8	2	102	8.2	25Cr-20Ni-Cb	Welded tube
A/SA-249	TP310MoLN	S31050	78 (540)	8	2	102	8.2	25Cr-22Ni-2Mo-N	Welded tube, $t > \frac{1}{4}$ in. (6 mm)
A/SA-249	TP310MoLN	S31050	84 (580)	8	2	102	8.2	25Cr-22Ni-2Mo-N	Welded tube, $t \leq \frac{1}{4}$ in. (6 mm)
A/SA-249	S31254	S31254	95 (655)	8	4	102	8.2	20Cr-18Ni-6Mo	Welded tube, $t > \frac{3}{16}$ in. (5 mm)
A/SA-249	S31254	S31254	98 (675)	8	4	102	8.2	20Cr-18Ni-6Mo	Welded tube, $t \leq \frac{3}{16}$ in. (5 mm)
A/SA-249	TP316	S31600	75 (515)	8	1	102	8.1	16Cr-12Ni-2Mo	Welded tube
A/SA-249	TP316L	S31603	70 (485)	8	1	102	8.1	16Cr-12Ni-2Mo	Welded tube
A/SA-249	TP316H	S31609	75 (515)	8	1	102	8.1	16Cr-12Ni-2Mo	Welded tube
A/SA-249	TP316N	S31651	80 (550)	8	1	102	8.1	16Cr-12Ni-2Mo-N	Welded tube
A/SA-249	TP316LN	S31653	75 (515)	8	1	102	8.1	16Cr-12Ni-2Mo-N	Welded tube
A/SA-249	TP317	S31700	75 (515)	8	1	102	8.1	18Cr-13Ni-3Mo	Welded tube
A/SA-249	TP317L	S31703	75 (515)	8	1	102	8.1	18Cr-13Ni-3Mo	Welded tube
A/SA-249	S31725	S31725	75 (515)	8	4	102	8.1	19Cr-15Ni-4Mo	Welded tube
A/SA-249	S31726	S31726	80 (550)	8	4	102	8.1	19Cr-15.5Ni-4Mo	Welded tube
A/SA-249	...	S32053	93 (640)	8	4	102	8.2	23Cr-25Ni-5.5Mo-N	Welded tube

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	Type or Grade	UNS No.	Minimum Specified Tensile, ksi (MPa)	Welding		Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	Group No.	P-No.			
Ferrous (Cont'd)									
A/SA-249	TP321	S32100	75 (515)	8	1	102	8.1	18Cr-10Ni-Ti	Welded tube
A/SA-249	TP321H	S32109	75 (515)	8	1	102	8.1	18Cr-10Ni-Ti	Welded tube
A/SA-249	TP347	S34700	75 (515)	8	1	102	8.1	18Cr-10Ni-Cb	Welded tube
A/SA-249	TP347H	S34709	75 (515)	8	1	102	8.1	18Cr-10Ni-Cb	Welded tube
A/SA-249	TP348	S34800	75 (515)	8	1	102	8.1	18Cr-10Ni-Cb	Welded tube
A/SA-249	TP348H	S34809	75 (515)	8	1	102	8.1	18Cr-10Ni-Cb	Welded tube
A/SA-249	TPXM-15	S38100	75 (515)	8	1	102	8.1	18Cr-18Ni-2Si	Welded tube
A/SA-250	T1b	K11422	53 (365)	3	1	101	1.1	C-0.5Mo	E.R.W. tube
A/SA-250	T1	K11522	55 (380)	3	1	101	1.1	C-0.5Mo	E.R.W. tube
A/SA-250	T2	K11547	60 (415)	3	1	101	4.2	0.5Cr-0.5Mo	E.R.W. tube
A/SA-250	T11	K11597	60 (415)	4	1	102	5.1	1.25Cr-0.5Mo-Si	E.R.W. tube
A/SA-250	T1a	K12023	60 (415)	3	1	101	1.1	C-0.5Mo	E.R.W. tube
A/SA-250	T12	K11562	60 (415)	4	1	102	5.1	1Cr-0.5Mo	E.R.W. tube
A/SA-250	T22	K21590	60 (415)	5A	1	102	5.2	2.25Cr-1Mo	E.R.W. tube
A254	Cl.1	K01001	42 (290)	101	NA	C	Cu brazed tube
A254	Cl.2	K01001	42 (290)	101	NA	C	Cu brazed tube
A/SA-266	4	K03017	70 (485)	1	2	101	11.1	C-Mn-Si	Forgings
A/SA-266	1	K03506	60 (415)	1	1	101	11.1	C-Si	Forgings
A/SA-266	2	K03506	70 (485)	1	2	101	11.1	C-Si	Forgings
A/SA-266	3	K05001	75 (515)	1	2	101	11.2	C-Si	Forgings
A/SA-268	TP405	S40500	60 (415)	7	1	102	7.1	12Cr-1Al	Smls. & welded tube
A/SA-268	S40800	S40800	55 (380)	7	1	102	7.1	12Cr-Ti	Smls. & welded tube
A/SA-268	TP409	S40900	55 (380)	7	1	102	7.1	11Cr-Ti	Smls. & welded tube
A/SA-268	TP410	S41000	60 (415)	6	1	102	7.2	13Cr	Smls. & welded tube
A/SA-268	S41500	S41500	115 (795)	6	4	102	7.2	13Cr-4.5Ni-Mo	Smls. & welded tube
A/SA-268	TP429	S42900	60 (415)	6	2	102	7.2	15Cr	Smls. & welded tube
A/SA-268	TP430	S43000	60 (415)	7	2	102	7.1	17Cr	Smls. & welded tube
A/SA-268	TP439	S43035	60 (415)	7	2	102	7.1	18Cr-Ti	Smls. & welded tube
A/SA-268	TP430Ti	S43036	60 (415)	7	2	102	7.1	18Cr-Ti	Smls. & welded tube
A/SA-268	18Cr-2Mo	S44400	60 (415)	7	2	102	7.1	18Cr-2Mo	Smls. & welded tube
A/SA-268	TP446-2	S44600	65 (450)	101	1	102	7.1	27Cr	Smls. & welded tube
A/SA-268	TP446-1	S44600	70 (485)	101	1	102	7.1	27Cr	Smls. & welded tube
A/SA-268	TPXM-33	S44626	68 (470)	101	1	102	7.1	27Cr-1Mo-Ti	Smls. & welded tube

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	Type or Grade	UNS No.	Minimum Specified Tensile, ksi (MPa)	Welding		Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	Group No.	P-No.			
Ferrous (Cont'd)									
A/SA-268	TPXM-27	S44627	65 (450)	10I	1	102	7.1	27Cr-1Mo	Smls. & welded tube
A/SA-268	25-4-4	S44635	90 (620)	10I	1	102	7.1	25Cr-4Ni-4Mo-Ti	Smls. & welded tube
A/SA-268	26-3-3	S44660	85 (585)	10K	1	102	7.1	26Cr-3Ni-3Mo	Smls. & welded tube
A/SA-268	29-4	S44700	80 (550)	10J	1	102	7.1	29Cr-4Mo	Smls. & welded tube
A/SA-268	S44735	S44735	75 (515)	10J	1	102	7.1	29Cr-4Mo-Ti	Smls. & welded tube
A/SA-268	29-4-2	S44800	80 (550)	10K	1	102	7.1	29Cr-4Mo-2Ni	Smls. & welded tube
A269	TP316	S31600	...	8	1	102	8.1	16Cr-12Ni-2Mo	Smls. & welded tube
A269	TP316L	S31603	...	8	1	102	8.1	16Cr-12Ni-2Mo	Smls. & welded tube
A269	TP304	S30400	...	8	1	102	8.1	18Cr-8Ni	Smls. & welded tube
A269	TP304L	S30403	...	8	1	102	8.1	18Cr-8Ni	Smls. & welded tube
A/SA-276	TP304	S30400	75 (515)	8	1	102	8.1	18Cr-8Ni	Bar
A/SA-276	TP304L	S30403	70 (485)	8	1	102	8.1	18Cr-8Ni	Bar
A/SA-276	TP316	S31600	75 (515)	8	1	102	8.1	16Cr-12Ni-2Mo	Bar
A/SA-276	TP316L	S31603	70 (485)	8	1	102	8.1	16Cr-12Ni-2Mo	Bar
A/SA-276	S32205	S32205	95 (655)	10H	1	102	10.1	22Cr-5Ni-3Mo-N	Bar
A/SA-276	TP410	S41000	70 (485)	6	1	102	7.2	13Cr	Bar
A/SA-283	A	K01400	45 (310)	1	1	101	1.1	C	Plate
A/SA-283	B	K01702	50 (345)	1	1	101	1.1	C	Plate
A/SA-283	C	K02401	55 (380)	1	1	101	1.1	C	Plate
A/SA-283	D	K02702	60 (415)	1	1	101	1.1	C	Plate
A/SA-285	A	K01700	45 (310)	1	1	101	1.1	C	Plate
A/SA-285	B	K02200	50 (345)	1	1	101	1.1	C	Plate
A/SA-285	C	K02801	55 (380)	1	1	101	11.1	C	Plate
A/SA-299	A	K02803	75 (515)	1	2	101	11.1	C-Mn-Si	Plate
A/SA-299	B	K02803	80 (550)	1	3	101	11.1	C-Mn-Si	Plate
A/SA-302	A	K12021	75 (515)	3	2	101	1.1	Mn-0.5Mo	Plate
A/SA-302	B	K12022	80 (550)	3	3	101	1.2	Mn-0.5Mo	Plate
A/SA-302	C	K12039	80 (550)	3	3	101	...	Mn-0.5Mo-0.5Ni	Plate
A/SA-302	D	K12054	80 (550)	3	3	101	...	Mn-0.5Mo-0.75Ni	Plate
A/SA-312	N08367	N08367	95 (655)	45	...	111	8.2	46Fe-24Ni-21Cr-6Mo-Cu-N	Smls. & welded pipe > 0.1875 in. (5 mm)
A/SA-312	N08367	N08367	100 (690)	45	...	111	8.2	46Fe-24Ni-21Cr-6Mo-Cu-N	Smls. & welded pipe ≤ 0.1875 in. (5 mm)

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	Type or Grade	UNS No.	Minimum Specified Tensile, ksi (MPa)	Welding		Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	Group No.	P-No.			
Ferrous (Cont'd)									
A/SA-312	...	N08904	71 (490)	45	...	111	8.2	44Fe-25Ni-21Cr-Mo	Smls. & welded pipe
A/SA-312	TPXM-19	S20910	100 (690)	8	3	102	8.3	22Cr-13Ni-5Mn	Smls. & welded pipe
A/SA-312	TPXM-11	S21904	90 (620)	8	3	102	8.3	21Cr-6Ni-9Mn	Smls. & welded pipe
A/SA-312	TPXM-29	S24000	100 (690)	8	3	102	8.3	18Cr-3Ni-12Mn	Smls. & welded pipe
A/SA-312	TP304	S30400	75 (515)	8	1	102	8.1	18Cr-8Ni	Smls. & welded pipe
A/SA-312	TP304L	S30403	70 (485)	8	1	102	8.1	18Cr-8Ni	Smls. & welded pipe
A/SA-312	TP304H	S30409	75 (515)	8	1	102	8.1	18Cr-8Ni	Smls. & welded pipe
A/SA-312	TP304N	S30451	80 (550)	8	1	102	8.1	18Cr-8Ni-N	Smls. & welded pipe
A/SA-312	TP304LN	S30453	75 (515)	8	1	102	8.1	18Cr-8Ni-N	Smls. & welded pipe
A/SA-312	S30600	S30600	78 (540)	8	1	102	8.1	18Cr-15Ni-4Si	Smls. & welded pipe
A/SA-312	S30815	S30815	87 (600)	8	2	102	8.2	21Cr-11Ni-N	Smls. & welded pipe
A/SA-312	S32615	S32615	80 (550)	8	1	102	8.1	18Cr-20Ni-5.5Si	Smls. & welded pipe
A/SA-312	TP309S	S30908	75 (515)	8	2	102	8.2	23Cr-12Ni	Smls. & welded pipe
A/SA-312	TP309H	S30909	75 (515)	8	2	102	8.2	23Cr-12Ni	Smls. & welded pipe
A/SA-312	TP309Cb	S30940	75 (515)	8	2	102	8.2	23Cr-12Ni-Cb	Smls. & welded pipe
A/SA-312	TP309Hcb	S30941	75 (515)	8	2	102	8.2	23Cr-12Ni-Cb	Smls. & welded pipe
A/SA-312	TP310S	S31008	75 (515)	8	2	102	8.2	25Cr-20Ni	Smls. & welded pipe
A/SA-312	TP310H	S31009	75 (515)	8	2	102	8.2	25Cr-20Ni	Smls. & welded pipe
A/SA-312	TP310Cb	S31040	75 (515)	8	2	102	8.2	25Cr-20Ni-Cb	Smls. & welded pipe
A/SA-312	TP310Hcb	S31041	75 (515)	8	2	102	8.2	25Cr-20Ni-Cb	Smls. & welded pipe
A/SA-312	TP310MoLN	S31050	78 (540)	8	2	102	8.2	25Cr-22Ni-2Mo-N	Smls. & welded pipe, $t > \frac{1}{4}$ in. (6 mm)
A/SA-312	TP310MoLN	S31050	84 (580)	8	2	102	8.2	25Cr-22Ni-2Mo-N	Smls. & welded pipe, $t \leq \frac{1}{4}$ in. (6 mm)
A/SA-312	S31254	S31254	95 (655)	8	4	102	8.2	20Cr-18Ni-6Mo	Smls. & welded pipe, $t > \frac{3}{16}$ in. (5 mm)
A/SA-312	S31254	S31254	98 (675)	8	4	102	8.2	20Cr-18Ni-6Mo	Smls. & welded pipe, $t \leq \frac{3}{16}$ in. (5 mm)
A/SA-312	TP316	S31600	75 (515)	8	1	102	8.1	16Cr-12Ni-2Mo	Smls. & welded pipe
A/SA-312	TP316L	S31603	70 (485)	8	1	102	8.1	16Cr-12Ni-2Mo	Smls. & welded pipe
A/SA-312	TP316H	S31609	75 (515)	8	1	102	8.1	16Cr-12Ni-2Mo	Smls. & welded pipe
A/SA-312	TP316Ti	S31635	75 (515)	8	1	102	8.1	16Cr-12Ni-2Mo-Ti	Smls. & welded pipe
A/SA-312	TP316N	S31651	80 (550)	8	1	102	8.1	16Cr-12Ni-2Mo-N	Smls. & welded pipe
A/SA-312	TP316LN	S31653	75 (515)	8	1	102	8.1	16Cr-12Ni-2Mo-N	Smls. & welded pipe
A/SA-312	TP317	S31700	75 (515)	8	1	102	8.1	18Cr-13Ni-3Mo	Smls. & welded pipe
A/SA-312	TP317L	S31703	75 (515)	8	1	102	8.1	18Cr-13Ni-3Mo	Smls. & welded pipe
A/SA-312	S31725	S31725	75 (515)	8	4	102	8.1	19Cr-15Ni-4Mo	Smls. & welded pipe

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	Type or Grade	UNS No.	Minimum Specified Tensile, ksi (MPa)	Welding		Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	Group No.	P-No.			
Ferrous (Cont'd)									
A/SA-312	S31726	S31726	80 (550)	8	4	102	8.1	19Cr-15.5Ni-4Mo	Smls. & welded pipe
A/SA-312	...	S32053	93 (640)	8	4	102	8.2	23Cr-25Ni-5.5Mo-N	Smls. & welded pipe
A/SA-312	TP321	S32100	70 (485)	8	1	102	8.1	18Cr-10Ni-Ti	Smls. pipe > 3⁄8 in. (10 mm)
A/SA-312	TP321	S32100	75 (515)	8	1	102	8.1	18Cr-10Ni-Ti	Smls. pipe ≤ 3⁄8 in. (10 mm)
A/SA-312	TP321	S32100	75 (515)	8	1	102	8.1	18Cr-10Ni-Ti	Welded pipe
A/SA-312	TP321H	S32109	70 (485)	8	1	102	8.1	18Cr-10Ni-Ti	Smls. pipe > 3⁄8 in. (10 mm)
A/SA-312	TP321H	S32109	75 (515)	8	1	102	8.1	18Cr-10Ni-Ti	Smls. pipe ≤ 3⁄8 in. (10 mm)
A/SA-312	TP321H	S32109	75 (515)	8	1	102	8.1	18Cr-10Ni-Ti	Welded pipe
A/SA-312	S34565	S34565	115 (795)	8	4	102	8.3	24Cr-17Ni-6Mn-4.5Mo-N	Smls. & welded pipe
A/SA-312	TP347	S34700	75 (515)	8	1	102	8.1	18Cr-10Ni-Cb	Smls. & welded pipe
A/SA-312	TP347H	S34709	75 (515)	8	1	102	8.1	18Cr-10Ni-Cb	Smls. & welded pipe
A/SA-312	TP347LN	S34751	75 (515)	8	1	102	8.1	18Cr-10Ni-Cb-N	Smls. & welded pipe
A/SA-312	TP348	S34800	75 (515)	8	1	102	8.1	18Cr-10Ni-Cb	Smls. & welded pipe
A/SA-312	TP348H	S34809	75 (515)	8	1	102	8.1	18Cr-10Ni-Cb	Smls. & welded pipe
A/SA-312	TPXM-15	S38100	75 (515)	8	1	102	8.1	18Cr-18Ni-2Si	Smls. & welded pipe
A/SA-333	6	K03006	60 (415)	1	1	101	11.1	C-Mn-Si	Smls. & welded pipe
A/SA-333	1	K03008	55 (380)	1	1	101	11.1	C-Mn	Smls. & welded pipe
A/SA-333	10	...	80 (550)	1	3	101	11.1	C-Mn-Si	Smls. & welded pipe
A/SA-333	4	K11267	60 (415)	4	2	102	4.1	0.75Cr-0.75Ni-Cu-Al	Smls. & welded pipe
A/SA-333	7	K21903	65 (450)	9A	1	101	9.1	2.5Ni	Smls. & welded pipe
A/SA-333	9	K22035	63 (435)	9A	1	101	9.1	2Ni-1Cu	Smls. & welded pipe
A/SA-333	3	K31918	65 (450)	9B	1	101	9.2	3.5Ni	Smls. & welded pipe
A/SA-333	8	K81340	100 (690)	11A	1	101	9.3	9Ni	Smls. & welded pipe
A/SA-334	6	K03006	60 (415)	1	1	101	11.1	C-Mn-Si	Welded tube
A/SA-334	1	K03008	55 (380)	1	1	101	11.1	C-Mn	Welded tube
A/SA-334	7	K21903	65 (450)	9A	1	101	9.1	2.5Ni	Welded tube
A/SA-334	9	K22035	63 (435)	9A	1	101	9.1	2Ni-1Cu	Welded tube
A/SA-334	3	K31918	65 (450)	9B	1	101	9.2	3.5Ni	Welded tube
A/SA-334	8	K81340	100 (690)	11A	1	101	9.3	9Ni	Welded tube
A/SA-335	P1	K11522	55 (380)	3	1	101	1.1	C-0.5Mo	Smls. pipe
A/SA-335	P2	K11547	55 (380)	3	1	101	4.2	0.5Cr-0.5Mo	Smls. pipe
A/SA-335	P12	K11562	60 (415)	4	1	102	5.1	1Cr-0.5Mo	Smls. pipe
A/SA-335	P15	K11578	60 (415)	3	1	101	...	1.5Si-0.5Mo	Smls. pipe

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	Type or Grade	UNS No.	Minimum Specified Tensile, ksi (MPa)	Welding		Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	Group No.	P-No.			
Ferrous (Cont'd)									
A/SA-335	P11	K11597	60 (415)	4	1	102	5.1	1.25Cr-0.5Mo-Si	Smls. pipe
A/SA-335	P22	K21590	60 (415)	5A	1	102	5.2	2.25Cr-1Mo	Smls. pipe
A/SA-335	P21	K31545	60 (415)	5A	1	102	5.2	3Cr-1Mo	Smls. pipe
A/SA-335	P5c	K41245	60 (415)	5B	1	102	5.3	5Cr-0.5Mo-Ti	Smls. pipe
A/SA-335	P5	K41545	60 (415)	5B	1	102	5.3	5Cr-0.5Mo	Smls. pipe
A/SA-335	P5b	K51545	60 (415)	5B	1	102	5.3	5Cr-0.5Mo-Si	Smls. pipe
A/SA-335	P9	K90941	60 (415)	5B	1	102	5.4	9Cr-1Mo	Smls. pipe
A/SA-335	P91	K90901	85 (585)	15E	1	102	6.4	9Cr-1Mo-V	Smls. pipe
A/SA-335	P92	K92460	90 (620)	15E	1	102	6.4	9Cr-2W	Smls. pipe
A/SA-336	F3VCb	K31390	85 (585)	5C	1	102	6.2	3Cr-1Mo-0.25V-Cb-Ca	Forgings
A/SA-336	F6	S41000	85 (585)	6	3	102	7.2	13Cr	Forgings
A/SA-336	F12	K11564	70 (485)	4	1	102	5.1	1Cr-0.5Mo	Forgings
A/SA-336	F11, Cl. 1	K11597	60 (415)	4	1	102	5.1	1.25Cr-0.5Mo-Si	Forgings
A/SA-336	F11, Cl. 2	K11572	70 (485)	4	1	102	5.1	1.25Cr-0.5Mo-Si	Forgings
A/SA-336	F11, Cl. 3	K11572	75 (515)	4	1	102	5.1	1.25Cr-0.5Mo-Si	Forgings
A/SA-336	F1	K12520	70 (485)	3	2	101	1.1	C-0.5Mo	Forgings
A/SA-336	F22, Cl. 1	K21590	60 (415)	5A	1	102	5.2	2.25Cr-1Mo	Forgings
A/SA-336	F22, Cl. 3	K21590	75 (515)	5A	1	102	5.2	2.25Cr-1Mo	Forgings
A/SA-336	F21, Cl. 1	K31545	60 (415)	5A	1	102	5.2	3Cr-1Mo	Forgings
A/SA-336	F21, Cl. 3	K31545	75 (515)	5A	1	102	5.2	3Cr-1Mo	Forgings
A/SA-336	F3V	K31830	85 (585)	5C	1	102	6.2	3Cr-1Mo-V-Ti-B	Forgings
A/SA-336	F22V	K31835	85 (585)	5C	1	102	6.2	2.25Cr-1Mo-V	Forgings
A/SA-336	F5	K41545	60 (415)	5B	1	102	5.3	5Cr-0.5Mo	Forgings
A/SA-336	F5A	K42544	80 (550)	5B	1	102	5.3	5Cr-0.5Mo	Forgings
A/SA-336	F9	K90941	85 (585)	5B	1	102	5.4	9Cr-1Mo	Forgings
A/SA-336	F91	K90901	85 (585)	15E	1	102	6.4	9Cr-1Mo-V	Forgings
A/SA-350	LF1	K03009	60 (415)	1	1	101	11.1	C-Mn-Si	Forgings
A/SA-350	LF2	K03011	70 (485)	1	2	101	11.1	C-Mn-Si	Forgings
A/SA-350	LF6, Cl. 2	K12202	75 (515)	1	3	101	4.1	C-Mn-Si-V	Forgings
A/SA-350	LF5, Cl. 1	K13050	60 (415)	9A	1	101	9.1	1.5Ni	Forgings
A/SA-350	LF5, Cl. 2	K13050	70 (485)	9A	1	101	9.1	1.5Ni	Forgings
A/SA-350	LF9	K22036	63 (435)	9A	1	101	9.1	2Ni-1Cu	Forgings
A/SA-350	LF3	K32025	70 (485)	9B	1	101	9.2	3.5Ni	Forgings

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	Type or Grade	UNS No.	Minimum Specified Tensile, ksi (MPa)	Welding		Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	Group No.	P-No.			
Ferrous (Cont'd)									
A/SA-351	CF3	J92500	70 (485)	8	1	102	8.1	18Cr-8Ni	Castings
A/SA-351	CF3A	J92500	77 (530)	8	1	102	8.1	18Cr-8Ni	Castings
A/SA-351	CF8	J92600	70 (485)	8	1	102	8.1	18Cr-8Ni	Castings
A/SA-351	CF8A	J92600	77 (530)	8	1	102	8.1	18Cr-8Ni	Castings
A/SA-351	CF8C	J92710	70 (485)	8	1	102	8.1	18Cr-10Ni-Cb	Castings
A/SA-351	CF3M	J92800	70 (485)	8	1	102	8.1	18Cr-12Ni-2Mo	Castings
A/SA-351	CF8M	J92900	70 (485)	8	1	102	8.1	18Cr-12Ni-2Mo	Castings
A/SA-351	CF10	J92590	70 (485)	8	1	102	8.1	19Cr-9Ni-0.5Mo	Castings
A/SA-351	CF10M	J92901	70 (485)	8	1	102	8.1	19Cr-9Ni-2Mo	Castings
A/SA-351	CG8M	J93000	75 (515)	8	1	102	8.1	19Cr-10Ni-3Mo	Castings
A/SA-351	CK3MCuN	J93254	80 (550)	8	4	102	8.2	20Cr-18Ni-6Mo	Castings
A/SA-351	CD3MWCuN	J93380	100 (690)	10H	1	102	10.2	25Cr-8Ni-3Mo-W-Cu-N	Castings
A/SA-351	CH8	J93400	65 (450)	8	2	102	8.2	25Cr-12Ni	Castings
A/SA-351	CH20	J93402	70 (485)	8	2	102	8.2	25Cr-12Ni	Castings
A/SA-351	CG6MMN	J93790	85 (585)	8	3	102	8.3	22Cr-12Ni-5Mn	Castings
A/SA-351	CK20	J94202	65 (450)	8	2	102	8.2	25Cr-20Ni	Castings
A/SA-351	CN7M	N08007	62 (425)	45	...	111	8.2	28Ni-19Cr-Cu-Mo	Castings
A/SA-351	CT15C	N08151	63 (435)	45	...	111	45	32Ni-45Fe-20Cr-Cb	Castings
A/SA-351	CN3MN	J94651	80 (550)	45	...	111	8.2	46Fe-24Ni-21Cr-6Mo-Cu-N	Castings
A/SA-351	CE20N	J92802	80 (550)	8	2	102	8.2	25Cr-8Ni-N	Castings
A/SA-351	CF10MC	J92971	70 (485)	8	1	102	8.1	16Cr-14Ni-2Mo	Castings
A/SA-351	CH10	J93401	70 (485)	8	2	102	8.2	25Cr-12Ni	Castings
A/SA-351	HK30	J94203	65 (450)	8	2	102	8.2	25Cr-20Ni-0.5Mo	Castings
A/SA-351	HK40	J94204	62 (425)	8	2	102	8.2	25Cr-20Ni-0.5Mo	Castings
A/SA-351	HT30	N08603	65 (450)	45	...	111	45	35Ni-15Cr-0.5Mo	Castings
A/SA-352	LCA	J02504	60 (415)	1	1	101	11.1	C-Si	Castings
A/SA-352	LCC	J02505	70 (485)	1	2	101	11.1	C-Mn-Si	Castings
A/SA-352	LCB	J03003	65 (450)	1	1	101	1.1	C-Si	Castings
A/SA-352	LC1	J12522	65 (450)	3	1	101	1.1	C-0.5Mo	Castings
A/SA-352	LC2	J22500	70 (485)	9A	1	101	9.1	2.5Ni	Castings
A/SA-352	LC3	J31550	70 (485)	9B	1	101	9.3	3.5Ni	Castings
A/SA-352	LC4	J41500	70 (485)	9C	1	101	9.3	4.5Ni	Castings

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	Type or Grade	UNS No.	Minimum Specified Tensile, ksi (MPa)	Welding		Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	Group No.	P-No.			
Ferrous (Cont'd)									
A/SA-352	LC2-1	J42215	105 (725)	11A	5	102	9.2	3Ni-1.5Cr-0.5Mo	Castings
A/SA-352	CA6NM	J91540	110 (760)	6	4	102	7.2	13Cr-4Ni	Castings
A/SA-353	...	K81340	100 (690)	11A	1	101	9.3	9Ni	Plate
A356	1	J03502	70 (485)	1	2	101	11.1	C-Si	Castings
A356	2	J12523	65 (450)	3	1	101	...	C-0.5Mo	Castings
A356	6	J12073	70 (485)	4	1	102	5.1	1.25Cr-0.5Mo	Castings
A356	8	J11697	80 (550)	4	1	102	...	1Cr-1Mo-V	Castings
A356	9	J21610	85 (585)	4	1	102	...	1Cr-1Mo-V	Castings
A356	10	J22090	85 (585)	5A	1	102	5.2	2.25Cr-1Mo	Castings
A356	12A	J84090	85 (585)	15E	1	102	6.4	9Cr-1Mo-V	Castings
A/SA-358	N08367	N08367	95 (655)	45	...	111	8.2	46Fe-24Ni-21Cr-6Mo-Cu-N	Fusion welded pipe > 0.1875 in. (5 mm)
A/SA-358	N08367	N08367	100 (690)	45	...	111	8.2	46Fe-24Ni-21Cr-6Mo-Cu-N	Fusion welded pipe ≤ 0.1875 in. (5 mm)
A/SA-358	XM-19	S20910	100 (690)	8	3	102	8.3	22Cr-13Ni-5Mn	Fusion welded pipe
A/SA-358	XM-29	S24000	100 (690)	8	3	102	8.3	18Cr-3Ni-12Mn	Fusion welded pipe
A/SA-358	304	S30400	75 (515)	8	1	102	8.1	18Cr-8Ni	Fusion welded pipe
A/SA-358	304L	S30403	70 (485)	8	1	102	8.1	18Cr-8Ni	Fusion welded pipe
A/SA-358	304H	S30409	75 (515)	8	1	102	8.1	18Cr-8Ni	Fusion welded pipe
A/SA-358	304N	S30451	80 (550)	8	1	102	8.1	18Cr-8Ni-N	Fusion welded pipe
A/SA-358	304LN	S30453	75 (515)	8	1	102	8.1	18Cr-8Ni-N	Fusion welded pipe
A/SA-358	S30815	S30815	87 (600)	8	2	102	8.2	21Cr-11Ni-N	Fusion welded pipe
A/SA-358	309S	S30908	75 (515)	8	2	102	8.2	23Cr-12Ni	Fusion welded pipe
A/SA-358	309Cb	S30940	75 (515)	8	2	102	8.2	23Cr-12Ni-Cb	Fusion welded pipe
A/SA-358	310S	S31008	75 (515)	8	2	102	8.2	25Cr-20Ni	Fusion welded pipe
A/SA-358	310Cb	S31040	75 (515)	8	2	102	8.2	25Cr-20Ni-Cb	Fusion welded pipe
A/SA-358	S31254	S31254	94 (650)	8	4	102	8.2	20Cr-18Ni-6Mo	Fusion welded pipe
A/SA-358	316	S31600	75 (515)	8	1	102	8.1	16Cr-12Ni-2Mo	Fusion welded pipe
A/SA-358	316L	S31603	70 (485)	8	1	102	8.1	16Cr-12Ni-2Mo	Fusion welded pipe
A/SA-358	316H	S31609	75 (515)	8	1	102	8.1	16Cr-12Ni-2Mo	Fusion welded pipe
A/SA-358	316N	S31651	80 (550)	8	1	102	8.1	16Cr-12Ni-2Mo-N	Fusion welded pipe
A/SA-358	316LN	S31653	75 (515)	8	1	102	8.1	16Cr-12Ni-2Mo-N	Fusion welded pipe
A/SA-358	S31725	S31725	75 (515)	8	4	102	8.1	19Cr-15Ni-4Mo	Fusion welded pipe

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	Type or Grade	UNS No.	Minimum Specified Tensile, ksi (MPa)	Welding		Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	Group No.	P-No.			
Ferrous (Cont'd)									
A/SA-358	S31726	S31726	80 (550)	8	4	102	8.1	19Cr-15.5Ni-4Mo	Fusion welded pipe
A/SA-358	...	S32053	93 (640)	8	4	102	8.2	23Cr-25Ni-5.5Mo-N	Fusion welded pipe
A/SA-358	321	S32100	75 (515)	8	1	102	8.1	18Cr-10Ni-Ti	Fusion welded pipe
A/SA-358	347	S34700	75 (515)	8	1	102	8.1	18Cr-10Ni-Cb	Fusion welded pipe
A/SA-358	348	S34800	75 (515)	8	1	102	8.1	18Cr-10Ni-Cb	Fusion welded pipe
A/SA-369	FPA	K02501	48 (330)	1	1	101	1.1	C-Si	Forged pipe
A/SA-369	FPB	K03006	60 (415)	1	1	101	1.1	C-Mn-Si	Forged pipe
A/SA-369	FP1	K11522	55 (380)	3	1	101	1.1	C-0.5Mo	Forged pipe
A/SA-369	FP2	K11547	55 (380)	3	1	101	4.2	0.5Cr-0.5Mo	Forged pipe
A/SA-369	FP12	K11562	60 (415)	4	1	102	5.1	1Cr-0.5Mo	Forged pipe
A/SA-369	FP11	K11597	60 (415)	4	1	102	5.1	1.25Cr-0.5Mo-Si	Forged pipe
A/SA-369	FP22	K21590	60 (415)	5A	1	102	5.2	2.25Cr-1Mo	Forged pipe
A/SA-369	FP21	K31545	60 (415)	5A	1	102	5.2	3Cr-1Mo	Forged pipe
A/SA-369	FP5	K41545	60 (415)	5B	1	102	5.3	5Cr-0.5Mo	Forged pipe
A/SA-369	FP9	K90941	60 (415)	5B	1	102	5.4	9Cr-1Mo	Forged pipe
A/SA-369	FP91	K90901	85 (585)	15E	1	102	6.4	9Cr-1Mo-V	Forged pipe
A/SA-369	FP92	K92460	90 (620)	15E	1	102	6.4	9Cr-2W	Forged pipe
A/SA-372	A	K03002	60 (415)	1	1	101	11.1	C-Si	Forgings
A/SA-372	B	K04001	75 (515)	1	2	101	11.1	C-Mn-Si	Forgings
A/SA-376	16-8-2H	S16800	75 (515)	8	1	102	8.1	16Cr-8Ni-2Mo	Smls. pipe
A/SA-376	TP304	S30400	70 (485)	8	1	102	8.1	18Cr-8Ni	Smls. pipe ≥ 0.812 in. (21 mm)
A/SA-376	TP304	S30400	75 (515)	8	1	102	8.1	18Cr-8Ni	Smls. pipe < 0.812 in. (21 mm)
A/SA-376	TP304H	S30409	75 (515)	8	1	102	8.1	18Cr-8Ni	Smls. pipe
A/SA-376	TP304N	S30451	80 (550)	8	1	102	8.1	18Cr-8Ni-N	Smls. pipe
A/SA-376	TP304LN	S30453	75 (515)	8	1	102	8.1	18Cr-8Ni-N	Smls. pipe
A/SA-376	TP316	S31600	75 (515)	8	1	102	8.1	16Cr-12Ni-2Mo	Smls. pipe
A/SA-376	TP316H	S31609	75 (515)	8	1	102	8.1	16Cr-12Ni-2Mo	Smls. pipe
A/SA-376	TP316N	S31651	80 (550)	8	1	102	8.1	16Cr-12Ni-2Mo-N	Smls. pipe
A/SA-376	TP316LN	S31653	75 (515)	8	1	102	8.1	16Cr-12Ni-2Mo-N	Smls. pipe
A/SA-376	S31725	S31725	75 (515)	8	4	102	8.1	19Cr-15Ni-4Mo	Smls. pipe
A/SA-376	S31726	S31726	80 (550)	8	4	102	8.1	19Cr-15.5Ni-4Mo	Smls. pipe
A/SA-376	TP321	S32100	70 (485)	8	1	102	8.1	18Cr-10Ni-Ti	Smls. pipe > 3⁄8 in. (10 mm)
A/SA-376	TP321	S32100	75 (515)	8	1	102	8.1	18Cr-10Ni-Ti	Smls. pipe ≤ 3⁄8 in. (10 mm)

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	Type or Grade	UNS No.	Minimum Specified Tensile, ksi (MPa)	Welding		Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	Group No.	P-No.			
Ferrous (Cont'd)									
A/SA-376	TP321H	S32109	70 (485)	8	1	102	8.1	18Cr-10Ni-Ti	Smls. pipe > 3/8 in. (10 mm)
A/SA-376	TP321H	S32109	75 (515)	8	1	102	8.1	18Cr-10Ni-Ti	Smls. pipe ≤ 3/8 in. (10 mm)
A/SA-376	S34565	S34565	115 (795)	8	4	102	8.3	24Cr-17Ni-6Mn-4.5Mo-N	Smls. pipe
A/SA-376	TP347	S34700	75 (515)	8	1	102	8.1	18Cr-10Ni-Cb	Smls. pipe
A/SA-376	TP347H	S34709	75 (515)	8	1	102	8.1	18Cr-10Ni-Cb	Smls. pipe
A/SA-376	TP348	S34800	75 (515)	8	1	102	8.1	18Cr-10Ni-Cb	Smls. pipe
A381	Y35	...	60 (415)	1	1	101	11.1	C	Welded pipe
A381	Y42	...	60 (415)	1	1	101	11.1	C	Welded pipe
A381	Y48	...	62 (425)	1	1	101	11.1	C	Welded pipe
A381	Y46	...	63 (435)	1	1	101	11.1	C	Welded pipe
A381	Y50	...	64 (440)	1	1	101	11.1	C	Welded pipe
A381	Y52	...	66 (455)	1	2	101	11.1	C	Welded pipe
A381	Y56	...	71 (490)	1	2	101	11.1	C	Welded pipe
A381	Y60	...	75 (515)	1	2	101	11.1	C	Welded pipe
A/SA-387	12, Cl. 1	K11757	55 (380)	4	1	102	5.1	1Cr-0.5Mo	Plate
A/SA-387	12, Cl. 2	K11757	65 (450)	4	1	102	5.1	1Cr-0.5Mo	Plate
A/SA-387	11, Cl. 1	K11789	60 (415)	4	1	102	5.1	1.25Cr-0.5Mo-Si	Plate
A/SA-387	11, Cl. 2	K11789	75 (515)	4	1	102	5.1	1.25Cr-0.5Mo-Si	Plate
A/SA-387	2, Cl. 1	K12143	55 (380)	3	1	101	4.2	0.5Cr-0.5Mo	Plate
A/SA-387	2, Cl. 2	K12143	70 (485)	3	2	101	4.2	0.5Cr-0.5Mo	Plate
A/SA-387	22, Cl. 1	K21590	60 (415)	5A	1	102	5.2	2.25Cr-1Mo	Plate
A/SA-387	22, Cl. 2	K21590	75 (515)	5A	1	102	5.2	2.25Cr-1Mo	Plate
A/SA-387	21, Cl. 1	K31545	60 (415)	5A	1	102	5.2	3Cr-1Mo	Plate
A/SA-387	21, Cl. 2	K31545	75 (515)	5A	1	102	5.2	3Cr-1Mo	Plate
A/SA-387	5, Cl. 1	K41545	60 (415)	5B	1	102	5.3	5Cr-0.5Mo	Plate
A/SA-387	5, Cl. 2	K41545	75 (515)	5B	1	102	5.3	5Cr-0.5Mo	Plate
A/SA-387	9, Cl. 1	K90941	60 (415)	5B	1	102	5.4	9Cr-1Mo	Plate
A/SA-387	9, Cl. 2	K90941	75 (515)	5B	1	102	5.4	9Cr-1Mo	Plate
A/SA-387	91, Cl. 2	K90901	85 (585)	15E	1	102	6.4	9Cr-1Mo-V	Plate
A/SA-403	WPXM-19	S20910	100 (690)	8	3	102	8.3	22Cr-13Ni-5Mn	Wrought piping fittings
A/SA-403	WP304	S30400	75 (515)	8	1	102	8.1	18Cr-8Ni	Wrought piping fittings
A/SA-403	WP304L	S30403	70 (485)	8	1	102	8.1	18Cr-8Ni	Wrought piping fittings
A/SA-403	WP304H	S30409	75 (515)	8	1	102	8.1	18Cr-8Ni	Wrought piping fittings

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	Type or Grade	UNS No.	Minimum Specified Tensile, ksi (MPa)	Welding		Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	Group No.	P-No.			
Ferrous (Cont'd)									
A/SA-403	WP304N	S30451	80 (550)	8	1	102	8.1	18Cr-8Ni-N	Wrought piping fittings
A/SA-403	WP304LN	S30453	75 (515)	8	1	102	8.1	18Cr-8Ni-N	Wrought piping fittings
A/SA-403	WP309	S30900	75 (515)	8	2	102	8.2	23Cr-12Ni	Wrought piping fittings
A/SA-403	WP310S	S31008	75 (515)	8	2	102	8.2	25Cr-20Ni	Wrought piping fittings
A/SA-403	WP316	S31600	75 (515)	8	1	102	8.1	16Cr-12Ni-2Mo	Wrought piping fittings
A/SA-403	WP316L	S31603	70 (485)	8	1	102	8.1	16Cr-12Ni-2Mo	Wrought piping fittings
A/SA-403	...	S31254	94 (650)	8	4	102	8.2	20Cr-18Ni-6Mo	Wrought piping fittings
A/SA-403	WP316H	S31609	75 (515)	8	1	102	8.1	16Cr-12Ni-2Mo	Wrought piping fittings
A/SA-403	WP316N	S31651	80 (550)	8	1	102	8.1	16Cr-12Ni-2Mo-N	Wrought piping fittings
A/SA-403	WP316LN	S31653	75 (515)	8	1	102	8.1	16Cr-12Ni-2Mo-N	Wrought piping fittings
A/SA-403	WP317	S31700	75 (515)	8	1	102	8.1	18Cr-13Ni-3Mo	Wrought piping fittings
A/SA-403	WP317L	S31703	75 (515)	8	1	102	8.1	18Cr-13Ni-3Mo	Wrought piping fittings
A/SA-403	...	S32053	93 (640)	8	4	102	8.2	23Cr-25Ni-5.5Mo-N	Wrought piping fittings
A/SA-403	WP321	S32100	75 (515)	8	1	102	8.1	18Cr-10Ni-Ti	Wrought piping fittings
A/SA-403	WP321H	S32109	75 (515)	8	1	102	8.1	18Cr-10Ni-Ti	Wrought piping fittings
A/SA-403	S34565	S34565	115 (795)	8	4	102	8.3	24Cr-17Ni-6Mn-4.5Mo-N	Wrought piping fittings
A/SA-403	WP347	S34700	75 (515)	8	1	102	8.1	18Cr-10Ni-Cb	Wrought piping fittings
A/SA-403	WP347H	S34709	75 (515)	8	1	102	8.1	18Cr-10Ni-Cb	Wrought piping fittings
A/SA-403	WP348	S34800	75 (515)	8	1	102	8.1	18Cr-10Ni-Cb	Wrought piping fittings
A/SA-403	WP348H	S34809	75 (515)	8	1	102	8.1	18Cr-10Ni-Cb	Wrought piping fittings
A/SA-409	TP304	S30400	75 (515)	8	1	102	8.1	18Cr-8Ni	Welded pipe
A/SA-409	TP304L	S30403	70 (485)	8	1	102	8.1	18Cr-8Ni	Welded pipe
A/SA-409	S30815	S30815	87 (600)	8	2	102	8.2	21Cr-11Ni-N	Welded pipe
A/SA-409	TP309S	S30908	75 (515)	8	2	102	8.2	23Cr-12Ni	Welded pipe
A/SA-409	TP309Cb	S30940	75 (515)	8	2	102	8.2	23Cr-12Ni-Cb	Welded pipe
A/SA-409	TP310S	S31008	75 (515)	8	2	102	8.2	25Cr-20Ni	Welded pipe
A/SA-409	TP310Cb	S31040	75 (515)	8	2	102	8.2	25Cr-20Ni-Cb	Welded pipe
A/SA-409	S31254	S31254	94 (650)	8	4	102	8.2	20Cr-18Ni-6Mo	Welded pipe
A/SA-409	TP316	S31600	75 (515)	8	1	102	8.1	16Cr-12Ni-2Mo	Welded pipe
A/SA-409	TP316L	S31603	70 (485)	8	1	102	8.1	16Cr-12Ni-2Mo	Welded pipe
A/SA-409	TP317	S31700	75 (515)	8	1	102	8.1	18Cr-13Ni-3Mo	Welded pipe
A/SA-409	S31725	S31725	75 (515)	8	4	102	8.1	19Cr-15Ni-4Mo	Welded pipe
A/SA-409	S31726	S31726	80 (550)	8	4	102	8.1	19Cr-15.5Ni-4Mo	Welded pipe

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	Type or Grade	UNS No.	Minimum Specified Tensile, ksi (MPa)	Welding		Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	Group No.	P-No.			
Ferrous (Cont'd)									
A/SA-409	...	S32053	93 (640)	8	4	102	8.2	23Cr-25Ni-5.5Mo-N	Welded pipe
A/SA-409	TP321	S32100	75 (515)	8	1	102	8.1	18Cr-10Ni-Ti	Welded pipe
A/SA-409	TP347	S34700	75 (515)	8	1	102	8.1	18Cr-10Ni-Cb	Welded pipe
A/SA-409	S34565	S34565	115 (795)	8	4	102	8.3	24Cr-17Ni-6Mn-4.5Mo-N	Welded pipe
A/SA-409	TP348	S34800	75 (515)	8	1	102	8.1	18Cr-10Ni-Cb	Welded pipe
A/SA-414	A	K01501	45 (310)	1	1	101	1.1	C	Sheet
A/SA-414	B	K02201	50 (345)	1	1	101	1.1	C	Sheet
A/SA-414	C	K02503	55 (380)	1	1	101	1.1	C	Sheet
A/SA-414	D	K02505	60 (415)	1	1	101	1.1	C-Mn	Sheet
A/SA-414	E	K02704	65 (450)	1	1	101	11.1	C-Mn	Sheet
A/SA-414	F	K03102	70 (485)	1	2	101	11.1	C-Mn	Sheet
A/SA-414	G	K03103	75 (515)	1	2	101	11.1	C-Mn	Sheet
A/SA-420	WPL6	K03006	60 (415)	1	1	101	11.1	C-Mn-Si	Piping fitting
A/SA-420	WPL9	K22035	63 (435)	9A	1	101	9.1	2Ni-1Cu	Piping fitting
A/SA-420	WPL3	K31918	65 (450)	9B	1	101	9.2	3.5Ni	Piping fitting
A/SA-420	WPL8	K81340	100 (690)	11A	1	101	9.3	9Ni	Piping fitting
A/SA-423	1	K11535	60 (415)	4	2	102	5.1	0.75Cr-0.5Ni-Cu	Smls. & welded tube
A/SA-423	2	K11540	60 (415)	4	2	102	5.1	0.75Ni-0.5Cu-Mo	Smls. & welded tube
A/SA-426	CP15	J11522	60 (415)	3	1	101	1.1	C-0.5Mo-Si	Centrifugal cast pipe
A/SA-426	CP2	J11547	60 (415)	3	1	101	4.2	0.5Cr-0.5Mo	Centrifugal cast pipe
A/SA-426	CP12	J11562	60 (415)	4	1	102	5.1	1Cr-0.5Mo	Centrifugal cast pipe
A/SA-426	CP11	J12072	70 (485)	4	1	102	5.1	1.25Cr-0.5Mo	Centrifugal cast pipe
A/SA-426	CP1	J12521	65 (450)	3	1	101	1.1	C-0.5Mo	Centrifugal cast pipe
A/SA-426	CP22	J21890	70 (485)	5A	1	102	5.2	2.25Cr-1Mo	Centrifugal cast pipe
A/SA-426	CP21	J31545	60 (415)	5A	1	102	5.2	3Cr-1Mo	Centrifugal cast pipe
A/SA-426	CP5	J42045	90 (620)	5B	1	102	5.3	5Cr-0.5Mo	Centrifugal cast pipe
A/SA-426	CP5b	J51545	60 (415)	5B	1	102	5.3	5Cr-1.5Si-0.5Mo	Centrifugal cast pipe
A/SA-426	CP9	J82090	90 (620)	5B	1	102	5.4	9Cr-1Mo	Centrifugal cast pipe
A/SA-426	CPCA15	J91150	90 (620)	6	3	102	7.2	13Cr	Centrifugal cast pipe
A/SA-451	CPF8	J92600	70 (485)	8	1	102	8.1	18Cr-8Ni	Centrifugal cast pipe
A/SA-451	CPF8A	J92600	77 (530)	8	1	102	8.1	18Cr-8Ni	Centrifugal cast pipe
A/SA-451	CPF8C	J92710	70 (485)	8	1	102	8.1	18Cr-10Ni-Cb	Centrifugal cast pipe
A/SA-451	CPF8M	J92900	70 (485)	8	1	102	8.1	18Cr-12Ni-2Mo	Centrifugal cast pipe

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	Type or Grade	UNS No.	Minimum Specified Tensile, ksi (MPa)	Welding		Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	Group No.	P-No.			
Ferrous (Cont'd)									
A/SA-451	CPF3	J92500	70 (485)	8	1	102	8.1	18Cr-8Ni	Centrifugal cast pipe
A/SA-451	CPF3M	J92800	70 (485)	8	1	102	8.1	16Cr-12Ni-2Mo	Centrifugal cast pipe
A/SA-451	CPF3A	J92500	77 (530)	8	1	102	8.1	18Cr-8Ni	Centrifugal cast pipe
A/SA-451	CPH8	J93400	65 (450)	8	2	102	8.2	25Cr-12Ni	Centrifugal cast pipe
A/SA-451	CPH20	J93402	70 (485)	8	2	102	8.2	25Cr-12Ni	Centrifugal cast pipe
A/SA-451	CPK20	J94202	65 (450)	8	2	102	8.2	25Cr-20Ni	Centrifugal cast pipe
A/SA-451	CPF10MC	J92971	70 (485)	8	1	102	8.1	16Cr-14Ni-2Mo	Centrifugal cast pipe
A/SA-451	CPE20N	J92802	80 (550)	8	2	102	8.2	25Cr-8Ni-N	Centrifugal cast pipe
A/SA-455	...	K03300	70 (485)	1	2	101	11.2	C-Mn-Si	Plate > 0.580 in. – 0.750 in. (15 mm – 19 mm)
A/SA-455	...	K03300	73 (505)	1	2	101	11.2	C-Mn-Si	Plate > 0.375 in. – 0.580 in. (10 mm – 15 mm)
A/SA-455	...	K03300	75 (515)	1	2	101	11.2	C-Mn-Si	Plate, up to 0.375 in. (10 mm)
A479	904L	N08904	71 (490)	45	...	111	8.2	44Fe-25Ni-21Cr-Mo	Bars & shapes
A/SA-479	XM-19	S20910	100 (690)	8	3	102	8.3	22Cr-13Ni-5Mn	Bars & shapes
A/SA-479	XM-17	S21600	90 (620)	8	3	102	8.3	19Cr-8Mn-6Ni-Mo-N	Bars & shapes
A/SA-479	XM-18	S21603	90 (620)	8	3	102	8.3	19Cr-8Mn-6Ni-Mo-N	Bars & shapes
A/SA-479	S21800	S21800	95 (655)	8	3	102	8.1	18Cr-8Ni-4Si-N	Bars & shapes
A/SA-479	XM-11	S21904	90 (620)	8	3	102	8.3	21Cr-6Ni-9Mn	Bars & shapes
A/SA-479	XM-29	S24000	100 (690)	8	3	102	8.3	18Cr-3Ni-12Mn	Bars & shapes
A/SA-479	302	S30200	75 (515)	8	1	102	8.1	18Cr-8Ni	Bars & shapes
A/SA-479	304	S30400	75 (515)	8	1	102	8.1	18Cr-8Ni	Bars & shapes
A/SA-479	304L	S30403	70 (485)	8	1	102	8.1	18Cr-8Ni	Bars & shapes
A/SA-479	304H	S30409	75 (515)	8	1	102	8.1	18Cr-8Ni	Bars & shapes
A/SA-479	304N	S30451	80 (550)	8	1	102	8.1	18Cr-8Ni-N	Bars & shapes
A/SA-479	304LN	S30453	75 (515)	8	1	102	8.1	18Cr-8Ni-N	Bars & shapes
A/SA-479	S30600	S30600	78 (540)	8	1	102	8.1	18Cr-15Ni-4Si	Bars & shapes
A/SA-479	S30815	S30815	87 (600)	8	2	102	8.2	21Cr-11Ni-N	Bars & shapes
A/SA-479	309S	S30908	75 (515)	8	2	102	8.2	23Cr-12Ni	Bars & shapes
A/SA-479	309Cb	S30940	75 (515)	8	2	102	8.2	23Cr-12Ni-Cb	Bars & shapes
A/SA-479	310S	S31008	75 (515)	8	2	102	8.2	25Cr-20Ni	Bars & shapes

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	Type or Grade	UNS No.	Minimum Specified Tensile, ksi (MPa)	Welding		Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	Group No.	P-No.			
Ferrous (Cont'd)									
A/SA-479	310Cb	S31040	75 (515)	8	2	102	8.2	25Cr-20Ni-Cb	Bars & shapes
A/SA-479	S31254	S31254	95 (655)	8	4	102	8.2	20Cr-18Ni-6Mo	Bars & shapes
A/SA-479	316	S31600	75 (515)	8	1	102	8.1	16Cr-12Ni-2Mo	Bars & shapes
A/SA-479	316L	S31603	70 (485)	8	1	102	8.1	16Cr-12Ni-2Mo	Bars & shapes
A/SA-479	316H	S31609	75 (515)	8	1	102	8.1	16Cr-12Ni-2Mo	Bars & shapes
A/SA-479	316Ti	S31635	75 (515)	8	1	102	8.1	16Cr-12Ni-2Mo-Ti	Bars & shapes
A/SA-479	316Cb	S31640	75 (515)	8	1	102	8.1	16Cr-12Ni-2Mo-Cb	Bars & shapes
A/SA-479	316N	S31651	80 (550)	8	1	102	8.1	16Cr-12Ni-2Mo-N	Bars & shapes
A/SA-479	316LN	S31653	75 (515)	8	1	102	8.1	16Cr-12Ni-2Mo-N	Bars & shapes
A/SA-479	S31725	S31725	75 (515)	8	4	102	8.1	19Cr-15Ni-4Mo	Bars & shapes
A/SA-479	S31726	S31726	80 (550)	8	4	102	8.1	19Cr-15.5Ni-4Mo	Bars & shapes
A/SA-479	...	S31803	90 (620)	10H	1	102	10.1	22Cr-5Ni-3Mo-N	Bars & shapes
A/SA-479	...	S32053	93 (640)	8	4	102	8.2	23Cr-25Ni-5.5Mo-N	Bars & shapes
A/SA-479	...	S32202	94 (650)	10H	1	102	10.1	22Cr-2Ni-Mo-N	Bars & shapes
A/SA-479	321	S32100	75 (515)	8	1	102	8.1	18Cr-10Ni-Ti	Bars & shapes
A/SA-479	...	S32101	94 (650)	10H	1	102	10.1	21Cr-5Mn-1.5Ni-Cu-N	Bars & shapes
A/SA-479	321H	S32109	75 (515)	8	1	102	8.1	18Cr-10Ni-Ti	Bars & shapes
A/SA-479	2205	S32205	95 (655)	10H	1	102	10.1	22Cr-5Ni-3Mo-N	Bars & shapes
A/SA-479	S32550	S32550	110 (760)	10H	1	102	10.2	25Cr-5Ni-3Mo-2Cu	Bars & shapes
A/SA-479	S32615	S32615	80 (550)	8	1	102	8.1	18Cr-20Ni-5.5Si	Bars & shapes
A/SA-479	S32750	S32750	116 (800)	10H	1	102	10.2	25Cr-7Ni-4Mo-N	Bars & shapes
A/SA-479	S32906	S32906	109 (750)	10H	1	102	10.2	29Cr-6.5Ni-2Mo-N	Bars & shapes
A/SA-479	S34565	S34565	115 (795)	8	4	102	8.3	24Cr-17Ni-6Mn-4.5Mo-N	Bars & shapes
A/SA-479	347	S34700	75 (515)	8	1	102	8.1	18Cr-10Ni-Cb	Bars & shapes
A/SA-479	347H	S34709	75 (515)	8	1	102	8.1	18Cr-10Ni-Cb	Bars & shapes
A/SA-479	348	S34800	75 (515)	8	1	102	8.1	18Cr-10Ni-Cb	Bars & shapes
A/SA-479	348H	S34809	75 (515)	8	1	102	8.1	18Cr-10Ni-Cb	Bars & shapes
A/SA-479	403	S40300	70 (485)	6	1	102	7.1	12Cr	Bars & shapes
A/SA-479	405	S40500	60 (415)	7	1	102	7.1	12Cr-1Al	Bars & shapes
A/SA-479	410	S41000	70 (485)	6	1	102	7.2	13Cr	Bars & shapes
A/SA-479	414	S41400	115 (795)	6	4	102	7.2	12.5Cr-2Ni-Si	Bars & shapes
A/SA-479	S41500	S41500	115 (795)	6	4	102	7.2	13Cr-4.5Ni-Mo	Bars & shapes
A/SA-479	430	S43000	70 (485)	7	2	102	7.1	17Cr	Bars & shapes
A/SA-479	439	S43035	70 (485)	7	2	102	7.1	18Cr-Ti	Bars & shapes

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	Type or Grade	UNS No.	Minimum Specified Tensile, ksi (MPa)	Welding		Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	Group No.	P-No.			
Ferrous (Cont'd)									
A/SA-479	S44400	S44400	60 (415)	7	2	102	7.1	18Cr-2Mo	Bars & shapes
A/SA-479	XM-27	S44627	65 (450)	10I	1	102	7.1	27Cr-1Mo	Bars & shapes
A/SA-479	S44700	S44700	70 (485)	10J	1	102	7.1	29Cr-4Mo	Bars & shapes
A/SA-479	S44800	S44800	70 (485)	10K	1	102	7.1	29Cr-4Mo-2Ni	Bars & shapes
A/SA-487	Gr. 16, Cl. A	J31200	70 (485)	1	2	101	1.1	Low C-Mn-Ni	Castings
A/SA-487	Gr. 1, Cl. A	J13002	85 (585)	10A	1	101	2.1	Mn-V	Castings
A/SA-487	Gr. 1, Cl. B	J13002	90 (620)	10A	1	101	2.1	Mn-V	Castings
A/SA-487	Gr. 2, Cl. A	J13005	85 (585)	3	3	101	2.1	Mn-0.25Mo-V	Castings
A/SA-487	Gr. 2, Cl. B	J13005	90 (620)	3	3	101	2.1	Mn-0.25Mo-V	Castings
A/SA-487	Gr. 4, Cl. A	J13047	90 (620)	3	3	101	3.1	0.5Ni-0.5Cr-0.25Mo-V	Castings
A/SA-487	Gr. 4, Cl. B	J13047	105 (725)	11A	3	101	3.1	0.5Ni-0.5Cr-0.25Mo-V	Castings
A/SA-487	Gr. 4, Cl. E	J13047	115 (795)	11A	3	101	3.1	0.5Ni-0.5Cr-0.25Mo-V	Castings
A/SA-487	Gr. 8, Cl. A	J22091	85 (585)	5C	1	102	5.2	2.25Cr-1Mo	Castings
A/SA-487	Gr. 8, Cl. C	J22091	100 (690)	5C	4	102	5.2	2.25Cr-1Mo	Castings
A/SA-487	Gr. 8, Cl. B	J22091	105 (725)	5C	4	102	5.2	2.25Cr-1Mo	Castings
A/SA-487	CA15M Cl. A	J91151	90 (620)	6	3	102	7.2	13Cr-Mo	Castings
A/SA-487	CA15 Cl. C	J91150	90 (620)	6	3	102	7.2	13Cr	Castings
A/SA-487	CA15 Cl. B	J91171	90 (620)	6	3	102	7.2	13Cr	Castings
A/SA-487	CA15 Cl. D	J91171	100 (690)	6	3	102	7.2	13Cr	Castings
A/SA-487	CA6NM Cl. B	J91540	100 (690)	6	4	102	7.2	13Cr-4Ni	Castings
A/SA-487	CA6NM Cl. A	J91540	110 (760)	6	4	102	7.2	13Cr-4Ni	Castings
A/SA-494	M35-2	N04020	65 (450)	42	...	110	42	67Ni-30Cu-Fe-Si	Castings
A/SA-494	CY40	N06040	70 (485)	43	...	111	43	72Ni-15Cr-8Fe-Si	Castings
A/SA-494	CU5MCuC	N08826	75 (515)	45	...	111	45	42Ni-21.5Cr-3Mo-2.3Cu	Castings
A/SA-494	M30C	N24130	65 (450)	42	...	110	42	67Ni-30Cu-2Fe-Cb	Castings
A/SA-494	M35-1	N24135	65 (450)	42	...	110	42	67Ni-30Cu-2Fe-Cb	Castings
A/SA-494	CX2MW	N26022	80 (550)	43	...	111	44	59Ni-22Cr-14Mo-4Fe-3W	Castings
A/SA-494	CW2M	N26455	72 (495)	43	...	111	43	66Ni-16Mo-16Cr-Fe-W	Castings
A/SA-494	CW6MC	N26625	70 (485)	43	...	111	43	60Ni-21.5Cr-9Mo-4Cb-Fe	Castings
A/SA-494	N7M	N30007	76 (525)	44	...	112	44	65Ni-31.5Mo-1.5Fe-Cr	Castings
A/SA-494	CW6M	N30107	72 (495)	44	...	112	44	56Ni-19Mo-18Cr-2Fe	Castings
A500	C	K02705	62 (425)	1	1	101	1.2	C	Smls. & welded tube
A500	B	K03000	58 (400)	1	1	101	11.1	C	Smls. & welded tube

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	Type or Grade	UNS No.	Minimum Specified Tensile, ksi (MPa)	Welding		Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	Group No.	P-No.			
Ferrous (Cont'd)									
A501	A	K03000	58 (400)	1	1	101	11.1	C	Smls. & welded tube
A501	B	K03000	70 (485)	1	2	101	1.2	C	Smls. & welded tube
A/SA-508	3, Cl. 1	K12042	80 (550)	3	3	101	3.1	0.75Ni-0.5Mo-Cr-V	Forgings
A/SA-508	3, Cl. 2	K12042	90 (620)	3	3	102	3.1	0.75Ni-0.5Mo-Cr-V	Forgings
A/SA-508	2, Cl. 1	K12766	80 (550)	3	3	101	3.1	0.75Ni-0.5Mo-0.3Cr-V	Forgings
A/SA-508	2, Cl. 2	K12766	90 (620)	3	3	101	3.1	0.75Ni-0.5Mo-0.3Cr-V	Forgings
A/SA-508	1	K13502	70 (485)	1	2	101	11.1	C	Forgings
A/SA-508	1A	K13502	70 (485)	1	2	101	11.1	C	Forgings
A/SA-508	22, Cl. 3	K21590	85 (585)	5C	1	102	5.2	2.25Cr-1Mo	Forgings
A/SA-508	4N, Cl. 3	K22375	90 (620)	3	3	102	3.1	3.5Ni-1.75Cr-0.5Mo-V	Forgings
A/SA-508	4N, Cl. 1	K22375	105 (725)	11A	5	102	3.1	3.5Ni-1.75Cr-0.5Mo-V	Forgings
A/SA-508	4N, Cl. 2	K22375	115 (795)	11B	10	102	3.1	3.5Ni-1.75Cr-0.5Mo-V	Forgings
A/SA-508	3V	K31830	85 (585)	5C	1	102	6.2	3Cr-1Mo-V-Ti-B	Forgings
A/SA-508	3VCb	K31390	85 (585)	5C	1	102	6.2	3Cr-1Mo-0.25V-Cb-Ca	Forgings
A/SA-508	5, Cl. 1	K42365	105 (725)	11A	5	102	3.1	3.5Ni-1.75Cr-0.5Mo-V	Forgings
A/SA-508	5, Cl. 2	K42365	115 (795)	11B	10	102	3.1	3.5Ni-1.75Cr-0.5Mo-V	Forgings
A/SA-513	1008	G10080	42 (290)	1	1	101	1.1	C	Tube
A/SA-513	1010	G10100	45 (310)	1	1	101	1.1	C	Tube
A/SA-513	1015	G10150	48 (330)	1	1	101	1.1	C	Tube
A513	1015 CW	G10150	...	1	1	101	1.1	C	Tube
A513	1020 CW	G10200	...	1	2	101	1.1	C	Tube
A513	1025 CW	G10250	...	1	2	101	1.2	C	Tube
A513	1026 CW	G10260	...	1	3	101	11.1	C	Tube
A514	F	K11576	110 (760)	11B	3	101	3.1	0.75Ni-0.5Cr-0.5Mo-V	Plate, 2½ in. (64 mm) max.
A514	B	K11630	110 (760)	11B	4	101	3.1	0.5Cr-0.2Mo-V	Plate, 1¼ in. (32 mm) max.
A514	A	K11856	110 (760)	11B	1	101	3.1	0.5Cr-0.25Mo-Si	Plate, 1¼ in. (32 mm) max.
A514	E	K21604	100 (690)	11B	2	102	3.1	1.75Cr-0.5Mo-Cu	Plate > 2½ in. - 6 in. (64 mm - 152 mm), incl.
A514	E	K21604	110 (760)	11B	2	102	3.1	1.75Cr-0.5Mo-Cu	Plate, 2½ in. (64 mm) max.
A514	P	K21650	100 (690)	11B	8	102	3.1	1.25Ni-1Cr-0.5Mo	Plate > 2½ in. - 6 in. (64 mm - 152 mm), incl.
A514	P	K21650	110 (760)	11B	8	102	3.1	1.25Ni-1Cr-0.5Mo	Plate, 2½ in. (64 mm) max.

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	Type or Grade	UNS No.	Minimum Specified Tensile, ksi (MPa)	Welding		Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	Group No.	P-No.			
Ferrous (Cont'd)									
A514	Q	...	100 (690)	11B	9	102	3.1	1.3Ni-1.3Cr-0.5Mo-V	Plate > 2½ in. – 6 in. (64 mm – 152 mm), incl.
A514	Q	...	110 (760)	11B	9	102	3.1	1.3Ni-1.3Cr-0.5Mo-V	Plate, 2½ in. (64 mm) max.
A/SA-515	60	K02401	60 (415)	1	1	101	1.1	C	Plate ≤ 1 in. (25 mm)
A/SA-515	60	...	60 (415)	1	1	101	11.1	C-Si	Plate > 1 in. (25 mm)
A/SA-515	65	K02800	65 (450)	1	1	101	11.1	C-Si	Plate
A/SA-515	70	K03101	70 (485)	1	2	101	11.1	C-Si	Plate
A/SA-516	55	K01800	55 (380)	1	1	101	1.1	C-Si	Plate
A/SA-516	60	K02100	60 (415)	1	1	101	1.1	C-Mn-Si	Plate
A/SA-516	65	K02403	65 (450)	1	1	101	1.1	C-Mn-Si	Plate
A/SA-516	70	K02700	70 (485)	1	2	101	11.1	C-Mn-Si	Plate
A/SA-517	F	K11576	115 (795)	11B	3	101	3.1	0.75Ni-0.5Cr-0.5Mo-V	Plate ≤ 2½ in. (64 mm)
A/SA-517	B	K11630	115 (795)	11B	4	101	3.1	0.5Cr-0.2Mo-V	Plate ≤ 1¼ in. (32 mm)
A/SA-517	A	K11856	115 (795)	11B	1	101	3.1	0.5Cr-0.25Mo-Si	Plate ≤ 1¼ in. (32 mm)
A/SA-517	E	K21604	105 (725)	11B	2	102	3.1	1.75Cr-0.5Mo-Cu	Plate > 2½ in. – 6 in. (64 mm – 152 mm), incl.
A/SA-517	E	K21604	115 (795)	11B	2	102	3.1	1.75Cr-0.5Mo-Cu	Plate ≤ 2½ in. (64 mm)
A/SA-517	P	K21650	105 (725)	11B	8	102	3.1	1.25Ni-1Cr-0.5Mo	Plate > 2½ in. – 4 in. (64 mm – 102 mm), incl.
A/SA-517	P	K21650	115 (795)	11B	8	102	3.1	1.25Ni-1Cr-0.5Mo	Plate ≤ 2½ in. (64 mm)
A519	1018 HR	G10180	...	1	1	101	1.1	C	Tube
A519	1018 CW	G10180	...	1	2	101	1.1	C	Tube
A519	1020 HR	G10200	...	1	1	101	1.1	C	Tube
A519	1020 CW	G10200	...	1	2	101	1.1	C	Tube
A519	1022 HR	G10220	...	1	1	101	1.1	C	Tube
A519	1022 CW	G10220	...	1	2	101	1.1	C	Tube
A519	1025 HR	G10250	...	1	1	101	1.1	C	Tube
A519	1025 CW	G10250	...	1	2	101	1.2	C	Tube
A519	1026 HR	G10260	...	1	1	101	11.1	C	Tube
A519	1026 CW	G10260	...	1	2	101	11.1	C	Tube
A/SA-522	Type II	K71340	100 (690)	11A	1	101	9.3	8Ni	Forgings

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	Type or Grade	UNS No.	Minimum Specified Tensile, ksi (MPa)	Welding		Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	Group No.	P-No.			
Ferrous (Cont'd)									
A/SA-522	Type I	K81340	100 (690)	11A	1	101	9.3	9Ni	Forgings
A/SA-524	II	K02104	55 (380)	1	1	101	1.1	C-Mn-Si	Smls. pipe
A/SA-524	I	K02104	60 (415)	1	1	101	1.1	C-Mn-Si	Smls. pipe
A/SA-533	Type A, Cl. 1	K12521	80 (550)	3	3	101	3.1	Mn-0.5Mo	Plate
A/SA-533	Type A, Cl. 2	K12521	90 (620)	3	3	101	3.1	Mn-0.5Mo	Plate
A/SA-533	Type A, Cl. 3	K12521	100 (690)	11A	4	101	3.1	Mn-0.5Mo	Plate
A/SA-533	Type D, Cl. 1	K12529	80 (550)	3	3	101	3.1	Mn-0.5Mo-0.25Ni	Plate
A/SA-533	Type D, Cl. 2	K12529	90 (620)	3	3	101	3.1	Mn-0.5Mo-0.25Ni	Plate
A/SA-533	Type D, Cl. 3	K12529	100 (690)	11A	4	101	3.1	Mn-0.5Mo-0.25Ni	Plate
A/SA-533	Type B, Cl. 1	K12539	80 (550)	3	3	101	3.1	Mn-0.5Mo-0.5Ni	Plate
A/SA-533	Type B, Cl. 2	K12539	90 (620)	3	3	101	3.1	Mn-0.5Mo-0.5Ni	Plate
A/SA-533	Type B, Cl. 3	K12539	100 (690)	11A	4	101	3.2	Mn-0.5Mo-0.5Ni	Plate
A/SA-533	Type C, Cl. 1	K12554	80 (550)	3	3	101	3.1	Mn-0.5Mo-0.75Ni	Plate
A/SA-533	Type C, Cl. 2	K12554	90 (620)	3	3	101	3.1	Mn-0.5Mo-0.75Ni	Plate
A/SA-533	Type E, Cl. 1	K12554	80 (550)	3	3	101	3.1	Mn-0.5Mo-0.75Ni	Plate
A/SA-533	Type E, Cl. 2	K12554	90 (620)	3	3	101	3.1	Mn-0.5Mo-0.75Ni	Plate
A/SA-533	Type C, Cl. 3	K12554	100 (690)	11A	4	101	3.2	Mn-0.5Mo-0.75Ni	Plate
A/SA-537	Cl. 1	K12437	65 (450)	1	2	101	1.2	C-Mn-Si	Plate > 2½ in. – 4 in. (64 mm – 102 mm), incl.
A/SA-537	Cl. 1	K12437	70 (485)	1	2	101	1.2	C-Mn-Si	Plate, 2½ in. (64 mm) & under
A/SA-537	Cl. 2	K12437	70 (485)	1	3	101	1.2	C-Mn-Si	Plate > 4 in. – 6 in. (102 mm – 152 mm), incl.
A/SA-537	Cl. 2	K12437	75 (515)	1	3	101	1.2	C-Mn-Si	Plate > 2½ in. – 4 in. (64 mm – 102 mm), incl.
A/SA-537	Cl. 2	K12437	80 (550)	1	3	101	1.2	C-Mn-Si	Plate, 2½ in. (64 mm) & under
A/SA-537	Cl. 3	K12437	70 (485)	1	3	101	1.2	C-Mn-Si	Plate > 4 in. (102 mm)
A/SA-537	Cl. 3	K12437	75 (515)	1	3	101	1.2	C-Mn-Si	Plate, 2½ in. < t ≤ 4 in. (64 mm) < t ≤ 102 mm)
A/SA-537	Cl. 3	K12437	80 (550)	1	3	101	1.2	C-Mn-Si	Plate ≤ 2½ in. (64 mm)
A/SA-541	1	K03506	70 (485)	1	2	101	11.1	C-Si	Forgings
A/SA-541	1A	K03020	70 (485)	1	2	101	11.1	C-Mn-Si	Forgings
A/SA-541	11, Cl. 4	K11572	80 (550)	4	1	102	5.2	1.25Cr-0.5Mo-Si	Forgings
A/SA-541	3, Cl. 1	K12045	80 (550)	3	3	101	4.1	0.5Ni-0.5Mo-V	Forgings

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	Type or Grade	UNS No.	Minimum Specified Tensile, ksi (MPa)	Welding		Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	Group No.	P-No.			
Ferrous (Cont'd)									
A/SA-541	3, Cl. 2	K12045	90 (620)	3	3	101	4.1	0.5Ni-0.5Mo-V	Forgings
A/SA-541	2, Cl. 1	K12765	80 (550)	3	3	101	4.2	0.75Ni-0.5Mo-0.3Cr-V	Forgings
A/SA-541	2, Cl. 2	K12765	90 (620)	3	3	101	4.2	0.75Ni-0.5Mo-0.3Cr-V	Forgings
A/SA-541	22, Cl. 3	K21390	85 (585)	5C	1	102	5.2	2.25Cr-1Mo	Forgings
A/SA-541	22, Cl. 4	K21390	105 (725)	5C	4	102	5.2	2.25Cr-1Mo	Forgings
A/SA-541	22, Cl. 5	K21390	115 (795)	5C	5	102	5.2	2.25Cr-1Mo	Forgings
A/SA-541	3V	K31830	85 (585)	5C	1	102	6.2	3Cr-1Mo-V-Ti-B	Forgings
A/SA-541	3VCb	K31390	85 (585)	5C	1	102	6.2	3Cr-1Mo-0.25V-Cb-Ca	Forgings
A/SA-541	22V	K31835	85 (585)	5C	1	102	5.2	2.25Cr-1Mo-V	Forgings
A/SA-542	B, Cl. 4a	K21590	85 (585)	5C	1	102	5.2	2.25Cr-1Mo	Plate
A/SA-542	B, Cl. 4	K21590	85 (585)	5C	1	102	5.2	2.25Cr-1Mo	Plate
A/SA-542	A, Cl. 4	K21590	85 (585)	5C	1	102	5.2	2.25Cr-1Mo	Plate
A/SA-542	A, Cl. 4a	K21590	85 (585)	5C	1	102	5.2	2.25Cr-1Mo	Plate
A/SA-542	A, Cl. 3	K21590	95 (655)	5C	3	102	5.2	2.25Cr-1Mo	Plate
A/SA-542	B, Cl. 3	K21590	95 (655)	5C	3	102	5.2	2.25Cr-1Mo	Plate
A/SA-542	A, Cl. 1	K21590	105 (725)	5C	4	102	5.2	2.25Cr-1Mo	Plate
A/SA-542	B, Cl. 1	K21590	105 (725)	5C	4	102	5.2	2.25Cr-1Mo	Plate
A/SA-542	B, Cl. 2	K21590	115 (795)	5C	5	102	5.2	2.25Cr-1Mo	Plate
A/SA-542	A, Cl. 2	K21590	115 (795)	5C	5	102	5.2	2.25Cr-1Mo	Plate
A/SA-542	C, Cl. 4	K31830	85 (585)	5C	1	102	6.2	3Cr-1Mo-V-Ti-B	Plate
A/SA-542	C, Cl. 4a	K31830	85 (585)	5C	1	102	6.2	3Cr-1Mo-V-Ti-B	Plate
A/SA-542	C, Cl. 3	K31830	95 (655)	5C	3	102	6.2	3Cr-1Mo-V-Ti-B	Plate
A/SA-542	C, Cl. 1	K31830	105 (725)	5C	4	102	6.2	3Cr-1Mo-V-Ti-B	Plate
A/SA-542	C, Cl. 2	K31830	115 (795)	5C	5	102	6.2	3Cr-1Mo-V-Ti-B	Plate
A/SA-542	D, Cl. 4a	K31835	85 (585)	5C	1	102	6.3	2.25Cr-1Mo-V	Plate
A/SA-542	E, Cl. 4a	K31390	85 (585)	5C	1	102	6.2	3Cr-1Mo-0.25V-Cb-Ca	Plate
A/SA-543	B, Cl. 3	K42339	90 (620)	3	3	102	3.1	3Ni-1.75Cr-0.5Mo	Plate
A/SA-543	B, Cl. 1	K42339	105 (725)	11A	5	102	3.1	3Ni-1.75Cr-0.5Mo	Plate
A/SA-543	B, Cl. 2	K42339	115 (795)	11B	10	102	3.1	3Ni-1.75Cr-0.5Mo	Plate
A/SA-543	C, Cl. 3	...	90 (620)	3	3	102	3.1	2.75Ni-1.5Cr-0.5Mo	Plate
A/SA-543	C, Cl. 1	...	105 (725)	11A	5	102	3.1	2.75Ni-1.5Cr-0.5Mo	Plate
A/SA-543	C, Cl. 2	...	115 (795)	11B	10	102	3.1	2.75Ni-1.5Cr-0.5Mo	Plate
A/SA-553	II	K71340	100 (690)	11A	1	101	9.3	8Ni	Plate

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	Type or Grade	UNS No.	Minimum Specified Tensile, ksi (MPa)	Welding		Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	Group No.	P-No.			
Ferrous (Cont'd)									
A/SA-553	I	K81340	100 (690)	11A	1	101	9.3	9Ni	Plate
A/SA-556	A2	K01807	47 (325)	1	1	101	1.1	C	Smls. tube
A/SA-556	B2	K02707	60 (415)	1	1	101	11.1	C-Si	Smls. tube
A/SA-556	C2	K03006	70 (485)	1	2	101	11.1	C-Mn-Si	Smls. tube
A/SA-557	A2	K01807	47 (325)	1	1	101	1.1	C	E.R.W. tube
A/SA-557	B2	K03007	60 (415)	1	1	101	11.1	C	E.R.W. tube
A/SA-557	C2	K03505	70 (485)	1	2	101	11.1	C-Mn	E.R.W. tube
A/SA-562	...	K11224	55 (380)	1	1	101	1.1	C-Mn-Ti	Plate
A/SA-572	42	...	60 (415)	1	1	101	1.2	C-Mn-Si	Plate & shapes
A/SA-572	50	...	65 (450)	1	1	101	1.2	C-Mn-Si	Plate & shapes
A/SA-572	60	...	75 (515)	1	2	101	11.1	C-Mn-Si	Plate & shapes
A573	58	...	58 (400)	1	1	101	11.1	C	Plate
A573	65	...	65 (450)	1	1	101	11.1	C	Plate
A573	70	...	70 (485)	1	2	101	11.1	C	Plate
A575	M 1008	1	1	101	1.1	C	Bar
A575	M 1010	1	1	101	1.1	C	Bar
A575	M 1012	1	1	101	1.1	C	Bar
A575	M 1015	1	1	101	1.1	C	Bar
A575	M 1017	1	1	101	1.1	C	Bar
A575	M 1020	1	1	101	11.1	C	Bar
A575	M 1023	1	1	101	11.1	C	Bar
A575	M 1025	1	1	101	11.1	C	Bar
A576	G10080	1	1	101	1.1	C	Bar
A576	G10100	1	1	101	1.1	C	Bar
A576	G10120	1	1	101	1.1	C	Bar
A576	G10150	1	1	101	1.1	C	Bar
A576	G10160	1	1	101	1.1	C	Bar
A576	G10170	1	1	101	1.1	C	Bar
A576	G10180	1	1	101	1.1	C	Bar
A576	G10190	1	1	101	1.1	C	Bar
A576	G10200	1	1	101	1.1	C	Bar
A576	G10210	1	1	101	11.1	C	Bar

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	Type or Grade	UNS No.	Minimum Specified Tensile, ksi (MPa)	Welding		Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	Group No.	P-No.			
Ferrous (Cont'd)									
A576	G10220	1	1	101	11.1	C	Bar
A576	G10230	1	1	101	11.1	C	Bar
A576	G10250	1	1	101	11.1	C	Bar
A/SA-587	...	K11500	48 (330)	1	1	101	1.1	C	E.R.W. pipe
A588	A	K11430	63 (435)	3	1	101	1.4	Mn-0.5Cr-0.3Cu-Si-V	Plate & bar > 5 in. – 8 in. (125 mm – 200 mm) incl.
A588	A	K11430	67 (460)	3	1	101	1.4	Mn-0.5Cr-0.3Cu-Si-V	Plate & bar > 4 in. – 5 in. (100 mm – 125 mm) incl.
A588	A	K11430	70 (485)	3	1	101	1.4	Mn-0.5Cr-0.3Cu-Si-V	Plate & bar ≤ 4 in. (100 mm)
A588	A	K11430	70 (485)	3	1	101	1.4	Mn-0.5Cr-0.3Cu-Si-V	Shapes
A588	B	K12043	63 (435)	3	1	101	1.4	Mn-0.6Cr-0.3Cu-Si-V	Plate & bar > 5 in. – 8 in. (125 mm – 200 mm) incl.
A588	B	K12043	67 (460)	3	1	101	1.4	Mn-0.6Cr-0.3Cu-Si-V	Plate & bar > 4 in. – 5 in. (100 mm – 125 mm) incl.
A588	B	K12043	70 (485)	3	1	101	1.4	Mn-0.6Cr-0.3Cu-Si-V	Plate & bar ≤ 4 in. (100 mm)
A588	B	K12043	70 (485)	3	1	101	1.4	Mn-0.6Cr-0.3Cu-Si-V	Shapes
A/SA-592	F	K11576	105 (725)	11B	3	101	3.1	0.75Ni-0.5Cr-0.5Mo-V	Forgings, 2½ in. – 4 in. (64 mm – 102 mm), incl.
A/SA-592	F	K11576	115 (795)	11B	3	101	3.1	0.75Ni-0.5Cr-0.5Mo-V	Forgings, 2½ in. (64 mm) & under
A/SA-592	E	K11695	105 (725)	11B	2	102	3.1	1.75Cr-0.5Mo-Cu	Forgings, 2½ in. – 4 in. (64 mm – 102 mm), incl.
A/SA-592	E	K11695	115 (795)	11B	2	102	3.1	1.75Cr-0.5Mo-Cu	Forgings, 2½ in. (64 mm) & under
A/SA-592	A	K11856	115 (795)	11B	1	101	3.1	0.5Cr-0.25Mo-Si	Forgings, 1½ in. (38 mm) & under
A/SA-612	...	K02900	81 (560)	10C	1	101	1.3	C-Mn-Si	Plate > ½ in. – 1 in. (13 mm – 25 mm)
A/SA-612	...	K02900	83 (570)	10C	1	101	1.3	C-Mn-Si	Plate, ½ in. (13 mm) & under
A618	Ia	...	67 (460)	1	2	101	...	Mn-Cu-V	Tube > ¾ in. – 1½ in. (19 mm – 38 mm)
A618	Ia	...	70 (485)	1	2	101	...	Mn-Cu-V	Tube ≤ ¾ in. (19 mm)
A618	Ib	K02601	67 (460)	1	2	101	...	Mn-Cu-V	Tube > ¾ in. – 1½ in. (19 mm – 38 mm)
A618	Ib	K02601	70 (485)	1	2	101	...	Mn-Cu-V	Tube ≤ ¾ in. (19 mm)
A618	II	K12609	67 (460)	1	2	101	1.2	Mn-Cu-V	Tube > ¾ in. – 1½ in. (19 mm – 38 mm)
A618	II	K12609	70 (485)	1	2	101	1.2	Mn-Cu-V	Tube, ¾ in. (19 mm) & under
A618	III	K12700	65 (450)	1	1	101	1.2	Mn-V	Tube

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	Type or Grade	UNS No.	Minimum Specified Tensile, ksi (MPa)	Welding		Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	Group No.	P-No.			
Ferrous (Cont'd)									
A633	A	K01802	63 (435)	1	1	101	1.1	Mn-Cb	Plate & shapes
A633	C	K12000	65 (450)	1	1	101	1.1	Mn-Cb	Plate > 2½ in. – 4 in. (64 mm – 102 mm) incl., shapes
A633	C	K12000	70 (485)	1	2	101	1.1	Mn-Cb	Plate to 2½ in. (64 mm), shapes
A633	D	K12037	65 (450)	1	1	101	1.1	C-Mn-Si	Plate > 2½ in. – 4 in. (64 mm – 102 mm) incl., shapes
A633	D	K12037	70 (485)	1	2	101	1.1	C-Mn-Si	Plate to 2½ in. (64 mm), shapes
A633	E	K12202	80 (550)	1	3	101	4.1	C-Mn-Si-V	Plate & shapes
A/SA-645	A	K41583	95 (655)	11A	2	101	9.2	5Ni-0.25Mo	Plate
A/SA-656	T3, Gr. 50	...	60 (345)	1	1	101	...	C-Mn-Si-V-Cb	Plate
A/SA-656	T3, Gr. 60	...	70 (415)	1	2	101	...	C-Mn-Si-V-Cb	Plate
A/SA-656	T3, Gr. 70	...	80 (485)	1	3	101	...	C-Mn-Si-V-Cb	Plate
A/SA-656	T3, Gr. 80	...	90 (550)	1	4	101	...	C-Mn-Si-V-Cb	Plate
A/SA-656	T7, Gr. 50	...	60 (345)	1	1	101	...	C-Mn-Si-V-Cb	Plate
A/SA-656	T7, Gr. 60	...	70 (415)	1	2	101	...	C-Mn-Si-V-Cb	Plate
A/SA-656	T7, Gr. 70	...	80 (485)	1	3	101	...	C-Mn-Si-V-Cb	Plate
A/SA-656	T7, Gr. 80	...	90 (550)	1	4	101	...	C-Mn-Si-V-Cb	Plate
A/SA-660	WCA	J02504	60 (415)	1	1	101	11.1	C-Si	Centrifugal cast pipe
A/SA-660	WCC	J02505	70 (485)	1	2	101	11.1	C-Mn-Si	Centrifugal cast pipe
A/SA-660	WCB	J03003	70 (485)	1	2	101	1.1	C-Si	Centrifugal cast pipe
A/SA-662	A	K01701	58 (400)	1	1	101	1.1	C-Mn-Si	Plate
A/SA-662	C	K02007	70 (485)	1	2	101	1.1	C-Mn-Si	Plate
A/SA-662	B	K02203	65 (450)	1	1	101	1.1	C-Mn-Si	Plate
A663	1	1	101	...	C	Bar
A/SA-666	201-1	S20100	75 (515)	8	3	102	8.3	17Cr-4Ni-6Mn	Plate, sheet & strip
A/SA-666	201-2	S20100	95 (655)	8	3	102	8.3	17Cr-4Ni-6Mn	Plate, sheet & strip
A/SA-666	XM-11	S21904	90 (620)	8	3	102	8.3	21Cr-6Ni-9Mn	Plate, sheet & strip
A/SA-666	302	S30200	75 (515)	8	1	102	8.1	18Cr-8Ni	Plate, sheet & strip
A/SA-666	304	S30400	75 (515)	8	1	102	8.1	18Cr-8Ni	Plate, sheet & strip
A/SA-666	304L	S30403	70 (485)	8	1	102	8.1	18Cr-8Ni	Plate, sheet & strip
A/SA-666	304N	S30451	80 (550)	8	1	102	8.1	18Cr-8Ni-N	Plate, sheet & strip

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	Type or Grade	UNS No.	Minimum Specified Tensile, ksi (MPa)	Welding		Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	Group No.	P-No.			
Ferrous (Cont'd)									
A/SA-666	304LN	S30453	75 (515)	8	1	102	8.1	18Cr-8Ni-N	Plate, sheet & strip
A/SA-666	316	S31600	75 (515)	8	1	102	8.1	16Cr-12Ni-2Mo	Plate, sheet & strip
A/SA-666	316L	S31603	70 (485)	8	1	102	8.1	16Cr-12Ni-2Mo	Plate, sheet & strip
A/SA-666	316N	S31651	80 (550)	8	1	102	8.1	16Cr-12Ni-2Mo-N	Plate, sheet & strip
A/SA-671	CC60	K02100	60 (415)	1	1	101	1.1	C-Mn-Si	Fusion welded pipe
A/SA-671	CE55	K02202	55 (380)	1	1	101	11.1	C	Fusion welded pipe
A/SA-671	CD70	K12437	70 (485)	1	2	101	1.2	C-Mn-Si	Fusion welded pipe
A/SA-671	CD80	K12437	80 (550)	1	3	101	1.2	C-Mn-Si	Fusion welded pipe
A/SA-671	CB60	K02401	60 (415)	1	1	101	1.1	C	Fusion welded pipe
A/SA-671	CE60	K02402	60 (415)	1	1	101	11.1	C-Mn-Si	Fusion welded pipe
A/SA-671	CC65	K02403	65 (450)	1	1	101	1.1	C-Mn-Si	Fusion welded pipe
A/SA-671	CC70	K02700	70 (485)	1	2	101	11.1	C-Mn-Si	Fusion welded pipe
A/SA-671	CB65	K02800	65 (450)	1	1	101	11.1	C-Si	Fusion welded pipe
A/SA-671	CA55	K02801	55 (380)	1	1	101	11.1	C	Fusion welded pipe
A/SA-671	CK75	K02803	75 (515)	1	2	101	11.1	C-Mn-Si	Fusion welded pipe
A/SA-671	CB70	K03101	70 (485)	1	2	101	11.1	C-Si	Fusion welded pipe
A/SA-672	A45	K01700	45 (310)	1	1	101	1.1	C	Fusion welded pipe
A/SA-672	C55	K01800	55 (380)	1	1	101	1.1	C-Si	Fusion welded pipe
A/SA-672	B55	K02001	55 (380)	1	1	101	1.1	C-Si	Fusion welded pipe
A/SA-672	C60	K02100	60 (415)	1	1	101	1.1	C-Mn-Si	Fusion welded pipe
A/SA-672	A50	K02200	50 (345)	1	1	101	1.1	C	Fusion welded pipe
A/SA-672	E55	K02202	55 (380)	1	1	101	11.1	C	Fusion welded pipe
A/SA-672	D70	K12437	70 (485)	1	2	101	1.2	C-Mn-Si	Fusion welded pipe
A/SA-672	D80	K12437	80 (550)	1	3	101	1.2	C-Mn-Si	Fusion welded pipe
A/SA-672	B60	K02401	60 (415)	1	1	101	1.1	C	Fusion welded pipe
A/SA-672	E60	K02402	60 (415)	1	1	101	11.1	C-Mn-Si	Fusion welded pipe
A/SA-672	C65	K02403	65 (450)	1	1	101	1.1	C-Mn-Si	Fusion welded pipe
A/SA-672	C70	K02700	70 (485)	1	2	101	11.1	C-Mn-Si	Fusion welded pipe
A/SA-672	B65	K02800	65 (450)	1	1	101	11.1	C-Si	Fusion welded pipe
A/SA-672	A55	K02801	55 (380)	1	1	101	11.1	C	Fusion welded pipe
A/SA-672	N75	K02803	75 (515)	1	2	101	11.1	C-Mn-Si	Fusion welded pipe
A/SA-672	B70	K03101	70 (485)	1	2	101	11.1	C-Si	Fusion welded pipe
A/SA-672	L65	K11820	65 (450)	3	1	101	1.1	C-0.5Mo	Fusion welded pipe

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	Type or Grade	UNS No.	Minimum Specified Tensile, ksi (MPa)	Welding		Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	Group No.	P-No.			
Ferrous (Cont'd)									
A/SA-672	L70	K12020	70 (485)	3	2	101	1.2	C-0.5Mo	Fusion welded pipe
A/SA-672	H75	K12021	75 (515)	3	2	101	1.1	Mn-0.5Mo	Fusion welded pipe
A/SA-672	H80	K12022	80 (550)	3	3	101	1.2	Mn-0.5Mo	Fusion welded pipe
A/SA-672	L75	K12320	75 (515)	3	2	101	1.2	C-0.5Mo	Fusion welded pipe
A/SA-672	J100	K12521	100 (690)	11A	4	101	3.2	Mn-0.5Mo	Fusion welded pipe
A/SA-672	J80	...	80 (550)	3	3	101	3.1	Mn-0.5Mo-0.75Ni	Fusion welded pipe
A/SA-672	J90	...	90 (620)	3	3	101	3.1	Mn-0.5Mo-0.75Ni	Fusion welded pipe
A/SA-675	45	...	45 (310)	1	1	101	11.1	C	Bar
A/SA-675	50	...	50 (345)	1	1	101	11.1	C	Bar
A/SA-675	55	...	55 (380)	1	1	101	11.1	C	Bar
A/SA-675	60	...	60 (415)	1	1	101	11.1	C	Bar
A/SA-675	65	...	65 (450)	1	1	101	11.1	C	Bar
A/SA-675	70	...	70 (485)	1	2	101	11.1	C	Bar
A/SA-688	XM-29	S24000	100 (690)	8	3	102	8.3	18Cr-3Ni-12Mn	Welded tube
A/SA-688	TP304	S30400	75 (515)	8	1	102	8.1	18Cr-8Ni	Welded tube
A/SA-688	TP304L	S30403	70 (485)	8	1	102	8.1	18Cr-8Ni	Welded tube
A/SA-688	TP304N	S30451	80 (550)	8	1	102	8.1	18Cr-8Ni-N	Welded tube
A/SA-688	TP304LN	S30453	75 (515)	8	1	102	8.1	18Cr-8Ni-N	Welded tube
A/SA-688	TP316	S31600	75 (515)	8	1	102	8.1	16Cr-12Ni-2Mo	Welded tube
A/SA-688	TP316L	S31603	70 (485)	8	1	102	8.1	16Cr-12Ni-2Mo	Welded tube
A/SA-688	TP316N	S31651	80 (550)	8	1	102	8.1	16Cr-12Ni-2Mo-N	Welded tube
A/SA-688	TP316LN	S31653	75 (515)	8	1	102	8.1	16Cr-12Ni-2Mo-N	Welded tube
A/SA-691	CMSH-70	K12437	65 (450)	1	2	101	1.2	C-Mn-Si	Fusion welded pipe > 2½ in. – 4 in. (64 mm – 102 mm)
A/SA-691	CMSH-70	K12437	70 (485)	1	2	101	1.2	C-Mn-Si	Fusion welded pipe ≤ 2½ in. (64 mm)
A/SA-691	CMSH-80	K12437	75 (515)	1	3	101	1.2	C-Mn-Si	Fusion welded pipe > 2½ in. – 4 in. (64 mm – 102 mm)
A/SA-691	CMSH-80	K12437	80 (550)	1	3	101	1.2	C-Mn-Si	Fusion welded pipe ≤ 2½ in. (64 mm)
A/SA-691	CMS-75	K02803	75 (515)	1	2	101	11.1	C-Mn-Si	Fusion welded pipe
A/SA-691	1CR, Cl. 1	K11757	55 (380)	4	1	102	5.1	1Cr-0.5Mo	Fusion welded pipe
A/SA-691	1CR, Cl. 2	K11757	65 (450)	4	1	102	5.1	1Cr-0.5Mo	Fusion welded pipe
A/SA-691	1.25CR, Cl. 1	K11789	60 (415)	4	1	102	5.1	1.25Cr-0.5Mo-Si	Fusion welded pipe
A/SA-691	1.25CR, Cl. 2	K11789	75 (515)	4	1	102	5.1	1.25Cr-0.5Mo-Si	Fusion welded pipe

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	Type or Grade	UNS No.	Minimum Specified Tensile, ksi (MPa)	Welding		Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	Group No.	P-No.			
Ferrous (Cont'd)									
A/SA-691	CM-65	K11820	65 (450)	3	1	101	1.1	C-0.5Mo	Fusion welded pipe
A/SA-691	CM-70	K12020	70 (485)	3	2	101	1.2	C-0.5Mo	Fusion welded pipe
A/SA-691	0.5CR, Cl. 1	K12143	55 (380)	3	1	101	4.2	0.5Cr-0.5Mo	Fusion welded pipe
A/SA-691	0.5CR, Cl. 2	K12143	70 (485)	3	2	101	4.2	0.5Cr-0.5Mo	Fusion welded pipe
A/SA-691	CM-75	K12320	75 (515)	3	2	101	1.2	C-0.5Mo	Fusion welded pipe
A/SA-691	2.25CR, Cl. 1	K21590	60 (415)	5A	1	102	5.2	2.25Cr-1Mo	Fusion welded pipe
A/SA-691	2.25CR, Cl. 2	K21590	75 (515)	5A	1	102	5.2	2.25Cr-1Mo	Fusion welded pipe
A/SA-691	3CR, Cl. 1	K31545	60 (415)	5A	1	102	5.2	3Cr-1Mo	Fusion welded pipe
A/SA-691	3CR, Cl. 2	K31545	75 (515)	5A	1	102	5.2	3Cr-1Mo	Fusion welded pipe
A/SA-691	5CR, Cl. 1	K41545	60 (415)	5B	1	102	5.3	5Cr-0.5Mo	Fusion welded pipe
A/SA-691	5CR, Cl. 2	K41545	75 (515)	5B	1	102	5.3	5Cr-0.5Mo	Fusion welded pipe
A/SA-691	91	K91560	85 (585)	15E	1	102	6.4	9Cr-1Mo-V	Fusion welded pipe
A694	F42	K03014	60 (415)	1	1	101	11.1	C-Mn	Forgings
A694	F46	K03014	60 (415)	1	1	101	11.1	C-Mn	Forgings
A694	F52	K03014	66 (455)	1	1	101	11.1	C-Mn	Forgings
A694	F56	K03014	68 (470)	1	2	101	11.1	C-Mn	Forgings
A694	F60	K03014	75 (515)	1	2	101	11.1	C-Mn	Forgings
A694	F65	K03014	77 (530)	1	2	101	11.1	C-Mn	Forgings
A694	F70	K03014	82 (565)	1	3	101	11.1	C-Mn	Forgings
A/SA-696	B	K03200	60 (415)	1	1	101	11.1	C-Mn-Si	Bar
A/SA-696	C	K03200	70 (485)	1	2	101	11.1	C-Mn-Si	Bar
A707	L1, Cl. 1	K02302	...	1	1	101	1.2	C-Mn	Forgings
A707	L1, Cl. 2	K02302	...	1	1	101	1.2	C-Mn	Forgings
A707	L2, Cl. 1	K03301	...	1	1	101	11.1	C-Mn	Forgings
A707	L2, Cl. 2	K03301	...	1	1	101	11.1	C-Mn	Forgings
A707	L2, Cl. 3	K03301	...	1	2	101	11.1	C-Mn	Forgings
A707	L3, Cl. 1	K12510	...	1	1	101	1.2	C-Mn-V-N	Forgings
A707	L3, Cl. 2	K12510	...	1	1	101	1.2	C-Mn-V-N	Forgings
A707	L3, Cl. 3	K12510	...	1	2	101	1.3	C-Mn-V-N	Forgings
A714	Gr. V, Tp. E	K22035	65 (450)	9A	1	102	9.1	2Ni-1Cu	Smls. & welded pipe
A714	Gr. V	K22035	65 (450)	9A	1	102	9.1	2Ni-1Cu	Smls. & welded pipe
A/SA-724	A	K11831	90 (620)	1	4	101	3.1	C-Mn-Si	Plate

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	Type or Grade	UNS No.	Minimum Specified Tensile, ksi (MPa)	Welding		Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	Group No.	P-No.			
Ferrous (Cont'd)									
A/SA-724	B	K12031	95 (655)	1	4	101	3.1	C-Mn-Si	Plate
A/SA-724	C	K12037	90 (620)	1	4	101	1.1	C-Mn-Si	Plate
A/SA-727	...	K02506	60 (415)	1	1	101	11.1	C-Mn-Si	Forgings
A/SA-731	S41500	S41500	115 (795)	6	4	102	7.2	13Cr-4.5Ni-Mo	Smls. & welded pipe
A/SA-731	TP439	S43035	60 (415)	7	2	102	7.1	18Cr-Ti	Smls. & welded pipe
A/SA-731	18Cr-2Mo	S44400	60 (415)	7	2	102	7.1	18Cr-2Mo	Smls. & welded pipe
A/SA-731	TPXM-33	S44626	65 (450)	10I	1	102	7.1	27Cr-1Mo-Ti	Smls. & welded pipe
A/SA-731	TPXM-27	S44627	65 (450)	10I	1	102	7.1	27Cr-1Mo	Smls. & welded pipe
A/SA-731	S44660	S44660	85 (585)	10K	1	102	7.1	26Cr-3Ni-3Mo	Smls. & welded pipe
A/SA-731	S44700	S44700	80 (550)	10J	1	102	7.1	29Cr-4Mo	Smls. & welded pipe
A/SA-731	S44800	S44800	80 (550)	10K	1	102	7.1	29Cr-4Mo-2Ni	Smls. & welded pipe
A/SA-737	B	K12001	70 (485)	1	2	101	11.1	C-Mn-Si-Cb	Plate
A/SA-737	C	K12202	80 (550)	1	3	101	4.1	C-Mn-Si-V	Plate
A/SA-738	A	K12447	75 (515)	1	2	101	11.1	C-Mn-Si	Plate
A/SA-738	B	K12007	85 (585)	1	3	101	11.1	C-Mn-Si-Cb	Plate
A/SA-738	C	K02008	70 (485)	1	3	101	11.1	C-Mn-Si	Plate > 4 in. – 6 in. (102 mm – 152 mm), incl.
A/SA-738	C	K02008	75 (515)	1	3	101	11.1	C-Mn-Si	Plate > 2½ in. – 4 in. (64 mm – 102 mm), incl.
A/SA-738	C	K02008	80 (550)	1	3	101	11.1	C-Mn-Si	Plate, 2½ in. (64 mm) & under
A/SA-739	B11	K11797	70 (485)	4	1	102	5.1	1.25Cr-0.5Mo	Bar
A/SA-739	B22	K21390	75 (515)	5A	1	102	5.2	2.25Cr-1Mo	Bar
A/SA-765	I	K03046	60 (415)	1	1	101	11.1	C-Mn-Si	Forgings
A/SA-765	II	K03047	70 (485)	1	2	101	11.1	C-Mn-Si	Forgings
A/SA-765	III	K32026	70 (485)	9B	1	101	9.2	3.5Ni	Forgings
A/SA-765	IV	K02009	80 (550)	1	3	101	1.1	C-Mn-Si	Forgings
A/SA-789	S31200	S31200	100 (690)	10H	1	102	10.2	25Cr-6Ni-Mo-N	Smls. & welded tube
A/SA-789	S31260	S31260	100 (690)	10H	1	102	10.2	25Cr-6.5Ni-3Mo-N	Smls. & welded tube
A/SA-789	S31500	S31500	92 (635)	10H	1	102	10.1	18Cr-5Ni-3Mo-N	Smls. & welded tube
A/SA-789	S31803	S31803	90 (620)	10H	1	102	10.1	22Cr-5Ni-3Mo-N	Smls. & welded tube
A/SA-789	...	S32003	100 (690)	10H	1	102	10.1	21Cr-3.5Ni-Mo-N	Smls. & welded tube
A/SA-789	...	S32202	94 (650)	10H	1	102	10.1	22Cr-2Ni-Mo-N	Smls. & welded tube

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	Type or Grade	UNS No.	Minimum Specified Tensile, ksi (MPa)	Welding		Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	Group No.	P-No.			
Ferrous (Cont'd)									
A/SA-789	...	S32101	94 (650)	10H	1	102	10.1	21Cr-5Mn-1.5Ni-Cu-N	Smls. & welded tube > 0.187 in. (5 mm)
A/SA-789	...	S32101	101 (700)	10H	1	102	10.1	21Cr-5Mn-1.5Ni-Cu-N	Smls. & welded tube ≤ 0.187 in. (5 mm)
A/SA-789	S32205	S32205	95 (655)	10H	1	102	10.1	22Cr-5Ni-3Mo-N	Smls. & welded tube
A/SA-789	S32304	S32304	87 (600)	10H	1	102	10.1	23Cr-4Ni-Mo-Cu-N	Smls. & welded tube > 1 in. (25 mm)
A/SA-789	S32304	S32304	100 (690)	10H	1	102	10.1	23Cr-4Ni-Mo-Cu-N	Smls. & welded tube ≤ 1 in. (25 mm)
A/SA-789	S32550	S32550	110 (760)	10H	1	102	10.2	25Cr-5Ni-3Mo-2Cu	Smls. & welded tube
A/SA-789	S32750	S32750	116 (800)	10H	1	102	10.2	25Cr-7Ni-4Mo-N	Smls. & welded tube
A/SA-789	S32900	S32900	90 (620)	10H	1	102	10.2	26Cr-4Ni-Mo	Smls. & welded tube
A/SA-789	S32906	S32906	109 (750)	10H	1	102	10.2	29Cr-6.5Ni-2Mo-N	Smls. & welded tube ≥ 0.40 in. (10 mm)
A/SA-789	S32906	S32906	116 (800)	10H	1	102	10.2	29Cr-6.5Ni-2Mo-N	Smls. & welded tube < 0.40 in. (10 mm)
A/SA-789	S32950	S32950	100 (690)	10H	1	102	10.2	26Cr-4Ni-Mo-N	Smls. & welded tube
A/SA-789	S32760	S32760	109 (750)	10H	1	102	10.2	25Cr-8Ni-3Mo-W-Cu-N	Smls. & welded tube
A/SA-789	S39274	S39274	116 (800)	10H	1	102	10.2	25Cr-7Ni-3Mo-2W-Cu-N	Smls. & welded tube
A/SA-790	S31200	S31200	100 (690)	10H	1	102	10.2	25Cr-6Ni-Mo-N	Smls. & welded pipe
A/SA-790	S31260	S31260	100 (690)	10H	1	102	10.2	25Cr-6.5Ni-3Mo-N	Smls. & welded pipe
A/SA-790	S31500	S31500	92 (635)	10H	1	102	10.1	18Cr-5Ni-3Mo-N	Smls. & welded pipe
A/SA-790	S31803	S31803	90 (620)	10H	1	102	10.1	22Cr-5Ni-3Mo-N	Smls. & welded pipe
A/SA-790	...	S32003	90 (620)	10H	1	102	10.1	21Cr-3.5Ni-Mo-N	Smls. & welded pipe
A/SA-790	...	S32202	94 (650)	10H	1	102	10.1	22Cr-2Ni-Mo-N	Smls. & welded pipe
A/SA-790	...	S32101	94 (650)	10H	1	102	10.1	21Cr-5Mn-1.5Ni-Cu-N	Smls. & welded pipe > 0.187 in. (5 mm)
A/SA-790	...	S32101	101 (700)	10H	1	102	10.1	21Cr-5Mn-1.5Ni-Cu-N	Smls. & welded pipe ≤ 0.187 in. (5 mm)
A/SA-790	S32205	S32205	95 (655)	10H	1	102	10.1	22Cr-5Ni-3Mo-N	Smls. & welded pipe
A/SA-790	S32304	S32304	87 (600)	10H	1	102	10.1	23Cr-4Ni-Mo-Cu-N	Smls. & welded pipe
A/SA-790	S32550	S32550	110 (760)	10H	1	102	10.2	25Cr-5Ni-3Mo-2Cu	Smls. & welded pipe
A/SA-790	S32750	S32750	116 (800)	10H	1	102	10.2	25Cr-7Ni-4Mo-N	Smls. & welded tube
A/SA-790	S32900	S32900	90 (620)	10H	1	102	10.2	26Cr-4Ni-Mo	Smls. & welded pipe
A/SA-790	S32906	S32906	109 (750)	10H	1	102	10.2	29Cr-6.5Ni-2Mo-N	Smls. & welded pipe ≥ 0.40 in. (10 mm)
A/SA-790	S32906	S32906	116 (800)	10H	1	102	10.2	29Cr-6.5Ni-2Mo-N	Smls. & welded pipe < 0.40 in. (10 mm)
A/SA-790	S32950	S32950	100 (690)	10H	1	102	10.2	26Cr-4Ni-Mo-N	Smls. & welded pipe
A/SA-790	S32760	S32760	109 (750)	10H	1	102	10.2	25Cr-8Ni-3Mo-W-Cu-N	Smls. & welded pipe
A/SA-790	S39274	S39274	116 (800)	10H	1	102	10.2	25Cr-7Ni-3Mo-2W-Cu-N	Smls. & welded pipe
A/SA-803	TP439	S43035	60 (415)	7	2	102	7.1	18Cr-Ti	Welded tube
A/SA-803	26-3-3	S44660	85 (585)	10K	1	102	7.1	26Cr-3Ni-3Mo	Welded tube
A/SA-813	N08367	N08367	95 (655)	45	...	111	8.2	46Fe-24Ni-21Cr-6Mo-Cu-N	Welded pipe > 0.1875 in. (5 mm)

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	Type or Grade	UNS No.	Minimum Specified Tensile, ksi (MPa)	Welding		Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	Group No.	P-No.			
Ferrous (Cont'd)									
A/SA-813	N08367	N08367	100 (690)	45	...	111	8.2	46Fe-24Ni-21Cr-6Mo-Cu-N	Welded pipe ≤ 0.1875 in. (5 mm)
A/SA-813	TPXM-19	S20910	100 (690)	8	3	102	8.3	22Cr-13Ni-5Mn	Welded pipe
A/SA-813	TPXM-11	S21904	90 (620)	8	3	102	8.3	21Cr-6Ni-9Mn	Welded pipe
A/SA-813	TPXM-29	S24000	100 (690)	8	3	102	8.3	18Cr-3Ni-12Mn	Welded pipe
A/SA-813	TP304	S30400	75 (515)	8	1	102	8.1	18Cr-8Ni	Welded pipe
A/SA-813	TP304L	S30403	70 (485)	8	1	102	8.1	18Cr-8Ni	Welded pipe
A/SA-813	TP304H	S30409	75 (515)	8	1	102	8.1	18Cr-8Ni	Welded pipe
A/SA-813	TP304N	S30451	80 (550)	8	1	102	8.1	18Cr-8Ni-N	Welded pipe
A/SA-813	TP304LN	S30453	75 (515)	8	1	102	8.1	18Cr-8Ni-N	Welded pipe
A/SA-813	S30815	S30815	87 (600)	8	2	102	8.2	21Cr-11Ni-N	Welded pipe
A/SA-813	TP309S	S30908	75 (515)	8	2	102	8.2	23Cr-12Ni	Welded pipe
A/SA-813	TP309Cb	S30940	75 (515)	8	2	102	8.2	23Cr-12Ni-Cb	Welded pipe
A/SA-813	TP310S	S31008	75 (515)	8	2	102	8.2	25Cr-20Ni	Welded pipe
A/SA-813	TP310Cb	S31040	75 (515)	8	2	102	8.2	25Cr-20Ni-Cb	Welded pipe
A/SA-813	S31254	S31254	94 (650)	8	4	102	8.2	20Cr-18Ni-6Mo	Welded pipe
A/SA-813	TP316	S31600	75 (515)	8	1	102	8.1	16Cr-12Ni-2Mo	Welded pipe
A/SA-813	TP316L	S31603	70 (485)	8	1	102	8.1	16Cr-12Ni-2Mo	Welded pipe
A/SA-813	TP316H	S31609	75 (515)	8	1	102	8.1	16Cr-12Ni-2Mo	Welded pipe
A/SA-813	TP316N	S31651	80 (550)	8	1	102	8.1	16Cr-12Ni-2Mo-N	Welded pipe
A/SA-813	TP316LN	S31653	75 (515)	8	1	102	8.1	16Cr-12Ni-2Mo-N	Welded pipe
A/SA-813	TP317	S31700	75 (515)	8	1	102	8.1	18Cr-13Ni-3Mo	Welded pipe
A/SA-813	TP317L	S31703	75 (515)	8	1	102	8.1	18Cr-13Ni-3Mo	Welded pipe
A/SA-813	...	S32053	93 (640)	8	4	102	8.2	23Cr-25Ni-5.5Mo-N	Welded pipe
A/SA-813	TP321	S32100	75 (515)	8	1	102	8.1	18Cr-10Ni-Ti	Welded pipe
A/SA-813	TP321H	S32109	75 (515)	8	1	102	8.1	18Cr-10Ni-Ti	Welded pipe
A/SA-813	TP347	S34700	75 (515)	8	1	102	8.1	18Cr-10Ni-Cb	Welded pipe
A/SA-813	TP347H	S34709	75 (515)	8	1	102	8.1	18Cr-10Ni-Cb	Welded pipe
A/SA-813	TP348	S34800	75 (515)	8	1	102	8.1	18Cr-10Ni-Cb	Welded pipe
A/SA-813	TP348H	S34809	75 (515)	8	1	102	8.1	18Cr-10Ni-Cb	Welded pipe
A/SA-813	TPXM-15	S38100	75 (515)	8	1	102	8.1	18Cr-18Ni-2Si	Welded pipe
A/SA-814	N08367	N08367	95 (655)	45	...	111	8.2	46Fe-24Ni-21Cr-6Mo-Cu-N	Cold worked welded pipe > 0.1875 in. (5 mm)
A/SA-814	N08367	N08367	100 (690)	45	...	111	8.2	46Fe-24Ni-21Cr-6Mo-Cu-N	Cold worked welded pipe ≤ 0.1875 in. (5 mm)

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	Type or Grade	UNS No.	Minimum Specified Tensile, ksi (MPa)	Welding		Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	Group No.	P-No.			
Ferrous (Cont'd)									
A/SA-814	TPXM-19	S20910	100 (690)	8	3	102	8.3	22Cr-13Ni-5Mn	Cold worked welded pipe
A/SA-814	TPXM-11	S21904	90 (620)	8	3	102	8.3	21Cr-6Ni-9Mn	Cold worked welded pipe
A/SA-814	TPXM-29	S24000	100 (690)	8	3	102	8.3	18Cr-3Ni-12Mn	Cold worked welded pipe
A/SA-814	TP304	S30400	75 (515)	8	1	102	8.1	18Cr-8Ni	Cold worked welded pipe
A/SA-814	TP304L	S30403	70 (485)	8	1	102	8.1	18Cr-8Ni	Cold worked welded pipe
A/SA-814	TP304H	S30409	75 (515)	8	1	102	8.1	18Cr-8Ni	Cold worked welded pipe
A/SA-814	TP304N	S30451	80 (550)	8	1	102	8.1	18Cr-8Ni-N	Cold worked welded pipe
A/SA-814	TP304LN	S30453	75 (515)	8	1	102	8.1	18Cr-8Ni-N	Cold worked welded pipe
A/SA-814	S30815	S30815	87 (600)	8	2	102	8.2	21Cr-11Ni-N	Cold worked welded pipe
A/SA-814	TP309S	S30908	75 (515)	8	2	102	8.2	23Cr-12Ni	Cold worked welded pipe
A/SA-814	TP309Cb	S30940	75 (515)	8	2	102	8.2	23Cr-12Ni-Cb	Cold worked welded pipe
A/SA-814	TP310S	S31008	75 (515)	8	2	102	8.2	25Cr-20Ni	Cold worked welded pipe
A/SA-814	TP310Cb	S31040	75 (515)	8	2	102	8.2	25Cr-20Ni-Cb	Cold worked welded pipe
A/SA-814	S31254	S31254	94 (650)	8	4	102	8.2	20Cr-18Ni-6Mo	Cold worked welded pipe
A/SA-814	TP316	S31600	75 (515)	8	1	102	8.1	16Cr-12Ni-2Mo	Cold worked welded pipe
A/SA-814	TP316L	S31603	70 (485)	8	1	102	8.1	16Cr-12Ni-2Mo	Cold worked welded pipe
A/SA-814	TP316H	S31609	75 (515)	8	1	102	8.1	16Cr-12Ni-2Mo	Cold worked welded pipe
A/SA-814	TP316N	S31651	80 (550)	8	1	102	8.1	16Cr-12Ni-2Mo-N	Cold worked welded pipe
A/SA-814	TP316LN	S31653	75 (515)	8	1	102	8.1	16Cr-12Ni-2Mo-N	Cold worked welded pipe
A/SA-814	TP317	S31700	75 (515)	8	1	102	8.1	18Cr-13Ni-3Mo	Cold worked welded pipe
A/SA-814	TP317L	S31703	75 (515)	8	1	102	8.1	18Cr-13Ni-3Mo	Cold worked welded pipe
A/SA-814	...	S32053	93 (640)	8	4	102	8.2	23Cr-25Ni-5.5Mo-N	Cold worked welded pipe
A/SA-814	TP321	S32100	75 (515)	8	1	102	8.1	18Cr-10Ni-Ti	Cold worked welded pipe
A/SA-814	TP321H	S32109	75 (515)	8	1	102	8.1	18Cr-10Ni-Ti	Cold worked welded pipe
A/SA-814	TP347	S34700	75 (515)	8	1	102	8.1	18Cr-10Ni-Cb	Cold worked welded pipe
A/SA-814	TP347H	S34709	75 (515)	8	1	102	8.1	18Cr-10Ni-Cb	Cold worked welded pipe
A/SA-814	TP348	S34800	75 (515)	8	1	102	8.1	18Cr-10Ni-Cb	Cold worked welded pipe
A/SA-814	TP348H	S34809	75 (515)	8	1	102	8.1	18Cr-10Ni-Cb	Cold worked welded pipe
A/SA-814	TPXM-15	S38100	75 (515)	8	1	102	8.1	18Cr-18Ni-2Si	Cold worked welded pipe
A/SA-815	S31803	S31803	90 (620)	10H	1	102	10.1	22Cr-5Ni-3Mo-N	Fittings
A/SA-815	...	S32202	94 (650)	10H	1	102	10.1	22Cr-2Ni-Mo-N	Fittings
A/SA-815	...	S32101	94 (650)	10H	1	102	10.1	21Cr-5Mn-1.5Ni-Cu-N	Fittings
A/SA-815	S41500	S41500	110 (760)	6	4	102	7.2	13Cr-4.5Ni-Mo	Fittings

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	Type or Grade	UNS No.	Minimum Specified Tensile, ksi (MPa)	Welding		Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	Group No.	P-No.			
Ferrous (Cont'd)									
A/SA-815	S32760	S32760	109 (750)	10H	1	102	10.2	25Cr-8Ni-3Mo-W-Cu-N	Fittings
A/SA-815	S32205	S32205	95 (655)	10H	1	102	10.1	22Cr-5Ni-3Mo-N	Fittings
A815	2507	S32750	116 (800)	10H	1	102	10.2	25Cr-7Ni-4Mo-N	Fittings
A/SA-832	21V	K31830	85 (585)	5C	1	102	6.2	3Cr-1Mo-V-Ti-B	Plate
A/SA-832	22V	K31835	85 (585)	5C	1	102	6.2	2.25Cr-1Mo-V	Plate
A/SA-832	23V	...	85 (585)	5C	1	102	6.2	3Cr-1Mo-0.25V-Cb-Ca	Plate
A/SA-836	55 (380)	1	1	101	1.1	C-Si-Ti	Forgings
A/SA-841	A, Cl. 1	...	65 (450)	1	2	101	1.2	C-Mn-Si	Plate > 2.5 in. (65 mm)
A/SA-841	A, Cl. 1	...	70 (485)	1	2	101	1.2	C-Mn-Si	Plate ≤ 2.5 in. (65 mm)
A/SA-841	B, Cl. 2	...	75 (515)	1	3	101	1.3	C-Mn-Si	Plate > 2.5 in. (65 mm)
A/SA-841	B, Cl. 2	...	80 (550)	1	3	101	1.3	C-Mn-Si	Plate ≤ 2.5 in. (65 mm)
A/SA-859	A, Cl. 1	...	65 (450)	11C	1	101	3.4	1Ni-1Cu-0.75Cr-Mo-Nb	Forgings
A/SA-859	A, Cl. 2	...	75 (515)	11C	1	101	3.4	1Ni-1Cu-0.75Cr-Mo-Nb	Forgings
A890	6A	J93380	100 (690)	10H	1	102	10.2	25Cr-8Ni-3Mo-W-Cu-N	Castings
A890	4A	J92205	90 (620)	10H	1	102	10.1	22Cr-5Ni-3Mo-N	Castings
A928	...	S32760	108 (745)	10H	1	102	10.2	25Cr-8Ni-3Mo-W-Cu-N	Welded pipe
A928	2205	S32205	90 (620)	10H	1	102	10.1	22Cr-5Ni-3Mo-N	Welded pipe
A/SA-965	F46	S30600	78 (540)	8	1	102	8.1	18Cr-15Ni-4Si	Forgings
A/SA-965	FXM-19	S20910	100 (690)	8	3	102	8.3	22Cr-13Ni-5Mn	Forgings
A/SA-965	FXM-11	S21904	90 (620)	8	3	102	8.3	21Cr-6Ni-9Mn	Forgings
A/SA-965	F304	S30400	70 (485)	8	1	102	8.1	18Cr-8Ni	Forgings
A/SA-965	F304L	S30403	65 (450)	8	1	102	8.1	18Cr-8Ni	Forgings
A/SA-965	F304H	S30409	70 (485)	8	1	102	8.1	18Cr-8Ni	Forgings
A/SA-965	F304N	S30451	80 (550)	8	1	102	8.1	18Cr-8Ni-N	Forgings
A/SA-965	F304LN	S30453	70 (485)	8	1	102	8.1	18Cr-8Ni-N	Forgings
A/SA-965	F310	S31000	75 (515)	8	2	102	8.2	25Cr-20Ni	Forgings
A/SA-965	F316	S31600	70 (485)	8	1	102	8.1	16Cr-12Ni-2Mo	Forgings
A/SA-965	F316L	S31603	65 (450)	8	1	102	8.1	16Cr-12Ni-2Mo	Forgings
A/SA-965	F316H	S31609	70 (485)	8	1	102	8.1	16Cr-12Ni-2Mo	Forgings
A/SA-965	F316N	S31651	80 (550)	8	1	102	8.1	16Cr-12Ni-2Mo-N	Forgings
A/SA-965	F316LN	S31653	70 (485)	8	1	102	8.1	16Cr-12Ni-2Mo-N	Forgings
A/SA-965	F321	S32100	70 (485)	8	1	102	8.1	18Cr-10Ni-Ti	Forgings
A/SA-965	F321H	S32109	70 (485)	8	1	102	8.1	18Cr-10Ni-Ti	Forgings
A/SA-965	F347	S34700	70 (485)	8	1	102	8.1	18Cr-10Ni-Cb	Forgings

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	Type or Grade	UNS No.	Minimum Specified Tensile, ksi (MPa)	Welding		Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	Group No.	P-No.			
Ferrous (Cont'd)									
A/SA-965	F347H	S34709	70 (485)	8	1	102	8.1	18Cr-10Ni-Cb	Forgings
A/SA-965	F348	S34800	70 (485)	8	1	102	8.1	18Cr-10Ni-Cb	Forgings
A/SA-965	F348H	S34809	70 (485)	8	1	102	8.1	18Cr-10Ni-Cb	Forgings
A992	65 (450)	1	1	101	1.1	C-Mn-Si	Shapes
A/SA-995	2A	J93345	95 (655)	10H	1	102	10.2	24Cr-10Ni-4Mo-N	Castings
A/SA-995	1B	J93372	100 (690)	10H	1	102	10.2	25Cr-5Ni-3Mo-2Cu	Castings
A/SA-995	6A	J93380	100 (690)	10H	1	102	10.2	25Cr-8Ni-3Mo-W-Cu-N	Castings
A/SA-995	4A	J92205	90 (620)	10H	1	102	10.1	22Cr-5Ni-3Mo-N	Castings
A/SA-1008	CS Type A	...	40 (275)	1	1	101	1.1	C	Sheet
A/SA-1008	CS Type B	...	40 (275)	1	1	101	1.1	C	Sheet
A/SA-1008	DS Type B	...	40 (275)	1	1	101	1.1	C	Sheet
A/SA-1010	40	S41003	66 (455)	7	1	102	...	12Cr-1Ni	Plate, sheet & strip
A/SA-1010	50	S41003	70 (485)	7	1	102	...	12Cr-1Ni	Plate, sheet & strip
A/SA-1011	CS Type B	...	40 (275)	1	1	101	1.1	C	Sheet & strip
A/SA-1011	DS Type B	...	40 (275)	1	1	101	1.1	C	Sheet & strip
API 5L	A	...	49 (330)	1	1	101	1.1	C-Mn	Smls. & welded pipe
API 5L	A25	...	45 (310)	1	1	101	1.1	C-Mn	Smls. & welded pipe
API 5L	A25P	...	45 (310)	1	1	101	1.1	C-Mn	Smls. & welded pipe
API 5L	B	...	60 (415)	1	1	101	11.1	C-Mn	Smls. & welded pipe
API 5L	BM	...	60 (415)	1	1	101	1.1	C-Mn	Welded pipe
API 5L	BMO	...	60 (415)	1	1	101	1.1	C-Mn	Welded pipe
API 5L	BMS	...	60 (415)	1	1	101	1.1	C-Mn	Welded pipe
API 5L	BN	...	60 (415)	1	1	101	1.1	C-Mn	Smls. & welded pipe
API 5L	BNO	...	60 (415)	1	1	101	1.1	C-Mn	Smls. & welded pipe
API 5L	BNS	...	60 (415)	1	1	101	1.1	C-Mn	Smls. & welded pipe
API 5L	BQ	...	60 (415)	1	1	101	1.1	C-Mn	Smls. & welded pipe
API 5L	BQO	...	60 (415)	1	1	101	1.1	C-Mn	Smls. & welded pipe
API 5L	BQS	...	60 (415)	1	1	101	1.1	C-Mn	Smls. & welded pipe
API 5L	BR	...	60 (415)	1	1	101	1.1	C-Mn	Smls. & welded pipe
API 5L	X42	...	60 (415)	1	1	101	11.1	C-Mn	Smls. & welded pipe
API 5L	X42M	...	60 (415)	1	1	101	1.2	C-Mn	Welded pipe
API 5L	X42MO	...	60 (415)	1	1	101	1.2	C-Mn	Welded pipe
API 5L	X42MS	...	60 (415)	1	1	101	1.2	C-Mn	Welded pipe

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	Type or Grade	UNS No.	Minimum Specified Tensile, ksi (MPa)	Welding		Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	Group No.	P-No.			
Ferrous (Cont'd)									
API 5L	X42N	...	60 (415)	1	1	101	1.2	C-Mn	Smls. & welded pipe
API 5L	X42NO	...	60 (415)	1	1	101	1.2	C-Mn	Smls. & welded pipe
API 5L	X42NS	...	60 (415)	1	1	101	1.2	C-Mn	Smls. & welded pipe
API 5L	X42Q	...	60 (415)	1	1	101	1.2	C-Mn	Smls. & welded pipe
API 5L	X42QO	...	60 (415)	1	1	101	1.2	C-Mn	Smls. & welded pipe
API 5L	X42QS	...	60 (415)	1	1	101	1.2	C-Mn	Smls. & welded pipe
API 5L	X42R	...	60 (415)	1	1	101	1.2	C-Mn	Smls. & welded pipe
API 5L	X46	...	63 (435)	1	1	101	11.1	C-Mn	Smls. & welded pipe
API 5L	X46M	...	63 (435)	1	1	101	1.2	C-Mn	Welded pipe
API 5L	X46MO	...	63 (435)	1	1	101	1.2	C-Mn	Welded pipe
API 5L	X46MS	...	63 (435)	1	1	101	1.2	C-Mn	Welded pipe
API 5L	X46N	...	63 (435)	1	1	101	1.2	C-Mn	Smls. & welded pipe
API 5L	X46NO	...	63 (435)	1	1	101	1.2	C-Mn	Smls. & welded pipe
API 5L	X46NS	...	63 (435)	1	1	101	1.2	C-Mn	Smls. & welded pipe
API 5L	X46Q	...	63 (435)	1	1	101	1.2	C-Mn	Smls. & welded pipe
API 5L	X46QO	...	63 (435)	1	1	101	1.2	C-Mn	Smls. & welded pipe
API 5L	X46QS	...	63 (435)	1	1	101	1.2	C-Mn	Smls. & welded pipe
API 5L	X52	...	67 (455)	1	1	101	11.1	C-Mn	Smls. & welded pipe
API 5L	X52M	...	67 (455)	1	1	101	1.2	C-Mn	Welded pipe
API 5L	X52MO	...	67 (455)	1	1	101	1.2	C-Mn	Welded pipe
API 5L	X52MS	...	67 (455)	1	1	101	1.2	C-Mn	Welded pipe
API 5L	X52N	...	67 (455)	1	1	101	1.2	C-Mn	Smls. & welded pipe
API 5L	X52NO	...	67 (455)	1	1	101	1.2	C-Mn	Smls. & welded pipe
API 5L	X52NS	...	67 (455)	1	1	101	1.2	C-Mn	Smls. & welded pipe
API 5L	X52Q	...	67 (455)	1	1	101	1.2	C-Mn	Smls. & welded pipe
API 5L	X52QO	...	67 (455)	1	1	101	1.2	C-Mn	Smls. & welded pipe
API 5L	X52QS	...	67 (455)	1	1	101	1.2	C-Mn	Smls. & welded pipe
API 5L	X56	...	71 (490)	1	2	101	11.1	C-Mn	Smls. & welded pipe
API 5L	X56M	...	71 (490)	1	2	101	2.1	C-Mn	Welded pipe
API 5L	X56MO	...	71 (490)	1	2	101	2.1	C-Mn	Welded pipe
API 5L	X56MS	...	71 (490)	1	2	101	2.1	C-Mn	Welded pipe
API 5L	X56N	...	71 (490)	1	2	101	1.3	C-Mn	Smls. & welded pipe
API 5L	X56Q	...	71 (490)	1	2	101	3.1	C-Mn	Smls. & welded pipe
API 5L	X56QO	...	71 (490)	1	2	101	3.1	C-Mn	Smls. & welded pipe
API 5L	X56QS	...	71 (490)	1	2	101	3.1	C-Mn	Smls. & welded pipe
API 5L	X60	...	75 (515)	1	2	101	11.1	C-Mn	Smls. & welded pipe
API 5L	X60M	...	75 (515)	1	2	101	2.1	C-Mn	Welded pipe

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	Type or Grade	UNS No.	Minimum Specified Tensile, ksi (MPa)	Welding		Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	Group No.	P-No.			
Ferrous (Cont'd)									
API 5L	X60MO	...	75 (515)	1	2	101	2.1	C-Mn	Welded pipe
API 5L	X60MS	...	75 (515)	1	2	101	2.1	C-Mn	Welded pipe
API 5L	X60N	...	75 (515)	1	2	101	1.3	C-Mn	Smls. & welded pipe
API 5L	X60Q	...	75 (515)	1	2	101	3.1	C-Mn	Smls. & welded pipe
API 5L	X60QO	...	75 (515)	1	2	101	3.1	C-Mn	Smls. & welded pipe
API 5L	X60QS	...	75 (515)	1	2	101	3.1	C-Mn	Smls. & welded pipe
API 5L	X65	...	78 (530)	1	2	101	11.1	C-Mn	Smls. & welded pipe
API 5L	X65M	...	78 (530)	1	2	101	2.1	C-Mn	Welded pipe
API 5L	X65MO	...	78 (530)	1	2	101	2.1	C-Mn	Welded pipe
API 5L	X65MS	...	78 (530)	1	2	101	2.1	C-Mn	Welded pipe
API 5L	X65Q	...	78 (530)	1	2	101	3.1	C-Mn	Smls. & welded pipe
API 5L	X65QO	...	78 (530)	1	2	101	3.1	C-Mn	Smls. & welded pipe
API 5L	X65QS	...	78 (530)	1	2	101	3.1	C-Mn	Smls. & welded pipe
API 5L	X70	...	83 (565)	1	3	101	11.1	C-Mn	Smls. & welded pipe
API 5L	X70M	...	83 (565)	1	3	101	2.2	C-Mn	Welded pipe
API 5L	X70MO	...	83 (565)	1	3	101	2.2	C-Mn	Welded pipe
API 5L	X70MS	...	83 (565)	1	3	101	2.2	C-Mn	Welded pipe
API 5L	X70Q	...	83 (565)	1	3	101	3.1	C-Mn	Smls. & welded pipe
API 5L	X70QO	...	83 (565)	1	3	101	3.1	C-Mn	Smls. & welded pipe
API 5L	X70QS	...	83 (565)	1	3	101	3.1	C-Mn	Smls. & welded pipe
API 5L	X80M	...	91 (620)	1	4	101	2.2	C-Mn	Welded pipe
API 5L	X80MO	...	91 (620)	1	4	101	2.2	C-Mn	Welded pipe
API 5L	X80Q	...	91 (620)	1	4	101	3.1	C-Mn	Smls. & welded pipe
API 5L	X80QO	...	91 (620)	1	4	101	3.1	C-Mn	Smls. & welded pipe
MSS SP-75	WPHY-42	...	60 (415)	1	1	101	11.1	C-Mn	Smls./welded fittings
MSS SP-75	WPHY-46	...	63 (435)	1	1	101	11.1	C-Mn	Smls./welded fittings
MSS SP-75	WPHY-52	...	66 (455)	1	1	101	11.1	C-Mn	Smls./welded fittings
MSS SP-75	WPHY-56	...	71 (490)	1	2	101	11.1	C-Mn	Smls./welded fittings
MSS SP-75	WPHY-60	...	75 (515)	1	2	101	11.1	C-Mn	Smls./welded fittings
MSS SP-75	WPHY-65	...	77 (530)	1	2	101	11.1	C-Mn	Smls./welded fittings
MSS SP-75	WPHY-70	...	82 (565)	1	3	101	...	C-Mn	Smls./welded fittings
SA/AS 1548	PT430	...	62.5 (430)	1	1	101	1.1	C	Plate
SA/AS 1548	PT430	...	66.5 (460)	1	1	101	1.1	C	Plate
SA/AS 1548	PT430	...	71 (490)	1	2	101	1.1	C	Plate
SA/CSA-G40.21	Gr. 38W	...	60 (415)	1	1	101	1.1	C-Mn-Si	Plate, bar & shapes

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	Type or Grade	UNS No.	Minimum Specified Tensile, ksi (MPa)	Welding		Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	Group No.	P-No.			
Ferrous (Cont'd)									
SA/CSA-G40.21	Gr. 44W	...	65 (450)	1	1	101	1.2	C-Mn-Si	Plate, bar & shapes
SA/CSA-G40.21	Gr. 50W	...	65 (450)	1	1	101	1.2	C-Mn-Si	Plate, bar & shapes
SA/EN 10025-2	S235JR	...	52 (360)	1	1	...	1.1	C	Plate
SA/EN 10028-2	10CrMo9-10	...	69.5 (480)	5A	1	102	5.2	2.25Cr-1Mo	Plate ≤ 2.4 in. (60 mm)
SA/EN 10028-2	10CrMo9-10	...	68.0 (470)	5A	1	102	5.2	2.25Cr-1Mo	Plate > 2.4 in. ≤ 4 in. (60 mm - 100 mm)
SA/EN 10028-2	10CrMo9-10	...	66.5 (460)	5A	1	102	5.2	2.25Cr-1Mo	Plate > 4 in. ≤ 6 in. (100 mm - 150 mm)
SA/EN 10028-2	10CrMo9-10	...	65.5 (450)	5A	1	102	5.2	2.25Cr-1Mo	Plate > 6 in. ≤ 10 in. (150 mm - 250 mm)
SA/EN 10028-2	13CrMo4-5	...	61 (420)	4	1	102	5.1	1Cr-0.5Mo	Plate > 6 in. ≤ 10 in. (150 mm - 250 mm)
SA/EN 10028-2	13CrMo4-5	...	62.5 (430)	4	1	102	5.1	1Cr-0.5Mo	Plate > 4 in. ≤ 6 in. (100 mm - 150 mm)
SA/EN 10028-2	13CrMo4-5	...	64 (440)	4	1	102	5.1	1Cr-0.5Mo	Plate > 2.4 in. ≤ 4 in. (60 mm - 100 mm)
SA/EN 10028-2	13CrMo4-5	...	65.5 (450)	4	1	102	5.1	1Cr-0.5Mo	Plate ≤ 2.4 in. (60 mm)
SA/EN 10028-2	13CrMoSi5-5+QT	...	71 (490)	4	1	102	5.1	1.25Cr-0.5Mo-Si	Plate >4-10 in. (100mm-250mm) incl.
SA/EN 10028-2	13CrMoSi5-5+QT	...	72.5 (500)	4	1	102	5.1	1.25Cr-0.5Mo-Si	Plate >2.4-4 in. (60mm-100mm) incl.
SA/EN 10028-2	13CrMoSi5-5+QT	...	74 (510)	4	1	102	5.1	1.25Cr-0.5Mo-Si	Plate ≤ 2.4 in. (60 mm) incl.
SA/EN 10028-2	P235GH	...	52 (360)	1	1	101	1.1	C-Mn	Plate ≤ 2.4 in. (60 mm)
SA/EN 10028-2	P265GH	...	59.5 (410)	1	1	101	1.1	C-Mn	Plate ≤ 2.4 in. (60 mm)
SA/EN 10028-2	P295GH	...	64 (440)	1	1	101	1.2	C-Mn-Si	Plate > 4 in. ≤ 6 in. (> 100 mm ≤ 150 mm)
SA/EN 10028-2	P295GH	...	66.5 (460)	1	1	101	1.2	C-Mn-Si	Plate ≤ 4 in. (100 mm)
SA/EN 10028-2	P295GH	...	62.5 (430)	1	1	101	1.2	C-Mn-Si	Plate > 6 in. ≤ 10 in. (> 150 mm ≤ 250 mm)
SA/EN 10028-2	P355GH	...	68 (470)	1	2	101	1.2	C-Mn-Si	Plate > 6 in. ≤ 10 in. (150 mm-250 mm)
SA/EN 10028-2	P355GH	...	69.5 (480)	1	2	101	1.2	C-Mn-Si	Plate > 4 in. ≤ 6 in. (100 mm-150 mm)
SA/EN 10028-2	P355GH	...	71 (490)	1	2	101	1.2	C-Mn-Si	Plate > 2.4 in. ≤ 4 in. (60 mm-100 mm)
SA/EN 10028-2	P355GH	...	74 (510)	1	2	101	1.2	C-Mn-Si	Plate ≤ 2.4 in. (60 mm)
SA/EN 10028-3	P275NH	...	51 (350)	1	1	101	1.1	C	Plate > 6 in. ≤ 10 in. (150 mm-250 mm)
SA/EN 10028-3	P275NH	...	52 (360)	1	2	101	1.1	C-Mn-Si	Plate > 4 in. ≤ 6 in. (100 mm-150 mm)
SA/EN 10028-3	P275NH	...	53.5 (370)	1	1	101	1.1	C	Plate > 2 in. ≤ 4 in. (50 mm - 100 mm)
SA/EN 10028-3	P275NH	...	56.5 (390)	1	1	101	1.1	C	Plate ≤ 2 in. (50 mm)
SA/EN 10028-4	X8Ni9	...	93 (640)	11A	1	...	9.3	9Ni	Plate
SA/EN 10028-4	X7Ni9	...	98.5 (680)	11A	1	...	9.3	9Ni	Plate
SA/EN 10028-7	X2CrNi18-9	...	72.5 (500)	8	1	102	8.1	18Cr-8Ni	Plate

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	Type or Grade	UNS No.	Minimum Specified Tensile, ksi (MPa)	Welding		Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	Group No.	P-No.			
Ferrous (Cont'd)									
SA/EN 10028-7	X2CrNiN18-10	...	80 (550)	8	1	102	8.1	18Cr-8Ni-N	Plate
SA/EN 10028-7	X2CrNiMo17-12-2	...	75.5 (520)	8	1	102	8.1	16Cr-12Ni-2Mo	Plate
SA/EN 10028-7	X2CrNiMoN17-11-2	...	84 (580)	8	1	102	8.1	16Cr-12Ni-2Mo-N	Plate
SA/EN 10028-7	X2CrNiMoN17-13-3	...	84 (580)	8	1	102	8.1	16Cr-12Ni-2Mo-N	Plate
SA/EN 10028-7	X5CrNi18-10	...	75.5 (520)	8	1	102	8.1	18Cr-8Ni	Plate
SA/EN 10028-7	X5CrNiMo17-12-2	...	75.5 (520)	8	1	102	8.1	16Cr-12Ni-2Mo	Plate
SA/EN 10028-7	X5CrNiN19-9	...	80 (550)	8	1	102	8.1	18Cr-8Ni-N	Plate
SA/EN 10028-7	X6CrNiTi18-10	...	72.5 (500)	8	1	102	8.1	18Cr-10Ni-Ti	Plate
SA/EN 10088-2	X6CrNiMoTi17-12-2	...	78.5 (540)	8	1	...	8.1	16Cr-12Ni-2Mo-Ti	Plate, sheet, and strip
SA/EN 10216-2	P235GH	...	52 (360)	1	1	...	1.1	C	Smls. tube
SA/EN 10216-2	P265GH	...	59.5 (410)	1	1	...	1.1	C	Smls. tube
SA/EN 10216-2	16Mo3	...	65.5 (450)	3	1	...	1.1	C-0.5Mo	Smls. tube
SA/EN 10216-2	13CrMo4-5	...	64 (440)	4	1	...	5.1	1Cr-0.5Mo	Smls. tube
SA/EN 10216-2	10CrMo9-10	...	69.5 (480)	5A	1	...	5.2	2.25Cr-1Mo	Smls. tube
SA/EN 10216-2	X10CrMoVNb9-1	...	91.5 (630)	15E	1	...	6.4	9Cr-1Mo-V	Smls. tube
SA/EN 10217-1	P235TR2	...	52 (360)	1	1	...	1.1	C	E.R.W. tube
SA/EN 10222-2	P280GH	...	66.5 (460)	1	1	101	1.2	C-Mn-Si	Forgings
SA/EN 10222-2	P305GH	...	71 (490)	1	2	101	1.2	C-Mn-Si	Forgings
SA/EN 10222-2	13CrMo4-5	...	64 (440)	4	1	102	5.1	1Cr-0.5Mo	Forgings ≤ 10 in. (≤ 250 mm)
SA/EN 10222-2	13CrMo4-5	...	61 (420)	4	1	102	5.1	1Cr-0.5Mo	Forgings > 10 in. ≤ 20 in. (> 250 mm ≤ 500 mm)
SA/EN 10222-2	11CrMo9-10	...	75.5 (520)	5A	1	102	5.2	2.25Cr-1Mo	Forgings ≤ 8 in. (≤ 200 mm)
SA/EN 10222-2	11CrMo9-10	...	65.5 (450)	5A	1	102	5.2	2.25Cr-1Mo	Forgings > 8 in. ≤ 20 in. (> 200 mm ≤ 500 mm)
SA/EN 10222-2	X10CrMoVNb9-1	...	91.5 (630)	15E	1	102	6.4	9Cr-1Mo-V	Forgings
SA/GB 713	Q345R	...	68 (470)	1	1	101	1.1	C-Mn	Plate > 6 in. (150 mm) ≤ 10 in. (250 mm)
SA/GB 713	Q345R	...	69.5 (480)	1	1	101	1.2	C-Mn	Plate > 4 in. (100 mm) ≤ 6 in. (150 mm)
SA/GB 713	Q345R	...	71 (490)	1	2	101	1.2	C-Mn	Plate > 2.4 in. (60 mm) ≤ 4 in. (100 mm)
SA/GB 713	Q345R	...	71 (490)	1	2	101	1.2	C-Mn	Plate > 1.5 in. (36 mm) ≤ 2.4 in. (60 mm)
SA/GB 713	Q345R	...	72.5 (500)	1	2	101	1.2	C-Mn	Plate > 0.65 in. (16 mm) ≤ 1.5 in. (36 mm)

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	Type or Grade	UNS No.	Minimum Specified Tensile, ksi (MPa)	Welding		Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	Group No.	P-No.			
Ferrous (Cont'd)									
SA/GB 713	Q345R	...	74 (510)	1	2	101	1.2	C-Mn	Plate > 0.125 in. (3 mm) ≤ 0.65 in. (16 mm)
SA/GB 713	Q370R	...	75.5 (520)	1	2	101	1.2	C	Plate > 1.4 in. (36 mm) ≤ 2.4 in. (60 mm)
SA/GB 713	Q370R	...	77 (530)	1	2	101	1.2	C	Plate > 0.65 in. (16 mm) ≤ 1.4 in. (36 mm)
SA/GB 713	Q370R	...	77 (530)	1	2	101	1.3	C	Plate > 0.375 in. (10 mm) ≤ 0.65 in. (16 mm)
SA/GB 713	15CrMoR	...	64 (440)	4	1	101	5.1	1Cr-0.5Mo	Plate > 4 in. (100 mm) ≤ 6 in. (150 mm)
SA/GB 713	15CrMoR	...	65 (450)	4	1	101	5.1	1Cr-0.5Mo	Plate > 2.4 in. (60 mm) ≤ 4 in. (100 mm)
SA/GB 713	15CrMoR	...	65 (450)	4	1	101	5.1	1Cr-0.5Mo	Plate > 0.25 in. (6 mm) ≤ 2.4 in. (60 mm)
SA/IS 2062	E250 A	...	59.5 (410)	1	1	101	1.3	C-Mn-Si	Plate, bars & shapes
SA/IS 2062	E250 B	...	59.5 (410)	1	1	101	1.3	C-Mn-Si	Plate, bars & shapes
SA/IS 2062	E250 C	...	59.5 (410)	1	1	101	1.3	C-Mn-Si	Plate, bars & shapes
SA/JIS G3118	SGV480	...	70 (485)	1	2	101	1.2	C-Mn-Si	Plate
SA/JIS G4303	SUS 302	S30200	75 (515)	8	1	102	8.1	18Cr-8Ni	Bars & shapes
SA/JIS G4303	SUS 304	S30400	75 (515)	8	1	102	8.1	18Cr-8Ni	Bars & shapes
SA/JIS G4303	SUS 304L	S30403	70 (485)	8	1	102	8.1	18Cr-8Ni	Bars & shapes
SA/JIS G4303	SUS 309S	S30908	75 (515)	8	2	102	8.2	23Cr-12Ni	Bars & shapes
SA/JIS G4303	SUS 310S	S31008	75 (515)	8	2	102	8.2	25Cr-20Ni	Bars & shapes
SA/JIS G4303	SUS 316	S31600	75 (515)	8	1	102	8.1	16Cr-12Ni-2Mo	Bars & shapes
SA/JIS G4303	SUS 316L	S31603	70 (485)	8	1	102	8.1	16Cr-12Ni-2Mo	Bars & shapes
SA/JIS G4303	SUS 321	S32100	75 (515)	8	1	102	8.1	18Cr-10Ni-Ti	Bars & shapes
SA/JIS G4303	SUS 347	S34700	75 (515)	8	1	102	8.1	18Cr-10Ni-Cb	Bars & shapes
SA/JIS G4303	SUS 405	S40500	60 (415)	7	1	102	7.1	12Cr-1Al	Bars & shapes
SA/NF A 36-215	P440 NJ4	...	91.5 (630)	10A	1	101	4.1	Mn-0.5Ni-V	Plate

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	UNS No.	Alloy, Type, or Grade	Minimum Specified Tensile, ksi (MPa)	Welding	Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	P-No.			
Nonferrous								
B16	C36000	...	48 (330)	...	107	NA	65Cu-Zn-3Pb	Rod ≤ 1 in. (25 mm)
B16	C36000	...	44 (305)	...	107	NA	65Cu-Zn-3Pb	Rod > 1 in. – 2 in. (25 mm – 51 mm), incl.
B16	C36000	...	40 (275)	...	107	NA	65Cu-Zn-3Pb	Rod > 2 in. (51 mm)
B16	C36000	...	44 (305)	...	107	NA	65Cu-Zn-3Pb	Bar ≤ 1 in. (25 mm)
B16	C36000	...	40 (275)	...	107	NA	65Cu-Zn-3Pb	Bar > 1 in. (25 mm)
B/SB-26	A24430	...	17 (115)	26	...	24.1	Al-Si	Castings
B/SB-26	A03560	T71	25 (170)	26	...	24.2	Al-Si-Mg	Castings
B/SB-26	A03560	T6	30 (205)	26	...	24.2	Al-Si-Mg	Castings
B/SB-42	C10200	...	30 (205)	31	107	31	99.95Cu-P	Smls. pipe
B/SB-42	C12000	...	30 (205)	31	107	31	99.9Cu-P	Smls. pipe
B/SB-42	C12200	...	30 (205)	31	107	31	99.9Cu-P	Smls. pipe
B/SB-43	C23000	...	40 (275)	32	107	32.1	85Cu-15Zn	Smls. pipe
B/SB-61	C92200	...	30 (205)	...	107	NA	88Cu-Sn-Zn-Pb	Castings
B/SB-62	C83600	...	30 (205)	...	107	NA	85Cu-5Sn-5Zn-5Pb	Castings
B68	C10200	...	30 (205)	31	107	31	99.95Cu-P	Tube
B68	C12000	...	30 (205)	31	107	31	99.9Cu-P	Tube
B68	C12200	...	30 (205)	31	107	31	99.9Cu-P	Tube
B/SB-75	C10200	...	30 (205)	31	107	31	99.95Cu-P	Smls. tube
B/SB-75	C12000	...	30 (205)	31	107	31	99.9Cu-P	Smls. tube
B/SB-75	C12200	...	30 (205)	31	107	31	99.9Cu-P	Smls. tube
B88	C10200	...	30 (205)	31	107	31	99.95Cu-P	Tube
B88	C12000	...	30 (205)	31	107	31	99.9Cu-P	Tube
B88	C12200	...	30 (205)	31	107	31	99.9Cu-P	Tube
B/SB-96	C65500	...	50 (345)	33	107	37	97Cu-3Si	Plate, sht, strip & bar
B/SB-98	C65100	...	40 (275)	33	107	37	98.5Cu-1.5Si	Rod, bar & shapes
B/SB-98	C65500	...	52 (360)	33	107	37	97Cu-3Si	Rod, bar & shapes
B/SB-98	C66100	...	52 (360)	33	107	37	94Cu-3Si	Rod, bar & shapes
B/SB-111	C10200	...	30 (205)	31	107	31	99.95Cu-P	Smls. tube
B/SB-111	C12000	...	30 (205)	31	107	31	99.9Cu-P	Smls. tube
B/SB-111	C12200	...	30 (205)	31	107	31	99.9Cu-P	Smls. tube
B/SB-111	C14200	...	30 (205)	31	107	31	99.4Cu-As-P	Smls. tube
B/SB-111	C19200	...	38 (260)	31	107	31	99.7Cu-Fe-P	Smls. tube
B/SB-111	C23000	...	40 (275)	32	107	32.1	85Cu-15Zn	Smls. tube

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	UNS No.	Alloy, Type, or Grade	Minimum Specified Tensile, ksi (MPa)	Welding	Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	P-No.			
Nonferrous (Cont'd)								
B/SB-111	C28000	...	50 (345)	32	107	32.1	60Cu-40Zn	Smls. tube
B/SB-111	C44300	...	45 (310)	32	107	32.2	71Cu-28Zn-1Sn-0.06As	Smls. tube
B/SB-111	C44400	...	45 (310)	32	107	32.2	71Cu-28Zn-1Sn-0.06Sb	Smls. tube
B/SB-111	C44500	...	45 (310)	32	107	32.2	71Cu-28Zn-1Sn-0.06P	Smls. tube
B/SB-111	C60800	...	50 (345)	35	108	35	95Cu-5Al	Smls. tube
B/SB-111	C68700	...	50 (345)	32	108	32.2	78Cu-20Zn-2Al	Smls. tube
B/SB-111	C70400	...	38 (260)	34	107	34	95Cu-5Ni	Smls. tube
B/SB-111	C70600	...	40 (275)	34	107	34	90Cu-10Ni	Smls. tube
B/SB-111	C71000	...	45 (310)	34	107	34	80Cu-20Ni	Smls. tube
B/SB-111	C71500	...	52 (360)	34	107	34	70Cu-30Ni	Smls. tube
B/SB-111	C72200	...	45 (310)	34	107	34	80Cu-16Ni-0.75Fe-0.5Cr	Smls. tube
B/SB-127	N04400	...	70 (485)	42	110	42	67Ni-30Cu	Plate, sheet & strip
B/SB-135	C23000	...	40 (275)	32	107	32.1	85Cu-15Zn	Smls. tube
B/SB-148	C95200	...	65 (450)	35	108	35	88Cu-9Al-3Fe	Castings
B/SB-148	C95400	...	75 (515)	35	108	35	85Cu-11Al-4Fe	Castings
B/SB-148	C95300	...	65 (450)	35	108	35	89Cu-10Al-1Fe	Castings
B/SB-148	C95500	...	90 (620)	35	108	35	82Cu-11Al-4Fe-3Mn	Castings
B/SB-148	C95600	...	60 (415)	35	108	35	90Cu-7Al-3Si	Castings
B/SB-150	C61400	...	70 (485)	35	108	35	90Cu-7Al-3Fe	Rod & bar
B/SB-150	C62300	...	75 (515)	35	108	35	88Cu-9Al-3Fe	Rod (round)
B/SB-150	C63000	...	85 (585)	35	108	35	81Cu-10Al-5Ni-3Fe	Rod & bar
B/SB-150	C64200	...	70 (485)	35	108	35	91Cu-7Al-2Si	Rod & bar
B/SB-151	C70600	...	38 (260)	34	107	34	90Cu-10Ni	Rod & bar
B/SB-152	C10200	...	30 (205)	31	107	31	99.95Cu-P	Plt, sht, strip & bar
B/SB-152	C10400	...	30 (205)	31	107	31	99.95Cu + Ag	Plt, sht, strip & bar
B/SB-152	C10500	...	30 (205)	31	107	31	99.95Cu + Ag	Plt, sht, strip & bar
B/SB-152	C10700	...	30 (205)	31	107	31	99.95Cu + Ag	Plt, sht, strip & bar
B/SB-152	C11000	...	30 (205)	31	107	31	99.90Cu	Plt, sht, strip & bar
B/SB-152	C12200	...	30 (205)	31	107	31	99.9Cu-P	Plt, sht, strip & bar
B/SB-152	C12300	...	30 (205)	31	107	31	99.9Cu-P	Plt, sht, strip & bar
B/SB-152	C14200	...	30 (205)	31	107	31	99.4Cu-As-P	Plt, sht, strip & bar

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	UNS No.	Alloy, Type, or Grade	Minimum Specified Tensile, ksi (MPa)	Welding	Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	P-No.			
Nonferrous (Cont'd)								
B/SB-160	N02200	...	55 (380)	41	110	41	99.0Ni	Rod & bar
B/SB-160	N02201	...	50 (345)	41	110	41	99.0Ni-Low C	Rod & bar
B/SB-161	N02200	...	55 (380)	41	110	41	99.0Ni	Smls. pipe & tube
B/SB-161	N02201	...	50 (345)	41	110	41	99.0Ni-Low C	Smls. pipe & tube
B/SB-162	N02200	...	55 (380)	41	110	41	99.0Ni	Plate, sheet & strip
B/SB-162	N02201	...	50 (345)	41	110	41	99.0Ni-Low C	Plate, sheet & strip
B/SB-163	N02200	...	55 (380)	41	110	41	99.0Ni	Smls. tube
B/SB-163	N02201	...	50 (345)	41	110	41	99.0Ni-Low C	Smls. tube
B/SB-163	N04400	...	70 (485)	42	110	42	67Ni-30Cu	Smls. tube
B/SB-163	N06600	...	80 (550)	43	111	43	72Ni-15Cr-8Fe	Smls. tube
B/SB-163	N06601	...	80 (550)	43	111	43	60Ni-23Cr-12Fe-Al	Smls. tube
B/SB-163	N06690	...	85 (585)	43	111	43	58Ni-29Cr-9Fe	Smls. tube
B/SB-163	N08120	...	90 (620)	45	111	45	37Ni-33Fe-25Cr	Smls. tube
B/SB-163	N08800	...	75 (515)	45	111	45	33Ni-42Fe-21Cr	Smls. tube
B/SB-163	N08801	...	65 (450)	45	111	45	32Ni-45Fe-20.5Cr-Ti	Smls. tube
B/SB-163	N08810	...	65 (450)	45	111	45	33Ni-42Fe-21Cr	Smls. tube
B/SB-163	N08811	...	65 (450)	45	111	45	33Ni-42Fe-21Cr-Al-Ti	Smls. tube
B/SB-163	N08825	...	85 (585)	45	111	45	42Ni-21.5Cr-3Mo-2.3Cu	Smls. tube
B/SB-164	N04400	...	70 (485)	42	110	42	67Ni-30Cu	Rod, bar & wire
B/SB-164	N04405	...	70 (485)	42	110	42	67Ni-30Cu	Rod, bar & wire
B/SB-165	N04400	...	70 (485)	42	110	42	67Ni-30Cu	Smls. pipe & tube
B/SB-166	N06045	...	90 (620)	46	111	45	46Ni-27Cr-23Fe-2.75Si	Rod, bar & wire
B/SB-166	N06600	...	80 (550)	43	111	43	72Ni-15Cr-8Fe	Rod, bar & wire
B/SB-166	N06601	...	80 (550)	43	111	43	60Ni-23Cr-12Fe-Al	Rod, bar & wire
B/SB-166	N06617	...	95 (655)	43	111	46	52Ni-22Cr-13Co-9Mo	Rod, bar & wire
B/SB-166	N06690	...	85 (585)	43	111	43	58Ni-29Cr-9Fe	Rod, bar & wire
B/SB-167	N06045	...	90 (620)	46	111	45	46Ni-27Cr-23Fe-2.75Si	Smls. pipe & tube
B/SB-167	N06600	...	75 (515)	43	111	43	72Ni-15Cr-8Fe	Smls. pipe & tube
B/SB-167	N06601	...	80 (550)	43	111	43	60Ni-23Cr-12Fe-Al	Smls. pipe & tube
B/SB-167	N06617	...	95 (655)	43	111	46	52Ni-22Cr-13Co-9Mo	Smls. pipe & tube
B/SB-167	N06690	...	75 (515)	43	111	43	58Ni-29Cr-9Fe	Smls. pipe & tube

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	UNS No.	Alloy, Type, or Grade	Minimum Specified Tensile, ksi (MPa)	Welding	Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	P-No.			
Nonferrous (Cont'd)								
B/SB-168	N06045	...	90 (620)	46	111	45	46Ni-27Cr-23Fe-2.75Si	Plate, sheet & strip
B/SB-168	N06600	...	80 (550)	43	111	43	72Ni-15Cr-8Fe	Plate, sheet & strip
B/SB-168	N06601	...	80 (550)	43	111	43	60Ni-23Cr-12Fe-Al	Plate, sheet & strip
B/SB-168	N06617	...	95 (655)	43	111	46	52Ni-22Cr-13Co-9Mo	Plate, sheet & strip
B/SB-168	N06690	...	85 (585)	43	111	43	58Ni-29Cr-9Fe	Plate, sheet & strip
B/SB-169	C61400	...	72 (495)	35	108	35	90Cu-7Al-3Fe	Plate, sheet, strip & bar ≤ ½ in (13 mm)
B/SB-169	C61400	...	70 (485)	35	108	35	90Cu-7Al-3Fe	Plate, sheet, strip & bar > ½ in. - 2 in. (13 mm-51 mm) incl.
B/SB-169	C61400	...	65 (450)	35	108	35	90Cu-7Al-3Fe	Plate, sheet, strip & bar > 2 in. - 5 in. (51 mm-127 mm) incl.
B/SB-171	C36500	...	40 (275)	32	107	32.2	60Cu-39Zn-Pb	Plate & sheet
B/SB-171	C44300	...	45 (310)	32	107	32.2	71Cu-28Zn-1Sn-0.06As	Plate & sheet
B/SB-171	C44400	...	45 (310)	32	107	32.2	71Cu-28Zn-1Sn-0.06Sb	Plate & sheet
B/SB-171	C44500	...	45 (310)	32	107	32.2	71Cu-28Zn-1Sn-0.06P	Plate & sheet
B/SB-171	C46400	...	50 (345)	32	107	32.2	60Cu-39Zn-Sn	Plate & sheet
B/SB-171	C46500	...	50 (345)	32	107	32.2	60Cu-39Zn-As	Plate & sheet
B/SB-171	C61400	...	65 (450)	35	108	35	90Cu-7Al-3Fe	Plate & sheet > 2 in. - 5 in. (51 mm - 127 mm), incl.
B/SB-171	C61400	...	70 (485)	35	108	35	90Cu-7Al-3Fe	Plate & sheet ≤ 2 in. (51 mm)
B/SB-171	C63000	...	80 (550)	35	108	35	81Cu-10Al-5Ni-3Fe	Plate & sheet > 3½ in. - 5 in. (89 mm - 127 mm), incl.
B/SB-171	C63000	...	85 (585)	35	108	35	81Cu-10Al-5Ni-3Fe	Plate & sheet > 2 in. - 3.5 in. (51 mm - 89 mm), incl.
B/SB-171	C63000	...	90 (620)	35	108	35	81Cu-10Al-5Ni-3Fe	Plate & sheet ≤ 2 in. (51 mm)
B/SB-171	C70600	...	40 (275)	34	107	34	90Cu-10Ni	Plate & sheet
B/SB-171	C71500	...	45 (310)	34	107	34	70Cu-30Ni	Plate & sheet > 2.5 in. - 5 in. (64 mm - 127 mm), incl.
B/SB-171	C71500	...	50 (345)	34	107	34	70Cu-30Ni	Plate & sheet ≤ 2.5 in. (64 mm)
B/SB-187	C10200	O60	28 (195)	31	107	31	99.95Cu-P	Rod & bar
B/SB-187	C11000	O60	28 (195)	31	107	31	99.9Cu	Rod & bar
B/SB-209	A91060	1060	8 (55)	21	104	21	99.60Al	Plate & sheet
B/SB-209	A91100	1100	11 (76)	21	104	21	99.0Al-Cu	Plate & sheet
B/SB-209	A93003	3003	14 (97)	21	104	22.1	Al-Mn-Cu	Plate & sheet

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	UNS No.	Alloy, Type, or Grade	Minimum Specified Tensile, ksi (MPa)	Welding	Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	P-No.			
Nonferrous (Cont'd)								
B/SB-209	A93004	3004	22 (150)	22	104	22.2	Al-Mn-Mg	Plate & sheet
B/SB-209	A95052	5052	25 (170)	22	105	22.3	Al-2.5Mg	Plate & sheet
B/SB-209	A95083	5083	36 (250)	25	105	22.4	Al-4.4Mg-Mn	Plate & sheet > 7 in. – 8 in. (178 mm – 203 mm), incl.
B/SB-209	A95083	5083	37 (255)	25	105	22.4	Al-4.4Mg-Mn	Plate & sheet > 5 in. – 7 in. (127 mm – 178 mm), incl.
B/SB-209	A95083	5083	38 (260)	25	105	22.4	Al-4.4Mg-Mn	Plate & sheet > 3 in. – 5 in. (76 mm – 127 mm), incl.
B/SB-209	A95083	5083	39 (270)	25	105	22.4	Al-4.4Mg-Mn	Plate & sheet > 1.5 in. – 3 in. (38 mm – 76 mm), incl.
B/SB-209	A95083	5083	40 (275)	25	105	22.4	Al-4.4Mg-Mn	Plate & sheet > 0.05 in. – 1.5 in. (1.3 mm – 38 mm), incl.
B/SB-209	A95086	5086	35 (240)	25	105	22.4	Al-4.0Mg-Mn	Plate & sheet
B/SB-209	A95154	5154	30 (205)	22	105	22.4	Al-3.5Mg	Plate & sheet
B/SB-209	A95254	5254	30 (205)	22	105	22.4	Al-3.5Mg	Plate & sheet
B/SB-209	A95454	5454	31 (215)	22	105	22.3	Al-2.7Mg-Mn	Plate & sheet
B/SB-209	A95456	5456	38 (260)	25	105	22.4	Al-5.1Mg-Mn	Plate & sheet > 7 in. – 8 in. (178 mm – 203 mm), incl.
B/SB-209	A95456	5456	39 (270)	25	105	22.4	Al-5.1Mg-Mn	Plate & sheet > 5 in. – 7 in. (127 mm – 178 mm), incl.
B/SB-209	A95456	5456	40 (275)	25	105	22.4	Al-5.1Mg-Mn	Plate & sheet > 3 in. – 5 in. (76 mm – 127 mm), incl.
B/SB-209	A95456	5456	41 (285)	25	105	22.4	Al-5.1Mg-Mn	Plate & sheet > 1.5 in. – 3 in. (38 mm – 76 mm), incl.
B/SB-209	A95456	5456	42 (290)	25	105	22.4	Al-5.1Mg-Mn	Plate & sheet > 0.05 in. – 1.5 in. (1.3 mm – 38 mm), incl.
B/SB-209	A95652	5652	25 (170)	22	105	22.3	Al-2.5Mg	Plate & sheet
B/SB-209	A96061	6061	24 (165)	23	105	23.1	Al-Mg-Si-Cu	Plate & sheet
B/SB-209	...	Alclad 3003	13 (90)	21	104	...	Al-Mn-Cu	Plate & sheet > 0.05 in. < 0.5 in. (> 1.3 mm < 13 mm)
B/SB-209	...	Alclad 3003	14 (97)	21	104	...	Al-Mn-Cu	Plate & sheet ≥ 0.5 in. – 3 in. (13 mm – 76 mm), incl.
B/SB-209	...	Alclad 3004	21 (145)	22	104	...	Al-Mn-Mg	Plate & sheet > 0.05 in. < 0.5 in. (> 1.3 mm < 13 mm)

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	UNS No.	Alloy, Type, or Grade	Minimum Specified Tensile, ksi (MPa)	Welding	Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	P-No.			
Nonferrous (Cont'd)								
B/SB-209	...	Alclad 3004	22 (150)	22	104	...	Al-Mn-Mg	Plate & sheet ≥ 0.5 in. – 3 in. (13 mm – 76 mm), incl.
B/SB-209	...	Alclad 6061	24 (165)	23	105	...	Al-Mg-Si-Cu	Plate & sheet
B/SB-209	A95050	5050	18 (125)	21	105	22.2	Al-1.5Mg	Plate & sheet
B/SB-210	A91060	1060	8.5 (59)	21	104	21	99.60Al	Smls. tube
B/SB-210	...	Alclad 3003	13 (90)	21	104	...	Al-Mn-Cu	Smls. tube
B/SB-210	A93003	3003	14 (97)	21	104	22.1	Al-Mn-Cu	Smls. tube
B/SB-210	A95052	5052	25 (170)	22	105	22.3	Al-2.5Mg	Smls. tube
B/SB-210	A95154	5154	30 (205)	22	105	22.4	Al-3.5Mg	Smls. tube
B/SB-210	A96061	6061	24 (165)	23	105	23.1	Al-Mg-Si-Cu	Smls. tube
B/SB-210	A96063	6063	17 (115)	23	105	23.1	Al-Mg-Si	Smls. tube
B210	A95083	5083	39 (270)	25	105	22.4	Al-4.4Mg-Mn	Smls. tube
B210	A95086	5086	35 (240)	25	105	22.4	Al-4.0Mg-Mn	Smls. tube
B210	A95456	5456	41 (285)	25	105	22.4	Al-5.1Mg-Mn	Smls. tube
B/SB-211	A96061	6061	24 (165)	23	105	23.1	Al-Mg-Si-Cu	Bar, rod & wire
B/SB-221	A91060	1060	8.5 (59)	21	104	21	99.60Al	Bar, rod & shapes
B/SB-221	A91100	1100	11 (76)	21	104	21	99.0Al-Cu	Bar, rod & shapes
B/SB-221	A93003	3003	14 (97)	21	104	22.1	Al-Mn-Cu	Bar, rod & shapes
B/SB-221	A95083	5083	39 (270)	25	105	22.4	Al-4.4Mg-Mn	Bar, rod & shapes
B/SB-221	A95154	5154	30 (205)	22	105	22.4	Al-3.5Mg	Bar, rod & shapes
B/SB-221	A95454	5454	31 (215)	22	105	22.3	Al-2.7Mg-Mn	Bar, rod & shapes
B/SB-221	A95456	5456	41 (285)	25	105	22.4	Al-5.1Mg-Mn	Bar, rod & shapes
B/SB-221	A96061	6061	24 (165)	23	105	23.1	Al-Mg-Si-Cu	Bar, rod & shapes
B/SB-221	A96063	6063	17 (115)	23	105	23.1	Al-Mg-Si	Bar, rod & shapes
B/SB-234	A91060	1060	8.5 (59)	21	104	21	99.60Al	Smls. tube
B/SB-234	...	Alclad 3003	13 (90)	21	104	...	Al-Mn-Cu	Smls. tube
B/SB-234	A93003	3003	14 (97)	21	104	22.1	Al-Mn-Cu	Smls. tube
B/SB-234	A95052	5052	25 (170)	22	105	22.3	Al-2.5Mg	Smls. tube
B/SB-234	A95454	5454	31 (215)	22	105	22.3	Al-2.7Mg-Mn	Smls. tube
B/SB-234	A96061	6061	24 (165)	23	105	23.1	Al-Mg-Si-Cu	Smls. tube
A/SA-240	S31277	...	112 (770)	45	111	8.2	27Ni-22Cr-7Mo-Mn-Cu	Plate, sheet & strip

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	UNS No.	Alloy, Type, or Grade	Minimum Specified Tensile, ksi (MPa)	Welding	Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	P-No.			
Nonferrous (Cont'd)								
B/SB-241	A91060	1060	8.5 (59)	21	104	21	99.60Al	Smls. pipe & tube
B/SB-241	A91100	1100	11 (76)	21	104	21	99.0Al-Cu	Smls. pipe & tube
B/SB-241	...	Alclad 3003	13 (90)	21	104	...	Al-Mn-Cu	Smls. pipe & tube
B/SB-241	A93003	3003	14 (97)	21	104	22.1	Al-Mn-Cu	Smls. pipe & tube
B/SB-241	A95052	5052	25 (170)	22	105	22.3	Al-2.5Mg	Smls. pipe & tube
B/SB-241	A95083	5083	39 (270)	25	105	22.4	Al-4.4Mg-Mn	Smls. pipe & tube
B/SB-241	A95086	5086	35 (240)	25	105	22.4	Al-4.0Mg-Mn	Smls. pipe & tube
B/SB-241	A95454	5454	31 (215)	22	105	22.3	Al-2.7Mg-Mn	Smls. pipe & tube
B/SB-241	A95456	5456	41 (285)	25	105	22.4	Al-5.1Mg-Mn	Smls. pipe & tube
B/SB-241	A96061	6061	24 (165)	23	105	23.1	Al-Mg-Si-Cu	Smls. pipe & tube
B/SB-241	A96063	6063	17 (115)	23	105	23.1	Al-Mg-Si	Smls. pipe & tube
B/SB-247	A93003	3003	14 (97)	21	104	22.1	Al-Mn-Cu	Forgings
B/SB-247	A95083	5083	38 (260)	25	105	22.4	Al-4.4Mg-Mn	Forgings
B/SB-247	A96061	6061	24 (165)	23	105	23.1	Al-Mg-Si-Cu	Forgings
B/SB-265	R50250	1	35 (240)	51	115	51	Ti	Plate, sheet & strip
B/SB-265	R50400	2	50 (345)	51	115	51	Ti	Plate, sheet & strip
B/SB-265	R50400	2H	58 (400)	51	115	...	Ti	Plate, sheet & strip
B/SB-265	R50550	3	65 (450)	52	115	52	Ti	Plate, sheet & strip
B/SB-265	R52250	11	35 (240)	51	115	51	Ti-Pd	Plate, sheet & strip
B/SB-265	R52252	17	35 (240)	51	...	51	Ti-Pd	Plate, sheet & strip
B/SB-265	R52254	27	35 (240)	51	115	51	Ti-Ru	Plate, sheet & strip
B/SB-265	R52400	7	50 (345)	51	115	51	Ti-Pd	Plate, sheet & strip
B/SB-265	R52400	7H	58 (400)	51	115	...	Ti-Pd	Plate, sheet & strip
B/SB-265	R52402	16	50 (345)	51	115	51	Ti-Pd	Plate, sheet & strip
B/SB-265	R52402	16H	58 (400)	51	115	...	Ti-Pd	Plate, sheet & strip
B/SB-265	R52404	26	50 (345)	51	115	51	Ti-Ru	Plate, sheet & strip
B/SB-265	R52404	26H	58 (400)	51	115	...	Ti-Ru	Plate, sheet & strip
B/SB-265	R53400	12	70 (485)	52	115	52	Ti-0.3Mo-0.8Ni	Plate, sheet & strip
B/SB-265	R56320	9	90 (620)	53	115	53	Ti-3Al-2.5V	Plate, sheet & strip
B/SB-265	R56323	28	90 (620)	53	115	53	Ti-3Al-2.5V-0.1Ru	Plate, sheet & strip
B/SB-271	C95200	...	65 (450)	35	108	35	88Cu-9Al-3Fe	Castings
B/SB-271	C95400	...	75 (515)	35	108	35	85Cu-11Al-4Fe	Castings

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	UNS No.	Alloy, Type, or Grade	Minimum Specified Tensile, ksi (MPa)	Welding	Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	P-No.			
Nonferrous (Cont'd)								
B280	C10200	102	30 (205)	31	107	31	99.95Cu-P	Smls. tube
B280	C12000	120	30 (205)	31	107	31	99.9Cu-P	Smls. tube
B280	C12200	122	30 (205)	31	107	31	99.9Cu-P	Smls. tube
B/SB-283	C11000	Cu	33 (230)	31	107	31	99.9Cu	Forgings
B/SB-283	C37700	Forging brass	46 (315)	...	107	NA	60Cu-38Zn-2Pb	Forgings > 1.5 in. (38 mm)
B/SB-283	C37700	Forging brass	50 (345)	...	107	NA	60Cu-38Zn-2Pb	Forgings ≤ 1.5 in. (38 mm)
B/SB-283	C46400	Naval brass	64 (440)	32	107	32.2	60Cu-39Zn-Sn	Forgings
B/SB-283	C65500	High Si bronze	52 (360)	33	107	31	97Cu-3Si	Forgings
B/SB-283	C67500	Mn bronze	72 (495)	32	107	32.2	59Cu-39Zn-Fe-Sn	Forgings
B302	C12000	...	30 (205)	31	107	31	99.9Cu-P	Pipe
B302	C12200	...	30 (205)	31	107	31	99.9Cu-P	Pipe
B/SB-308	A96061	6061	24 (165)	23	105	23.1	Al-Mg-Si-Cu	Shapes
B/SB-315	C65500	...	50 (345)	33	107	33	97Cu-3Si	Smls. pipe & tube
B/SB-333	N10001	...	100 (690)	44	112	44	62Ni-28Mo-5Fe	Plate, sheet & strip ≥ 0.1875 in. – 2.5 in. (5 mm – 64 mm), incl.
B/SB-333	N10001	...	115 (795)	44	112	44	62Ni-28Mo-5Fe	Plate, sheet & strip < 0.1875 in. (5 mm)
B/SB-333	N10629	...	110 (760)	44	112	44	66Ni-28Mo-3Fe-1.3Cr-0.25Al	Plate, sheet & strip
B/SB-333	N10665	...	110 (760)	44	112	44	65Ni-28Mo-2Fe	Plate, sheet & strip
B/SB-333	N10675	...	110 (760)	44	112	44	65Ni-29.5Mo-2Fe-2Cr	Plate, sheet & strip
B/SB-335	N10001	...	100 (690)	44	112	44	62Ni-28Mo-5Fe	Rod > 1.5 in. – 3.5 in. (38 mm – 89 mm), incl.
B/SB-335	N10001	...	115 (795)	44	112	44	62Ni-28Mo-5Fe	Rod ≥ 0.3125 in. – 1.5 in. (8 mm – 38 mm), incl.
B/SB-335	N10629	...	110 (760)	44	112	44	66Ni-28Mo-3Fe-1.3Cr-0.25Al	Rod
B/SB-335	N10665	...	110 (760)	44	112	44	65Ni-28Mo-2Fe	Rod
B/SB-335	N10675	...	110 (760)	44	112	44	65Ni-29.5Mo-2Fe-2Cr	Rod
B/SB-338	R50250	1	35 (240)	51	115	51	Ti	Smls. & welded tube
B/SB-338	R50400	2	50 (345)	51	115	51	Ti	Smls. & welded tube
B/SB-338	R50400	2H	58 (400)	51	115	...	Ti	Smls. & welded tube
B/SB-338	R50550	3	65 (450)	52	115	52	Ti	Smls. & welded tube
B/SB-338	R52400	7	50 (345)	51	115	51	Ti-Pd	Smls. & welded tube
B/SB-338	R52400	7H	58 (400)	51	115	...	Ti-Pd	Smls. & welded tube
B/SB-338	R52402	16	50 (345)	51	115	51	Ti-Pd	Smls. & welded tube
B/SB-338	R52402	16H	58 (400)	51	115	...	Ti-Pd	Smls. & welded tube

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	UNS No.	Alloy, Type, or Grade	Minimum Specified Tensile, ksi (MPa)	Welding	Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	P-No.			
Nonferrous (Cont'd)								
B/SB-338	R52404	26	50 (345)	51	115	51	Ti-Ru	Smls. & welded tube
B/SB-338	R52404	26H	58 (400)	51	115	...	Ti-Ru	Smls. & welded tube
B/SB-338	R53400	12	70 (485)	52	115	52	Ti-0.3Mo-0.8Ni	Smls. & welded tube
B/SB-338	R56320	9	90 (620)	53	115	53	Ti-3Al-2.5V	Smls. & welded tube
B/SB-338	R56323	28	90 (620)	53	115	53	Ti-3Al-2.5V-0.1Ru	Smls. & welded tube
B345	A91060	1060	8.5 (59)	21	104	21	99.60Al	Smls. pipe & tube
B345	A93003	3003	14 (97)	21	104	22.1	Al-Mn-Cu	Smls. pipe & tube
B345	A95083	5083	39 (270)	25	105	22.4	Al-4.4Mg-Mn	Smls. pipe & tube
B345	A95086	5086	35 (240)	25	105	22.4	Al-4.0Mg-Mn	Smls. pipe & tube
B345	A96061	6061	24 (165)	23	105	23.1	Al-Mg-Si-Cu	Smls. pipe & tube
B345	A96063	6063	17 (115)	23	105	23.1	Al-Mg-Si	Smls. pipe & tube
B/SB-348	R50250	1	35 (240)	51	115	51	Ti	Bars & billets
B/SB-348	R50400	2	50 (345)	51	115	51	Ti	Bars & billets
B/SB-348	R50400	2H	58 (400)	51	115	...	Ti	Bars & billets
B/SB-348	R50550	3	65 (450)	52	115	52	Ti	Bars & billets
B/SB-348	R52400	7	50 (345)	51	115	51	Ti-Pd	Bars & billets
B/SB-348	R52400	7H	58 (400)	51	115	...	Ti-Pd	Bars & billets
B/SB-348	R52402	16H	58 (400)	51	115	...	Ti-Pd	Bars & billets
B/SB-348	R52404	26	50 (345)	51	115	51	Ti-Ru	Bars & billets
B/SB-348	R52404	26H	58 (400)	51	115	...	Ti-Ru	Bars & billets
B/SB-348	R53400	12	70 (485)	52	115	52	Ti-0.3Mo-0.8Ni	Bars & billets
B/SB-348	R52402	16	50 (345)	51	115	51	Ti-Pd	Bars & billets
B/SB-348	R56320	9	90 (620)	53	115	53	Ti-3Al-2.5V	Bars & billets
B/SB-348	R56323	28	90 (620)	53	115	53	Ti-3Al-2.5V-0.1Ru	Bars & billets
A/SA-351	N08603	HT30	65 (450)	45	111	45	35Ni-15Cr-0.5Mo	Castings
A/SA-351	J94651	CN3MN	80 (550)	45	111	8.2	46Fe-24Ni-21Cr-6Mo-Cu-N	Castings
A/SA-351	N08007	CN7M	62 (425)	45	111	8.2	28Ni-19Cr-Cu-Mo	Castings
A/SA-351	N08151	CT15C	63 (435)	45	111	45	32Ni-45Fe-20Cr-Cb	Castings
B/SB-359	C12200	...	30 (205)	31	107	31	99.9Cu-P	Smls. tube
B/SB-359	C44300	...	45 (310)	32	107	32.2	71Cu-28Zn-1Sn-0.06As	Smls. tube
B/SB-359	C44400	...	45 (310)	32	107	32.2	71Cu-28Zn-1Sn-0.06Sb	Smls. tube
B/SB-359	C44500	...	45 (310)	32	107	32.2	71Cu-28Zn-1Sn-0.06P	Smls. tube

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	UNS No.	Alloy, Type, or Grade	Minimum Specified Tensile, ksi (MPa)	Welding	Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	P-No.			
Nonferrous (Cont'd)								
B/SB-359	C70600	...	40 (275)	34	107	34	90Cu-10Ni	Smls. tube
B/SB-359	C71000	...	45 (310)	34	107	34	80Cu-20Ni	Smls. tube
B/SB-359	C71500	...	52 (360)	34	107	34	70Cu-30Ni	Smls. tube
B361	A91060	WP1060	8.5 (59)	21	104	21	99.60Al	Fittings
B361	A91100	WP1100	11 (76)	21	104	21	99.0Al-Cu	Fittings
B361	A83003	WP Alclad 3003	13 (90)	21	104	...	Al-Mn-Cu	Fittings
B361	A93003	WP3003	14 (97)	21	104	22.1	Al-Mn-Cu	Fittings
B361	A95083	5083	39 (270)	25	105	22.4	Al-4.4Mg-Mn	Fittings
B361	A95154	5154	30 (205)	22	105	22.3	Al-3.5Mg	Fittings
B361	A96061	WP6061	24 (165)	23	105	23.1	Al-Mg-Si-Cu	Fittings
B361	A96063	WP6063	17 (115)	23	105	23.1	Al-Mg-Si	Fittings
B/SB-363	R50250	WPT 1	35 (240)	51	115	51	Ti	Smls. & welded fittings
B/SB-363	R50400	WPT 2	50 (345)	51	115	51	Ti	Smls. & welded fittings
B/SB-363	R50550	WPT 3	65 (450)	52	115	52	Ti	Smls. & welded fittings
B/SB-363	R52400	WPT 7	50 (345)	51	115	51	Ti-Pd	Smls. & welded fittings
B/SB-363	R52400	WPT 7H	58 (400)	51	115	...	Ti-Pd	Smls. & welded fittings
B/SB-363	R52402	WPT 16	50 (345)	51	115	...	Ti-Pd	Smls. & welded fittings
B/SB-363	R52402	WPT 16H	58 (400)	51	115	...	Ti-Pd	Smls. & welded fittings
B/SB-363	R52404	WPT 26	50 (345)	51	115	51	Ti-Ru	Smls. & welded fittings
B/SB-363	R52404	WPT 26H	58 (400)	51	115	...	Ti-Ru	Smls. & welded fittings
B/SB-363	R53400	WPT 12	70 (485)	52	115	52	Ti-0.3Mo-0.8Ni	Smls. & welded fittings
B/SB-363	R56320	WPT 9	90 (620)	53	115	53	Ti-3Al-2.5V	Smls. & welded fittings
B/SB-363	R56323	WPT28	90 (620)	53	115	53	Ti-3Al-2.5V-0.1Ru	Smls. & welded fittings
B/SB-366	N02200	...	55 (380)	41	110	41	99.0Ni	Fittings
B/SB-366	N02201	...	50 (345)	41	110	41	99.0Ni-Low C	Fittings
B/SB-366	N04400	...	70 (485)	42	110	42	67Ni-30Cu	Fittings
B/SB-366	N06002	...	100 (690)	43	111	43	47Ni-22Cr-18Fe-9Mo	Fittings
B/SB-366	N06007	...	90 (620)	45	111	43	47Ni-22Cr-19Fe-6Mo	Fittings
B/SB-366	N06022	...	100 (690)	43	111	44	55Ni-21Cr-13.5Mo	Fittings
B/SB-366	N06030	...	85 (585)	45	111	45	40Ni-29Cr-15Fe-5Mo	Fittings
B/SB-366	N06035	...	85 (585)	43	111	...	58Ni-33Cr-8Mo	Fittings
B/SB-366	N06045	...	90 (620)	46	111	45	46Ni-27Cr-23Fe-2.75Si	Fittings
B/SB-366	N06059	...	100 (690)	43	111	43	59Ni-23Cr-16Mo	Fittings

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	UNS No.	Alloy, Type, or Grade	Minimum Specified Tensile, ksi (MPa)	Welding	Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	P-No.			
Nonferrous (Cont'd)								
B/SB-366	N06200	...	100 (690)	43	111	43	59Ni-23Cr-16Mo-1.6Cu	Fittings
B/SB-366	N06210	...	100 (690)	43	111	...	60Ni-19Cr-19Mo-1.8Ta	Fittings
B/SB-366	N06230	...	110 (760)	43	111	43	53Ni-22Cr-14W-Co-Fe-Mo	Fittings
B/SB-366	N06455	...	100 (690)	43	111	43	61Ni-15Mo-16Cr	Fittings
B/SB-366	N06600	...	80 (550)	43	111	43	72Ni-15Cr-8Fe	Fittings
B/SB-366	N06625	...	110 (760)	43	111	43	60Ni-22Cr-9Mo-3.5Cb	Fittings
B/SB-366	N06985	...	90 (620)	45	111	45	47Ni-22Cr-20Fe-7Mo	Fittings
B/SB-366	N08020	...	80 (550)	45	111	45	35Ni-35Fe-20Cr-Cb	Fittings
B/SB-366	N08031	...	94 (650)	45	111	45	31Ni-31Fe-27Cr-7Mo	Fittings
B/SB-366	N08120	...	90 (620)	45	111	45	37Ni-33Fe-25Cr	Fittings
B/SB-366	N08330	...	70 (485)	46	111	45	35Ni-19Cr-1.25Si	Fittings
B/SB-366	N08367	...	95 (655)	45	111	8.2	46Fe-24Ni-21Cr-6Mo-Cu-N	Fittings > 3⁄16 in. (5 mm)
B/SB-366	N08367	...	100 (690)	45	111	8.2	46Fe-24Ni-21Cr-6Mo-Cu-N	Fittings ≤ 3⁄16 in. (5 mm)
B/SB-366	N08800	...	75 (515)	45	111	45	33Ni-42Fe-21Cr	Fittings
B/SB-366	N08825	...	85 (585)	45	111	45	42Ni-21.5Cr-3Mo-2.3Cu	Fittings
B/SB-366	N08925	...	87 (600)	45	111	8.2	25Ni-20Cr-6Mo-Cu-N	Fittings
B/SB-366	N10001	...	100 (690)	44	112	44	62Ni-28Mo-5Fe	Fittings
B/SB-366	N10003	...	100 (690)	44	112	44	70Ni-16Mo-7Cr-5Fe	Fittings
B/SB-366	N10242	...	105 (725)	44	112	44	62Ni-25Mo-8Cr-2Fe	Fittings
B/SB-366	N10276	...	100 (690)	43	111	43	54Ni-16Mo-15Cr	Fittings
B/SB-366	N10629	...	110 (760)	44	112	44	66Ni-28Mo-3Fe-1.3Cr-0.25Al	Fittings
B/SB-366	N10665	...	110 (760)	44	112	44	65Ni-28Mo-2Fe	Fittings
B/SB-366	N10675	...	110 (760)	44	112	44	65Ni-29.5Mo-2Fe-2Cr	Fittings
B/SB-366	N12160	...	90 (620)	46	...	46	37Ni-30Co-28Cr-2.7Si	Fittings
B/SB-366	R20033	...	109 (750)	45	111	45	33Cr-31Ni-32Fe-1.5Mo-0.6Cu-N	Fittings
B/SB-366	R30556	...	100 (690)	45	111	45	21Ni-30Fe-22Cr-18Co-3Mo-3W	Fittings
B/SB-366	N08926	...	94 (650)	45	111	8.2	25Ni-20Cr-6Mo-Cu-N	Fittings
B/SB-367	R50400	Gr. C-2	50 (345)	51	115	51	Ti	Castings
B/SB-367	R50550	Gr. C-3	65 (450)	52	115	52	Ti	Castings
B/SB-369	C96200	...	45 (310)	34	107	34	87.5Cu-10Ni-Fe-Mn	Castings
B/SB-381	R50250	F-1	35 (240)	51	115	51	Ti	Forgings

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	UNS No.	Alloy, Type, or Grade	Minimum Specified Tensile, ksi (MPa)	Welding	Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	P-No.			
Nonferrous (Cont'd)								
B/SB-381	R50400	F-2	50 (345)	51	115	51	Ti	Forgings
B/SB-381	R50400	F-2H	58 (400)	51	115	...	Ti	Forgings
B/SB-381	R50550	F-3	65 (450)	52	115	52	Ti	Forgings
B/SB-381	R52400	F-7	50 (345)	51	115	51	Ti-Pd	Forgings
B/SB-381	R52400	F-7H	58 (400)	51	115	...	Ti-Pd	Forgings
B/SB-381	R52402	F-16	50 (345)	51	115	51	Ti-Pd	Forgings
B/SB-381	R52402	F-16H	58 (400)	51	115	...	Ti-Pd	Forgings
B/SB-381	R52404	F-26	50 (345)	51	115	51	Ti-Ru	Forgings
B/SB-381	R52404	F-26H	58 (400)	51	115	...	Ti-Ru	Forgings
B/SB-381	R53400	F-12	70 (485)	52	115	52	Ti-0.3Mo-0.8Ni	Forgings
B/SB-381	R56320	F-9	90 (620)	53	115	53	Ti-3Al-2.5V	Forgings
B/SB-381	R56323	F-28	90 (620)	53	115	53	Ti-3Al-2.5V-0.1Ru	Forgings
B/SB-395	C10200	...	30 (205)	31	107	31	99.95Cu-P	Smls. tube
B/SB-395	C12000	...	30 (205)	31	107	31	99.9Cu-P	Smls. tube
B/SB-395	C12200	...	30 (205)	31	107	31	99.9Cu-P	Smls. tube
B/SB-395	C14200	...	30 (205)	31	107	31	99.4Cu-As-P	Smls. tube
B/SB-395	C19200	...	38 (260)	31	107	31	99.7Cu-Fe-P	Smls. tube
B/SB-395	C23000	...	40 (275)	32	107	32.1	85Cu-15Zn	Smls. tube
B/SB-395	C44300	...	45 (310)	32	107	32.2	71Cu-28Zn-1Sn-0.06As	Smls. tube
B/SB-395	C44400	...	45 (310)	32	107	32.2	71Cu-28Zn-1Sn-0.06Sb	Smls. tube
B/SB-395	C44500	...	45 (310)	32	107	32.2	71Cu-28Zn-1Sn-0.06P	Smls. tube
B/SB-395	C60800	...	50 (345)	35	108	35	95Cu-5Al	Smls. tube
B/SB-395	C68700	...	50 (345)	32	108	32.2	78Cu-20Zn-2Al	Smls. tube
B/SB-395	C70600	...	40 (275)	34	107	34	90Cu-10Ni	Smls. tube
B/SB-395	C71000	...	45 (310)	34	107	34	80Cu-20Ni	Smls. tube
B/SB-395	C71500	...	52 (360)	34	107	34	70Cu-30Ni	Smls. tube
B/SB-407	N08120	...	90 (620)	45	111	45	37Ni-33Fe-25Cr	Smls. pipe & tube
B/SB-407	N08800	...	75 (515)	45	111	45	33Ni-42Fe-21Cr	Smls. pipe & tube
B/SB-407	N08801	...	65 (450)	45	111	45	32Ni-45Fe-20.5Cr-Ti	Smls. pipe & tube
B/SB-407	N08810	...	65 (450)	45	111	45	33Ni-42Fe-21Cr	Smls. pipe & tube
B/SB-407	N08811	...	65 (450)	45	111	45	33Ni-42Fe-21Cr-Al-Ti	Smls. pipe & tube
B/SB-408	N08120	...	90 (620)	45	111	45	37Ni-33Fe-25Cr	Rod & bar
B/SB-408	N08800	...	75 (515)	45	111	45	33Ni-42Fe-21Cr	Rod & bar

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	UNS No.	Alloy, Type, or Grade	Minimum Specified Tensile, ksi (MPa)	Welding	Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	P-No.			
Nonferrous (Cont'd)								
B/SB-408	N08810	...	65 (450)	45	111	45	33Ni-42Fe-21Cr	Rod & bar
B/SB-408	N08811	...	65 (450)	45	111	45	33Ni-42Fe-21Cr-Al-Ti	Rod & bar
B/SB-409	N08120	...	90 (620)	45	111	45	37Ni-33Fe-25Cr	Plate, sheet & strip
B/SB-409	N08800	...	75 (515)	45	111	45	33Ni-42Fe-21Cr	Plate, sheet & strip
B/SB-409	N08810	...	65 (450)	45	111	45	33Ni-42Fe-21Cr	Plate, sheet & strip
B/SB-409	N08811	...	65 (450)	45	111	45	33Ni-42Fe-21Cr-Al-Ti	Plate, sheet & strip
B/SB-423	N08825	...	75 (515)	45	111	45	42Ni-21.5Cr-3Mo-2.3Cu	Smls. pipe & tube
B/SB-424	N08825	...	85 (585)	45	111	45	42Ni-21.5Cr-3Mo-2.3Cu	Plate, sheet & strip
B/SB-425	N08825	...	85 (585)	45	111	45	42Ni-21.5Cr-3Mo-2.3Cu	Rod & bar
B/SB-434	N10003	...	100 (690)	44	112	44	70Ni-16Mo-7Cr-5Fe	Plate, sheet & strip
B/SB-434	N10242	...	105 (725)	44	112	44	62Ni-25Mo-8Cr-2Fe	Plate, sheet & strip
B/SB-435	N06002	...	95 (655)	43	111	43	47Ni-22Cr-9Mo-18Fe	Plate, sheet & strip
B/SB-435	N06230	...	110 (760)	43	111	43	53Ni-22Cr-14W-Co-Fe-Mo	Plate, sheet & strip
B/SB-435	N12160	...	90 (620)	46	...	46	37Ni-30Co-28Cr-2.7Si	Plate, sheet, & strip
B/SB-435	R30556	...	100 (690)	45	111	45	21Ni-30Fe-22Cr-18Co-3Mo-3W	Plate, sheet & strip
B/SB-443	N06625	2	100 (690)	43	111	43	60Ni-22Cr-9Mo-3.5Cb	Plate, sheet & strip
B/SB-443	N06625	1	110 (760)	43	111	43	60Ni-22Cr-9Mo-3.5Cb	Plate, sheet & strip
B/SB-444	N06625	1	120 (825)	43	111	43	60Ni-22Cr-9Mo-3.5Cb	Smls. pipe & tube
B/SB-444	N06625	2	100 (690)	43	111	43	60Ni-22Cr-9Mo-3.5Cb	Smls. pipe & tube
B/SB-446	N06625	1	120 (825)	43	111	43	60Ni-22Cr-9Mo-3.5Cb	Rod & bar
B/SB-446	N06625	2	100 (690)	43	111	43	60Ni-22Cr-9Mo-3.5Cb	Rod & bar
B/SB-462	N06022	...	100 (690)	43	111	44	55Ni-21Cr-13.5Mo	Forgings
B/SB-462	N06030	...	85 (585)	45	111	45	40Ni-29Cr-15Fe-5Mo	Forgings
B/SB-462	N06035	...	85 (585)	43	111	...	58Ni-33Cr-8Mo	Forgings
B/SB-462	N06045	...	90 (620)	46	111	45	46Ni-27Cr-23Fe-2.75Si	Forgings
B/SB-462	N06059	...	100 (690)	43	111	43	59Ni-23Cr-16Mo	Forgings
B/SB-462	N06200	...	100 (690)	43	111	43	59Ni-23Cr-16Mo-1.6Cu	Forgings
B/SB-462	N06686	...	100 (690)	43	111	43	58Ni-21Cr-16Mo-3.5N	Forgings
B/SB-462	N08020	...	80 (550)	45	111	45	35Ni-35Fe-20Cr-Cb	Forgings
B/SB-462	N08031	...	94 (650)	45	111	45	31Ni-33Fe-22Cr-6.5Mo-Cu-N	Forgings
B/SB-462	N08367	...	95 (655)	45	111	8.2	46Fe-24Ni-21Cr-6Mo-Cu-N	Forgings

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	UNS No.	Alloy, Type, or Grade	Minimum Specified Tensile, ksi (MPa)	Welding	Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	P-No.			
Nonferrous (Cont'd)								
B/SB-462	N10276	...	100 (690)	43	111	43	54Ni-16Mo-15Cr	Forgings
B/SB-462	N10629	...	110 (760)	44	112	44	66Ni-28Mo-3Fe-1.3Cr-0.25Al	Forgings
B/SB-462	N10665	...	110 (760)	44	112	44	65Ni-28Mo-2Fe	Forgings
B/SB-462	N10675	...	110 (760)	44	112	44	65Ni-29.5Mo-2Fe-2Cr	Forgings
B/SB-462	R20033	...	109 (750)	45	111	45	33Cr-31Ni-32Fe-1.5Mo-0.6Cu-N	Forgings
B/SB-463	N08020	...	80 (550)	45	111	45	35Ni-35Fe-20Cr-Cb	Plate, sheet & strip
B/SB-463	N08024	...	80 (550)	45	111	45	37Ni-33Fe-23Cr-4Mo	Plate, sheet & strip
B/SB-463	N08026	...	80 (550)	45	111	45	35Ni-30Fe-24Cr-6Mo-3Cu	Plate, sheet & strip
B/SB-464	N08020	...	80 (550)	45	111	45	35Ni-35Fe-20Cr-Cb	Welded pipe
B/SB-464	N08024	...	80 (550)	45	111	45	37Ni-33Fe-23Cr-4Mo	Welded pipe
B/SB-464	N08026	...	80 (550)	45	111	45	35Ni-30Fe-24Cr-6Mo-3Cu	Welded pipe
B/SB-466	C70600	...	38 (260)	34	107	34	90Cu-10Ni	Smls. pipe & tube
B/SB-466	C71000	...	45 (310)	34	107	34	80Cu-20Ni	Smls. pipe & tube
B/SB-466	C71500	...	52 (360)	34	107	34	70Cu-30Ni	Smls. pipe & tube
B/SB-467	C70600	...	38 (260)	34	107	34	90Cu-10Ni	Welded pipe > 4.5 in. (114 mm) O.D.
B/SB-467	C70600	...	40 (275)	34	107	34	90Cu-10Ni	Welded pipe ≤ 4.5 in. (114 mm) O.D.
B/SB-467	C71500	...	45 (310)	34	107	34	70Cu-30Ni	Welded pipe > 4.5 in. (114 mm) O.D.
B/SB-467	C71500	...	50 (345)	34	107	34	70Cu-30Ni	Welded pipe ≤ 4.5 in. (114 mm) O.D.
B/SB-468	N08020	...	80 (550)	45	111	45	35Ni-35Fe-20Cr-Cb	Welded tube
B/SB-468	N08024	...	80 (550)	45	111	45	37Ni-33Fe-23Cr-4Mo	Welded tube
B/SB-468	N08026	...	80 (550)	45	111	45	35Ni-30Fe-24Cr-6Mo-3Cu	Welded tube
B/SB-473	N08020	...	80 (550)	45	111	45	35Ni-35Fe-20Cr-Cb	Bar
B491	A93003	3003	14 (97)	21	104	22.1	Al-Mn-Cu	Extruded tubes
B/SB-493	R60702	R60702	55 (380)	61	117	61	99.2Zr	Forgings
B/SB-493	R60705	R60705	70 (485)	62	117	62	95.5Zr + 2.5Cb	Forgings
A/SA-494	N04020	M35-2	65 (450)	42	110	42	67Ni-30Cu-Fe-Si	Castings
A/SA-494	N06040	CY40	70 (485)	43	111	43	72Ni-15Cr-8Fe-Si	Castings
A/SA-494	N08826	CU5MCuC	75 (515)	45	111	45	42Ni-21.5Cr-3Mo-2.3Cu	Castings
A/SA-494	N24130	M30C	65 (450)	42	110	42	67Ni-30Cu-2Fe-Cb	Castings
A/SA-494	N24135	M35-1	65 (450)	42	110	42	67Ni-30Cu-2Fe-Cb	Castings
A/SA-494	N26022	CX2MW	80 (550)	43	111	44	59Ni-22Cr-14Mo-4Fe-3W	Castings

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	UNS No.	Alloy, Type, or Grade	Minimum Specified Tensile, ksi (MPa)	Welding	Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	P-No.			
Nonferrous (Cont'd)								
A/SA-494	N26455	CW2M	72 (495)	43	111	43	66Ni-16Mo-16Cr-Fe-W	Castings
A/SA-494	N26625	CW6MC	70 (485)	43	111	43	60Ni-21.5Cr-9Mo-4Cb-Fe	Castings
A/SA-494	N30007	N7M	76 (525)	44	112	44	65Ni-31.5Mo-1.5Fe-Cr	Castings
A/SA-494	N30107	CW6M	72 (495)	44	112	44	56Ni-19Mo-18Cr-2Fe	Castings
B/SB-505	C95200	...	68 (470)	35	108	35	88Cu-9Al-3Fe	Castings
B/SB-511	N08330	...	70 (485)	46	111	45	35Ni-19Cr-1.25Si	Bars & shapes
B/SB-514	N08120	...	90 (620)	45	111	45	37Ni-33Fe-25Cr	Welded pipe
B/SB-514	N08800	...	75 (515)	45	111	45	33Ni-42Fe-21Cr	Welded pipe
B/SB-514	N08810	...	65 (450)	45	111	45	33Ni-42Fe-21Cr	Welded pipe
B/SB-515	N08120	...	90 (620)	45	111	45	37Ni-33Fe-25Cr	Welded tube
B/SB-515	N08800	...	75 (515)	45	111	45	33Ni-42Fe-21Cr	Welded tube
B/SB-515	N08810	...	65 (450)	45	111	45	33Ni-42Fe-21Cr	Welded tube
B/SB-515	N08811	...	65 (450)	45	111	45	33Ni-42Fe-21Cr-Al-Ti	Welded tube
B/SB-516	N06045	...	90 (620)	46	111	45	46Ni-27Cr-23Fe-2.75Si	Welded tube
B/SB-516	N06600	...	80 (550)	43	111	43	72Ni-15Cr-8Fe	Welded tube
B/SB-517	N06045	...	90 (620)	46	111	45	46Ni-27Cr-23Fe-2.75Si	Welded pipe
B/SB-517	N06600	...	80 (550)	43	111	43	72Ni-15Cr-8Fe	Welded pipe
B/SB-523	R60702	R60702	55 (380)	61	117	61	99.2Zr	Smls. & welded tube
B/SB-523	R60705	R60705	80 (550)	62	117	62	95.5Zr + 2.5Cb	Smls. & welded tube
B/SB-535	N08330	...	70 (485)	46	111	45	35Ni-19Cr-1.25Si	Smls. pipe & tube
B/SB-536	N08330	...	70 (485)	46	111	45	35Ni-19Cr-1.25Si	Plate, sheet & strip
B/SB-543	C12200	...	30 (205)	31	107	31	99.9Cu-P	Welded tube
B/SB-543	C19400	...	45 (310)	31	107	31	97.5Cu-P	Welded tube
B/SB-543	C23000	...	40 (275)	32	107	32.1	85Cu-15Zn	Welded tube
B/SB-543	C44300	...	45 (310)	32	107	32.2	71Cu-28Zn-1Sn-0.06As	Welded tube
B/SB-543	C44400	...	45 (310)	32	107	32.2	71Cu-28Zn-1Sn-0.06Sb	Welded tube
B/SB-543	C44500	...	45 (310)	32	107	32.2	71Cu-28Zn-1Sn-0.06P	Welded tube
B/SB-543	C68700	...	50 (345)	32	108	32.2	78Cu-20Zn-2Al	Welded tube
B/SB-543	C70400	...	38 (260)	34	107	34	95Cu-5Ni	Welded tube
B/SB-543	C70600	...	40 (275)	34	107	34	90Cu-10Ni	Welded tube

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	UNS No.	Alloy, Type, or Grade	Minimum Specified Tensile, ksi (MPa)	Welding	Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	P-No.			
Nonferrous (Cont'd)								
B/SB-543	C71500	...	52 (360)	34	107	34	70Cu-30Ni	Welded tube
B547	A83003	Alclad 3003	13 (90)	21	104	...	Al-Mn-Cu	Welded tube
B547	A93003	3003	14 (97)	21	104	22.1	Al-Mn-Cu	Welded tube
B547	A95083	5083	40 (275)	25	105	22.4	Al-4.4Mg-Mn	Welded tube
B547	A95454	5454	31 (215)	22	105	22.3	Al-2.7Mg-Mn	Welded tube
B547	A96061	6061	24 (165)	23	105	23.1	Al-Mg-Si-Cu	Welded tube
B/SB-550	R60702	R60702	55 (380)	61	117	61	99.2Zr	Bar & wire
B/SB-550	R60705	R60705	80 (550)	62	117	62	95.5Zr + 2.5Cb	Bar & wire
B/SB-551	R60702	R60702	55 (380)	61	117	61	99.2Zr	Plate, sheet & strip
B/SB-551	R60705	R60705	80 (550)	62	117	62	95.5Zr + 2.5Cb	Plate, sheet & strip
B/SB-564	N04400	...	70 (485)	42	110	42	67Ni-30Cu	Forgings
B/SB-564	N06022	...	100 (690)	43	111	44	55Ni-21Cr-13.5Mo	Forgings
B/SB-564	N06035	...	85 (585)	43	111	...	58Ni-33Cr-8Mo	Forgings
B/SB-564	N06045	...	90 (620)	46	111	45	46Ni-27Cr-23Fe-2.75Si	Forgings
B/SB-564	N06059	...	100 (690)	43	111	43	59Ni-23Cr-16Mo	Forgings
B/SB-564	N06200	...	100 (690)	43	111	43	59Ni-23Cr-16Mo-1.6Cu	Forgings
B/SB-564	N06210	...	100 (690)	43	111	...	60Ni-19Cr-19Mo-1.8Ta	Forgings
B/SB-564	N06230	...	110 (760)	43	111	43	53Ni-22Cr-14W-Co-Fe-Mo	Forgings
B/SB-564	N06600	...	80 (550)	43	111	43	72Ni-15Cr-8Fe	Forgings
B/SB-564	N06617	...	95 (655)	43	111	46	52Ni-22Cr-13Co-9Mo	Forgings
B/SB-564	N06625	...	110 (760)	43	111	43	60Ni-22Cr-9Mo-3.5Cb	Forgings > 4 in. - 10 in. (102 mm - 254 mm), incl.
B/SB-564	N06686	...	100 (690)	43	111	43	58Ni-21Cr-16Mo-3.5W	Forgings
B/SB-564	N06625	...	120 (825)	43	111	43	60Ni-22Cr-9Mo-3.5Cb	Forgings ≤ 4 in. (102 mm)
B/SB-564	N06690	...	85 (585)	43	111	43	58Ni-29Cr-9Fe	Forgings
B/SB-564	N08031	...	94 (650)	45	111	45	31Ni-31Fe-27Cr-7Mo	Forgings
B/SB-564	N08120	...	90 (620)	45	111	45	37Ni-33Fe-25Cr	Forgings
B/SB-564	N08367	...	95 (655)	45	111	8.2	46Fe-24Ni-21Cr-6Mo-Cu-N	Forgings
B/SB-564	N08800	...	75 (515)	45	111	45	33Ni-42Fe-21Cr	Forgings
B/SB-564	N08810	...	65 (450)	45	111	45	33Ni-42Fe-21Cr	Forgings
B/SB-564	N08811	...	65 (450)	45	111	44	33Ni-42Fe-21Cr-Al-Ti	Forgings
B/SB-564	N08825	...	85 (585)	45	111	45	42Ni-21.5Cr-3Mo-2.3Cu	Forgings
B/SB-564	N10242	...	105 (725)	44	112	44	62Ni-25Mo-8Cr-2Fe	Forgings
B/SB-564	N10276	...	100 (690)	43	111	43	54Ni-16Mo-15Cr	Forgings

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	UNS No.	Alloy, Type, or Grade	Minimum Specified Tensile, ksi (MPa)	Welding	Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	P-No.			
Nonferrous (Cont'd)								
B/SB-564	N10629	...	110 (760)	44	112	44	66Ni-28Mo-3Fe-1.3Cr-0.25Al	Forgings
B/SB-564	N10665	...	110 (760)	44	112	...	65Ni-28Mo-2Fe	Forgings
B/SB-564	N10675	...	110 (760)	44	112	44	65Ni-29.5Mo-2Fe-2Cr	Forgings
B/SB-564	R20033	...	109 (750)	45	111	45	33Cr-31Ni-32Fe-1.5Mo-0.6Cu-N	Forgings
B/SB-564	N12160	...	90 (620)	46	...	46	37Ni-30Co-28Cr-2.7Si	Forgings
B/SB-572	N06002	...	95 (655)	43	111	43	47Ni-22Cr-9Mo-18Fe	Rod
B/SB-572	N06230	...	110 (760)	43	111	43	53Ni-22Cr-14W-Co-Fe-Mo	Rod
B/SB-572	N12160	...	90 (620)	46	...	46	37Ni-30Co-28Cr-2.7Si	Rod
B/SB-572	R30556	...	100 (690)	45	111	45	21Ni-30Fe-22Cr-18Co-3Mo-3W	Rod
B/SB-573	N10003	...	100 (690)	44	112	44	70Ni-16Mo-7Cr-5Fe	Rod
B/SB-573	N10242	...	105 (725)	44	112	44	62Ni-25Mo-8Cr-2Fe	Rod
B/SB-574	N06022	...	100 (690)	43	111	44	55Ni-21Cr-13.5Mo	Rod
B/SB-574	N06035	...	85 (585)	43	111	...	58Ni-33Cr-8Mo	Rod
B/SB-574	N06059	...	100 (690)	43	111	43	59Ni-23Cr-16Mo	Rod
B/SB-574	N06200	...	100 (690)	43	111	43	59Ni-23Cr-16Mo-1.6Cu	Rod
B/SB-574	N06210	...	100 (690)	43	111	...	60Ni-19Cr-19Mo-1.8Ta	Rod
B/SB-574	N06455	...	100 (690)	43	111	43	61Ni-16Mo-16Cr	Rod
B/SB-574	N06686	...	100 (690)	43	111	43	58Ni-21Cr-16Mo-3.5W	Rod
B/SB-574	N10276	...	100 (690)	43	111	43	54Ni-16Mo-15Cr	Rod
B/SB-575	N06022	...	100 (690)	43	111	44	55Ni-21Cr-13.5Mo	Plate, sheet & strip
B/SB-575	N06035	...	85 (585)	43	111	...	58Ni-33Cr-8Mo	Plate, sheet & strip
B/SB-575	N06059	...	100 (690)	43	111	43	59Ni-23Cr-16Mo	Plate, sheet & strip
B/SB-575	N06200	...	100 (690)	43	111	43	59Ni-23Cr-16Mo-1.6Cu	Plate, sheet & strip
B/SB-575	N06210	...	100 (690)	43	111	...	60Ni-19Cr-19Mo-1.8Ta	Plate, sheet & strip
B/SB-575	N06455	...	100 (690)	43	111	43	61Ni-16Mo-16Cr	Plate, sheet & strip
B/SB-575	N06686	...	100 (690)	43	111	43	58Ni-21Cr-16Mo-3.5W	Plate, sheet & strip
B/SB-575	N10276	...	100 (690)	43	111	43	54Ni-16Mo-15Cr	Plate, sheet & strip
B/SB-581	N06007	...	85 (585)	45	111	43	47Ni-22Cr-19Fe-6Mo	Rod > 0.75 in. - 3.5 in. (19 mm - 89 mm), incl.
B/SB-581	N06007	...	90 (620)	45	111	43	47Ni-22Cr-19Fe-6Mo	Rod, 0.3125 in. - 0.75 in. (8 mm - 19 mm), incl.
B/SB-581	N06030	...	85 (585)	45	111	45	40Ni-29Cr-15Fe-5Mo	Rod
B/SB-581	N06975	...	85 (585)	45	111	45	49Ni-25Cr-18Fe-6Mo	Rod
B/SB-581	N06985	...	85 (585)	45	111	45	47Ni-22Cr-20Fe-7Mo	Rod > 0.75 in. - 3.5 in. (19 mm - 89 mm), incl.
B/SB-581	N06985	...	90 (620)	45	111	45	47Ni-22Cr-20Fe-7Mo	Rod, 0.3125 in. - 0.75 in. (8 mm - 19 mm), incl.

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	UNS No.	Alloy, Type, or Grade	Minimum Specified Tensile, ksi (MPa)	Welding	Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	P-No.			
Nonferrous (Cont'd)								
B/SB-581	N08031	...	94 (650)	45	111	45	31Ni-31Fe-27Cr-7Mo	Rod
B/SB-582	N06007	...	85 (585)	45	111	43	47Ni-22Cr-19Fe-6Mo	Plate, sheet & strip > 0.75 in. – 2.5 in. (19 mm – 64 mm), incl.
B/SB-582	N06007	...	90 (620)	45	111	43	47Ni-22Cr-19Fe-6Mo	Plate, sheet & strip ≤ 0.75 in. (19 mm)
B/SB-582	N06030	...	85 (585)	45	111	45	40Ni-29Cr-15Fe-5Mo	Plate, sheet & strip
B/SB-582	N06975	...	85 (585)	45	111	45	49Ni-25Cr-18Fe-6Mo	Plate, sheet & strip
B/SB-582	N06985	...	85 (585)	45	111	45	47Ni-22Cr-20Fe-7Mo	Plate, sheet & strip > 0.75 in. – 2.5 in. (19 mm – 64 mm), incl.
B/SB-582	N06985	...	90 (620)	45	111	45	47Ni-22Cr-20Fe-7Mo	Plate, sheet & strip ≤ 0.75 in. (19 mm)
B/SB-599	N08700	...	80 (550)	45	111	8.2	25Ni-47Fe-21Cr-5Mo	Plate, sheet & strip
B/SB-619	N06002	...	100 (690)	43	111	43	47Ni-22Cr-9Mo-18Fe	Welded pipe
B/SB-619	N06007	...	90 (620)	45	111	43	47Ni-22Cr-19Fe-6Mo	Welded pipe
B/SB-619	N06022	...	100 (690)	43	111	44	55Ni-21Cr-13.5Mo	Welded pipe
B/SB-619	N06030	...	85 (585)	45	111	45	40Ni-29Cr-15Fe-5Mo	Welded pipe
B/SB-619	N06035	...	85 (585)	43	111	...	58Ni-33Cr-8Mo	Welded pipe
B/SB-619	N06059	...	100 (690)	43	111	43	59Ni-23Cr-16Mo	Welded pipe
B/SB-619	N06200	...	100 (690)	43	111	43	59Ni-23Cr-16Mo-1.6Cu	Welded pipe
B/SB-619	N06210	...	100 (690)	43	111	...	60Ni-19Cr-19Mo-1.8Ta	Welded pipe
B/SB-619	N06230	...	110 (760)	43	111	43	53Ni-22Cr-14W-Co-Fe-Mo	Welded pipe
B/SB-619	N06455	...	100 (690)	43	111	43	61Ni-16Mo-16Cr	Welded pipe
B/SB-619	N06686	...	100 (690)	43	111	43	58Ni-21Cr-16Mo-3.5W	Welded pipe
B/SB-619	N06975	...	85 (585)	45	111	45	49Ni-25Cr-18Fe-6Mo	Welded pipe
B/SB-619	N06985	...	90 (620)	45	111	45	47Ni-22Cr-20Fe-7Mo	Welded pipe
B/SB-619	N08031	...	94 (650)	45	111	45	31Ni-31Fe-27Cr-7Mo	Welded pipe
B/SB-619	N08320	...	75 (515)	45	111	8.2	26Ni-22Cr-5Mo-Ti	Welded pipe
B/SB-619	N10001	...	100 (690)	44	112	44	62Ni-28Mo-5Fe	Welded pipe
B/SB-619	N10242	...	105 (725)	44	112	44	62Ni-25Mo-8Cr-2Fe	Welded pipe
B/SB-619	N10276	...	100 (690)	43	111	43	54Ni-16Mo-15Cr	Welded pipe
B/SB-619	N10629	...	110 (760)	44	112	44	66Ni-28Mo-3Fe-1.3Cr-0.25Al	Welded pipe
B/SB-619	N10665	...	110 (760)	44	112	44	65Ni-28Mo-2Fe	Welded pipe
B/SB-619	N10675	...	110 (760)	44	112	44	65Ni-29.5Mo-2Fe-2Cr	Welded pipe
B/SB-619	N12160	...	90 (620)	46	...	46	37Ni-30Co-28Cr-2.7Si	Welded pipe
B/SB-619	R20033	...	109 (750)	45	111	45	33Cr-31Ni-32Fe-1.5Mo-0.6Cu-N	Welded pipe

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	UNS No.	Alloy, Type, or Grade	Minimum Specified Tensile, ksi (MPa)	Welding	Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	P-No.			
Nonferrous (Cont'd)								
B/SB-619	R30556	...	100 (690)	45	111	45	21Ni-30Fe-22Cr-18Co-3Mo-3W	Welded pipe
B/SB-620	N08320	...	75 (515)	45	111	8.2	26Ni-22Cr-5Mo-Ti	Plate, sheet & strip
B/SB-621	N08320	...	75 (515)	45	111	8.2	26Ni-22Cr-5Mo-Ti	Rod
B/SB-622	N06002	...	100 (690)	43	111	43	47Ni-22Cr-9Mo-18Fe	Smls. pipe & tube
B/SB-622	N06007	...	90 (620)	45	111	43	47Ni-22Cr-19Fe-6Mo	Smls. pipe & tube
B/SB-622	N06022	...	100 (690)	43	111	44	55Ni-21Cr-13.5Mo	Smls. pipe & tube
B/SB-622	N06030	...	85 (585)	45	111	45	40Ni-29Cr-15Fe-5Mo	Smls. pipe & tube
B/SB-622	N06035	...	85 (585)	43	111	...	58Ni-33Cr-8Mo	Smls. pipe & tube
B/SB-622	N06059	...	100 (690)	43	111	43	59Ni-23Cr-16Mo	Smls. pipe & tube
B/SB-622	N06200	...	100 (690)	43	111	43	59Ni-23Cr-16Mo-1.6Cu	Smls. pipe & tube
B/SB-622	N06210	...	100 (690)	43	111	...	60Ni-19Cr-19Mo-1.8Ta	Smls. pipe & tube
B/SB-622	N06230	...	110 (760)	43	111	43	53Ni-22Cr-14W-Co-Fe-Mo	Smls. pipe & tube
B/SB-622	N06455	...	100 (690)	43	111	43	61Ni-16Mo-16Cr	Smls. pipe & tube
B/SB-622	N06686	...	100 (690)	43	111	43	58Ni-21Cr-16Mo-3.5W	Smls. pipe & tube
B/SB-622	N06975	...	85 (585)	45	111	45	49Ni-25Cr-18Fe-6Mo	Smls. pipe & tube
B/SB-622	N06985	...	90 (620)	45	111	45	47Ni-22Cr-20Fe-7Mo	Smls. pipe & tube
B/SB-622	N08031	...	94 (650)	45	111	45	31Ni-31Fe-27Cr-7Mo	Smls. pipe & tube
B/SB-622	N08320	...	75 (515)	45	111	8.2	26Ni-22Cr-5Mo-Ti	Smls. pipe & tube
B/SB-622	N10001	...	100 (690)	44	112	44	62Ni-28Mo-5Fe	Smls. pipe & tube
B/SB-622	N10242	...	105 (725)	44	112	44	62Ni-25Mo-8Cr-2Fe	Smls. pipe & tube
B/SB-622	N10276	...	100 (690)	43	111	43	54Ni-16Mo-15Cr	Smls. pipe & tube
B/SB-622	N10629	...	110 (760)	44	112	44	66Ni-28Mo-3Fe-1.3Cr-0.25Al	Smls. pipe & tube
B/SB-622	N10665	...	110 (760)	44	112	44	65Ni-28Mo-2Fe	Smls. pipe & tube
B/SB-622	R20033	...	109 (750)	45	111	45	33Cr-31Ni-32Fe-1.5Mo-0.6Cu-N	Smls. pipe & tube
B/SB-622	R30556	...	100 (690)	45	111	45	21Ni-30Fe-22Cr-18Co-3Mo-3W	Smls. pipe & tube
B/SB-622	N10675	...	110 (760)	44	112	44	65Ni-29.5Mo-2Fe-2Cr	Smls. pipe & tube
B/SB-622	N12160	...	90 (620)	46	...	46	37Ni-30Co-28Cr-2.7Si	Smls. pipe & tube
B/SB-625	N08926	...	94 (650)	45	111	8.2	25Ni-20Cr-6Mo-Co-N	Plate, sheet & strip
B/SB-625	N08031	...	94 (650)	45	111	45	31Ni-31Fe-27Cr-7Mo	Plate, sheet & strip
B/SB-625	N08904	...	71 (490)	45	111	8.2	44Fe-25Ni-21Cr-Mo	Plate, sheet & strip
B/SB-625	N08925	...	87 (600)	45	111	8.2	25Ni-20Cr-6Mo-Cu-N	Plate, sheet & strip

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	UNS No.	Alloy, Type, or Grade	Minimum Specified Tensile, ksi (MPa)	Welding	Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	P-No.			
Nonferrous (Cont'd)								
B/SB-625	R20033	...	109 (750)	45	111	45	33Cr-31Ni-32Fe-1.5Mo-0.6Cu-N	Plate, sheet & strip
B/SB-626	N06002	...	100 (690)	43	111	43	47Ni-22Cr-9Mo-18Fe	Welded tube
B/SB-626	N06007	...	90 (620)	45	111	43	47Ni-22Cr-19Fe-6Mo	Welded tube
B/SB-626	N06022	...	100 (690)	43	111	44	55Ni-21Cr-13.5Mo	Welded tube
B/SB-626	N06030	...	85 (585)	45	111	45	40Ni-29Cr-15Fe-5Mo	Welded tube
B/SB-626	N06035	...	85 (585)	43	111	...	58Ni-33Cr-8Mo	Welded tube
B/SB-626	N06059	...	100 (690)	43	111	43	59Ni-23Cr-16Mo	Welded tube
B/SB-626	N06200	...	100 (690)	43	111	43	59Ni-23Cr-16Mo-1.6Cu	Welded tube
B/SB-626	N06210	...	100 (690)	43	111	...	60Ni-19Cr-19Mo-1.8Ta	Welded tube
B/SB-626	N06230	...	110 (760)	43	111	43	53Ni-22Cr-14W-Co-Fe-Mo	Welded tube
B/SB-626	N06455	...	100 (690)	43	111	43	61Ni-16Mo-16Cr	Welded tube
B/SB-626	N06686	...	100 (690)	43	111	43	58Ni-21Cr-16Mo-3.5W	Welded tube
B/SB-626	N06975	...	85 (585)	45	111	45	49Ni-25Cr-18Fe-6Mo	Welded tube
B/SB-626	N06985	...	90 (620)	45	111	45	47Ni-22Cr-20Fe-7Mo	Welded tube
B/SB-626	N08031	...	94 (650)	45	111	45	31Ni-31Fe-27Cr-7Mo	Welded tube
B/SB-626	N08320	...	75 (515)	45	111	8.2	26Ni-22Cr-5Mo-Ti	Welded tube
B/SB-626	N10001	...	100 (690)	44	112	44	62Ni-28Mo-5Fe	Welded tube
B/SB-626	N10242	...	105 (725)	44	112	44	62Ni-25Mo-8Cr-2Fe	Welded tube
B/SB-626	N10276	...	100 (690)	43	111	43	54Ni-16Mo-15Cr	Welded tube
B/SB-626	N10629	...	110 (760)	44	112	44	66Ni-28Mo-3Fe-1.3Cr-0.25Al	Welded tube
B/SB-626	N10665	...	110 (760)	44	112	44	65Ni-28Mo-2Fe	Welded tube
B/SB-626	R20033	...	109 (750)	45	111	45	33Cr-31Ni-32Fe-1.5Mo-0.6Cu-N	Welded tube
B/SB-626	R30556	...	100 (690)	45	111	45	21Ni-30Fe-22Cr-18Co-3Mo-3W	Welded tube
B/SB-626	N10675	...	110 (760)	44	112	44	65Ni-29.5Mo-2Fe-2Cr	Welded tube
B/SB-626	N12160	...	90 (620)	46	...	46	37Ni-30Co-28Cr-2.7Si	Welded tube
B/SB-649	N08926	...	94 (650)	45	111	8.2	25Ni-20Cr-6Mo-Cu-N	Bar & wire
B/SB-649	N08904	...	71 (490)	45	111	8.2	44Fe-25Ni-21Cr-Mo	Bar & wire
B/SB-649	N08925	...	87 (600)	45	111	8.2	25Ni-20Cr-6Mo-Cu-N	Bar & wire
B/SB-649	R20033	...	109 (750)	45	111	45	33Cr-31Ni-32Fe-1.5Mo-0.6Cu-N	Bar & wire
B/SB-653	R60702	R60702	55 (380)	61	117	...	99.2Zr	Seamless & welded fittings
B/SB-658	R60702	R60702	55 (380)	61	117	61	99.2Zr	Smls. & welded pipe
B/SB-658	R60705	R60705	80 (550)	62	117	62	95.5Zr + 2.5Cb	Smls. & welded pipe

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	UNS No.	Alloy, Type, or Grade	Minimum Specified Tensile, ksi (MPa)	Welding	Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	P-No.			
Nonferrous (Cont'd)								
B/SB-668	N08028	...	73 (505)	45	111	45	31Ni-31Fe-29Cr-Mo	Smls. tube
B/SB-672	N08700	...	80 (550)	45	111	8.2	25Ni-47Fe-21Cr-5Mo	Bar & wire
B/SB-673	N08926	...	94 (650)	45	111	8.2	25Ni-20Cr-6Mo-Cu-N	Welded pipe
B/SB-673	N08904	...	71 (490)	45	111	8.2	44Fe-25Ni-21Cr-Mo	Welded pipe
B/SB-673	N08925	...	87 (600)	45	111	8.2	25Ni-20Cr-6Mo-Cu-N	Welded pipe
B/SB-674	N08904	...	71 (490)	45	111	8.2	44Fe-25Ni-21Cr-Mo	Welded tube
B/SB-674	N08925	...	87 (600)	45	111	8.2	25Ni-20Cr-6Mo-Cu-N	Welded tube
B/SB-674	N08926	...	94 (650)	45	111	8.2	25Ni-20Cr-6Mo-Cu-N	Welded tube
B/SB-675	N08367	...	95 (655)	45	111	8.2	46Fe-24Ni-21Cr-6Mo-Cu-N	Welded pipe > 3⁄16 in. (5 mm)
B/SB-675	N08367	...	100 (690)	45	111	8.2	46Fe-24Ni-21Cr-6Mo-Cu-N	Welded pipe ≤ 3⁄16 in. (5 mm)
B/SB-676	N08367	...	95 (655)	45	111	8.2	46Fe-24Ni-21Cr-6Mo-Cu-N	Welded tube > 3⁄16 in. (5 mm)
B/SB-676	N08367	...	100 (690)	45	111	8.2	46Fe-24Ni-21Cr-6Mo-Cu-N	Welded tube ≤ 3⁄16 in. (5 mm)
B/SB-677	N08926	...	94 (650)	45	111	8.2	25Ni-20Cr-6Mo-Cu-N	Smls. pipe & tube
B/SB-677	N08904	...	71 (490)	45	111	8.2	44Fe-25Ni-21Cr-Mo	Smls. pipe & tube
B/SB-677	N08925	...	87 (600)	45	111	8.2	25Ni-20Cr-6Mo-Cu-N	Smls. pipe & tube
B/SB-688	N08367	...	95 (655)	45	111	8.2	46Fe-24Ni-21Cr-6Mo-Cu-N	Plate, sheet & strip > 3⁄16 in. (4.8 mm)
B/SB-688	N08367	...	100 (690)	45	111	8.2	46Fe-24Ni-21Cr-6Mo-Cu-N	Plate, sheet & strip ≤ 3⁄16 in. (4.8 mm)
B/SB-690	N08367	...	95 (655)	45	111	8.2	46Fe-24Ni-21Cr-6Mo-Cu-N	Smls. pipe & tube > 3⁄16 in. (4.8 mm)
B/SB-690	N08367	...	100 (690)	45	111	8.2	46Fe-24Ni-21Cr-6Mo-Cu-N	Smls. pipe & tube ≤ 3⁄16 in. (4.8 mm)
B/SB-691	N08367	...	95 (655)	45	111	8.2	46Fe-24Ni-21Cr-6Mo-Cu-N	Rod, bar & wire
B/SB-704	N06625	...	120 (825)	43	111	43	60Ni-22Cr-9Mo-3.5Cb	Welded tube
B/SB-704	N08825	...	85 (585)	45	111	45	42Ni-21.5Cr-3Mo-2.3Cu	Welded tube
B/SB-705	N06625	...	120 (825)	43	111	43	60Ni-22Cr-9Mo-3.5Cb	Welded pipe
B/SB-705	N08825	...	85 (585)	45	111	45	42Ni-21.5Cr-3Mo-2.3Cu	Welded pipe
B/SB-709	N08028	...	73 (505)	45	111	45	31Ni-31Fe-29Cr-Mo	Plate, sheet & strip
B/SB-710	N08330	...	70 (485)	46	111	45	35Ni-19Cr-1.25Si	Welded pipe

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	UNS No.	Alloy, Type, or Grade	Minimum Specified Tensile, ksi (MPa)	Welding	Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	P-No.			
Nonferrous (Cont'd)								
B/SB-729	N08020	...	80 (550)	45	111	45	35Ni-35Fe-20Cr-Cb	Smls. pipe & tube
B725	N02200	...	55 (380)	41	110	41	99.0Ni	Welded pipe
B/SB-815	R31233	...	120 (825)	49	Co-26Cr-9Ni-5Mo-3Fe-2W	Rod
B/SB-818	R31233	...	120 (825)	49	Co-26Cr-9Ni-5Mo-3Fe-2W	Plate, sheet & strip
B819	C12200	C12200	30 (205)	...	107	NA	99.9Cu-P	Wrought pipe
B/SB-861	R50250	1	35 (240)	51	115	51	Ti	Smls. pipe
B/SB-861	R50400	2	50 (345)	51	115	51	Ti	Smls. pipe
B/SB-861	R50400	2H	58 (400)	51	115	...	Ti	Smls. pipe
B/SB-861	R50550	3	65 (450)	52	115	52	Ti	Smls. pipe
B/SB-861	R52400	7	50 (345)	51	115	51	Ti-Pd	Smls. pipe
B/SB-861	R52400	7H	58 (400)	51	115	...	Ti-Pd	Smls. pipe
B/SB-861	R52402	16	50 (345)	51	115	...	Ti-Pd	Smls. pipe
B/SB-861	R52402	16H	58 (400)	51	115	...	Ti-Pd	Smls. pipe
B/SB-861	R52404	26	50 (345)	51	115	51	Ti-Ru	Smls. pipe
B/SB-861	R52404	26H	58 (400)	51	115	...	Ti-Ru	Smls. pipe
B/SB-861	R53400	12	70 (485)	52	115	52	Ti-0.3Mo-0.8Ni	Smls. pipe
B/SB-861	R56320	9	90 (620)	53	115	53	Ti-3Al-2.5V	Smls. pipe
B/SB-861	R56323	28	90 (620)	53	115	53	Ti-3Al-2.5V-0.1Ru	Smls. pipe
B/SB-862	R50250	1	35 (240)	51	115	51	Ti	Welded pipe
B/SB-862	R50400	2	50 (345)	51	115	51	Ti	Welded pipe
B/SB-862	R50400	2H	58 (400)	51	115	...	Ti	Welded pipe
B/SB-862	R50550	3	65 (450)	52	115	52	Ti	Welded pipe
B/SB-862	R52400	7	50 (345)	51	115	51	Ti-Pd	Welded pipe
B/SB-862	R52400	7H	58 (400)	51	115	...	Ti-Pd	Welded pipe
B/SB-862	R52402	16	50 (345)	51	115	...	Ti-Pd	Welded pipe
B/SB-862	R52402	16H	58 (400)	51	115	...	Ti-Pd	Welded pipe
B/SB-862	R52404	26	50 (345)	51	115	51	Ti-Ru	Welded pipe
B/SB-862	R52404	26H	58 (400)	51	115	...	Ti-Ru	Welded pipe
B/SB-862	R53400	12	70 (485)	52	115	52	Ti-0.3Mo-0.8Ni	Welded pipe
B/SB-862	R56320	9	90 (620)	53	115	53	Ti-3Al-2.5V	Welded pipe
B/SB-862	R56323	28	90 (620)	53	115	53	Ti-3Al-2.5V-0.1Ru	Welded pipe

Table QW/QB-422
Ferrous/Nonferrous P-Numbers
Grouping of Base Metals for Qualification (Cont'd)

Spec. No.	UNS No.	Alloy, Type, or Grade	Minimum Specified Tensile, ksi (MPa)	Welding	Brazing	ISO 15608 Group	Nominal Composition	Product Form
				P-No.	P-No.			
Nonferrous (Cont'd)								
B/SB-928	A95083	5083	39 (270)	25	105	22.4	Al-4.4Mg-Mn	Plate & sheet > 1.5 in. – 3 in. (38 mm – 76 mm), incl.
B/SB-928	A95086	5086	35 (240)	25	105	22.4	Al-4.0Mg-Mn	Plate & sheet > 0.05 in. – 2 in. (1.3 mm – 51 mm), incl.
B/SB-928	A95456	5456	41 (285)	25	105	22.4	Al-5.1Mg-Mn	Plate & sheet > 1.5 in. – 3 in. (38 mm – 76 mm), incl.
B/SB-956	C70600	...	40 (275)	34	107	...	90Cu-10Ni	Finned welded tube
B/SB-956	C71500	...	52 (360)	34	107	...	70Cu-30Ni	Finned welded tube
SB/EN 1706	...	EN AC 43000	22 (150)	26	104	...	Al-10Si-Mg	Casting
B16.18	C83600	...	30 (205)	...	107	NA	5Sn-5Zn-5Pb	Cast fittings
B16.18	C83800	...	30 (205)	...	107	NA	4Sn-6.5Zn-6Pb	Cast fittings
B16.18	C84400	...	29 (200)	...	107	NA	2.5Sn-8.5Zn-7Pb	Cast fittings
B16.22	C10200	...	30 (205)	...	107	NA	99.95Cu-P	Wrought pipe fittings
B16.22	C12000	...	30 (205)	...	107	NA	99.9Cu-P	Wrought pipe fittings
B16.22	C12200	...	30 (205)	...	107	NA	99.9Cu-P	Wrought pipe fittings
B16.22	C23000	...	40 (275)	...	107	NA	85Cu-15Zn	Wrought pipe fittings
B16.50	C10200	...	30 (205)	...	107	...	99.95Cu-P	Wrought pipe fittings
B16.50	C12000	...	30 (205)	...	107	...	99.9Cu-P	Wrought pipe fittings
B16.50	C12200	...	30 (205)	...	107	...	99.9Cu-P	Wrought pipe fittings
B16.50	C23000	...	40 (275)	...	107	...	85Cu-15Zn	Wrought pipe fittings

QW-423 ALTERNATE BASE MATERIALS FOR WELDER QUALIFICATION

- (13) **QW-423.1** Base metal used for welder qualification may be substituted for the metal specified in the WPS in accordance with the following table. When a base metal shown in the left column is used for welder qualification, the welder is qualified to weld all combinations of base metals shown in the right column, including unassigned metals of similar chemical composition to these metals.

Base Metals for Welder Qualification	Qualified Production Base Metals
P-No. 1 through P-No. 15F, P-No. 34, or P-No. 41 through P-No. 49	P-No. 1 through P-No. 15F, P-No. 34, and P-No. 41 through P-No. 49
P-No. 21 through P-No. 26	P-No. 21 through P-No. 26
P-No. 51 through P-No. 53 or P-No. 61 or P-No. 62	P-No. 51 through P-No. 53 and P-No. 61 and P-No. 62

QW-423.2 Metals used for welder qualification conforming to national or international standards or specifications may be considered as having the same P-Number as an assigned metal provided it meets the mechanical and chemical requirements of the assigned metal. The base metal specification and corresponding P-Number shall be recorded on the qualification record.

QW-424 BASE METALS USED FOR PROCEDURE QUALIFICATION

QW-424.1 Base metals are assigned P-Numbers in [Table QW/QB-422](#); metals that do not appear in [Table QW/QB-422](#) are considered to be unassigned metals except as otherwise defined for base metals having the same UNS numbers. Unassigned metals shall be identified in the WPS and on the PQR by specification, type and grade, or by chemical analysis and mechanical properties. The minimum tensile strength shall be defined by the organization that specified the unassigned metal if the tensile strength of that metal is not defined by the material specification.

Base Metal(s) Used for Procedure Qualification	Base Metals Qualified
Coupon	
One metal from a P-Number to any metal from the same P-Number	Any metals assigned that P-Number
One metal from P-No. 15E to any metal from P-No. 15E	Any P-No. 15E or 5B metal to any metal assigned P-No. 15E or 5B
One metal from a P-Number to any metal from any other P- Number	Any metal assigned the first P-Number to any metal assigned the second P-Number

Table continued

Base Metal(s) Used for Procedure Qualification	Base Metals Qualified
Coupon	
One metal from P-No. 15E to any metal from any other P-Number	Any P-No. 15E or 5B metal to any metal assigned the second P-Number
One metal from P-No. 3 to any metal from P-No. 3	Any P-No. 3 metal to any metal assigned P-No. 3 or 1
One metal from P-No. 4 to any metal from P-No. 4	Any P-No. 4 metal to any metal assigned P-No. 4, 3, or 1
One metal from P-No. 5A to any metal from P-No. 5A	Any P-No. 5A metal to any metal assigned P-No. 5A, 4, 3, or 1
One metal from P-No. 5A to a metal from P-No. 4, or P-No. 3, or P-No. 1	Any P-No. 5A metal to any metal assigned to P-No. 4, 3, or 1
One metal from P-No. 4 to a metal from P-No. 3 or P-No. 1	Any P-No. 4 metal to any metal assigned to P-No. 3 or 1
Any unassigned metal to the same unassigned metal	The unassigned metal to itself
Any unassigned metal to any P-Number metal	The unassigned metal to any metal assigned to the same P-Number as the qualified metal
Any unassigned metal to any metal from P-No. 15E	The unassigned metal to any metal assigned P-No. 15E or 5B
Any unassigned metal to any other unassigned metal	The first unassigned metal to the second unassigned metal

- (13) **QW-424.2** For welds joining base metals to weld metal buildup or corrosion-resistant weld metal overlay, the buildup or overlay portion of the joint may be substituted in the test coupon by any P-Number base material that nominally matches the chemical analysis of the buildup or overlay.

QW-430 F-NUMBERS**QW-431 GENERAL**

The following F-Number grouping of electrodes and welding rods in [Table QW-432](#) is based essentially on their usability characteristics, which fundamentally determine the ability of welders to make satisfactory welds with a given filler metal. This grouping is made to reduce the number of welding procedure and performance qualifications, where this can logically be done. The grouping does not imply that base metals or filler metals within a group may be indiscriminately substituted for a metal that was used in the qualification test without consideration of the compatibility of the base and filler metals from the standpoint of metallurgical properties, postweld heat treatment design and service requirements, and mechanical properties.

Table QW-432
F-Numbers
Grouping of Electrodes and Welding Rods for Qualification

F-No.	ASME Specification	AWS Classification	UNS No.
Steel and Steel Alloys			
1	SFA-5.1	EXX20	...
1	SFA-5.1	EXX22	...
1	SFA-5.1	EXX24	...
1	SFA-5.1	EXX27	...
1	SFA-5.1	EXX28	...
1	SFA-5.4	EXXX(X)-26	...
1	SFA-5.5	EXX20-X	...
1	SFA-5.5	EXX27-X	...
2	SFA-5.1	EXX12	...
2	SFA-5.1	EXX13	...
2	SFA-5.1	EXX14	...
2	SFA-5.1	EXX19	...
2	SFA-5.5	E(X)XX13-X	...
3	SFA-5.1	EXX10	...
3	SFA-5.1	EXX11	...
3	SFA-5.5	E(X)XX10-X	...
3	SFA-5.5	E(X)XX11-X	...
4	SFA-5.1	EXX15	...
4	SFA-5.1	EXX16	...
4	SFA-5.1	EXX18	...
4	SFA-5.1	EXX18M	...
4	SFA-5.1	EXX48	...
4	SFA-5.4 other than austenitic and duplex	EXXX(X)-15	...
4	SFA-5.4 other than austenitic and duplex	EXXX(X)-16	...
4	SFA-5.4 other than austenitic and duplex	EXXX(X)-17	...
4	SFA-5.5	E(X)XX15-X	...
4	SFA-5.5	E(X)XX16-X	...
4	SFA-5.5	E(X)XX18-X	...
4	SFA-5.5	E(X)XX18M	...
4	SFA-5.5	E(X)XX18M1	...
4	SFA-5.5	E(X)XX45	...
5	SFA-5.4 austenitic and duplex	EXXX(X)-15	...
5	SFA-5.4 austenitic and duplex	EXXX(X)-16	...
5	SFA-5.4 austenitic and duplex	EXXX(X)-17	...
6	SFA-5.2	All classifications	...
6	SFA-5.9	All classifications	...
6	SFA-5.17	All classifications	...
6	SFA-5.18	All classifications	...
6	SFA-5.20	All classifications	...
6	SFA-5.22	All classifications	...
6	SFA-5.23	All classifications	...
6	SFA-5.25	All classifications	...
6	SFA-5.26	All classifications	...
6	SFA-5.28	All classifications	...
6	SFA-5.29	All classifications	...
6	SFA-5.30	INMs-X	...
6	SFA-5.30	IN5XX	...
6	SFA-5.30	IN3XX(X)	...

Table QW-432
F-Numbers
Grouping of Electrodes and Welding Rods for Qualification (Cont'd)

F-No.	ASME Specification	AWS Classification	UNS No.
Aluminum and Aluminum Alloys			
21	SFA-5.3	E1100	A91100
21	SFA-5.3	E3003	A93003
21	SFA-5.10	ER1100	A91100
21	SFA-5.10	ER1188	A91188
21	SFA-5.10	R1100	A91100
21	SFA-5.10	R1188	A91188
22	SFA-5.10	ER5183	A95183
22	SFA-5.10	ER5356	A95356
22	SFA-5.10	ER5554	A95554
22	SFA-5.10	ER5556	A95556
22	SFA-5.10	ER5654	A95654
22	SFA-5.10	R5183	A95183
22	SFA-5.10	R5356	A95356
22	SFA-5.10	R5554	A95554
22	SFA-5.10	R5556	A95556
22	SFA-5.10	R5654	A95654
23	SFA-5.3	E4043	A94043
23	SFA-5.10	ER4009	A94009
23	SFA-5.10	ER4010	A94010
23	SFA-5.10	ER4043	A94043
23	SFA-5.10	ER4047	A94047
23	SFA-5.10	ER4145	A94145
23	SFA-5.10	ER4643	A94643
23	SFA-5.10	ER4943	A94943
23	SFA-5.10	R4009	A94009
23	SFA-5.10	R4010	A94010
23	SFA-5.10	R4011	A94011
23	SFA-5.10	R4043	A94043
23	SFA-5.10	R4047	A94047
23	SFA-5.10	R4145	A94145
23	SFA-5.10	R4643	A94643
23	SFA-5.10	R4943	A94943
24	SFA-5.10	R-A356.0	A13560
24	SFA-5.10	R-A357.0	A13570
24	SFA-5.10	R-C355.0	A33550
24	SFA-5.10	R206.0	A02060
24	SFA-5.10	R357.0	A03570
25	SFA-5.10	ER2319	A92319
25	SFA-5.10	R2319	A92319
Copper and Copper Alloys			
31	SFA-5.6	ECu	W60189
31	SFA-5.7	ERCu	C18980
32	SFA-5.6	ECuSi	W60656
32	SFA-5.7	ERCuSi-A	C65600
33	SFA-5.6	ECuSn-A	W60518
33	SFA-5.6	ECuSn-C	W60521
33	SFA-5.7	ERCuSn-A	WC51800
33	SFA-5.7	ERCuSn-C	C52100

Table QW-432
F-Numbers
Grouping of Electrodes and Welding Rods for Qualification (Cont'd)

F-No.	ASME Specification	AWS Classification	UNS No.
Copper and Copper Alloys (Cont'd)			
34	SFA-5.6	ECuNi	W60715
34	SFA-5.7	ERCuNi	C71580
34	SFA-5.30	IN67	C71581
35	SFA-5.8	RBCuZn-A	C47000
35	SFA-5.8	RBCuZn-B	C68000
35	SFA-5.8	RBCuZn-C	C68100
35	SFA-5.8	RBCuZn-D	C77300
36	SFA-5.6	ECuAl-A2	W60614
36	SFA-5.6	ECuAl-B	W60619
36	SFA-5.7	ERCuAl-A1	C61000
36	SFA-5.7	ERCuAl-A2	C61800
36	SFA-5.7	ERCuAl-A3	C62400
37	SFA-5.6	ECuMnNiAl	C60633
37	SFA-5.6	ECuNiAl	C60632
37	SFA-5.7	ERCuMnNiAl	C63380
37	SFA-5.7	ERCuNiAl	C63280
Nickel and Nickel Alloys			
41	SFA-5.11	ENi-1	W82141
41	SFA-5.14	ERNi-1	N02061
41	SFA-5.30	IN61	N02061
42	SFA-5.11	ENiCu-7	W84190
42	SFA-5.14	ERNiCu-7	N04060
42	SFA-5.14	ERNiCu-8	N05504
42	SFA-5.30	IN60	N04060
43	SFA-5.11	ENiCr-4	W86172
43	SFA-5.11	ENiCrCoMo-1	W86117
43	SFA-5.11	ENiCrFe-1	W86132
43	SFA-5.11	ENiCrFe-2	W86133
43	SFA-5.11	ENiCrFe-3	W86182
43	SFA-5.11	ENiCrFe-4	W86134
43	SFA-5.11	ENiCrFe-7	W86152
43	SFA-5.11	ENiCrFe-9	W86094
43	SFA-5.11	ENiCrFe-10	W86095
43	SFA-5.11	ENiCrFe-12	W86025
43	SFA-5.11	ENiCrMo-2	W86002
43	SFA-5.11	ENiCrMo-3	W86112
43	SFA-5.11	ENiCrMo-4	W80276
43	SFA-5.11	ENiCrMo-5	W80002
43	SFA-5.11	ENiCrMo-6	W86620
43	SFA-5.11	ENiCrMo-7	W86455
43	SFA-5.11	ENiCrMo-10	W86022
43	SFA-5.11	ENiCrMo-12	W86032
43	SFA-5.11	ENiCrMo-13	W86059
43	SFA-5.11	ENiCrMo-14	W86026
43	SFA-5.11	ENiCrMo-17	W86200
43	SFA-5.11	ENiCrMo-18	W86650
43	SFA-5.11	ENiCrMo-19	W86058
43	SFA-5.11	ENiCrWMo-1	W86231
43	SFA-5.14	ERNiCr-3	N06082

Table QW-432
F-Numbers
Grouping of Electrodes and Welding Rods for Qualification (Cont'd)

F-No.	ASME Specification	AWS Classification	UNS No.
Nickel and Nickel Alloys (Cont'd)			
43	SFA-5.14	ERNiCr-4	N06072
43	SFA-5.14	ERNiCr-6	N06076
43	SFA-5.14	ERNiCr-7	N06073
43	SFA-5.14	ERNiCrCoMo-1	N06617
43	SFA-5.14	ERNiCrFe-5	N06062
43	SFA-5.14	ERNiCrFe-6	N07092
43	SFA-5.14	ERNiCrFe-7	N06052
43	SFA-5.14	ERNiCrFe-7A	N06054
43	SFA-5.14	ERNiCrFe-8	N07069
43	SFA-5.14	ERNiCrFe-11	N06601
43	SFA-5.14	ERNiCrFe-12	N06025
43	SFA-5.14	ERNiCrFe-13	N06055
43	SFA-5.14	ERNiCrFe-14	N06043
43	SFA-5.14	ERNiCrFeAl-1	N06693
43	SFA-5.14	ERNiCrMo-2	N06002
43	SFA-5.14	ERNiCrMo-3	N06625
43	SFA-5.14	ERNiCrMo-4	N10276
43	SFA-5.14	ERNiCrMo-7	N06455
43	SFA-5.14	ERNiCrMo-10	N06022
43	SFA-5.14	ERNiCrMo-13	N06059
43	SFA-5.14	ERNiCrMo-14	N06686
43	SFA-5.14	ERNiCrMo-16	N06057
43	SFA-5.14	ERNiCrMo-17	N06200
43	SFA-5.14	ERNiCrMo-18	N06650
43	SFA-5.14	ERNiCrMo-19	N07058
43	SFA-5.14	ERNiCrMo-20	N06660
43	SFA-5.14	ERNiCrMo-21	N06205
43	SFA-5.14	ERNiCrMo-22	N06035
43	SFA-5.14	ERNiCrWMo-1	N06231
43	SFA-5.30	IN52	N06052
43	SFA-5.30	IN62	N06062
43	SFA-5.30	IN6A	N07092
43	SFA-5.30	IN82	N06082
43	SFA-5.34	All classifications	...
44	SFA-5.11	ENiMo-1	W80001
44	SFA-5.11	ENiMo-3	W80004
44	SFA-5.11	ENiMo-7	W80665
44	SFA-5.11	ENiMo-8	W80008
44	SFA-5.11	ENiMo-9	W80009
44	SFA-5.11	ENiMo-10	W80675
44	SFA-5.11	ENiMo-11	W80675
44	SFA-5.14	ERNiMo-1	N10001
44	SFA-5.14	ERNiMo-2	N10003
44	SFA-5.14	ERNiMo-3	N10004
44	SFA-5.14	ERNiMo-7	N10665
44	SFA-5.14	ERNiMo-8	N10008
44	SFA-5.14	ERNiMo-9	N10009
44	SFA-5.14	ERNiMo-10	N10675
44	SFA-5.14	ERNiMo-11	N10629
44	SFA-5.14	ERNiMo-12	N10242

Table QW-432
F-Numbers
Grouping of Electrodes and Welding Rods for Qualification (Cont'd)

F-No.	ASME Specification	AWS Classification	UNS No.
Nickel and Nickel Alloys (Cont'd)			
45	SFA-5.11	ENiCrMo-1	W86007
45	SFA-5.11	ENiCrMo-9	W86985
45	SFA-5.11	ENiCrMo-11	W86030
45	SFA-5.14	ERNiCrMo-1	N06007
45	SFA-5.14	ERNiCrMo-8	N06975
45	SFA-5.14	ERNiCrMo-9	N06985
45	SFA-5.14	ERNiCrMo-11	N06030
45	SFA-5.14	ERNiFeCr-1	N08065
46	SFA-5.11	ENiCrFeSi-1	W86045
46	SFA-5.14	ERNiCrFeSi-1	N06045
46	SFA-5.14	ERNiCoCrSi-1	N12160
Titanium and Titanium Alloys			
51	SFA-5.16	ERTi-1	R50100
51	SFA-5.16	ERTi-11	R52251
51	SFA-5.16	ERTi-13	R53423
51	SFA-5.16	ERTi-17	R52253
51	SFA-5.16	ERTi-27	R52255
51	SFA-5.16	ERTi-2	R50120
51	SFA-5.16	ERTi-7	R52401
51	SFA-5.16	ERTi-14	R53424
51	SFA-5.16	ERTi-16	R52403
51	SFA-5.16	ERTi-26	R52405
51	SFA-5.16	ERTi-30	R53531
51	SFA-5.16	ERTi-33	R53443
51	SFA-5.16	ERTi-3	R50125
51	SFA-5.16	ERTi-15A	R53416
51	SFA-5.16	ERTi-31	R53533
51	SFA-5.16	ERTi-34	R53444
52	SFA-5.16	ERTi-4	R50130
53	SFA-5.16	ERTi-9	R56320
53	SFA-5.16	ERTi-9ELI	R56321
53	SFA-5.16	ERTi-18	R56326
53	SFA-5.16	ERTi-28	R56324
54	SFA-5.16	ERTi-12	R53400
55	SFA-5.16	ERTi-5	R56400
55	SFA-5.16	ERTi-23	R56408
55	SFA-5.16	ERTi-29	R56414
55	SFA-5.16	ERTi-24	R56415
55	SFA-5.16	ERTi-25	R56413
56	SFA-5.16	ERTi-32	R55112
Zirconium and Zirconium Alloys			
61	SFA-5.24	ERZr2	R60702
61	SFA-5.24	ERZr3	R60704
61	SFA-5.24	ERZr4	R60705
Hard-Facing Weld Metal Overlay			
71	SFA-5.13	ECoCr-A	W73006
71	SFA-5.13	ECoCr-B	W73012

Table QW-432
F-Numbers
Grouping of Electrodes and Welding Rods for Qualification (Cont'd)

F-No.	ASME Specification	AWS Classification	UNS No.
Hard-Facing Weld Metal Overlay (Cont'd)			
71	SFA-5.13	ECrCo-C	W73001
71	SFA-5.13	ECrCo-E	W73021
71	SFA-5.13	ECuAl-A2	W60617
71	SFA-5.13	ECuAl-B	W60619
71	SFA-5.13	ECuAl-C	W60625
71	SFA-5.13	ECuAl-D	W61625
71	SFA-5.13	ECuAl-E	W62625
71	SFA-5.13	ECuMnNiAl	W60633
71	SFA-5.13	ECuNi	W60715
71	SFA-5.13	ECuNiAl	W60632
71	SFA-5.13	ECuSi	W60656
71	SFA-5.13	ECuSn-A	W60518
71	SFA-5.13	ECuSn-C	W60521
71	SFA-5.13	EFe1	W74001
71	SFA-5.13	EFe2	W74002
71	SFA-5.13	EFe3	W74003
71	SFA-5.13	EFe4	W74004
71	SFA-5.13	EFe5	W75110
71	SFA-5.13	EFe6	W77510
71	SFA-5.13	EFe7	W77610
71	SFA-5.13	EFeCr-A1A	W74011
71	SFA-5.13	EFeCr-A2	W74012
71	SFA-5.13	EFeCr-A3	W74013
71	SFA-5.13	EFeCr-A4	W74014
71	SFA-5.13	EFeCr-A5	W74015
71	SFA-5.13	EFeCr-A6	W74016
71	SFA-5.13	EFeCr-A7	W74017
71	SFA-5.13	EFeCr-A8	W74018
71	SFA-5.13	EFeCr-E1	W74211
71	SFA-5.13	EFeCr-E2	W74212
71	SFA-5.13	EFeCr-E3	W74213
71	SFA-5.13	EFeCr-E4	W74214
71	SFA-5.13	EFeMn-A	W79110
71	SFA-5.13	EFeMn-B	W79310
71	SFA-5.13	EFeMn-C	W79210
71	SFA-5.13	EFeMn-D	W79410
71	SFA-5.13	EFeMn-E	W79510
71	SFA-5.13	EFeMn-F	W79610
71	SFA-5.13	EFeMnCr	W79710
71	SFA-5.13	ENiCr-C	W89606
71	SFA-5.13	ENiCrFeCo	W83002
71	SFA-5.13	ENiCrMo-5A	W80002
71	SFA-5.13	EWCX-12/30	...
71	SFA-5.13	EWCX-20/30	...
71	SFA-5.13	EWCX-30/40	...
71	SFA-5.13	EWCX-40	...
71	SFA-5.13	EWCX-40/120	...
72	SFA-5.21	ERCCoCr-A	W73036
72	SFA-5.21	ERCCoCr-B	W73042
72	SFA-5.21	ERCCoCr-C	W73031

Table QW-432
F-Numbers
Grouping of Electrodes and Welding Rods for Qualification (Cont'd)

F-No.	ASME Specification	AWS Classification	UNS No.
Hard-Facing Weld Metal Overlay (Cont'd)			
72	SFA-5.21	ERCCoCr-E	W73041
72	SFA-5.21	ERCCoCr-G	W73032
72	SFA-5.21	ERCCuAl-A2	W60618
72	SFA-5.21	ERCCuAl-A3	W60624
72	SFA-5.21	ERCCuAl-C	W60626
72	SFA-5.21	ERCCuAl-D	W61626
72	SFA-5.21	ERCCuAl-E	W62626
72	SFA-5.21	ERCCuSi-A	W60657
72	SFA-5.21	ERCCuSn-A	W60518
72	SFA-5.21	ERCCuSn-D	W60524
72	SFA-5.21	ERCFE-1	W74030
72	SFA-5.21	ERCFE-1A	W74031
72	SFA-5.21	ERCFE-2	W74032
72	SFA-5.21	ERCFE-3	W74033
72	SFA-5.21	ERCFE-5	W74035
72	SFA-5.21	ERCFE-6	W77530
72	SFA-5.21	ERCFE-8	W77538
72	SFA-5.21	ERCFEcr-A	W74531
72	SFA-5.21	ERCFEcr-A1A	W74530
72	SFA-5.21	ERCFEcr-A3A	W74533
72	SFA-5.21	ERCFEcr-A4	W74534
72	SFA-5.21	ERCFEcr-A5	W74535
72	SFA-5.21	ERCFEcr-A9	W74539
72	SFA-5.21	ERCFEcr-A10	W74540
72	SFA-5.21	ERCFEMn-C	W79230
72	SFA-5.21	ERCFEMn-F	W79630
72	SFA-5.21	ERCFEMn-G	W79231
72	SFA-5.21	ERCFEMn-H	W79232
72	SFA-5.21	ERCFEMnCr	W79730
72	SFA-5.21	ERCNiCr-A	W89634
72	SFA-5.21	ERCNiCr-B	W89635
72	SFA-5.21	ERCNiCr-C	W89636
72	SFA-5.21	ERCNiCrFeCo	W83032
72	SFA-5.21	ERCNiCrMo-5A	W80036
72	SFA-5.21	ERCoCr-A	R30006
72	SFA-5.21	ERCoCr-B	R30012
72	SFA-5.21	ERCoCr-C	R30001
72	SFA-5.21	ERCoCr-E	R30021
72	SFA-5.21	ERCoCr-F	R30002
72	SFA-5.21	ERCoCr-G	R30014
72	SFA-5.21	ERCuAl-A2	C61800
72	SFA-5.21	ERCuAl-A3	C62400
72	SFA-5.21	ERCuAl-C	C62580
72	SFA-5.21	ERCuAl-D	C62581
72	SFA-5.21	ERCuAl-E	C62582
72	SFA-5.21	ERCuSi-A	C65600
72	SFA-5.21	ERCuSn-A	C51800
72	SFA-5.21	ERCuSn-D	C52400
72	SFA-5.21	ERFe-1	T74000
72	SFA-5.21	ERFe-1A	T74001

Table QW-432
F-Numbers
Grouping of Electrodes and Welding Rods for Qualification (Cont'd)

F-No.	ASME Specification	AWS Classification	UNS No.
Hard-Facing Weld Metal Overlay (Cont'd)			
72	SFA-5.21	ERFe-2	T74002
72	SFA-5.21	ERFe-3	T74003
72	SFA-5.21	ERFe-5	T74005
72	SFA-5.21	ERFe-6	T74006
72	SFA-5.21	ERFe-8	T74008
72	SFA-5.21	ERFeCr-A	...
72	SFA-5.21	ERFeCr-A1A	...
72	SFA-5.21	ERFeCr-A3A	...
72	SFA-5.21	ERFeCr-A4	...
72	SFA-5.21	ERFeCr-A5	...
72	SFA-5.21	ERFeCr-A9	...
72	SFA-5.21	ERFeCr-A10	...
72	SFA-5.21	ERFeMn-C	...
72	SFA-5.21	ERFeMn-F	...
72	SFA-5.21	ERFeMn-G	...
72	SFA-5.21	ERFeMn-H	...
72	SFA-5.21	ERFeMnCr	...
72	SFA-5.21	ERNiCr-A	N99644
72	SFA-5.21	ERNiCr-B	N99645
72	SFA-5.21	ERNiCr-C	N99646
72	SFA-5.21	ERNiCr-D	N99647
72	SFA-5.21	ERNiCr-E	N99648
72	SFA-5.21	ERNiCrFeCo	F46100
72	SFA-5.21	ERNiCrMo-5A	N10006
72	SFA-5.21	ERWCX-20/30	...
72	SFA-5.21	ERWCX-30/40	...
72	SFA-5.21	ERWCX-40	...
72	SFA-5.21	ERWCX-40/120	...
72	SFA-5.21	RWCX-20/30	...
72	SFA-5.21	RWCX-30/40	...
72	SFA-5.21	RWCX-40	...
72	SFA-5.21	RWCX-40/120	...

QW-433 ALTERNATE F-NUMBERS FOR WELDER PERFORMANCE QUALIFICATION

The following tables identify the filler metal or electrode that the welder used during qualification testing as “Qualified With,” and the electrodes or filler metals that the welder is qualified to use in production welding as “Qualified For.” See [Table QW-432](#) for the F-Number assignments.

Qualified With → Qualified For ↓	F-No. 1 With Backing	F-No. 1 Without Backing	F-No. 2 With Backing	F-No. 2 Without Backing	F-No. 3 With Backing	F-No. 3 Without Backing	F-No. 4 With Backing	F-No. 4 Without Backing	F-No. 5 With Backing	F-No. 5 Without Backing
F-No. 1 With Backing	X	X	X	X	X	X	X	X	X	X
F-No. 1 Without Backing		X								
F-No. 2 With Backing			X	X	X	X	X	X		
F-No. 2 Without Backing				X						
F-No. 3 With Backing					X	X	X	X		
F-No. 3 Without Backing						X				
F-No. 4 With Backing							X	X		
F-No. 4 Without Backing								X		
F-No. 5 With Backing									X	X
F-No. 5 Without Backing										X

Qualified With	Qualified For
Any F-No. 6	All F-No. 6 [Note (1)]
Any F-No. 21 through F-No. 25	All F-No. 21 through F-No. 25
Any F-No. 31, F-No. 32, F-No. 33, F-No. 35, F-No. 36, or F-No. 37	Only the same F-Number as was used during the qualification test
F-No. 34 or any F-No. 41 through F-No. 46	F-No. 34 and all F-No. 41 through F-No. 46
Any F-No. 51 through F-No. 55	All F-No. 51 through F-No. 55
Any F-No. 61	All F-No. 61
Any F-No. 71 through F-No. 72	Only the same F-Number as was used during the qualification test

NOTE:
(1) Deposited weld metal made using a bare rod not covered by an SFA Specification but which conforms to an analysis listed in QW-442 shall be considered to be classified as F-No. 6.

QW-440 WELD METAL CHEMICAL COMPOSITION**QW-441 GENERAL**

Identification of weld metal chemical composition designated on the PQR and WPS shall be as given in [QW-404.5](#).

(13)

Table QW-442 A-Numbers Classification of Ferrous Weld Metal Analysis for Procedure Qualification							
A-No.	Types of Weld Deposit	Analysis, % [Note (1)] and [Note (2)]					
		C	Cr	Mo	Ni	Mn	Si
1	Mild Steel	0.20	0.20	0.30	0.50	1.60	1.00
2	Carbon-Molybdenum	0.15	0.50	0.40-0.65	0.50	1.60	1.00
3	Chrome (0.4% to 2%)-Molybdenum	0.15	0.40-2.00	0.40-0.65	0.50	1.60	1.00
4	Chrome (2% to 4%)-Molybdenum	0.15	2.00-4.00	0.40-1.50	0.50	1.60	2.00
5	Chrome (4% to 10.5%)-Molybdenum	0.15	4.00-10.50	0.40-1.50	0.80	1.20	2.00
6	Chrome-Martensitic	0.15	11.00-15.00	0.70	0.80	2.00	1.00
7	Chrome-Ferritic	0.15	11.00-30.00	1.00	0.80	1.00	3.00
8	Chromium-Nickel	0.15	14.50-30.00	4.00	7.50-15.00	2.50	1.00
9	Chromium-Nickel	0.30	19.00-30.00	6.00	15.00-37.00	2.50	1.00
10	Nickel to 4%	0.15	0.50	0.55	0.80-4.00	1.70	1.00
11	Manganese-Molybdenum	0.17	0.50	0.25-0.75	0.85	1.25-2.25	1.00
12	Nickel-Chrome—Molybdenum	0.15	1.50	0.25-0.80	1.25-2.80	0.75-2.25	1.00
NOTES: (1) Single values shown above are maximum. (2) Only listed elements are used to determine A-numbers.							

QW-450 SPECIMENS**QW-451 PROCEDURE QUALIFICATION THICKNESS LIMITS AND TEST SPECIMENS**

(13)

Table QW-451.1
Groove-Weld Tension Tests and Transverse-Bend Tests

Thickness <i>T</i> of Test Coupon, Welded, in. (mm)	Range of Thickness <i>T</i> of Base Metal, Qualified, in. (mm) [Note (1)] and [Note (2)]		Maximum Thickness <i>t</i> of Deposited Weld Metal, Qualified, in. (mm) [Note (1)] and [Note (2)]	Type and Number of Tests Required (Tension and Guided-Bend Tests) [Note (2)]			
	Min.	Max.		Tension, QW-150	Side Bend, QW-160	Face Bend, QW-160	Root Bend, QW-160
Less than $\frac{1}{16}$ (1.5)	<i>T</i>	2 <i>T</i>	2 <i>t</i>	2	...	2	2
$\frac{1}{16}$ to $\frac{3}{8}$ (1.5 to 10), incl.	$\frac{1}{16}$ (1.5)	2 <i>T</i>	2 <i>t</i>	2	[Note (5)]	2	2
Over $\frac{3}{8}$ (10), but less than $\frac{3}{4}$ (19)	$\frac{3}{16}$ (5)	2 <i>T</i>	2 <i>t</i>	2	[Note (5)]	2	2
$\frac{3}{4}$ (19) to less than $1\frac{1}{2}$ (38)	$\frac{3}{16}$ (5)	2 <i>T</i>	2 <i>t</i> when <i>t</i> < $\frac{3}{4}$ (19)	2 [Note (4)]	4
$\frac{3}{4}$ (19) to less than $1\frac{1}{2}$ (38)	$\frac{3}{16}$ (5)	2 <i>T</i>	2 <i>T</i> when <i>t</i> ≥ $\frac{3}{4}$ (19)	2 [Note (4)]	4
$1\frac{1}{2}$ (38) to 6 (150), incl.	$\frac{3}{16}$ (5)	8 (200) [Note (3)]	2 <i>t</i> when <i>t</i> < $\frac{3}{4}$ (19)	2 [Note (4)]	4
$1\frac{1}{2}$ (38) to 6 (150), incl.	$\frac{3}{16}$ (5)	8 (200) [Note (3)]	8 (200) [Note (3)] when <i>t</i> ≥ $\frac{3}{4}$ (19)	2 [Note (4)]	4
Over 6 (150) [Note (6)]	$\frac{3}{16}$ (5)	1.33 <i>T</i>	2 <i>t</i> when <i>t</i> < $\frac{3}{4}$ (19)	2 [Note (4)]	4
Over 6 (150) [Note (6)]	$\frac{3}{16}$ (5)	1.33 <i>T</i>	1.33 <i>T</i> when <i>t</i> ≥ $\frac{3}{4}$ (19)	2 [Note (4)]	4

NOTES:

- (1) The following variables further restrict the limits shown in this table when they are referenced in [QW-250](#) for the process under consideration: [QW-403.9](#), [QW-403.10](#), [QW-404.32](#), and [QW-407.4](#). Also, [QW-202.2](#), [QW-202.3](#), and [QW-202.4](#) provide exemptions that supersede the limits of this table.
- (2) For combination of welding procedures, see [QW-200.4](#).
- (3) For the SMAW, SAW, GMAW, PAW, and GTAW welding processes only; otherwise per Note (1) or 2*T*, or 2*t*, whichever is applicable.
- (4) see [QW-151.1](#), [QW-151.2](#), and [QW-151.3](#) for details on multiple specimens when coupon thicknesses are over 1 in. (25 mm).
- (5) Four side-bend tests may be substituted for the required face- and root-bend tests, when thickness *T* is $\frac{3}{8}$ in. (10 mm) and over.
- (6) For test coupons over 6 in. (150 mm) thick, the full thickness of the test coupon shall be welded.

Table QW-451.2
Groove-Weld Tension Tests and Longitudinal-Bend Tests

Thickness <i>T</i> of Test Coupon Welded, in. (mm)	Range of Thickness <i>T</i> of Base Metal Qualified, in. (mm) [Note (1)] and [Note (2)]		Thickness <i>t</i> of Deposited Weld Metal Qualified, in. (mm) [Note (1)] and [Note (2)]	Type and Number of Tests Required (Tension and Guided-Bend Tests) [Note (2)]		
	Min.	Max.	Max.	Tension, QW-150	Face Bend, QW-160	Root Bend, QW-160
Less than $\frac{1}{16}$ (1.5)	<i>T</i>	2 <i>T</i>	2 <i>t</i>	2	2	2
$\frac{1}{16}$ to $\frac{3}{8}$ (1.5 to 10), incl.	$\frac{1}{16}$ (1.5)	2 <i>T</i>	2 <i>t</i>	2	2	2
Over $\frac{3}{8}$ (10)	$\frac{3}{16}$ (5)	2 <i>T</i>	2 <i>t</i>	2	2	2

NOTES:

- (1) The following variables further restrict the limits shown in this table when they are referenced in QW-250 for the process under consideration: QW-403.9, QW-403.10, QW-404.32, and QW-407.4. Also, QW-202.2, QW-202.3, and QW-202.4 provide exemptions that supersede the limits of this table.
- (2) For combination of welding procedures, see QW-200.4.

Table QW-451.3
Fillet-Weld Tests

Type of Joint	Thickness of Test Coupons as Welded, in.	Range Qualified	Type and Number of Tests Required [QW-462.4(a) or QW-462.4(d)] Macro
Fillet	Per QW-462.4(a)	All fillet sizes on all base metal thicknesses and all diameters	5
Fillet	Per QW-462.4(d)		4

GENERAL NOTE: A production assembly mockup may be substituted in accordance with QW-181.1.1. When a production assembly mockup is used, the range qualified shall be limited to the fillet weld size, base metal thickness, and configuration of the mockup. Alternatively, multiple production assembly mockups may be qualified. The range of thickness of the base metal qualified shall be no less than the thickness of the thinner member tested and no greater than the thickness of the thicker member tested. The range for fillet weld sizes qualified shall be limited to no less than the smallest fillet weld tested and no greater than the largest fillet weld tested. The configuration of production assemblies shall be the same as that used in the production assembly mockup.

Table QW-451.4
Fillet Welds Qualified by Groove-Weld Tests

Thickness <i>T</i> of Test Coupon (Plate or Pipe) as Welded	Range Qualified	Type and Number of Tests Required
All groove tests	All fillet sizes on all base metal thicknesses and all diameters	Fillet welds are qualified when the groove weld is qualified in accordance with either QW-451.1 or QW-451.2 (see QW-202.2)

GENERAL NOTE: Supplementary essential variables apply when notch toughness is required by other Sections.

QW-452 PERFORMANCE QUALIFICATION THICKNESS LIMITS AND TEST SPECIMENS

QW-452.1 Groove-Weld Test. The following tables identify the required type and number of tests and the thickness of weld metal qualified.

**Table QW-452.1(a)
Test Specimens**

Thickness of Weld Metal, in. (mm)	Type and Number of Examinations and Test Specimens Required			
	Visual Examination per QW-302.4	Side Bend QW-462.2 [Note (1)]	Face Bend QW-462.3(a) or QW-462.3(b) [Note (1)], [Note (2)]	Root Bend QW-462.3(a) or QW-462.3(b) [Note (1)], [Note (2)]
Less than $\frac{3}{8}$ (10)	X	...	1	1
$\frac{3}{8}$ (10) to less than $\frac{3}{4}$ (19)	X	2 [Note (3)]	[Note (3)]	[Note (3)]
$\frac{3}{4}$ (19) and over	X	2

GENERAL NOTE: The "Thickness of Weld Metal" is the total weld metal thickness deposited by all welders and all processes in the test coupon exclusive of the weld reinforcement.

NOTES:

- (1) To qualify using positions 5G or 6G, a total of four bend specimens are required. To qualify using a combination of 2G and 5G in a single test coupon, a total of six bend specimens are required. see QW-302.3. The type of bend test shall be based on weld metal thickness.
- (2) Coupons tested by face and root bends shall be limited to weld deposit made by one welder with one or two processes or two welders with one process each. Weld deposit by each welder and each process shall be present on the convex surface of the appropriate bent specimen.
- (3) One face and root bend may be substituted for the two side bends.

**Table QW-452.1(b)
Thickness of Weld Metal Qualified**

Thickness, t , of Weld Metal in the Coupon, in. (mm) [Note (1)] and [Note (2)]	Thickness of Weld Metal Qualified [Note (3)]
All	$2t$
$\frac{1}{2}$ (13) and over with a minimum of three layers	Maximum to be welded

NOTES:

- (1) When more than one welder and/or more than one process and more than one filler metal F-Number is used to deposit weld metal in a coupon, the thickness, t , of the weld metal in the coupon deposited by each welder with each process and each filler metal F-Number in accordance with the applicable variables under QW-404 shall be determined and used individually in the "Thickness, t , of Weld Metal in the Coupon" column to determine the "Thickness of Weld Metal Qualified."
- (2) Two or more pipe test coupons with different weld metal thickness may be used to determine the weld metal thickness qualified and that thickness may be applied to production welds to the smallest diameter for which the welder is qualified in accordance with QW-452.3.
- (3) Thickness of test coupon of $\frac{3}{4}$ in. (19 mm) or over shall be used for qualifying a combination of three or more welders each of whom may use the same or a different welding process.

Table QW-452.3
Groove-Weld Diameter Limits

Outside Diameter of Test Coupon, in. (mm)	Outside Diameter Qualified, in. (mm)	
	Min.	Max.
Less than 1 (25)	Size welded	Unlimited
1 (25) to $2\frac{7}{8}$ (73)	1 (25)	Unlimited
Over $2\frac{7}{8}$ (73)	$2\frac{7}{8}$ (73)	Unlimited

GENERAL NOTES:

- (a) Type and number of tests required shall be in accordance with [QW-452.1](#).
 (b) $2\frac{7}{8}$ in. (73 mm) O.D. is the equivalent of NPS $2\frac{1}{2}$ (DN 65).

Table QW-452.4
Small Diameter Fillet-Weld Test

Outside Diameter of Test Coupon, in. (mm)	Minimum Outside Diameter, Qualified, in. (mm)	Qualified Thick- ness
Less than 1 (25)	Size welded	All
1 (25) to $2\frac{7}{8}$ (73)	1 (25)	All
Over $2\frac{7}{8}$ (73)	$2\frac{7}{8}$ (73)	All

GENERAL NOTES:

- (a) Type and number of tests required shall be in accordance with QW-452.5.
 (b) $2\frac{7}{8}$ in. (73 mm) O.D. is considered the equivalent of NPS $2\frac{1}{2}$ (DN 65).

Table QW-452.5
Fillet-Weld Test

Type of Joint	Thickness of Test Coupon as Welded, in. (mm)	Qualified Range	Type and Number of Tests Required [QW-462.4(b) or QW-462.4(c)]	
			Macro	Fracture
Tee fillet [Note (1)]	$\frac{3}{16}$ (5) or greater	All base material thicknesses, fillet sizes, and diameters $2\frac{7}{8}$ (73) O.D. and over [Note (1)]	1	1
	Less than $\frac{3}{16}$ (5)	T to 2 T base material thickness, T maximum fillet size, and all diameters $2\frac{7}{8}$ (73) O.D. and over [Note (1)]	1	1

GENERAL NOTE: Production assembly mockups may be substituted in accordance with [QW-181.2.1](#). When production assembly mockups are used, range qualified shall be limited to the fillet sizes, base metal thicknesses, and configuration of the mockup.

NOTES:

- (1) Test coupon prepared as shown in QW-462.4(b) for plate or QW-462.4(c) for pipe.
 (2) $2\frac{7}{8}$ in. (73 mm) O.D. is considered the equivalent of NPS $2\frac{1}{2}$ (DN 65). For smaller diameter qualifications, refer to QW-452.4 or QW-452.6.

Table QW-452.6
Fillet Qualification by Groove-Weld Tests

Type of Joint	Thickness of Test Coupon as Welded, in. (mm)	Qualified Range	Type and Number of Tests Required
Any groove	All thicknesses	All base material thicknesses, fillet sizes, and diameters	Fillet welds are qualified when a welder/welding operator qualifies on a groove weld test

Table QW-453
Procedure/Performance Qualification Thickness Limits and Test Specimens for Hard-Facing (Wear-Resistant) and Corrosion-Resistant Overlays

Thickness of Test Coupon (<i>T</i>)	Corrosion-Resistant Overlay [Note (1)]		Hard-facing Overlay (Wear-Resistant) [Note (2)]	
	Nominal Base Metal Thickness Qualified (<i>T</i>)	Type and Number of Tests Required	Nominal Base Metal Thickness Qualified (<i>T</i>)	Type and Number of Tests Required
Procedure Qualification Testing				
Less than 1 in. (25 mm) <i>T</i>	<i>T</i> qualified to unlimited	Notes [Note (4)] , [Note (5)] , and [Note (9)]	<i>T</i> qualified up to 1 in. (25 mm)	Notes [Note (3)] , [Note (7)] , [Note (8)] , and [Note (9)]
1 in. (25 mm) and over <i>T</i>	1 in. (25 mm) to unlimited		1 in. (25 mm) to unlimited	
Performance Qualification Testing				
Less than 1 in. (25 mm) <i>T</i>	<i>T</i> qualified to unlimited	[Note (6)]	<i>T</i> qualified to unlimited	Notes [Note (8)] and [Note (10)]
1 in. (25 mm) and over <i>T</i>	1 in. (25 mm) to unlimited		1 in. (25 mm) to unlimited	

NOTES:

- The qualification test coupon shall consist of base metal not less than 6 in. (150 mm) × 6 in. (150 mm). The weld overlay cladding shall be a minimum of 1½ in. (38 mm) wide by approximately 6 in. (150 mm) long. For qualification on pipe, the pipe length shall be a minimum of 6 in. (150 mm), and a minimum diameter to allow the required number of test specimens. The weld overlay shall be continuous around the circumference of the test coupon. For processes (performance qualification only) depositing a weld bead width greater than ½ in. (13 mm) wide, the weld overlay shall consist of a minimum of three weld beads in the first layer.
- The test base metal coupon shall have minimum dimensions of 6 in. (150 mm) wide × approximately 6 in. (150 mm) long with a hard-facing layer a minimum of 1½ in. (38 mm) wide × 6 in. (150 mm) long. The minimum hard-faced thickness shall be as specified in the Welding Procedures Specification. Alternatively, the qualification may be performed on a test base metal coupon that represents the size of the production part. For qualification on pipe, the pipe length shall be 6 in. (150 mm) minimum, and of a minimum diameter to allow the required number of test specimens. The weld overlay shall be continuous around the circumference of the test coupon.
- The hard-facing surface shall be examined by the liquid penetrant method and shall meet the acceptance standards in QW-195.2 or as specified in the WPS. Surface conditioning prior to liquid penetrant examination is permitted.
- The corrosion-resistant surface shall be examined by the liquid penetrant method and shall meet the acceptance standards as specified in QW-195.
- Following the liquid penetrant examination, four guided side-bend tests shall be made from the test coupon in accordance with QW-161. The test specimens shall be cut so that there are either two specimens parallel and two specimens perpendicular to the direction of the welding, or four specimens perpendicular to the direction of the welding. For coupons that are less than ⅜ in. (10 mm) thick, the width of the side-bend specimens may be reduced to the thickness of the test coupon. The side-bend specimens shall be removed from locations specified in QW-462.5(c) or QW-462.5(d).
- The test coupon shall be sectioned to make side-bend test specimens perpendicular to the direction of the welding in accordance with QW-161. Test specimens shall be removed at locations specified in QW-462.5(c) or QW-462.5(d).
- After surface conditioning to the minimum thickness specified in the WPS, a minimum of three hardness readings shall be made on each of the specimens from the locations shown in QW-462.5(b) or QW-462.5(e). All readings shall meet the requirements of the WPS.
- The base metal shall be sectioned transversely to the direction of the hard-facing overlay. The two faces of the hard-facing exposed by sectioning shall be polished and etched with a suitable etchant and shall be visually examined with × 5 magnification for cracks in the base metal or the heat-affected zone, lack of fusion, or other linear defects. The overlay and the base metal shall meet the requirements specified in the WPS. All exposed faces shall be examined. See QW-462.5(b) for pipe and QW-462.5(e) for plate.
- When a chemical composition is specified in the WPS, chemical analysis specimens shall be removed at locations specified in QW-462.5(b) or QW-462.5(e). The chemical analysis shall be performed in accordance with QW-462.5(a) and shall be within the range specified in the WPS. This chemical analysis is not required when a chemical composition is not specified on the WPS.

Table QW-453
Procedure/Performance Qualification Thickness Limits and Test Specimens for Hard-Facing
(Wear-Resistant) and Corrosion-Resistant Overlays (Cont'd)

NOTES (CONT'D):


- (10) At a thickness greater than or equal to the minimum thickness specified in the WPS, the weld surface shall be examined by the liquid penetrant method and shall meet the acceptance standards in [QW-195.2](#) or as specified in the WPS. Surface conditioning prior to liquid penetrant examination is permitted.

QW-460 GRAPHICS

QW-461 POSITIONS

Figure QW-461.1
Positions of Welds — Groove Welds

Tabulation of Positions of Welds			
Position	Diagram Reference	Inclination of Axis, deg.	Rotation of Face, deg.
Flat	A	0 to 15	150 to 210
Horizontal	B	0 to 15	80 to 150 210 to 280
Overhead	C	0 to 80	0 to 80 280 to 360
Vertical	D	15 to 80	80 to 280
	E	80 to 90	0 to 360

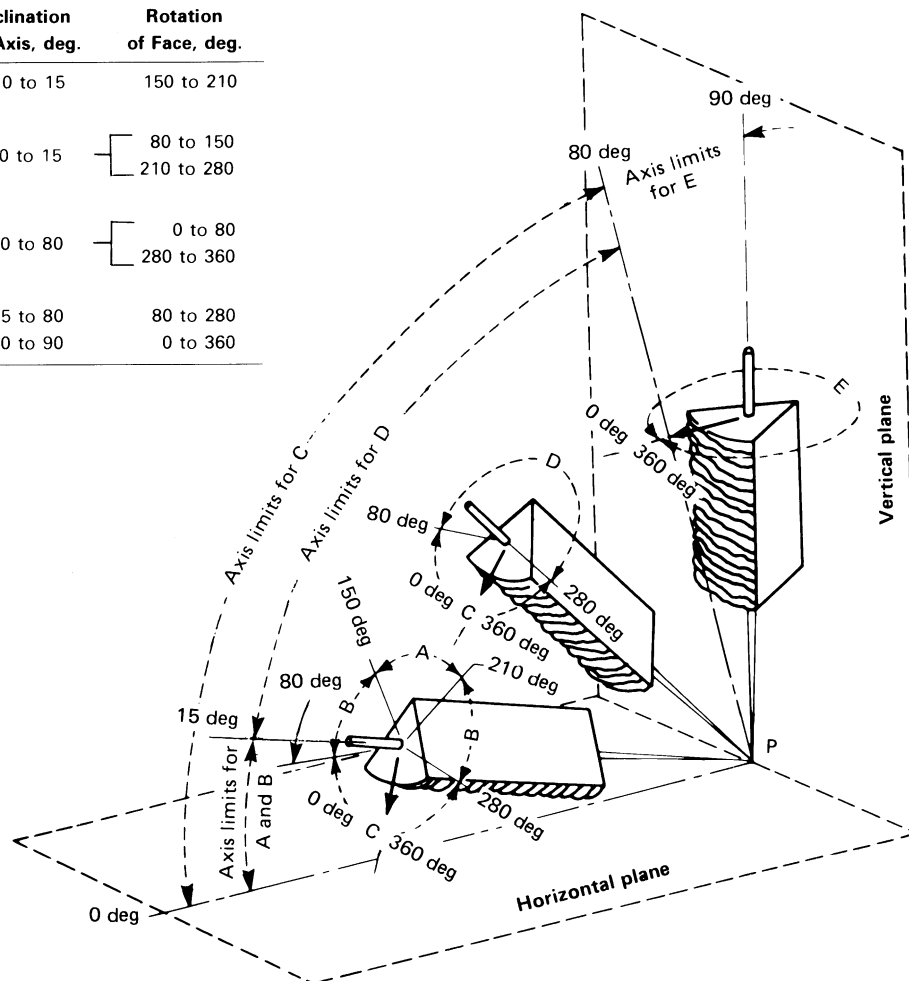

GENERAL NOTE: The horizontal reference plane is taken to lie always below the weld under consideration.

Inclination of axis is measured from the horizontal reference plane toward the vertical.

Angle of rotation of face is measured from a line perpendicular to the axis of the weld and lying in a vertical plane containing this axis. The reference position (0 deg) of rotation of the face invariably points in the direction opposite to that in which the axis angle increases. The angle of rotation of the face of weld is measured in a clockwise direction from this reference position (0 deg) when looking at point P.

Figure QW-461.2
Positions of Welds — Fillet Welds

Tabulation of Positions of Fillet Welds			
Position	Diagram Reference	Inclination of Axis, deg.	Rotation of Face, deg.
Flat	A	0 to 15	150 to 210
Horizontal	B	0 to 15	125 to 150 210 to 235
Overhead	C	0 to 80	0 to 125 235 to 360
Vertical	D	15 to 80	125 to 235
	E	80 to 90	0 to 360

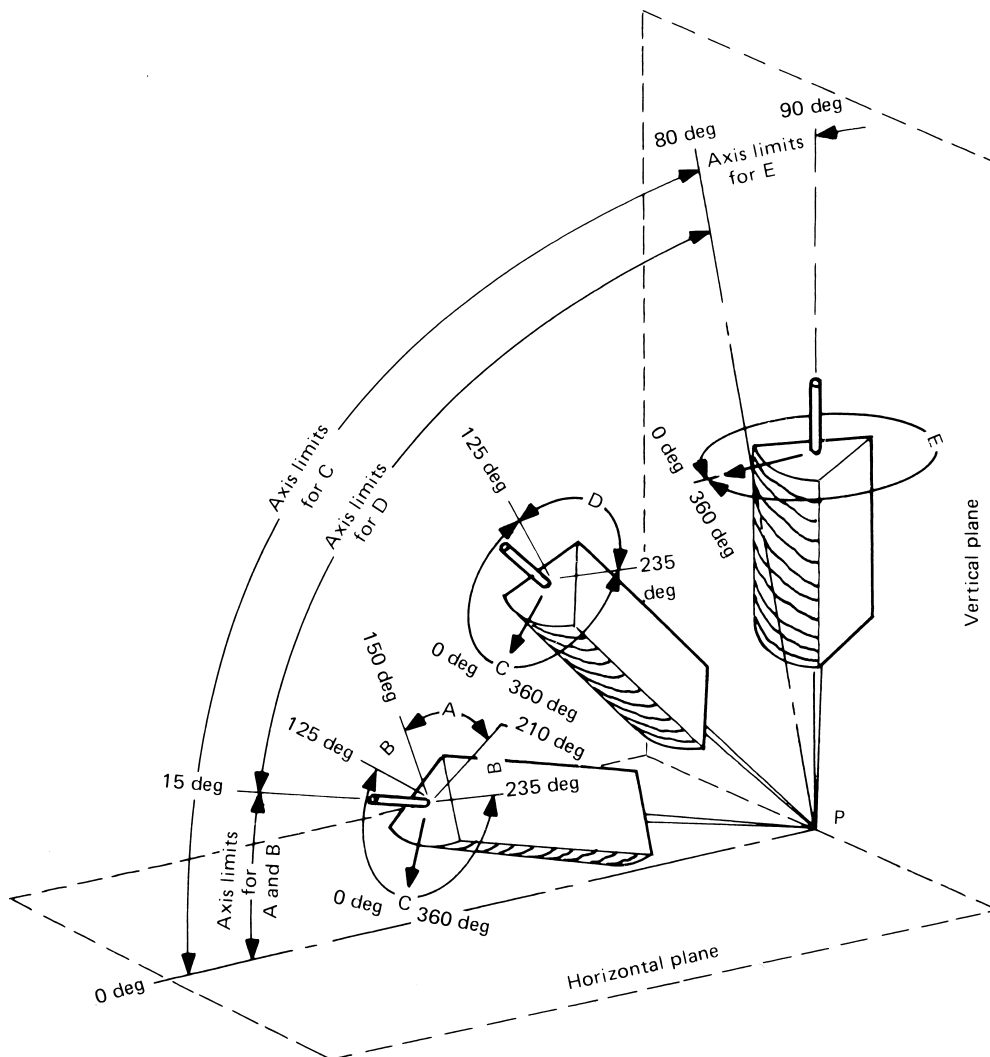


Figure QW-461.3
Groove Welds in Plate — Test Positions

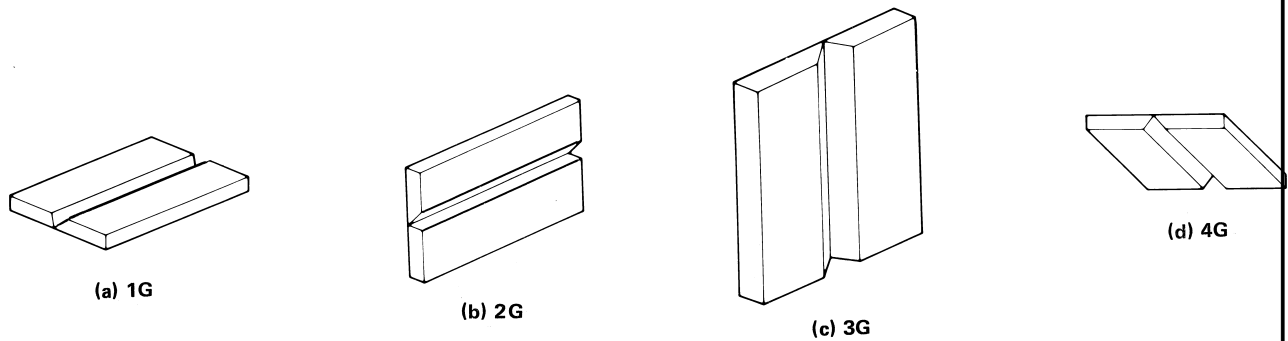


Figure QW-461.4
Groove Welds in Pipe — Test Positions

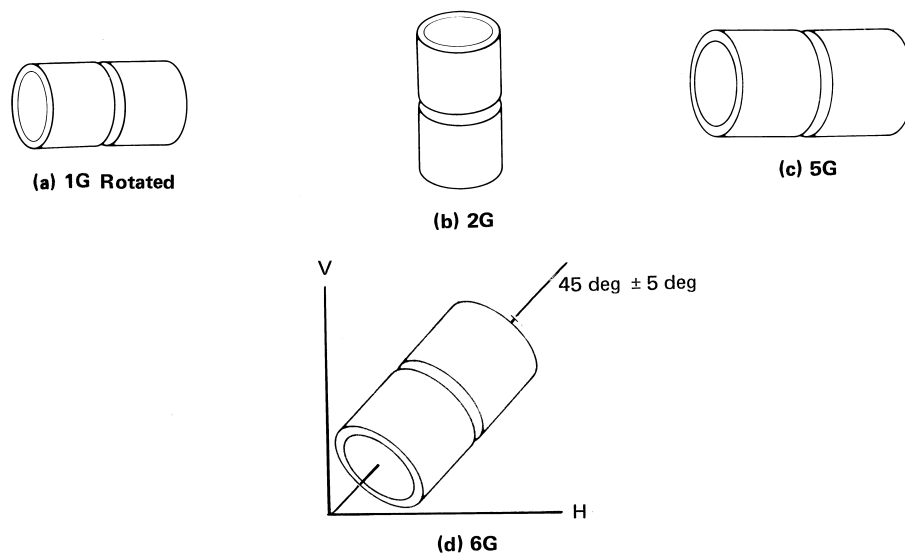


Figure QW-461.5
Fillet Welds in Plate — Test Positions

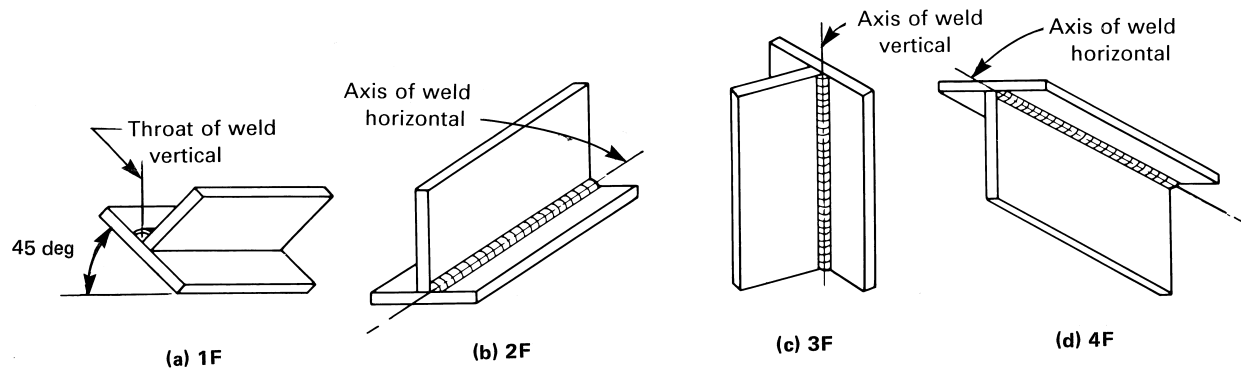


Figure QW-461.6
Fillet Welds in Pipe — Test Positions

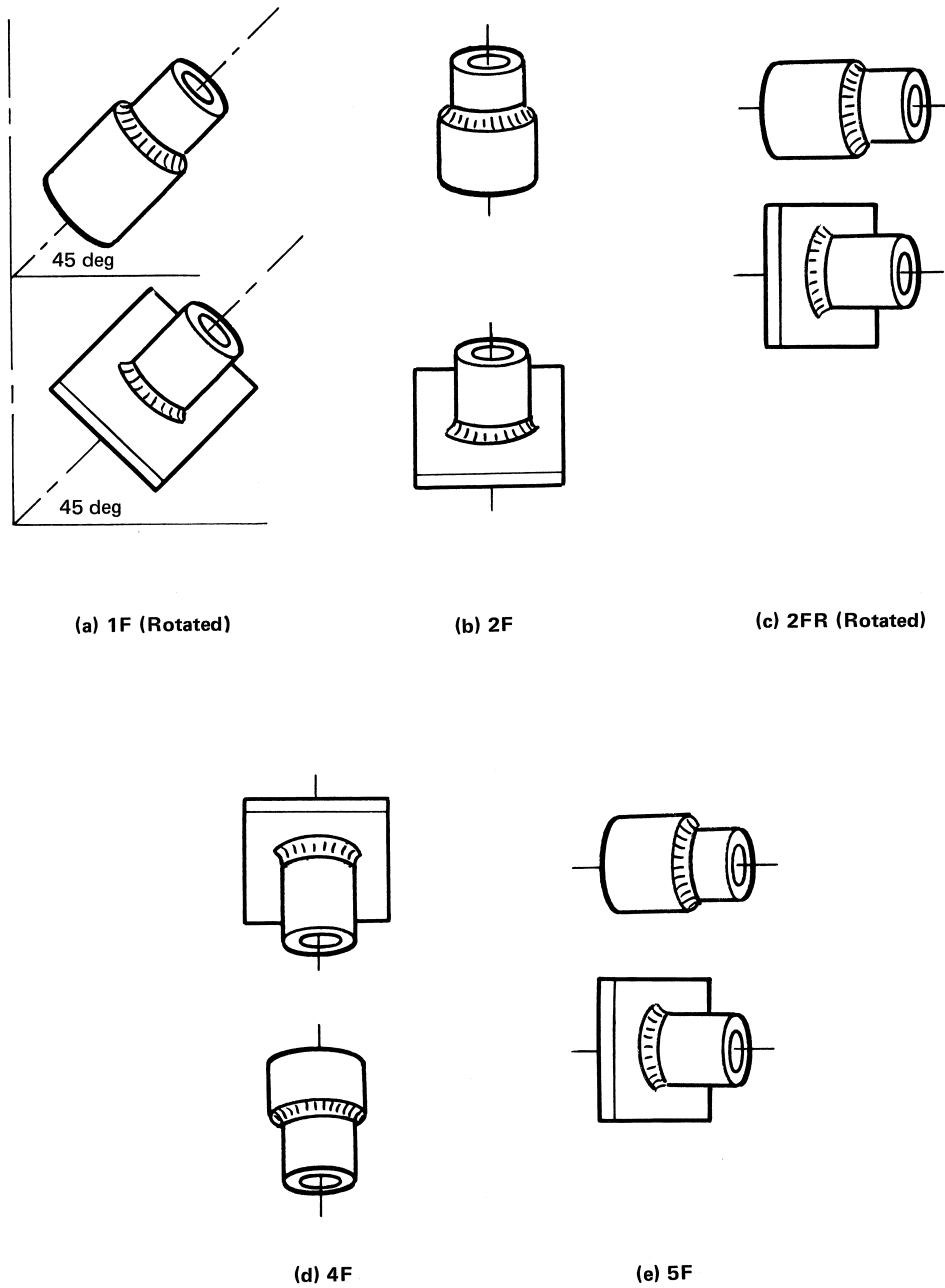


Figure QW-461.7
Stud Welds — Test Positions

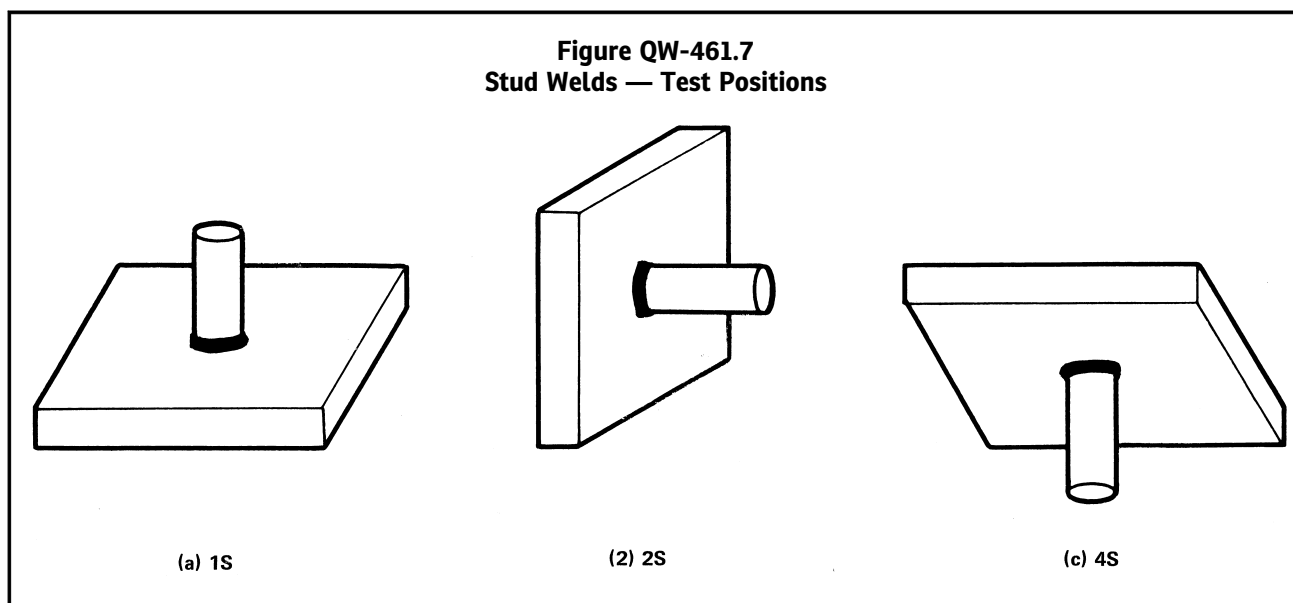


Figure QW-461.8
Stud Welds — Welding Positions

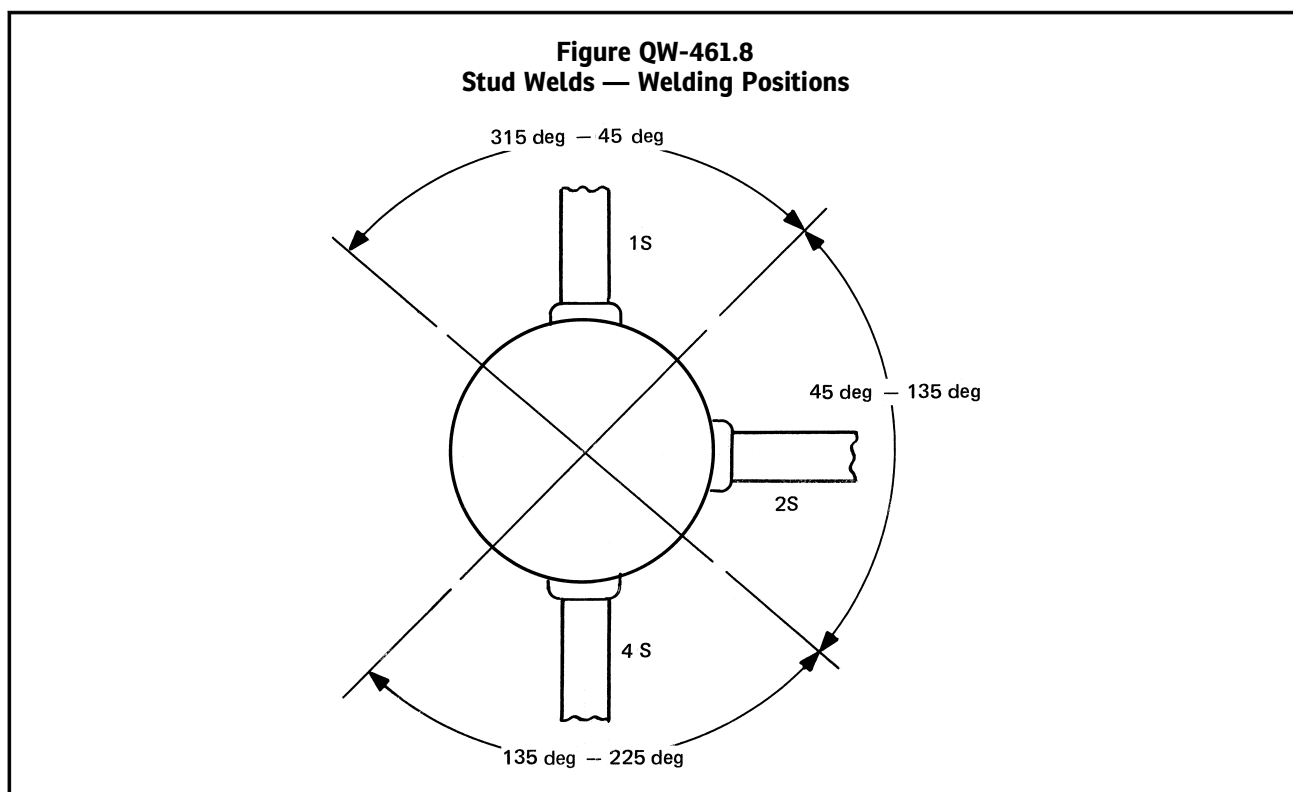


Table QW-461.9
Performance Qualification — Position and Diameter Limitations
(Within the Other Limitations of QW-303)

Qualification Test		Position and Type Weld Qualified [Note (1)]		
		Groove		Fillet
Weld	Position	Plate and Pipe Over 24 in. (610 mm) O.D.	Pipe ≤ 24 in. (610 mm) O.D.	Plate and Pipe
Plate — Groove	1G	F	F [Note (2)]	F
	2G	F,H	F,H [Note (2)]	F,H
	3G	F,V	F [Note (2)]	F,H,V
	4G	F,O	F [Note (2)]	F,H,O
	3G and 4G	F,V,O	F [Note (2)]	All
	2G, 3G, and 4G	All	F,H [Note (2)]	All
	Special Positions (SP)	SP,F	SP,F	SP,F
Plate — Fillet	1F	F [Note (2)]
	2F	F,H [Note (2)]
	3F	F,H,V [Note (2)]
	4F	F,H,O [Note (2)]
	3F and 4F	All [Note (2)]
	Special Positions (SP)	SP,F [Note (2)]
Pipe — Groove [Note (3)]	1G	F	F	F
	2G	F,H	F,H	F,H
	5G	F,V,O	F,V,O	All
	6G	All	All	All
	2G and 5G	All	All	All
	Special Positions (SP)	SP,F	SP,F	SP,F
Pipe — Fillet [Note (3)]	1F	F
	2F	F,H
	2FR	F,H
	4F	F,H,O
	5F	All
	Special Positions (SP)	SP,F

NOTES:

(1) Positions of welding as shown in QW-461.1 and QW-461.2.


F = Flat
H = Horizontal
V = Vertical
O = Overhead

(2) Pipe $2\frac{7}{8}$ in. (73 mm) O.D. and over.

(3) See diameter restrictions in QW-452.3, QW-452.4, and QW-452.6.

(13)

Figure QW-461.10
Rotating Tool Design Characteristics (FSW) Referenced in QW-410

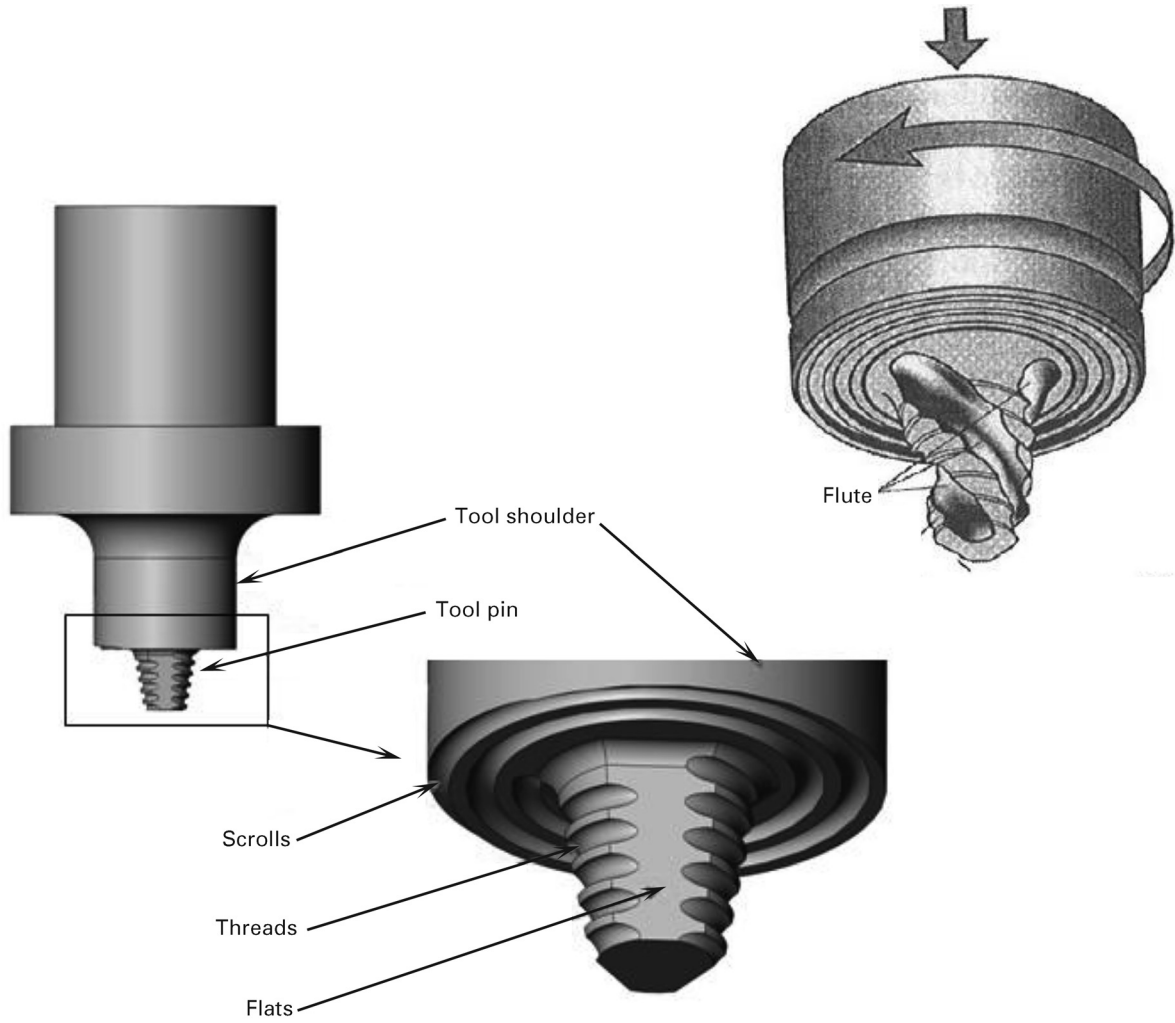

(13) **QW-462 TEST SPECIMENS**

The purpose of the QW-462 figures is to give the organization guidance in dimensioning test specimens for tests required for procedure and performance qualifications. Unless a minimum, maximum, or tolerance is given in the figures (or as QW-150, QW-160, or QW-180 requires),

the dimensions are to be considered approximate. All welding processes and filler material to be qualified must be included in the test specimen.

T = coupon thickness excluding reinforcement

W = specimen width, $\frac{3}{4}$ in. (19 mm)

x = coupon thickness including reinforcement

y = specimen thickness

Figure QW-462.1(a)
Tension — Reduced Section — Plate

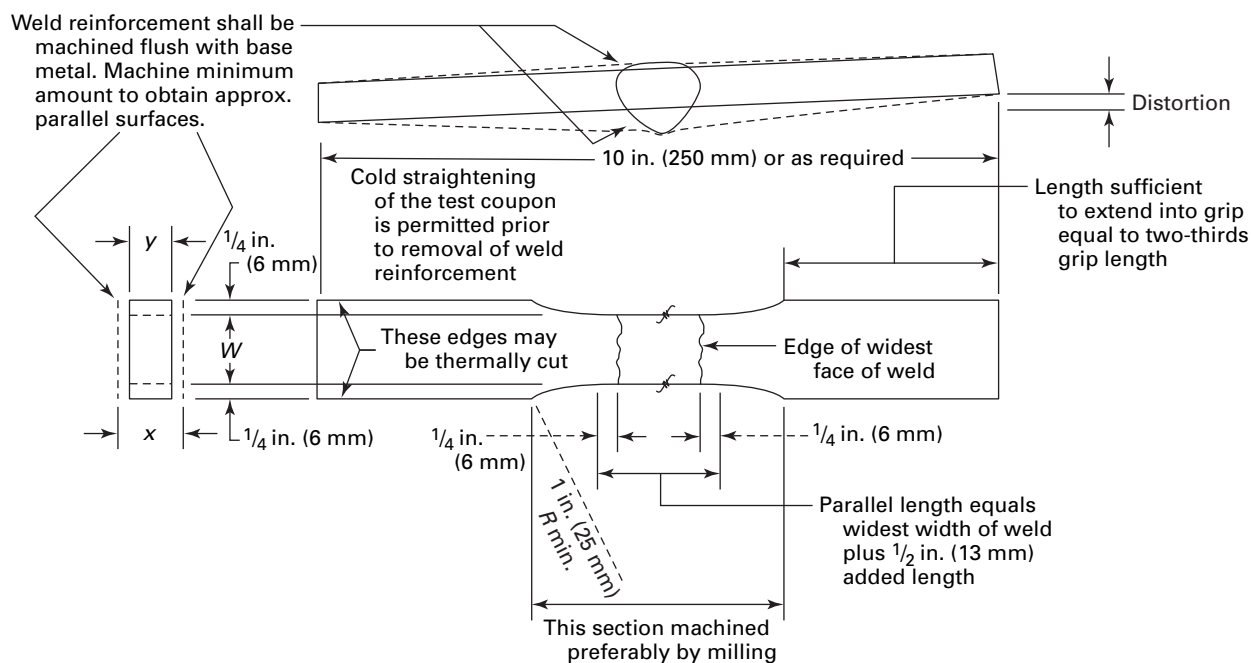


Figure QW-462.1(b)
Tension — Reduced Section — Pipe

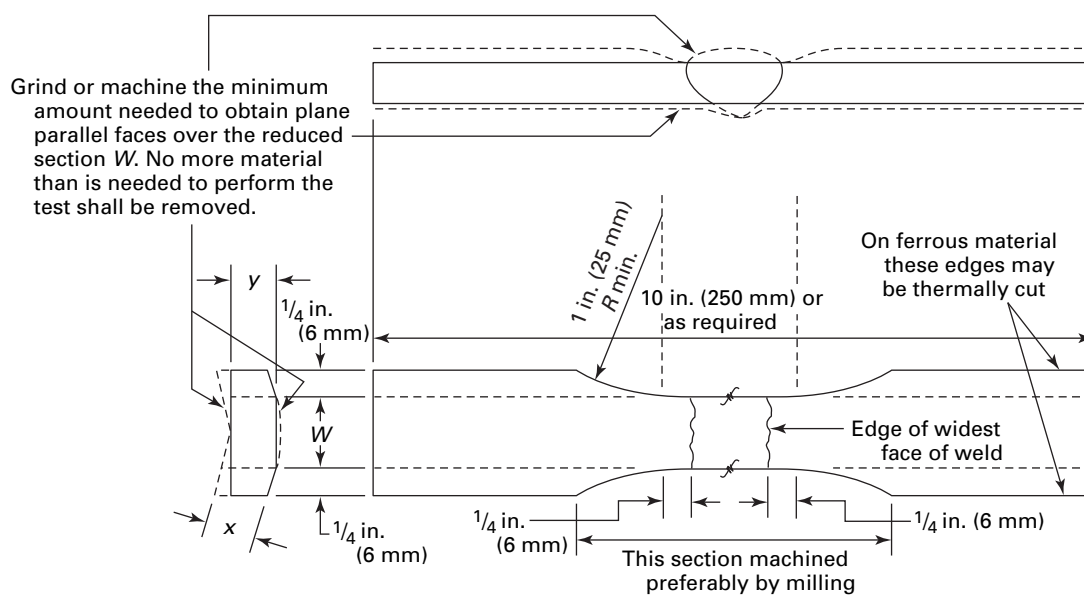


Figure QW-462.1(e)
Tension — Full Section — Small Diameter Pipe



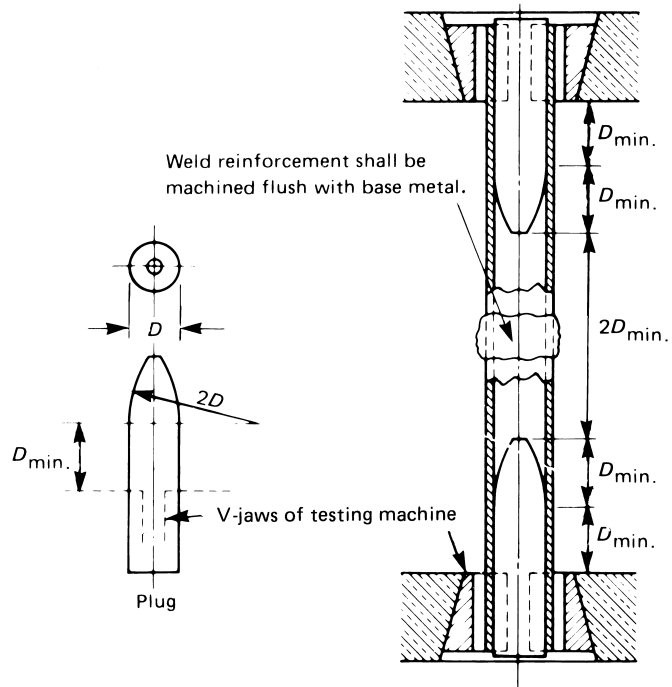


Figure QW-462.2
Side Bend

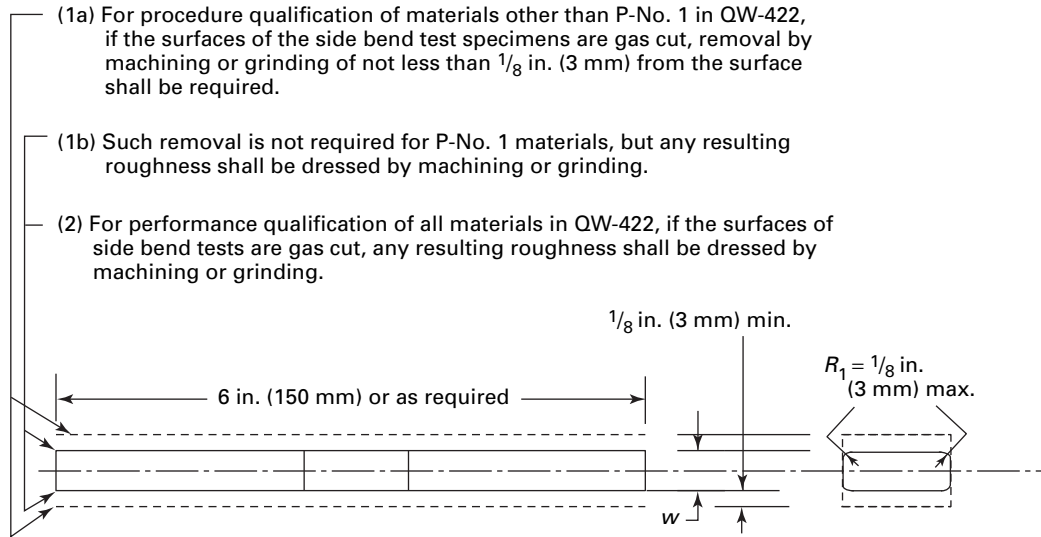

T , in. (mm)	y , in. (mm)	w , in. (mm)	
		P-No. 23, F-No. 23, or P-No. 35	All other metals
$\frac{3}{8}$ to $< 1\frac{1}{2}$ (10 to < 38)	T [Note (1)]	$\frac{1}{8}$ (3)	$\frac{3}{8}$ (10)
$\geq 1\frac{1}{2}$ (≥ 38)	Notes (1) and (2)	$\frac{1}{8}$ (3)	$\frac{3}{8}$ (10)



GENERAL NOTE: Weld reinforcement and backing strip or backing ring, if any, may be removed flush with the surface of the specimen. Thermal cutting, machining, or grinding may be employed. Cold straightening is permitted prior to removal of the reinforcement.

NOTES:

(1) When weld deposit t is less than coupon thickness T , side-bend specimen thickness may be t .


(2) When coupon thickness T equals or exceeds $1\frac{1}{2}$ in. (38 mm), use one of the following:

(a) Cut specimen into multiple test specimens of thickness y of approximately equal dimensions $\frac{3}{4}$ in. to $1\frac{1}{2}$ in. (19 mm to 38 mm).


y = tested specimen thickness when multiple specimens are taken from one coupon.

(b) The specimen may be bent at full width. See requirements on jig width in [QW-466.1](#).

Figure QW-462.3(a)
Face and Root Bends — Transverse

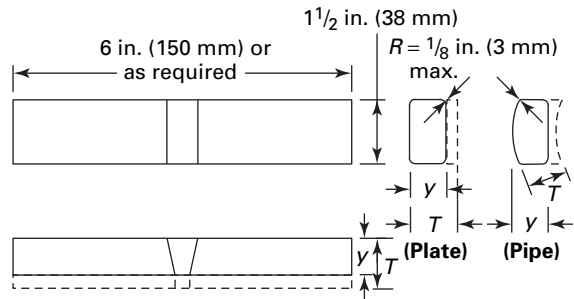

Face-Bend Specimen — Plate and Pipe

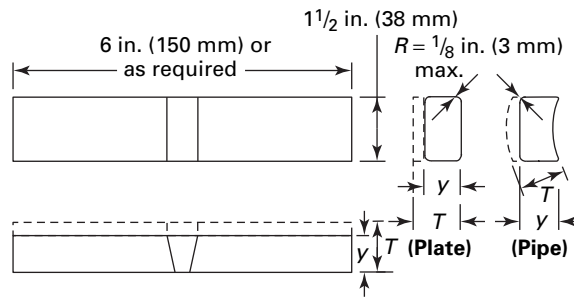


Root-Bend Specimen — Plate and Pipe

T, in. (mm)	Y, in. (mm)	
	P-No. 23, F-No. 23, or P-No. 35	All Other Metals
$\frac{1}{16} < \frac{1}{8}$ (1.5 < 3)	T	T
$\frac{1}{8} - \frac{3}{8}$ (3 - 10)	$\frac{1}{8}$ (3)	T
$> \frac{3}{8}$ (10)	$\frac{1}{8}$ (3)	$\frac{3}{8}$ (10)

GENERAL NOTES:

- Weld reinforcement and backing strip or backing ring, if any, may be removed flush with the surface of the specimen. If a recessed ring is used, this surface of the specimen may be machined to a depth not exceeding the depth of the recess to remove the ring, except that in such cases the thickness of the finished specimen shall be that specified above. Do not flame-cut nonferrous material.
- If the pipe being tested has a diameter of NPS 4 (DN 100) or less, the width of the bend specimen may be $\frac{3}{4}$ in. (19 mm) for pipe diameters NPS 2 (DN 50) to and including NPS 4 (DN 100). The bend specimen width may be $\frac{3}{8}$ in. (10 mm) for pipe diameters less than NPS 2 (DN 50) down to and including NPS $\frac{3}{8}$ (DN 10) and as an alternative, if the pipe being tested is equal to or less than NPS 1 (DN 25) pipe size, the width of the bend specimens may be that obtained by cutting the pipe into quarter sections, less an allowance for saw cuts or machine cutting. These specimens cut into quarter sections are not required to have one surface machined flat as shown in [QW-462.3\(a\)](#). Bend specimens taken from tubing of comparable sizes may be handled in a similar manner.


Figure QW-462.3(b)
Face and Root Bends — Longitudinal

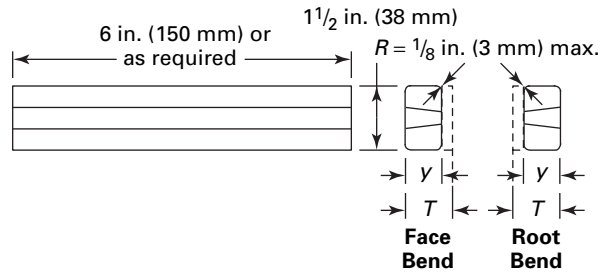

T, in. (mm)	Y, in. (mm)	
	P-No. 23, F-No. 23, or P-No. 35	All Other Metals
$\frac{1}{16} < \frac{1}{8}$ (1.5 < 3)	T	T
$\frac{1}{8} - \frac{3}{8}$ (3 - 10)	$\frac{1}{8}$ (3)	T
$> \frac{3}{8}$ (10)	$\frac{1}{8}$ (3)	$\frac{3}{8}$ (10)


GENERAL NOTE: Weld reinforcements and backing strip or backing ring, if any, shall be removed essentially flush with the undisturbed surface of the base material. If a recessed strip is used, this surface of the specimen may be machined to a depth not exceeding the depth of the recess to remove the strip, except that in such cases the thickness of the finished specimen shall be that specified above.

Figure QW-462.4(a)
Fillet Welds in Plate — Procedure

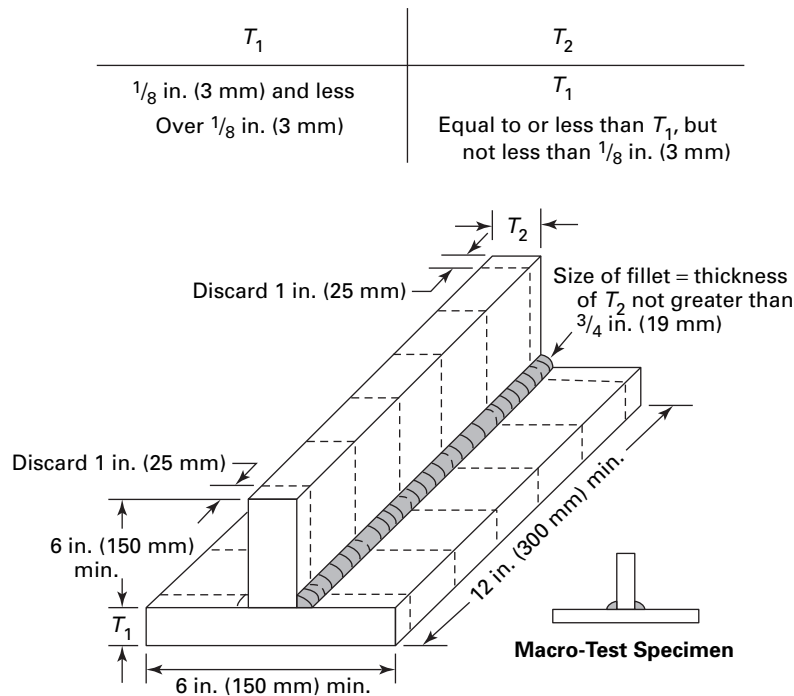


GENERAL NOTE: Macro-test — the fillet shall show fusion at the root of the weld but not necessarily beyond the root. The weld metal and heat-affected zone shall be free of cracks.

Figure QW-462.4(b)
Fillet Welds in Plate — Performance

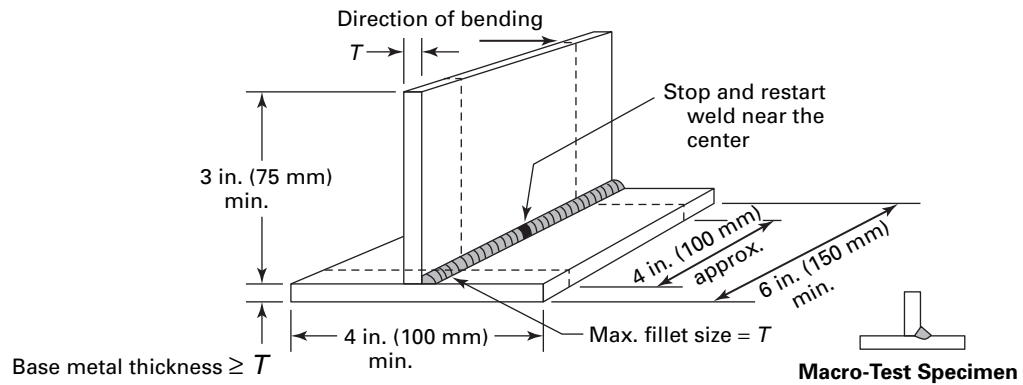


GENERAL NOTE: Refer to QW-452.5 for T thickness/qualification ranges.

Figure QW-462.4(c)
Fillet Welds in Pipe — Performance

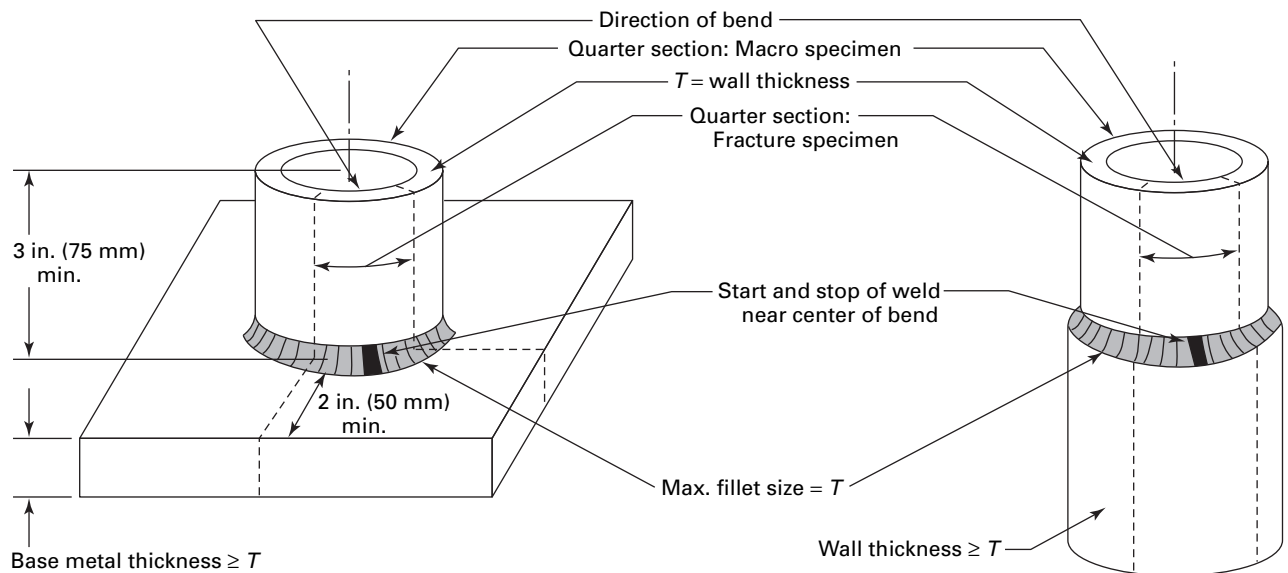

GENERAL NOTE: Either pipe-to-plate or pipe-to-pipe may be used as shown.

Figure QW-462.4(d)
Fillet Welds in Pipe — Procedure

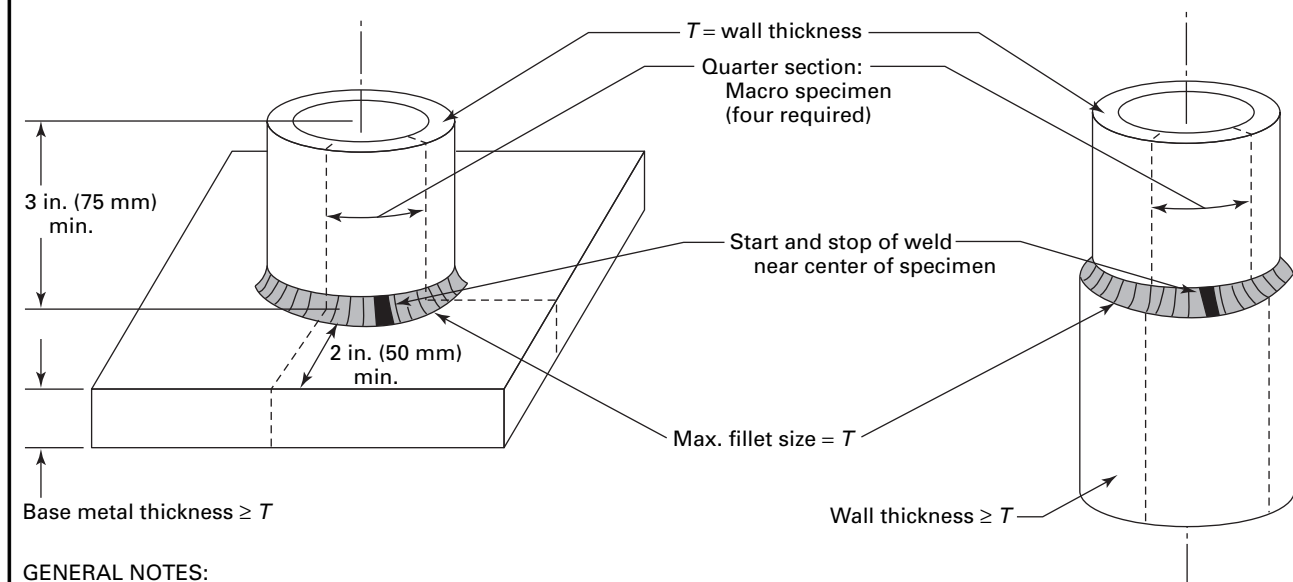


GENERAL NOTES:

(a) Either pipe-to-plate or pipe-to-pipe may be used as shown.

(b) Macro test:

- (1) The fillet shall show fusion at the root of the weld but not necessarily beyond the root.
- (2) The weld metal and the heat-affected zone shall be free of cracks.


Figure QW-462.5(a)
Chemical Analysis and Hardness Specimen Corrosion-Resistant and Hard-Facing Weld Metal Overlay

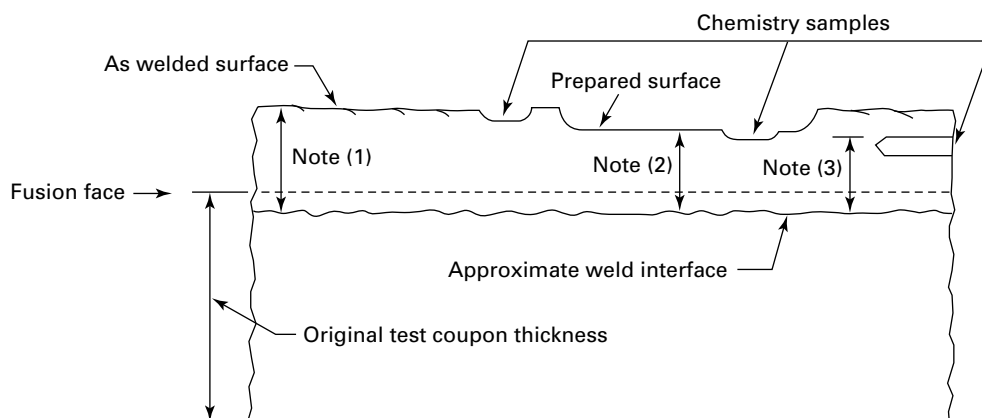

NOTES:

- (1) When a chemical analysis or hardness test is conducted on the as welded surface, the distance from the approximate weld interface to the final as welded surface shall become the minimum qualified overlay thickness. The chemical analysis may be performed directly on the as welded surface or on chips of material taken from the as welded surface.
- (2) When a chemical analysis or hardness test is conducted after material has been removed from the as welded surface, the distance from the approximate weld interface to the prepared surface shall become the minimum qualified overlay thickness. The chemical analysis may be made directly on the prepared surface or from chips removed from the prepared surface.
- (3) When a chemical analysis test is conducted on material removed by a horizontal drilled sample, the distance from the approximate weld interface to the uppermost side of the drilled cavity shall become the minimum qualified overlay thickness. The chemical analysis shall be performed on chips of material removed from the drilled cavity.

Figure QW-462.5(b)
Chemical Analysis Specimen, Hard-Facing Overlay Hardness, and Macro Test Location(s) for
Corrosion-Resistant and Hard-Facing Weld Metal Overlay

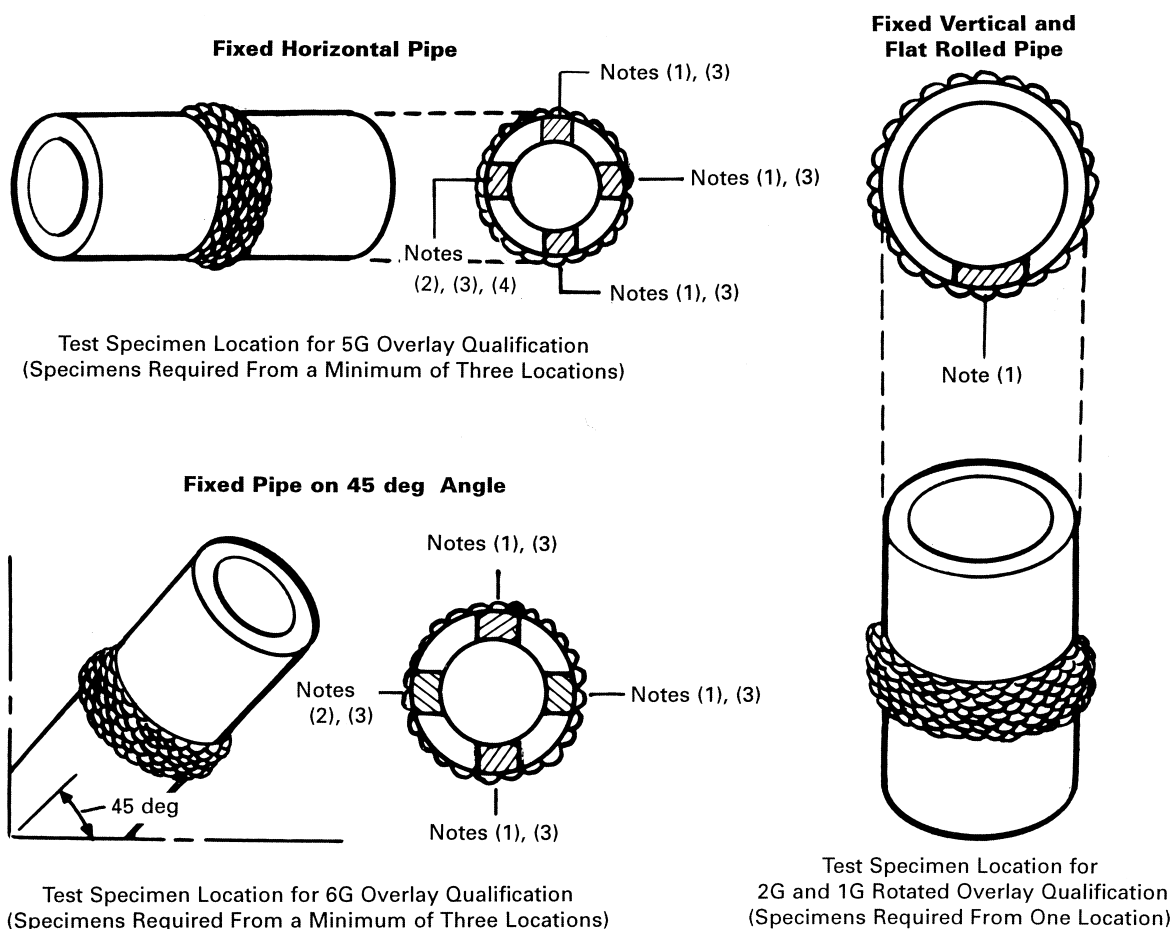


GENERAL NOTE: Overlay may be on the inside or outside of pipe.

NOTES:

- (1) Location of required test specimen removal (QW-453). Refer to QW-462.5(a) for chemical analysis and hardness test surface locations and minimum qualified thickness.
- (2) Testing of circumferential hard-facing weld metal on pipe procedure qualification coupons may be limited to a single segment (completed utilizing the vertical, up-hill progression) for the chemical analysis, hardness, and macro-etch tests required in QW-453. Removal is required for a change from vertical down to vertical up-hill progression (but not vice-versa).
- (3) Location of test specimens shall be in accordance with the angular position limitations of QW-120.
- (4) When overlay welding is performed using machine or automatic welding and the vertical travel direction of adjacent weld beads is reversed on alternate passes, only one chemical analysis or hardness specimen is required to represent the vertical portion. Qualification is then restricted in production to require alternate pass reversal of rotation direction method.

Figure QW-462.5(c)
Pipe Bend Specimen — Corrosion-Resistant Weld Metal Overlay

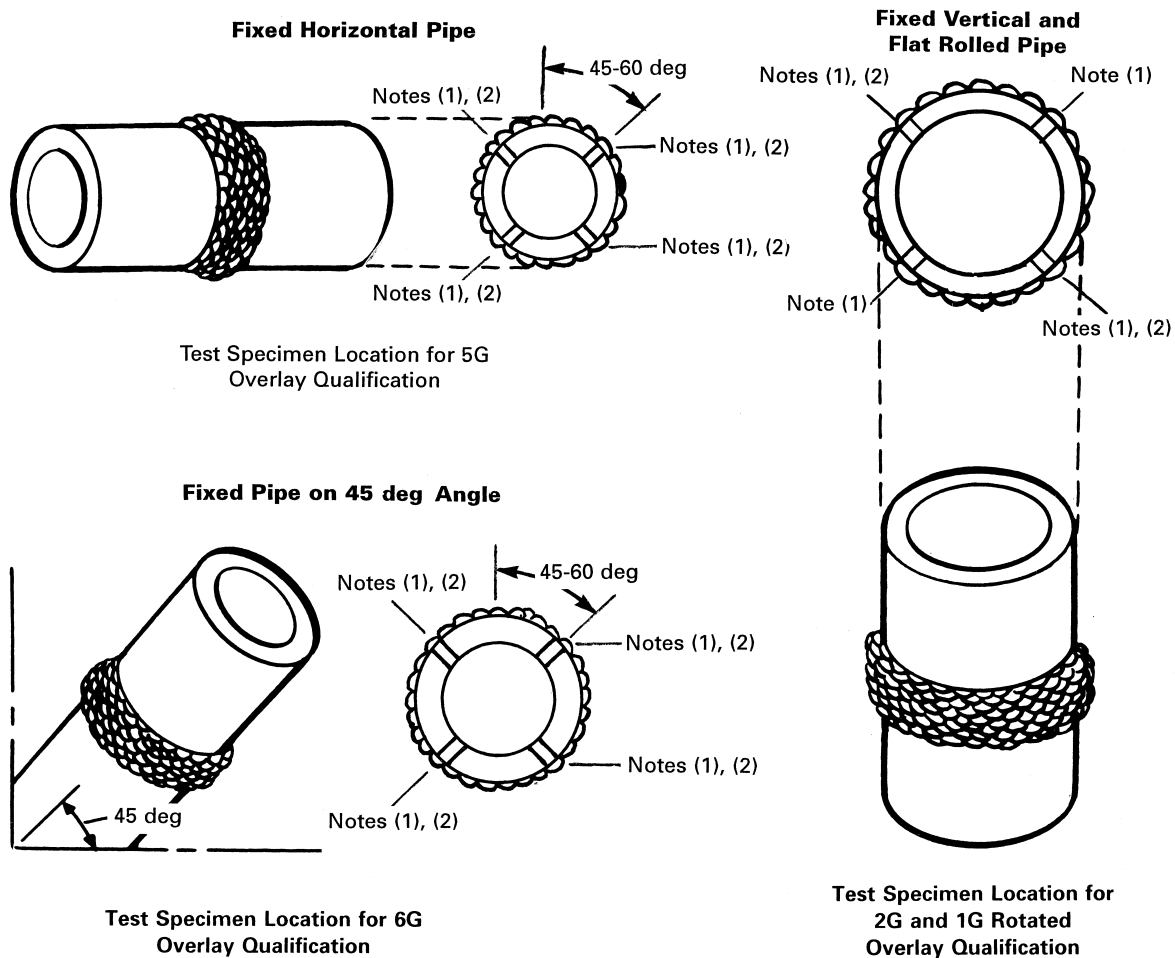


GENERAL NOTE: Overlay may be on the inside or outside of pipe.

NOTES:

- (1) Location for required test specimen removal — Procedure (QW-453).
- (2) Location for required test specimen removal — Performance (QW-453).


Figure QW-462.5(d)
Plate Bend Specimens — Corrosion-Resistant Weld Metal Overlay

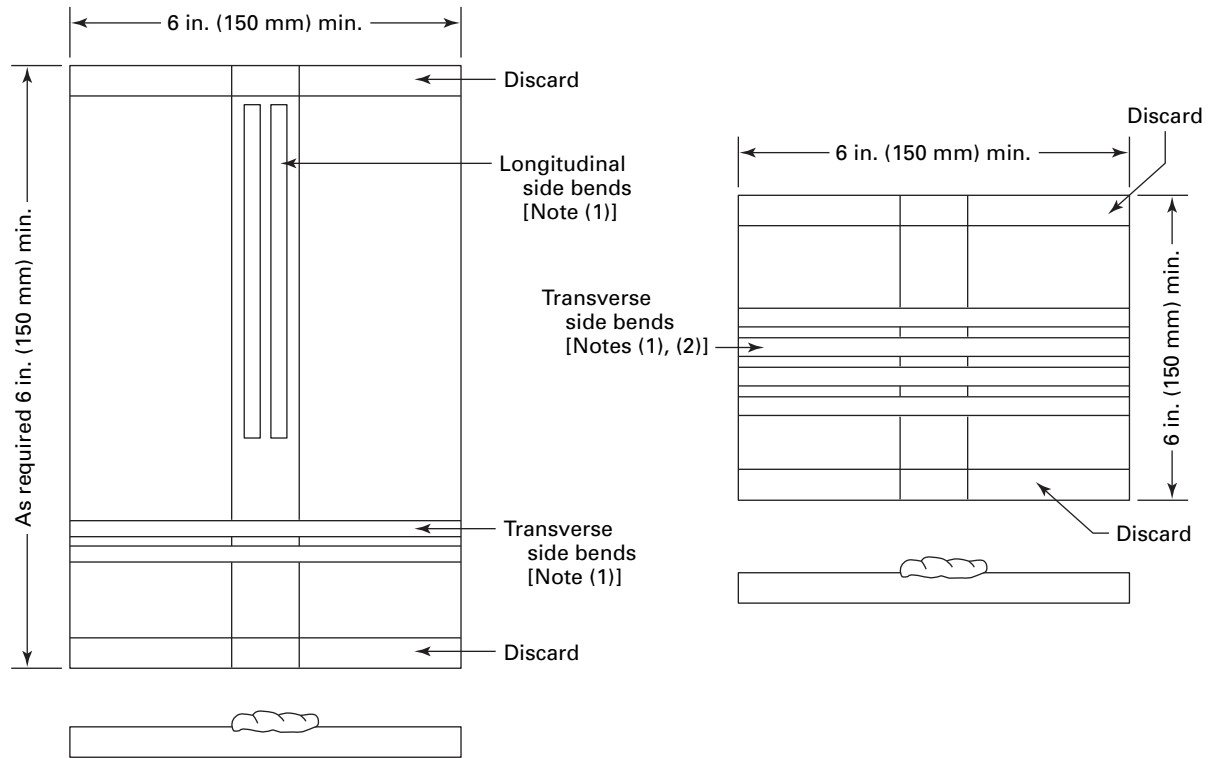

NOTES:

- (1) Location for required test specimen removal — Procedure (QW-453). Four-side-bend test specimens are required for each position.
- (2) Location for required test specimen removal — Performance (QW-453). Two-side-bend test specimens are required for each position.

Figure QW-462.5(e)
Plate Macro, Hardness, and Chemical Analysis Specimens — Corrosion-Resistant and Hard-Facing Weld Metal Overlay

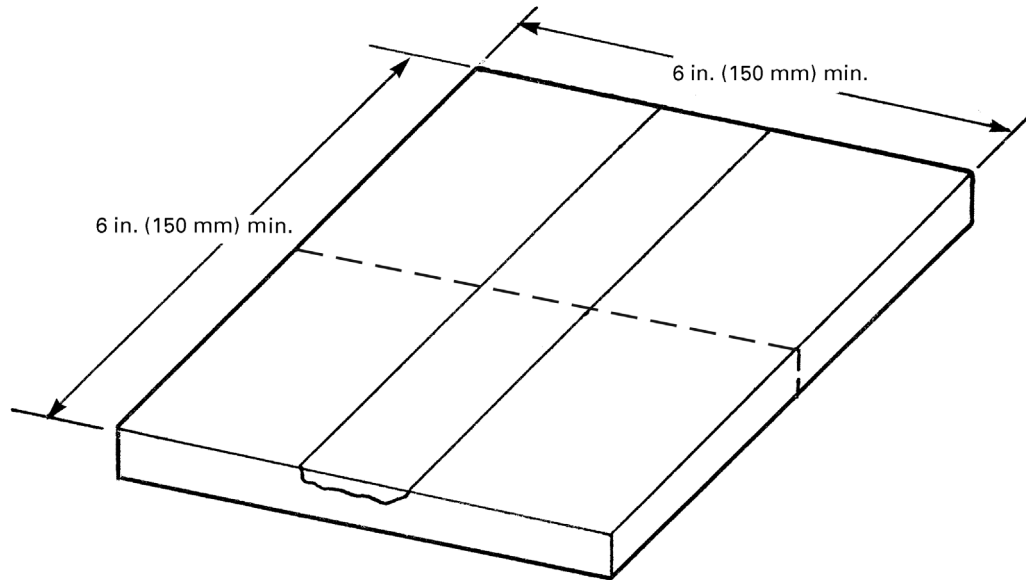

GENERAL NOTES:

- (a) Location of required test specimen removal (QW-453). One required for each position. Refer to QW-462.5(a) for chemical analysis and hardness test surface locations and minimum qualified thickness.
- (b) Removal required for a change from vertical up to vertical down and vice versa.

Figure QW-462.7.1
Resistance Seam Weld Test Coupon


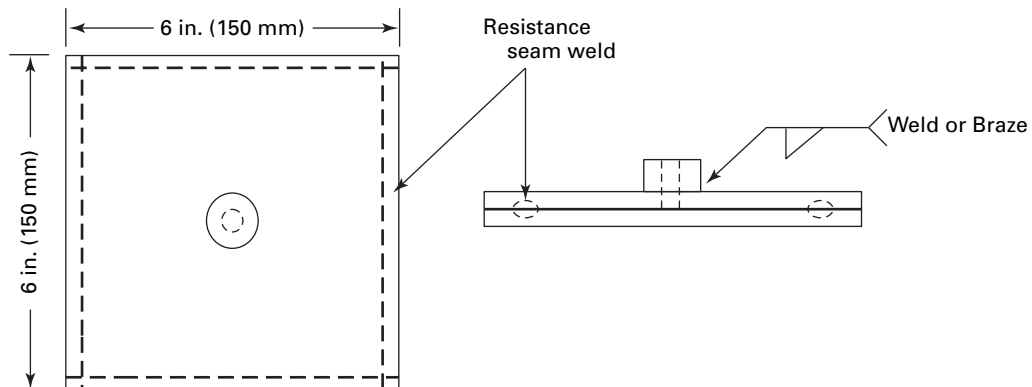


Figure QW-462.7.2
Seam Weld Section Specimen Removal

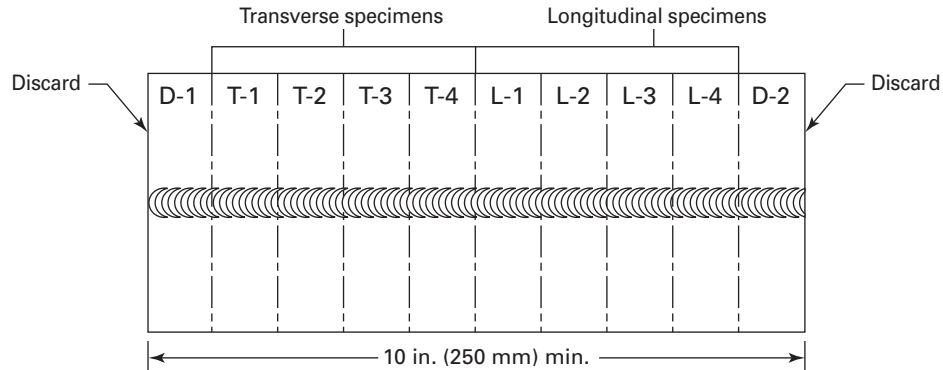

GENERAL NOTE: Mark the coupon into ten equal length specimens, label one end of the coupon D-1 the other end D-2. Cut the 10 in. (250 mm) coupon (transverse to the weld length) into pieces 5 in. (125 mm) long each.

(1) Transverse Weld Cross Section Instructions

(a) Cut five specimens each approximately 1 in. (25 mm) in length from the coupon labeled D-1 and discard the piece marked D-1.

(b) Mark the remaining four specimens T-1 through T-4, prepare the specimens as detailed in (b)(2)(a) below for examination, adjacent faces at the cut shall not be used.


(2) Longitudinal Weld Cross Section Instructions

(a) Cut five specimens each approximately 1 in. (25 mm) in length from the coupon labeled D-2 and discard the piece marked D-2.


(b) Mark the remaining four specimens L-1 through L-4, cut the specimens at approximately $\frac{1}{3}$ of the weld width from the weld centerline through the length of each specimen in the longitudinal weld direction. Discard the four specimens containing approximately the $\frac{1}{3}$ weld width, the remaining four specimens containing approximately the $\frac{2}{3}$ weld width shall be prepared as detailed in (a) below for examination.

(-1) The specimens shall be smoothed and etched with a suitable etchant (see [QW-470](#)) to give a clear definition to the weld metal and heat-affected zone.

Figure QW-462.7.3
Resistance Weld Nugget Section Test Specimens

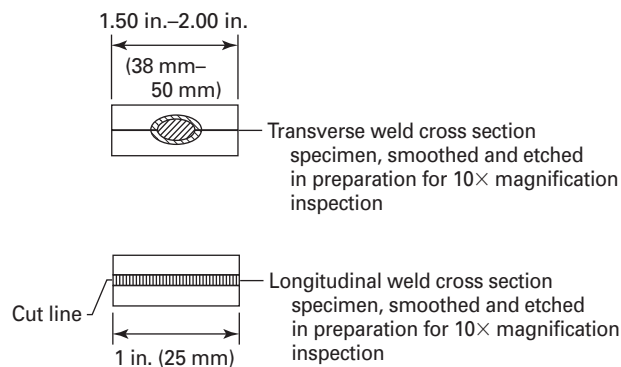

**Figure QW-462.8.1
Spot Welds in Sheets**

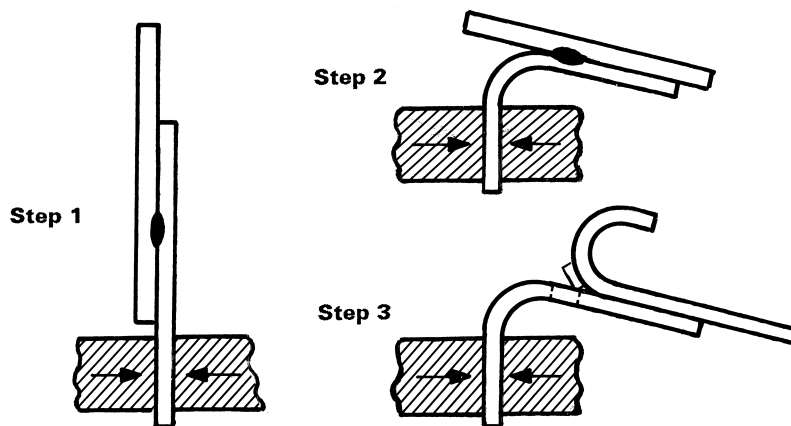


Peel Test

Step 1 - Grip in vise or other suitable device.

Step 2 - Bend specimen.

Step 3 - Peel pieces apart with pincers or other suitable tool.


Figure QW-462.8.2
Seam Weld Peel Test Specimen and Method

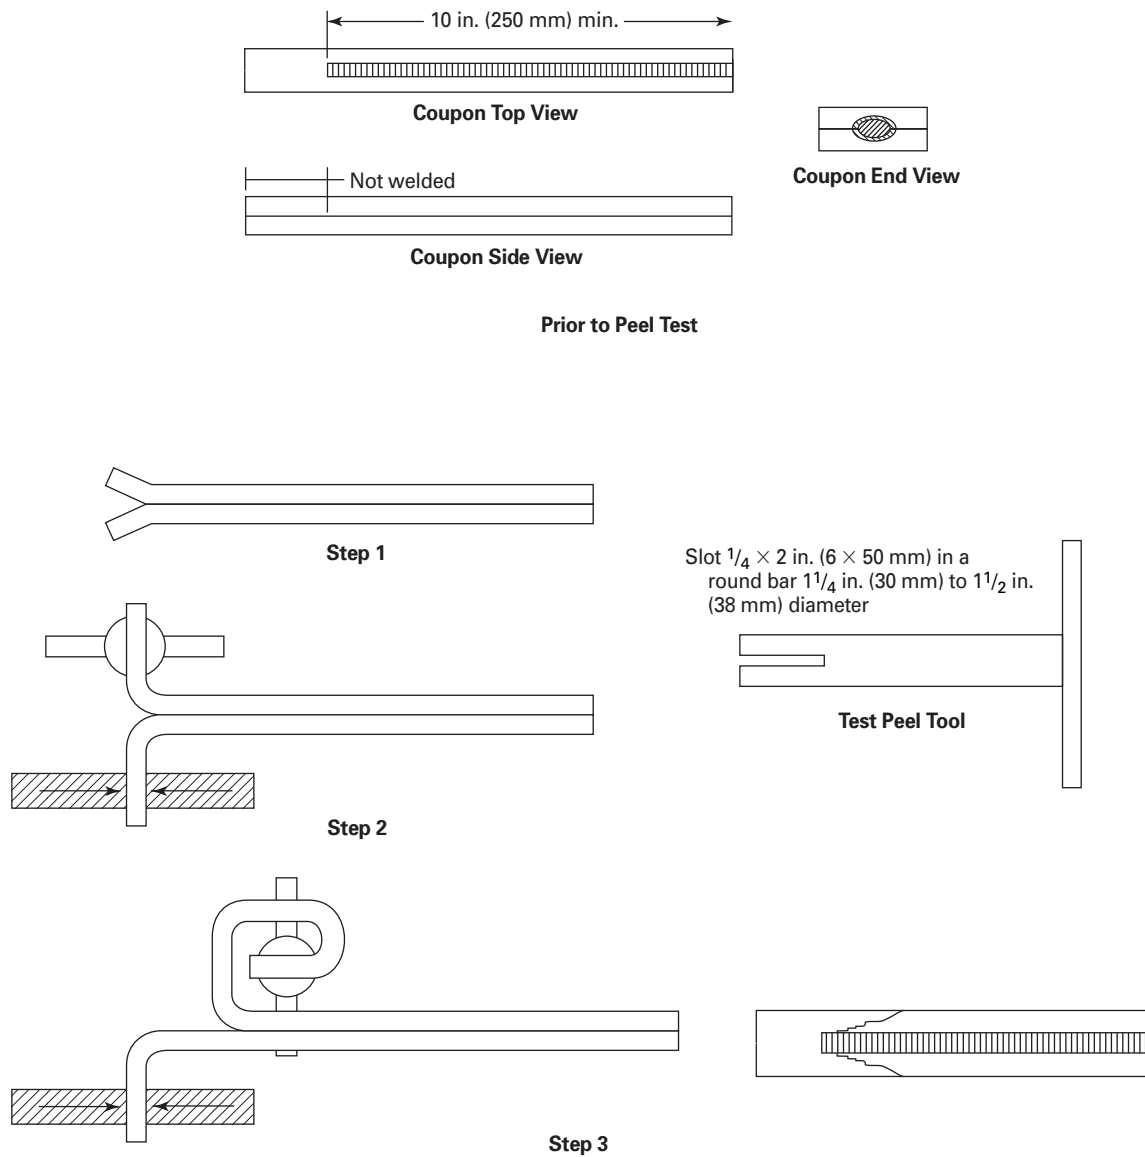

Peel Test

- Step 1 — Separate coupon plies in nonwelded end.
 Step 2 — Grip in vise or other suitable device, bend specimen.
 Step 3 — Peel pieces apart with pincers or other suitable tool.

Figure QW-462.9
Spot Welds in Sheet

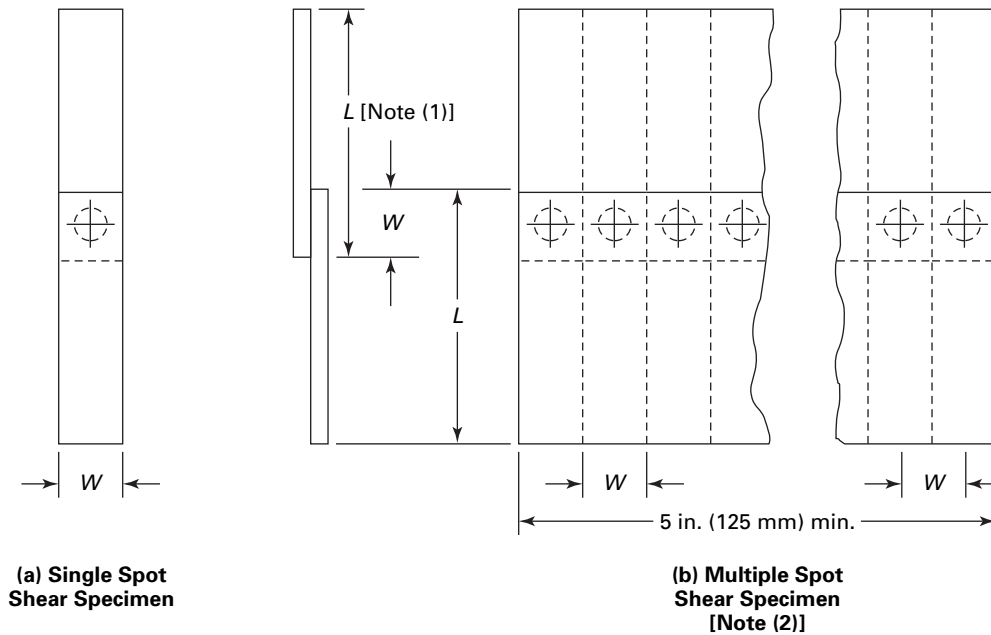

Nominal Thickness of Thinner Sheet, in. (mm)	W, in. (mm) Min.
Over 0.008 to 0.030 (0.20 to 0.8)	0.68 (17)
Over 0.030 to 0.100 (0.8 to 2.5)	1.00 (25)
Over 0.100 to 0.130 (2.5 to 3)	1.25 (30)
Over 0.130 (3)	1.50 (38)

NOTES:

- (1) L shall be not less than $4W$.
 (2) Sketch (b) shall be made of 5 specimens or more.

Table QW-462.10(a)
Shear Strength Requirements for Spot or Projection Weld Specimens

Customary Units					SI Units				
P-No. 1 Through P-No. 11 and P-No. 41 Through P-No. 49 Metals					P-No. 1 Through P-No. 15F and P-No. 41 Through P-No. 49 Metals				
Nominal Thickness of Thinner Sheet, in.	Ultimate Strength 90,000 to 149,000 psi		Ultimate Strength Below 90,000 psi		Nominal Thickness of Thinner Sheet, mm	Ultimate Strength 620 MPa to 1 027 MPa		Ultimate Strength Below 620 MPa	
	lbf per Spot		lbf per Spot			N per Spot		N per Spot	
	Min.	Min. Avg.	Min.	Min. Avg.		Min.	Min. Avg.	Min.	Min. Avg.
0.009	130	160	100	125	0.23	580	710	440	560
0.010	160	195	115	140	0.25	710	870	510	620
0.012	200	245	150	185	0.30	890	1 090	670	820
0.016	295	365	215	260	0.41	1 310	1 620	960	1 160
0.018	340	415	250	305	0.46	1 510	1 850	1 110	1 360
0.020	390	480	280	345	0.51	1 730	2 140	1 250	1 530
0.022	450	550	330	405	0.56	2 000	2 450	1 470	1 800
0.025	530	655	400	495	0.64	2 360	2 910	1 780	2 200
0.028	635	785	465	575	0.71	2 820	3 490	2 070	2 560
0.032	775	955	565	695	0.81	3 450	4 250	2 510	3 090
0.036	920	1,140	690	860	0.91	4 090	5 070	3 070	3 830
0.040	1,065	1,310	815	1,000	1.02	4 740	5 830	3 630	4 450
0.045	1,285	1,585	1,005	1,240	1.14	5 720	7 050	4 470	5 520
0.050	1,505	1,855	1,195	1,475	1.27	6 690	8 250	5 320	6 560
0.056	1,770	2,185	1,460	1,800	1.42	7 870	9 720	6 490	8 010
0.063	2,110	2,595	1,760	2,170	1.60	9 390	11 540	7 830	9 650
0.071	2,535	3,125	2,080	2,560	1.80	11 280	13 900	9 250	11 390
0.080	3,005	3,705	2,455	3,025	2.03	13 370	16 480	10 920	13 460
0.090	3,515	4,335	2,885	3,560	2.29	15 640	19 280	12 830	15 840
0.100	4,000	4,935	3,300	4,070	2.54	17 790	21 950	14 680	18 100
0.112	4,545	5,610	3,795	4,675	2.84	20 220	24 950	16 880	20 800
0.125	5,065	6,250	4,300	5,310	3.18	22 530	27 800	19 130	23 620


Table QW-462.10(b)
Shear Strength Requirements for Spot or Projection Weld Specimens

U.S. Customary Units							SI Units						
P-No. 21 Through P-No. 25 Aluminum Alloys							P-No. 21 Through P-No. 26 Aluminum Alloys						
Nominal Thickness of Thinner Sheet, in.	Ultimate Strength 35,000 to 55,999 psi, lbf per Spot		Ultimate Strength 19,500 to 34,999 psi, lbf per Spot		Ultimate Strength Below 19,500 psi, lbf per Spot		Nominal Thickness of Thinner Sheet, mm	Ultimate Strength 241 MPa to 386 MPa, N per Spot		Ultimate Strength 134 MPa to 241 MPa, N per Spot		Ultimate Strength Below 134 MPa, N per Spot	
	Min.	Min. Avg.	Min.	Min. Avg.	Min.	Min. Avg.		Min.	Min. Avg.	Min.	Min. Avg.	Min.	Min. Avg.
0.010	50	65	0.25	220	290
0.012	65	85	30	40	20	25	0.30	290	380	130	180	90	110
0.016	100	125	70	90	50	65	0.41	440	560	310	400	220	290
0.018	115	145	85	110	65	85	0.46	510	640	380	490	290	380
0.020	135	170	100	125	80	100	0.51	600	760	440	560	360	440
0.022	155	195	120	150	95	120	0.56	690	870	530	670	420	530
0.025	175	200	145	185	110	140	0.64	780	890	640	820	490	620
0.028	205	260	175	220	135	170	0.71	910	1 160	780	980	600	760
0.032	235	295	210	265	165	210	0.81	1 050	1 310	930	1 180	730	930
0.036	275	345	255	320	195	245	0.91	1 220	1 530	1 130	1 420	870	1 090
0.040	310	390	300	375	225	285	1.02	1 380	1 730	1 330	1 670	1 000	1 270
0.045	370	465	350	440	260	325	1.14	1 650	2 070	1 560	1 960	1 160	1 450
0.050	430	540	400	500	295	370	1.27	1 910	2 400	1 780	2 220	1 310	1 650
0.057	515	645	475	595	340	425	1.45	2 290	2 870	2 110	2 650	1 510	1 890
0.063	610	765	570	715	395	495	1.60	2 710	3 400	2 540	3 180	1 760	2 200
0.071	720	900	645	810	450	565	1.80	3 200	4 000	2 870	3 600	2 000	2 510
0.080	855	1,070	765	960	525	660	2.03	3 800	4 760	3 400	4 270	2 340	2 940
0.090	1,000	1,250	870	1,090	595	745	2.29	4 450	5 560	3 870	4 850	2 650	3 310
0.100	1,170	1,465	940	1,175	675	845	2.54	5 200	6 520	4 180	5 230	3 000	3 760
0.112	1,340	1,675	1,000	1,255	735	920	2.84	5 960	7 450	4 450	5 580	3 270	4 090
0.125	1,625	2,035	1,050	1,315	785	985	3.18	7 230	9 050	4 670	5 850	3 490	4 380
0.140	1,920	2,400	3.56	8 540	10 680
0.160	2,440	3,050	4.06	10 850	13 570
0.180	3,000	3,750	4.57	13 340	16 680
0.190	3,240	4,050	4.83	14 410	18 020
0.250	6,400	8,000	6.35	28 470	35 590

Table QW-462.10(c)
Shear Strength Requirements for Spot or Projection Weld Specimens

U.S. Customary Units					SI Units				
Titanium Alloys					Titanium Alloys				
Nominal Thickness of Thinner Sheet, in.	Ultimate Strength Above 100,000 psi		Ultimate Strength 100,000 psi and Below		Nominal Thickness of Thinner Sheet, mm	Ultimate Strength 690 MPa and Above		Ultimate Strength Below 690 MPa	
	lbf per Spot		lbf per Spot			N per Spot		N per Spot	
	Min.	Min. Avg.	Min.	Min. Avg.		Min.	Min. Avg.	Min.	Min. Avg.
0.01	205	265	160	210	0.25	910	1 180	710	930
0.012	275	360	200	260	0.30	1 220	1 600	890	1 160
0.016	400	520	295	385	0.41	1 780	2 310	1 310	1 710
0.018	490	635	340	445	0.46	2 180	2 820	1 510	1 980
0.02	530	690	390	510	0.51	2 360	3 070	1 730	2 270
0.022	610	795	450	585	0.56	2 710	3 540	2 000	2 600
0.025	725	945	530	690	0.64	3 220	4 200	2 360	3 070
0.028	855	1,110	635	825	0.71	3 800	4 940	2 820	3 670
0.032	1,045	1,360	775	1,000	0.81	4 650	6 050	3 450	4 450
0.036	1,255	1,630	920	1,200	0.91	5 580	7 250	4 090	5 340
0.04	1,460	1,900	1,065	1,385	1.02	6 490	8 450	4 740	6 160
0.045	1,795	2,340	1,285	1,670	1.14	7 980	10 410	5 720	7 430
0.05	2,125	2,760	1,505	1,910	1.27	9 450	12 280	6 690	8 500
0.056	2,550	3,320	1,770	2,300	1.42	11 340	14 770	7 870	10 230
0.063	3,000	3,900	2,110	2,730	1.60	13 340	17 350	9 390	12 140
0.071	3,380	4,400	2,395	3,115	1.80	15 030	19 570	10 650	13 860
0.08	3,810	4,960	2,700	3,510	2.03	16 950	22 060	12 010	15 610
0.09	4,290	5,570	3,040	3,955	2.29	19 080	24 780	13 520	17 590
0.1	4,760	6,170	3,380	4,395	2.54	21 170	27 450	15 030	19 550
0.112	5,320	6,800	3,785	4,925	2.84	23 660	30 250	16 840	21 910
0.125	5,950	7,700	4,220	5,490	3.18	26 470	34 250	18 770	24 420

Figure QW-462.12
Nomenclature for Temper Bead Welding

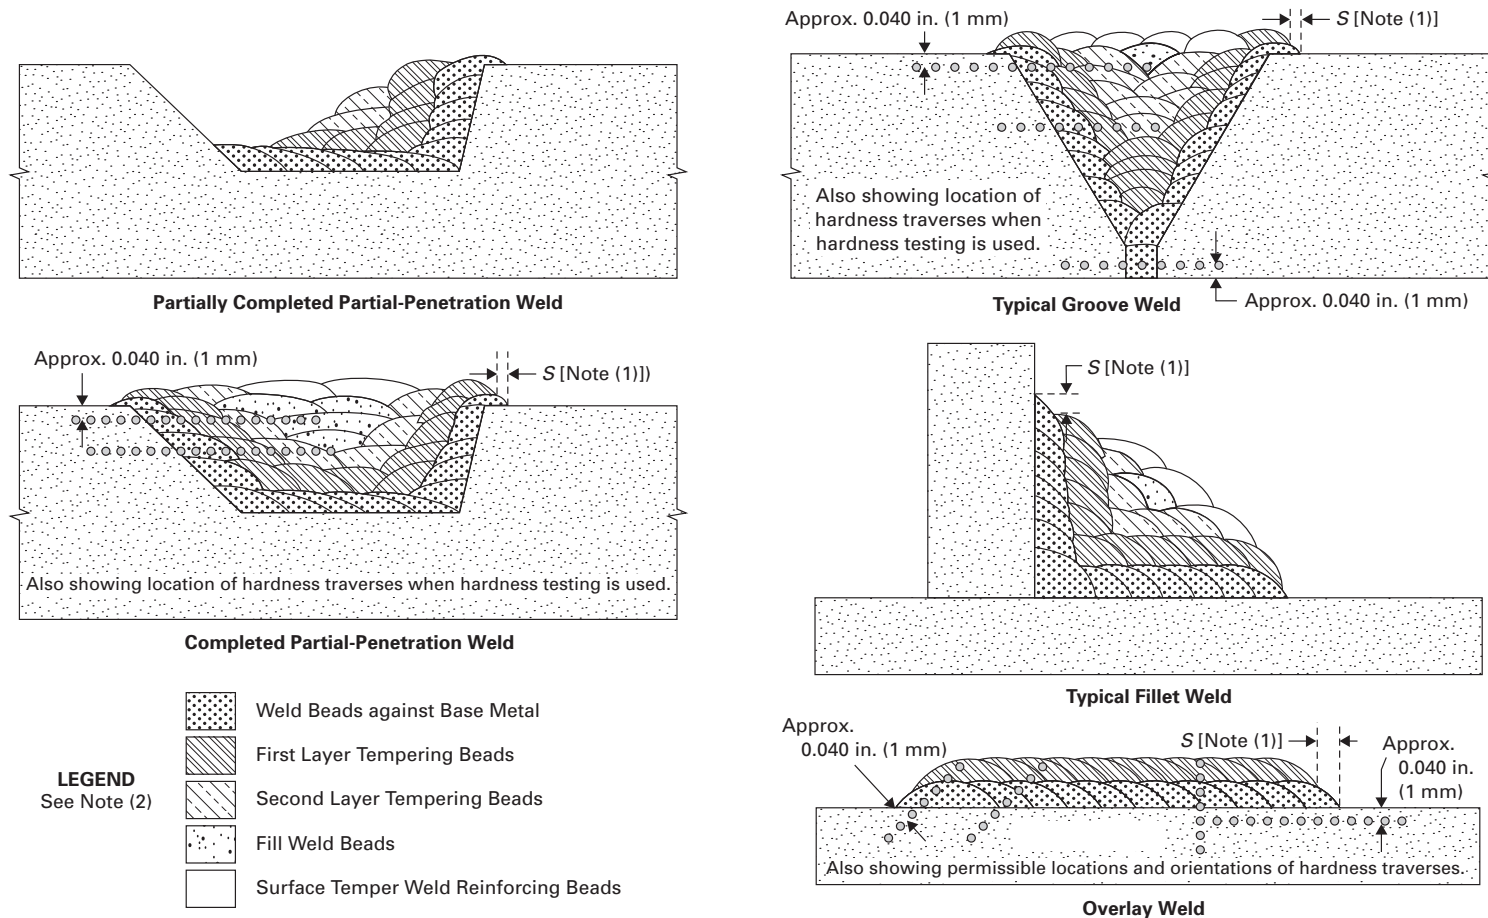


GENERAL NOTES:

- (a) Weld beads shown above may be deposited in any sequence that will result in placement of the beads as shown.
- (b) Surface temper reinforcing beads may cover the entire weld surface, or may only be placed at the toe of the weld; they may or may not be mechanically removed.

NOTES:

- (1) The distance, S , is measured from the toe of the weld to the edge of the temper beads. Measurements shall be made parallel to the base metal surface.
- (2) Beads near the finished surface may be both tempering beads and surface temper reinforcing beads.

Figure QW-462.13
Measurement of Temper Bead Overlap

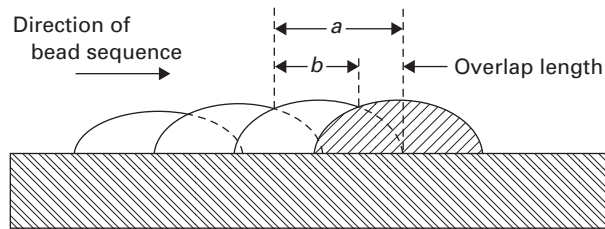

GENERAL NOTE: Measurement of bead overlap - % overlap length = $(a-b)/a \times 100\%$. In this figure, the shaded bead overlaps previous bead by 30% to 40%. The distance a is measured before the next bead is deposited.

Figure QW-463.1(a)
Plates — Less Than $\frac{3}{4}$ in. (19 mm)
Thickness Procedure Qualification

Discard		this piece
Reduced section		tensile specimen
Root bend		specimen
Face bend		specimen
Root bend		specimen
Face bend		specimen
Reduced section		tensile specimen
Discard		this piece



Figure QW-463.1(b)
Plates — $\frac{3}{4}$ in. (19 mm) and Over Thickness
and Alternate From $\frac{3}{8}$ in. (10 mm) but Less
Than $\frac{3}{4}$ in. (19 mm) Thickness Procedure
Qualification

Discard		this piece
Side bend		specimen
Reduced section		tensile specimen
Side bend		specimen
Side bend		specimen
Reduced section		tensile specimen
Side bend		specimen
Discard		this piece



Figure QW-463.1(c)
Plates — Longitudinal Procedure Qualification



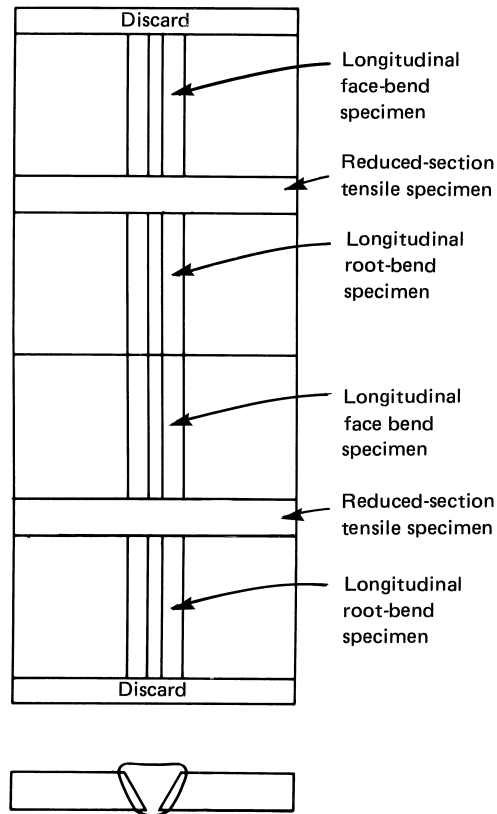


Figure QW-463.1(d)
Procedure Qualification

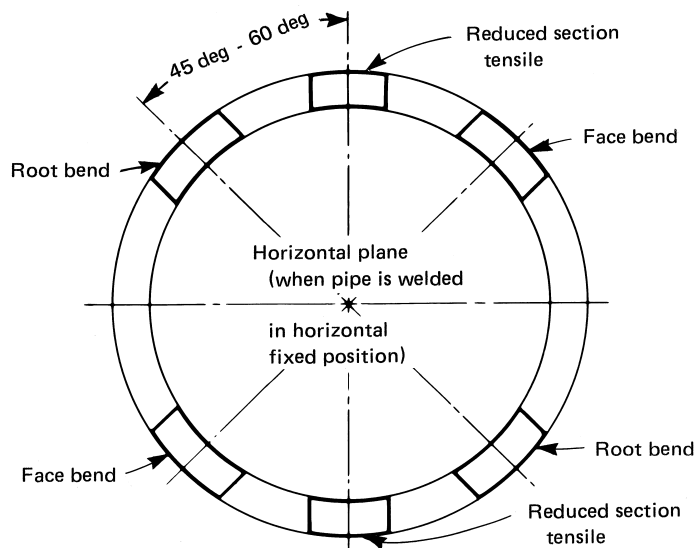

**Figure QW-463.1(e)
Procedure Qualification**

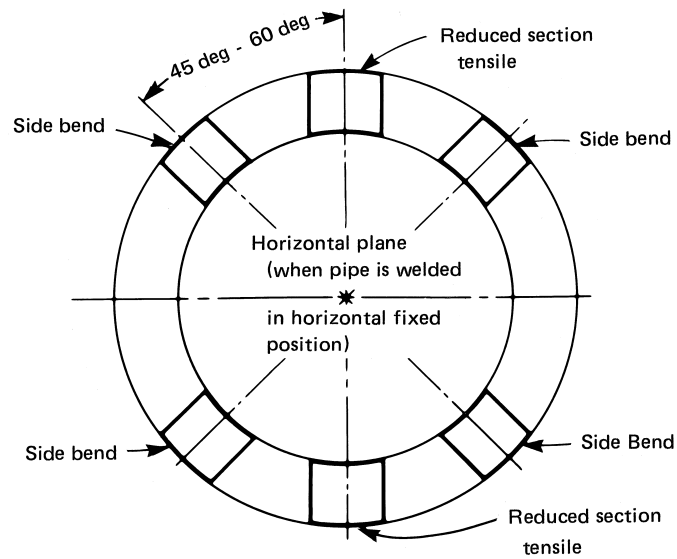

**Figure QW-463.1(f)
Notch-Toughness Test Specimen Location**

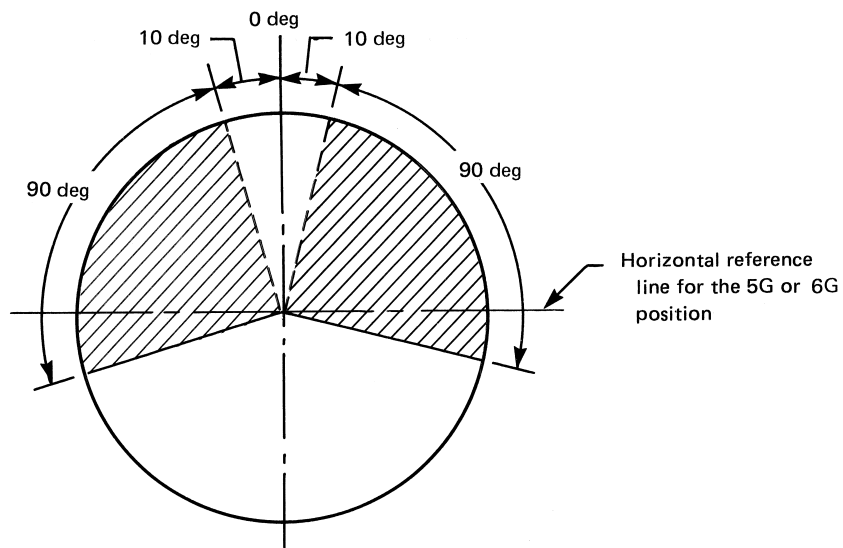


Figure QW-463.2(a)
Plates — Less Than $\frac{3}{4}$ in. (19 mm) Thickness Performance Qualification

Discard		this piece
Root-bend		specimen
Face-bend		specimen
Discard		this piece



Figure QW-463.2(b)
Plates — $\frac{3}{4}$ in. (19 mm) and Over Thickness and Alternate From $\frac{3}{8}$ in. (10 mm) but Less Than $\frac{3}{4}$ in. (19 mm) Thickness Performance Qualification

Discard		this piece
Side-bend		specimen
Side-bend		specimen
Discard		this piece



Figure QW--463.2(c)
Plates — Longitudinal Performance Qualification

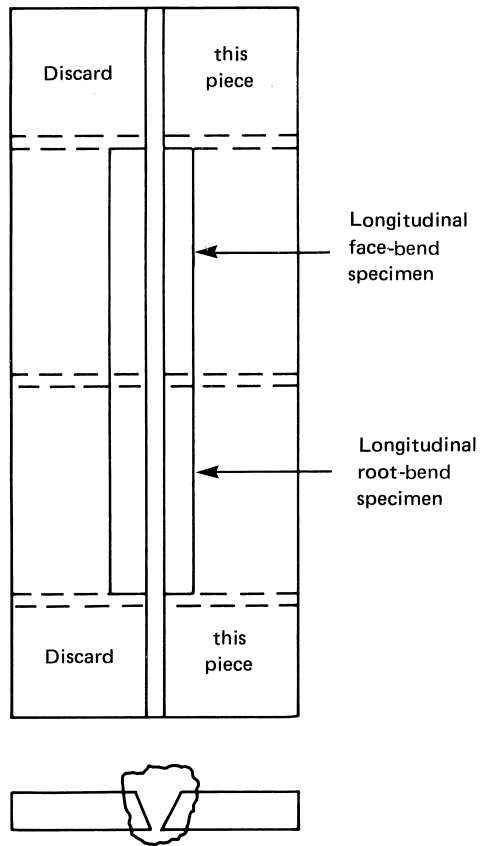


Figure QW-463.2(d)
Performance Qualification

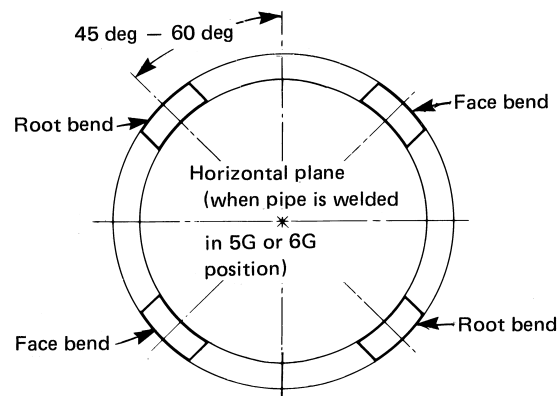


Figure QW-463.2(e)
Performance Qualification

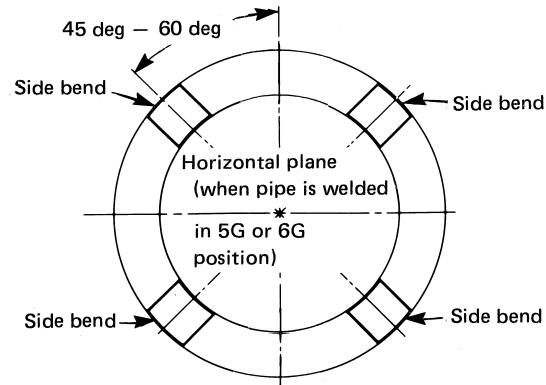


Figure QW-463.2(f)
Pipe — NPS 10 (DN 250) Assembly Performance Qualification


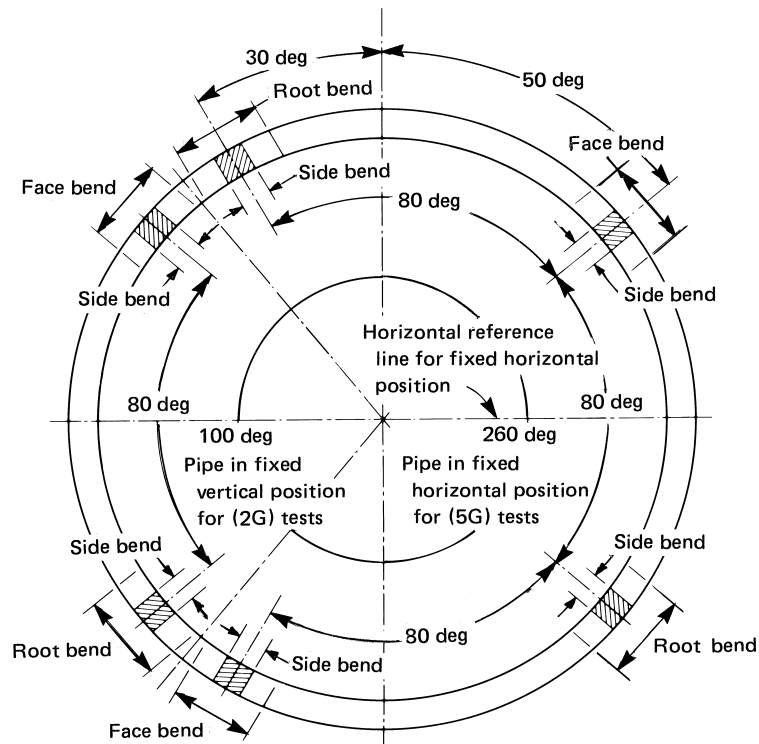


Figure QW-463.2(g)
NPS 6 (DN 150) or NPS 8 (DN 200) Assembly Performance Qualification

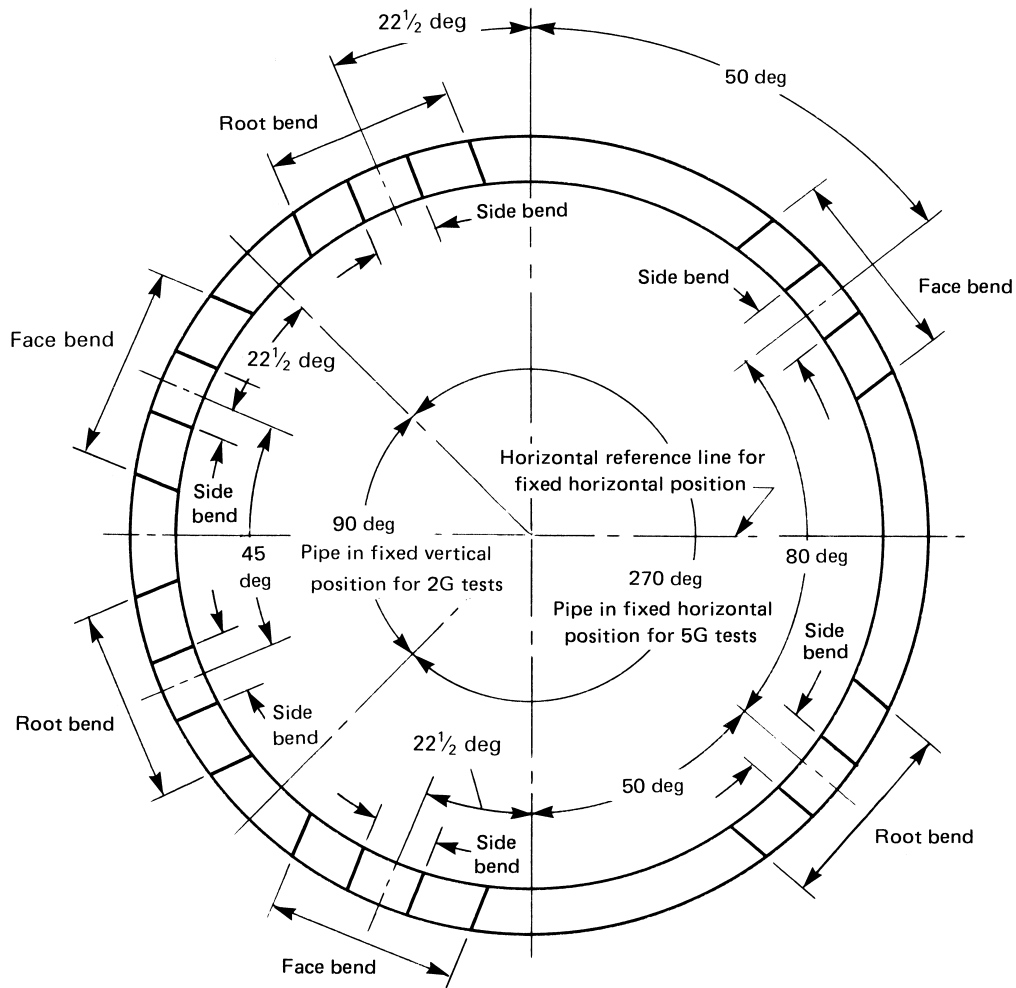

GENERAL NOTE: When side bend tests are made in accordance with [QW-452.1](#) and [QW-452.3](#), they shall be removed as shown in [QW-463.2\(g\)](#) in place of the face and root bends.

Figure QW-463.2(h)
Performance Qualification



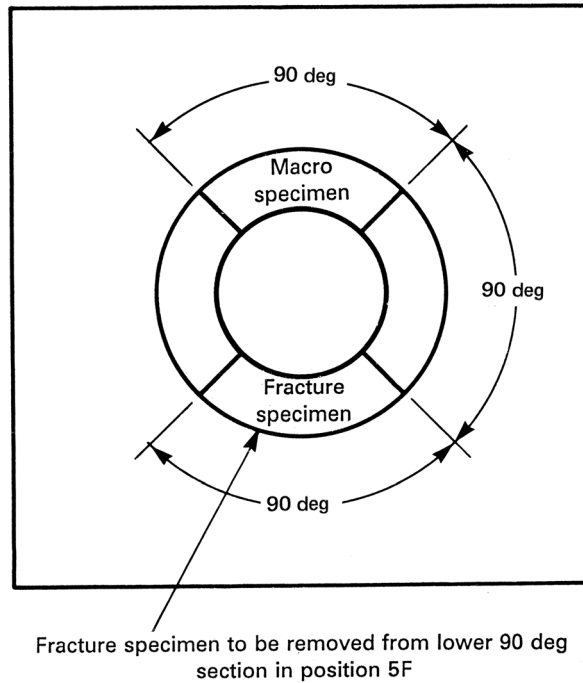


Figure QW-464.1
Procedure Qualification Test Coupon and Test Specimens

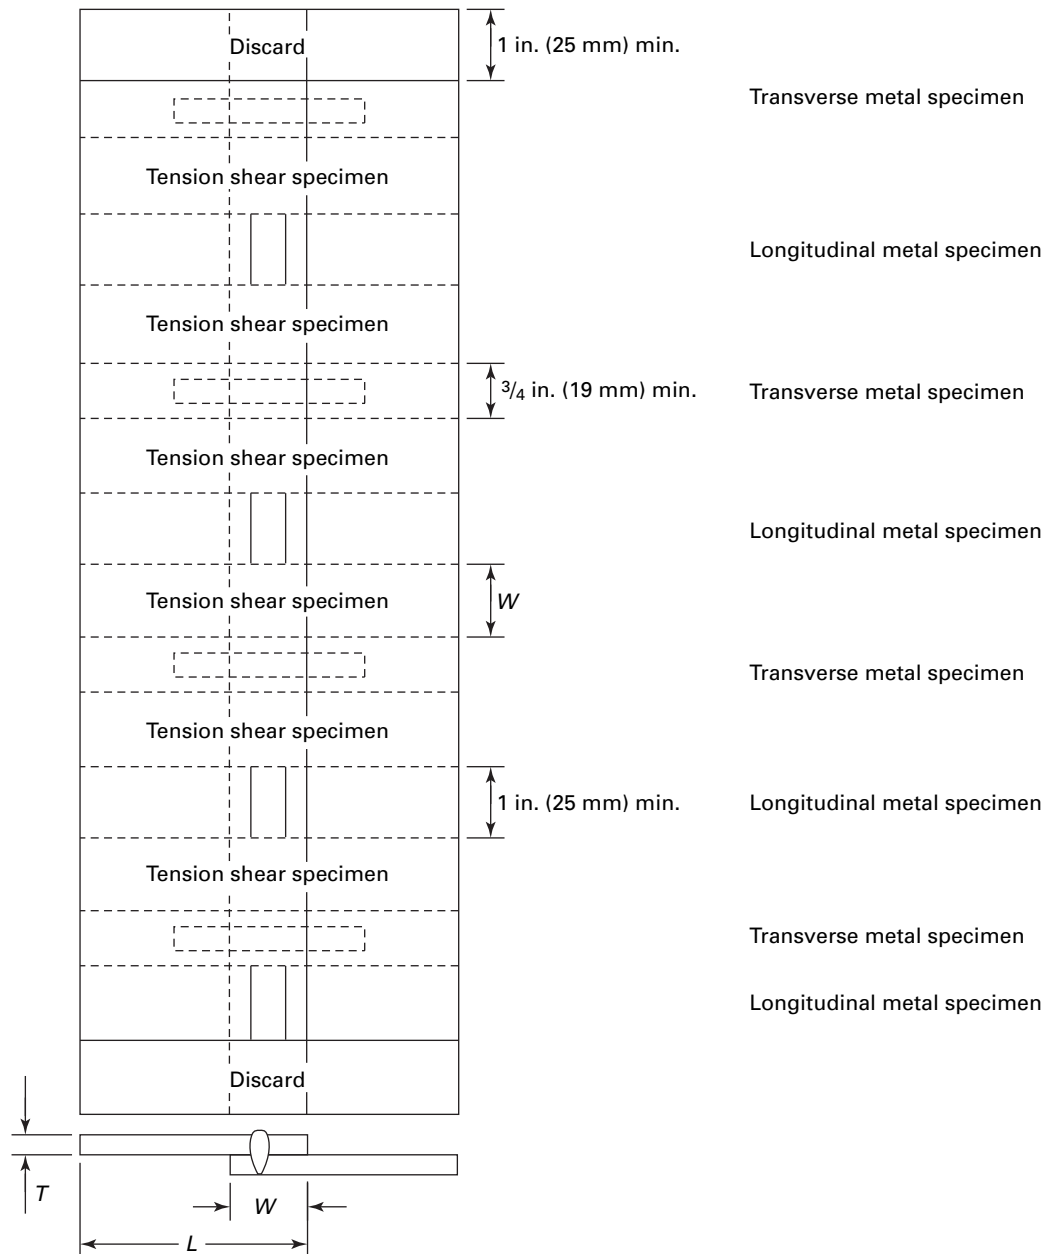

Thickness of Thinner, Sheet, T , in. (mm)	Specimen Width, W , in. (mm)	Recommended Length, L , in. (mm)
Up to 0.029 (0.74)	$\frac{5}{8}$ (16)	3 (75)
0.031 to 0.050 (0.79 to 1.2)	$\frac{3}{4}$ (19)	3 (75)
0.051 to 0.100 (1.3 to 2.54)	1 (25)	4 (100)
0.101 to 0.130 (2.57 to 3.30)	$1\frac{1}{4}$ (32)	5 (125)
0.131 to 0.190 (3.33 to 4.83)	$1\frac{1}{2}$ (38)	5 (125)
0.191 (4.85) and over	2 (50)	6 (150)

Figure QW-464.2
Performance Qualification Test Coupons and Test Specimens

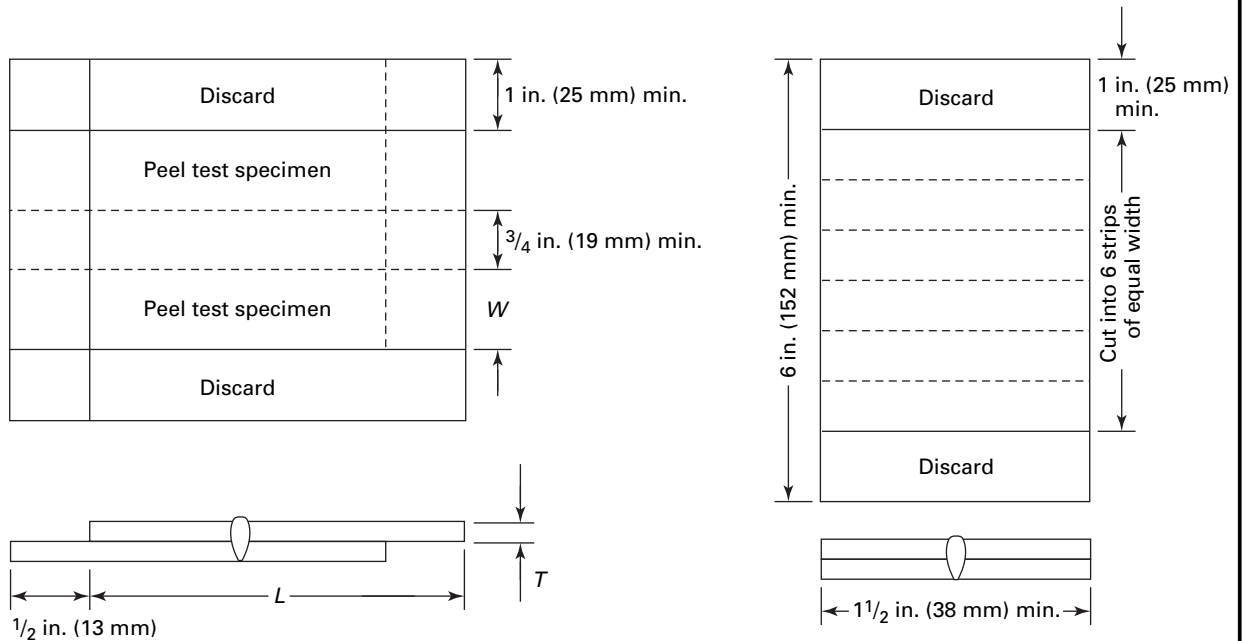


Thickness of Thinner Sheet, T , in. (mm)	Specimen Width, W , in. (mm)	Recommended, Length L , in. (mm)
Up to 0.029 (0.74)	$\frac{5}{8}$ (16)	2 (50)
0.030 to 0.058 (0.75 to 1.4)	1 (25)	1 (25)
0.059 to 0.125 (1.5 to 3.2)	$1\frac{1}{2}$ (38)	4 (100)

(a) Peel Test Coupon and Specimens

**(b) Metallurgical Examination
Coupon and Transverse Specimens**

Figure QW-466.1
Test Jig Dimensions

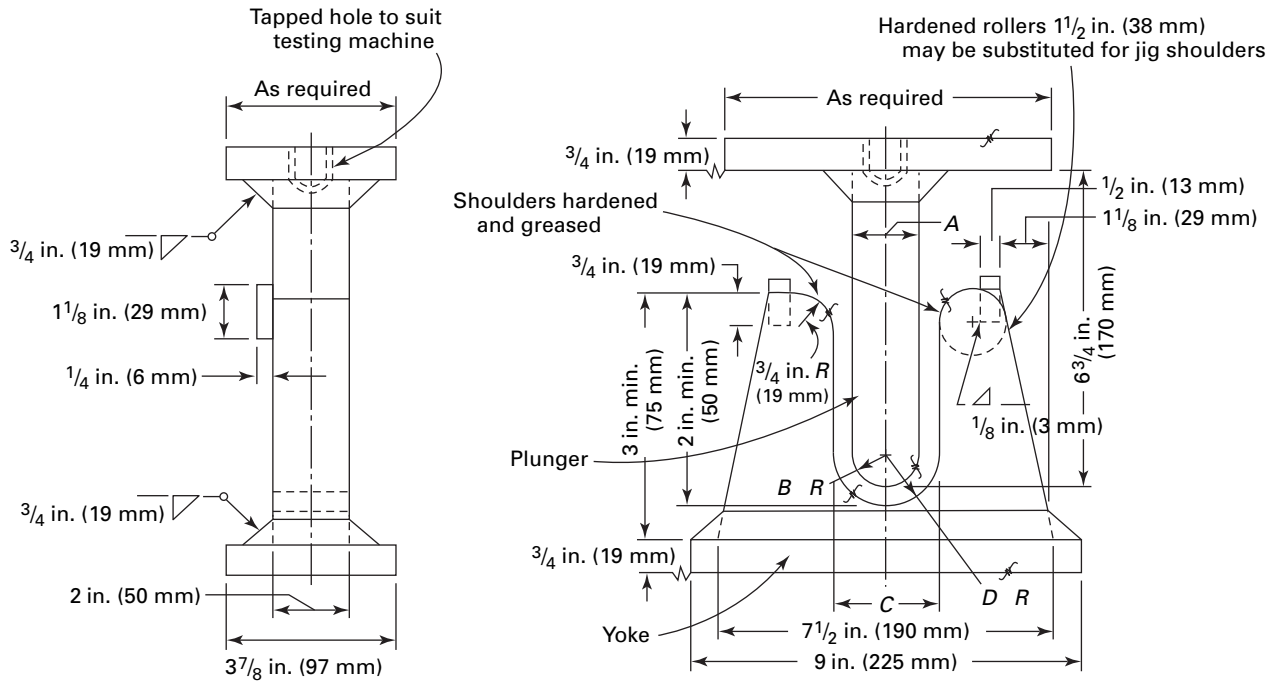

Customary Units

Material	Thickness of Specimen, in.	A, in.	B, in.	C, in.	D, in.
P-No. 23 to P-No. 21 through P-No. 25; P-No. 21 through P-No. 25 with F-No. 23; P-No. 35; any P-No. metal with F-No. 33, 36, or 37	$\frac{1}{8}$ $t = \frac{1}{8}$ or less	$2\frac{1}{16}$ $16\frac{1}{2} t$	$1\frac{1}{32}$ $8\frac{1}{4} t$	$2\frac{3}{8}$ $18\frac{1}{2} t + \frac{1}{16}$	$1\frac{3}{16}$ $9\frac{1}{4} t + \frac{1}{32}$
P-No. 11A, P-No. 11B; P-No. 25 to P-No. 21 or P-No. 22 or P-No. 25	$\frac{3}{8}$ $t = \frac{3}{8}$ or less	$2\frac{1}{2}$ $6\frac{2}{3} t$	$1\frac{1}{4}$ $3\frac{1}{3} t$	$3\frac{3}{8}$ $8\frac{2}{3} t + \frac{1}{8}$	$1\frac{11}{16}$ $4\frac{1}{3} t + \frac{1}{16}$
P-No. 51; P-No. 49	$\frac{3}{8}$ $t = \frac{3}{8}$ or less	3 8t	$1\frac{1}{2}$ 4t	$3\frac{7}{8}$ $10t + \frac{1}{8}$	$1\frac{15}{16}$ $5t + \frac{1}{16}$
P-No. 52; P-No. 53; P-No. 61; P-No. 62	$\frac{3}{8}$ $t = \frac{3}{8}$ or less	$3\frac{3}{4}$ 10t	$1\frac{7}{8}$ 5t	$4\frac{5}{8}$ $12t + \frac{1}{8}$	$2\frac{5}{16}$ $6t + \frac{1}{16}$
All others with greater than or equal to 20% elongation	$\frac{3}{8}$ $t = \frac{3}{8}$ or less	$1\frac{1}{2}$ 4t	$\frac{3}{4}$ 2t	$2\frac{3}{8}$ $6t + \frac{1}{8}$	$1\frac{3}{16}$ $3t + \frac{1}{16}$
Materials with 3% to less than 20% elongation	$t = [\text{see Note (1)}]$	$32\frac{7}{8} t$ max.	$16\frac{7}{16} t$ max.	$A + 2t + \frac{1}{16}$ max.	$\frac{1}{2} C + \frac{1}{32}$ max.

SI Units

Material	Thickness of Specimen, mm	A, mm	B, mm	C, mm	D, mm
P-No. 23 to P-No. 21 through P-No. 25; P-No. 21 through P-No. 25 with F-No. 23; P-No. 35; any P-No. metal with F-No. 33, 36, or 37	3 $t = 3$ or less	50 $16\frac{1}{2} t$	25 $8\frac{1}{4} t$	57 $18\frac{1}{2} t + 1.6$	29 $9\frac{1}{4} t + 0.8$
P-No. 11A, P-No. 11B; P-No. 25 to P-No. 21 or P-No. 22 or P-No. 25	10 $t = 10$ or less	67 $6\frac{2}{3} t$	33 $3\frac{1}{3} t$	90 $8\frac{2}{3} t + 3.2$	45 $4\frac{1}{3} t + 1.6$
P-No. 51; P-No. 49	10 $t = 10$ or less	80 8t	40 4t	103 $10t + 3.2$	52 $5t + 1.6$
P-No. 52; P-No. 53; P-No. 61; P-No. 62	10 $t = 10$ or less	100 10t	50 5t	123 $12t + 3.2$	62 $6t + 1.6$

Figure QW-466.1
Test Jig Dimensions (Cont'd)

Table continued

SI Units					
Material	Thickness of Specimen, mm	A, mm	B, mm	C, mm	D, mm
All others with greater than or equal to 20% elongation	10 $t = 10$ or less	40 $4t$	20 $2t$	63 $6t + 3.2$	32 $3t + 1.6$
Materials with 3% to less than 20% elongation	$t = [\text{see Note (1)}]$	$32\frac{7}{8}$ $t \text{ max.}$	$16\frac{7}{16} t$ max.	$A + 2t + 1.6$ max.	$\frac{1}{2} C + 0.8$ max.

GENERAL NOTES:

- (a) For P-Numbers, see [QW/QB-422](#); for F-Numbers, see [QW-432](#).
 (b) For guided-bend jig configuration, see [QW-466.2](#), [QW-466.3](#), and [QW-466.4](#).
 (c) The weld and heat-affected zone, in the case of a transverse weld bend specimen, shall be completely within the bend portion of the specimen after testing.
 (d) For materials with less than 3% elongation, a macro-etch specimen shall be used in lieu of bend test at each bend test location. Acceptance criteria shall be in accordance with [QW-183\(a\)](#).

NOTE:


- (1) The dimensions of the test jig shall be such as to give the bend test specimen a calculated percent outer fiber elongation equal to at least that of the base material with the lower minimum elongation as specified in the base material specification.

$$\text{percent outer fiber elongation} = \frac{100t}{A + t}$$

The following equation is provided for convenience in calculating the bend specimen thickness:

$$\text{thickness of specimen}(t) = \frac{A \times \text{percent elongation}}{[100 - (\text{percent elongation})]}$$

Figure QW-466.2
Guided-Bend Roller Jig

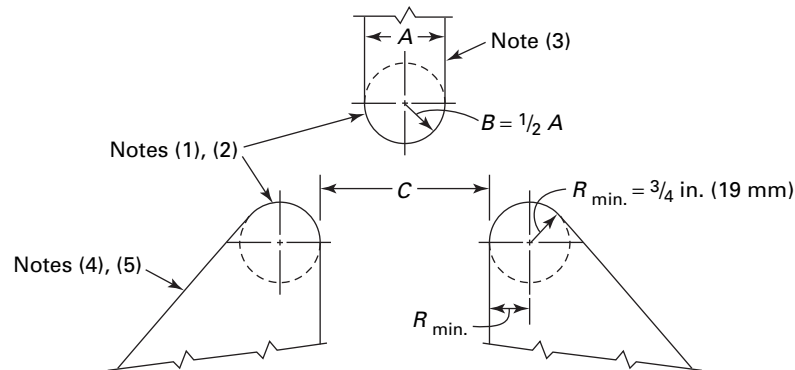


GENERAL NOTE: See QW-466.1 for jig dimensions and general notes.

NOTES:

- (1) Either hardened and greased shoulders or hardened rollers free to rotate shall be used.
- (2) The shoulders or rollers shall have a minimum bearing surface of 2 in. (50 mm) for placement of the specimen. The rollers shall be high enough above the bottom of the jig so that the specimens will clear the rollers when the ram is in the low position.
- (3) The ram shall be fitted with an appropriate base and provision made for attachment to the testing machine, and shall be of a sufficiently rigid design to prevent deflection and misalignment while making the bend test. The body of the ram may be less than the dimensions shown in column A of QW-466.1.
- (4) If desired, either the rollers or the roller supports may be made adjustable in the horizontal direction so that specimens of t thickness may be tested on the same jig.
- (5) The roller supports shall be fitted with an appropriate base designed to safeguard against deflection and misalignment and equipped with means for maintaining the rollers centered midpoint and aligned with respect to the ram.


Figure QW-466.3
Guided-Bend Wrap Around Jig

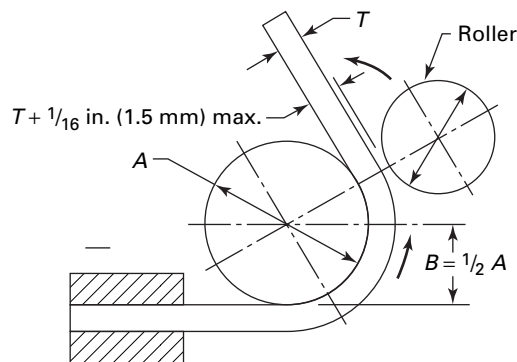

GENERAL NOTES:


- (a) See QW-466.1 for jig dimensions and other general notes.
- (b) Dimensions not shown are the option of the designer. The essential consideration is to have adequate rigidity so that the jig parts will not spring.
- (c) The specimen shall be firmly clamped on one end so that there is no sliding of the specimen during the bending operation.
- (d) Test specimens shall be removed from the jig when the outer roll has been removed 180 deg from the starting point.

Figure QW-466.4
Stud-Weld Bend Jig

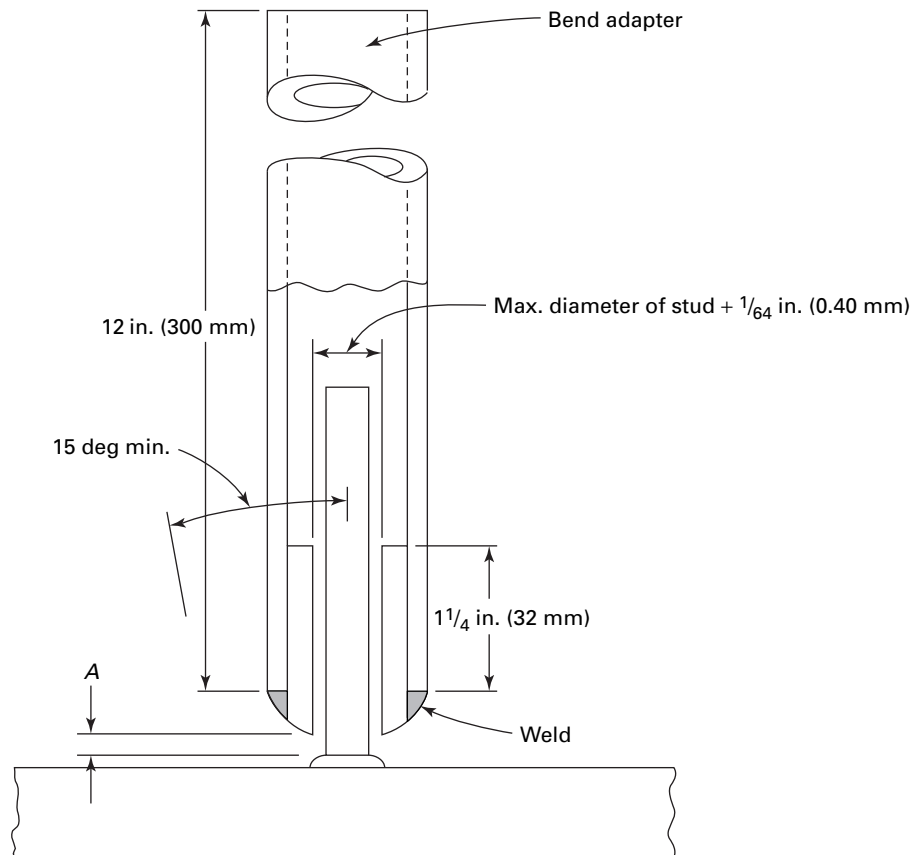

For Stud Diameter, in. (mm)	Use Adapter Gap, A, in. (mm)
1/8 (3)	1/8 (3)
3/16 (5)	1/8 (3)
1/4 (6)	3/16 (5)
3/8 (10)	7/32 (5.5)
1/2 (13)	5/16 (8)
5/8 (16)	11/32 (9)
3/4 (19)	15/32 (12)
7/8 (22)	15/32 (12)
1 (25)	19/32 (15)

Figure QW-466.5
Torque Testing Arrangement for Stud Welds

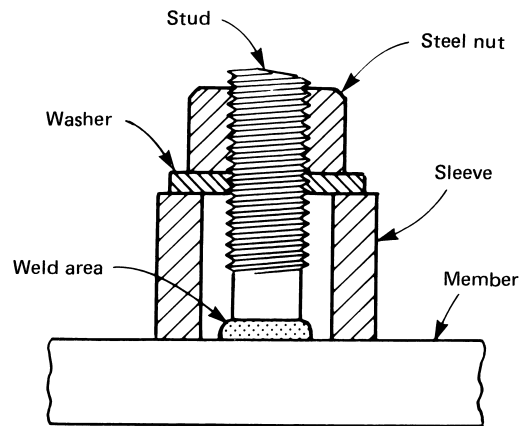

GENERAL NOTES:

- (a) Dimensions are appropriate to the size of the stud.
- (b) Threads of the stud shall be clean and free of lubricant other than residual cutting oil.

Figure QW-466.6
Suggested Type Tensile Test Figure for Stud Welds

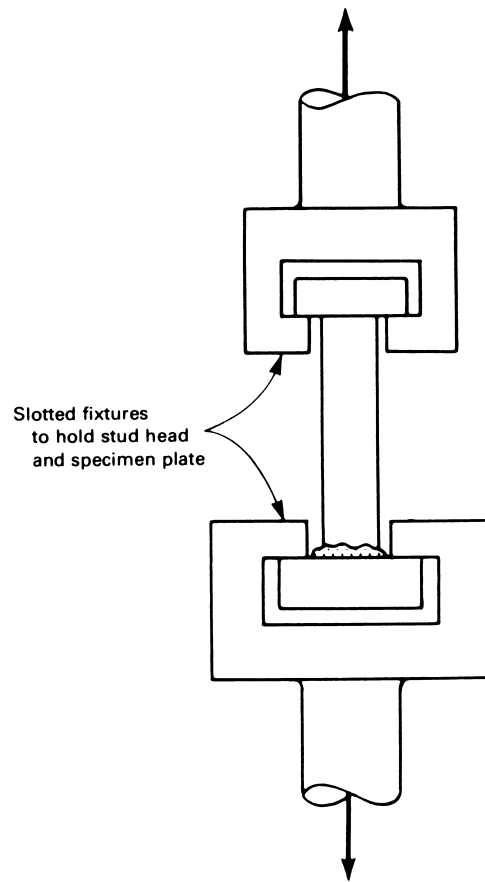


Figure QW-469.1
Butt Joint


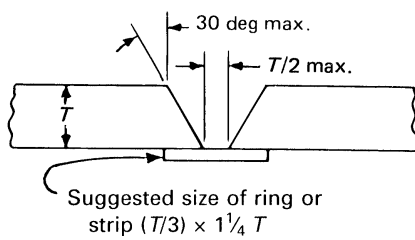


Figure QW-469.2
Alternative Butt Joint

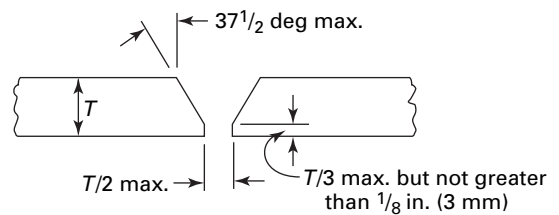

QW-470 ETCHING — PROCESSES AND REAGENTS

(13) QW-471 GENERAL

The surfaces to be etched should be prepared by filing, machining, grinding, or polishing to delineate the macro-features of the specimen's weld and HAZ after etching. With different alloys and tempers, the etching period will vary from a few seconds to several minutes, and should be continued until the desired contrast is obtained. As a protection from the fumes liberated during the etching process, this work should be done under a hood. After etching, the specimens should be thoroughly rinsed and then dried with a blast of warm air. Coating the surface with a thin clear lacquer will preserve the appearance. (Reference ASTM E340, Standard Test Method for Macro-etching Metals and Alloys, or other industry-accepted standards.)

QW-472 FOR FERROUS METALS

Etching solutions suitable for carbon and low alloy steels, together with directions for their use, are suggested in [QW-472.1](#) through [QW-472.4](#).

QW-472.1 Hydrochloric Acid. Hydrochloric (muratic) acid and water, equal parts, by volume. The solution should be kept at or near the boiling temperature during the etching process. The specimens are to be immersed in the solution for a sufficient period of time to reveal all lack of soundness that might exist at their cross-sectional surfaces.

QW-472.2 Ammonium Persulfate. One part of ammonium persulfate to nine parts of water, by weight. The solution should be used at room temperature, and should be applied by vigorously rubbing the surface to be etched with a piece of cotton saturated with the solution. The etching process should be continued until there is a clear definition of the structure in the weld.

QW-472.3 Iodine and Potassium Iodide. One part of powdered iodine (solid form), two parts of powdered potassium iodide, and ten parts of water, all by weight. The solution should be used at room temperature, and brushed on the surface to be etched until there is a clear definition or outline of the weld.

QW-472.4 Nitric Acid. One part of nitric acid and three parts of water, by volume.

CAUTION: Always pour the acid into the water. Nitric acid causes bad stains and severe burns.

The solution may be used at room temperature and applied to the surface to be etched with a glass stirring rod. The specimens may also be placed in a boiling solution of the acid, but the work should be done in a well-ventilated room. The etching process should be continued for a sufficient period of time to reveal all lack of soundness that might exist at the cross-sectional surfaces of the weld.

QW-473 FOR NONFERROUS METALS

The following etching reagents and directions for their use are suggested for revealing the macrostructure.

QW-473.1 Aluminum and Aluminum-Base Alloys.

Solution	Volume
Hydrochloric acid (concentrated)	15 ml
Hydrofluoric acid (48%)	10 ml
Water	85 ml

This solution is to be used at room temperature, and etching is accomplished by either swabbing or immersing the specimen.

QW-473.2 For Copper and Copper-Base Alloys: Cold Concentrated Nitric Acid. Etching is accomplished by either flooding or immersing the specimen for several seconds under a hood. After rinsing with a flood of water, the process is repeated with a 50-50 solution of concentrated nitric acid and water.

In the case of the silicon bronze alloys, it may be necessary to swab the surface to remove a white (SiO_2) deposit.

QW-473.3 For Nickel and Nickel-Base Alloys.

Material	Formula
Nickel	Nitric Acid or Lepito's Etch
Low Carbon Nickel	Nitric Acid or Lepito's Etch
Nickel-Copper (400)	Nitric Acid or Lepito's Etch
Nickel-Chromium-Iron (600 and 800)	Aqua Regia or Lepito's Etch

Table QW-473.3-1
Makeup of Equations for Aqua Regia and Lepito's Etch

Solution	Aqua Regia [Note (1)], [Note (2)]	Lepito's Etch [Note (2)], [Note (3)]
Nitric Acid, Concentrated — HNO_3	1 part	3 ml
Hydrochloric Acid, Concentrated — HCl	2 parts	10 ml
Ammonium Sulfate — $(\text{NH}_4)_2 (\text{SO}_4)$...	1.5 g
Ferric Chloride — FeCl_3	...	2.5 g
Water	...	7.5 ml

NOTES:

- (1) Warm the parts for faster action.
- (2) Etching is accomplished by either swabbing or immersing the specimen.
- (3) Mix solution as follows:
 - (a) Dissolve $(\text{NH}_4)_2 (\text{SO}_4)$ in H_2O .
 - (b) Dissolve powdered FeCl_3 in warm HCl .
 - (c) Mix (a) and (b) above and add HNO_3 .

QW-473.4 For Titanium.

Solution	Kroll's Etch	Keller's Etch
Hydrofluoric acid (48%)	1 to 3 ml	$\frac{1}{2}$ ml
Nitric acid (concentrated)	2 to 6 ml	$2\frac{1}{2}$ ml
Hydrochloric Acid (concentrated)	...	$1\frac{1}{2}$ ml
Water	To make 100 ml	To make 100 ml

Apply by swab and rinse in cold water.

These are general purpose etchants which are applied at room temperature by swabbing or immersion of the specimen.

QW-490 REDESIGNATED AS QG-109

(13)

QW-473.5 For Zirconium.

Solution	Volume
Hydrofluoric acid	3 ml
Nitric acid (concentrated)	22 ml
Water	22 ml

ARTICLE V

STANDARD WELDING PROCEDURE SPECIFICATIONS (SWPSS)

QW-500 GENERAL

The SWPSS listed in [Mandatory Appendix E](#) are acceptable for construction in which the requirements of the ASME Boiler and Pressure Vessel Code, Section IX are specified. Any requirements of the applicable Construction Code Section regarding SWPS take precedence over the requirements of Section IX. These SWPSS are not permitted for construction where impact testing of the WPS is required by the Construction Code.

Only SWPSS (including edition) that have been accepted in [Mandatory Appendix E](#) within the 1998 Edition or any later edition of Section IX may be used in accordance with this Article. Adoption of SWPSS (including edition) shall be in accordance with the current edition (see Foreword) and addenda of Section IX.

(11) if more than one process or electrode type is used, the approximate weld metal deposit thickness for each process or electrode type

(12) maximum interpass temperature

(13) post weld heat treatment used, including holding time and temperature range

(14) visual inspection and mechanical testing results

(15) the results of volumetric examination when permitted as an alternative to mechanical testing by [QW-304](#)

(e) The coupon shall be visually examined in accordance with [QW-302.4](#) and mechanically tested in accordance with [QW-302.1](#) or volumetrically examined in accordance with [QW-302.2](#). If visual examination, volumetric examination, or any test specimen fails to meet the required acceptance criteria, the test coupon shall be considered as failed and a new test coupon shall be welded before the organization may use the SWPS.

(13) QW-510 ADOPTION OF SWPSS

Prior to use, the organization that will be responsible for and provide operational control over production welding shall comply with the following for each SWPS that it intends to use, except as noted in [QW-520](#).

(a) Enter the name of the organization on the SWPS.

(b) An employee of that organization shall sign and date the SWPS.

(c) The applicable Code Section(s) (Section VIII, B31.1, etc.) and/or any other fabrication document (contract, specification, etc.) that must be followed during welding shall be listed on the SWPS.

(d) The organization shall weld and test one groove weld test coupon following that SWPS. The following information shall be recorded:

(1) the specification, type, and grade of the base metal welded

(2) groove design

(3) initial cleaning method

(4) presence or absence of backing

(5) The ASME or AWS specification and AWS classification of electrode or filler metal used and manufacturer's trade name

(6) size and classification of tungsten electrode for GTAW

(7) size of consumable electrode or filler metal

(8) shielding gas and flow rate for GTAW and GMAW

(9) preheat temperature

(10) position of the groove weld and, if applicable, the progression

QW-511 USE OF DEMONSTRATED SWPSS

Code Sections or fabrication documents that are required to be referenced by [QW-510\(c\)](#) may be added or deleted from a demonstrated SWPS without further demonstrations.

QW-520 USE OF SWPSS WITHOUT DISCRETE DEMONSTRATION

Once an SWPS has been demonstrated, additional SWPSS that are similar to the SWPS that was demonstrated may be used without further demonstration. Such additional SWPSS shall be compared to the SWPS that was used for the demonstration, and the following limitations shall not be exceeded:

(a) a change in the welding process.

(b) a change in the P-Number.

(c) a change from the as-welded condition to the heat-treated condition. This limitation also applies for SWPSS that allow use in both conditions (e.g., SWPS B2.1-021 allows production welding with or without heat treatment; if the demonstration was performed without heat treatment, production welding with heat treatment is not permitted). Once heat treatment has been demonstrated for any SWPS, this limitation no longer applies.

(d) a change from a gas-shielded flux-cored wire or solid wire to a self-shielded flux-cored wire or vice versa.

(e) a change from globular, spray or pulsed spray transfer welding to short circuiting transfer welding or vice versa.

- (f) a change in the F-Number of the welding electrode.
- (g) the addition of preheat above ambient temperature.
- (h) a change from an SWPS that is identified as for sheet metal to one that is not and vice versa.

QW-530 FORMS

A suggested [Form QW-485](#) for documenting the welding variables and test results of the demonstration is provided in [Nonmandatory Appendix B](#).

(13) QW-540 PRODUCTION USE OF SWPSS

As with any WPS, welding that is done following an SWPS shall be done in strict accordance with the SWPS. In addition, the following requirements apply to the use of SWPSS:

- (a) The organization may not deviate from the welding conditions specified on the SWPS.
- (b) SWPSS may not be supplemented with PQRs or revised in any manner except for reference to the applicable Code Section or other fabrication documents as provided by [QW-511](#).
- (c) Only the welding processes shown on an SWPS shall be used in given production joint. When a multi-process SWPS is selected, the processes shown on the SWPS shall be used in the order and manner specified on the SWPS.
- (d) SWPSS shall not be used in the same production joint together with WPSs qualified by the organization.
- (e) The organization may supplement an SWPS by attaching additional instructions to provide the welder with further direction for making production welds to Code or other requirements. When SWPSS are supplemented with instructions that address any condition shown on the SWPS, such instructions shall be within the limits of the SWPS. For example, when an SWPS permits use of several electrode sizes, supplemental instructions may direct the welder to use only one electrode size out of those permitted by the SWPS; however, the supplemental instructions may not permit the welder to use a size other than one or more of those permitted by the SWPS.
- (f) SWPSS may not be used until the demonstration of [QW-510](#) has been satisfactorily welded, tested, and certified.
- (g) The identification number of the Supporting Demonstration shall be noted on each SWPS that it supports prior to using the SWPS.
- (h) The certified Supporting Demonstration Record shall be available for review by Authorized Inspector.

PART QB BRAZING

ARTICLE XI BRAZING GENERAL REQUIREMENTS

(13) QB-100 SCOPE

The rules in this Part apply to the preparation of brazing procedure specifications, and the qualification of brazing procedures, brazers, and brazing operators for all types of manual and machine brazing processes permitted in this Section. These rules may also be applied, insofar as they are applicable, to other manual or machine brazing processes, permitted in other Sections.

QB-101

In performance qualification, the basic criterion established for brazer qualification is to determine the brazer's ability to make a sound brazed joint. The purpose of the performance qualification test for the brazing operator is to determine the operator's mechanical ability to operate the brazing equipment to make a sound braze joint.

QB-103 RESPONSIBILITY

QB-103.1 Brazing. Each organization shall conduct the tests required in this Section to qualify the brazing procedures used in the construction of the brazed assemblies built under this Code and the performance of brazers and brazing operators who apply these procedures.

QB-103.2 Records. Each organization shall maintain a record of the results obtained in brazing procedure and brazer or brazing operator performance qualifications. Refer to recommended Forms in [Nonmandatory Appendix B](#).

QB-110 BRAZE ORIENTATION

NOTE: In the following paragraphs the word *position* is synonymous with *flow position*.

The orientations of brazes with respect to planes of reference are classified in accordance with [Figure QB-461.1](#) into four positions (A, B, C, and D in column 1), based on the basic flow of brazing filler metal through joints. These positions are flat flow, vertical downflow, vertical upflow, and horizontal flow.

The maximum permitted angular deviation from the specified flow plane is ± 45 deg.

QB-120 TEST POSITIONS FOR LAP, BUTT, SCARF, OR RABBIT JOINTS

Brazed joints may be made in test coupons oriented in any of the positions in [Figure QB-461.2](#) and as described in the following paragraphs, except that angular deviation from the specified horizontal and vertical flow planes in accordance with column 1 of [Figure QB-461.2](#) is permitted during brazing.

QB-121 FLAT-FLOW POSITION

The test coupon joints in position suitable for applying brazing filler metal in rod, strip, or other suitable form under the flat-flow conditions are shown in illustrations (1) through (5) of Line A in [Figure QB-461.2](#). The maximum permitted angular deviation from the specified flow plane is ± 15 deg.

QB-122 VERTICAL-DOWNFLOW POSITION

The test coupon joints in a position suitable for applying brazing filler metal in rod, strip, or other suitable form under the vertical-downflow conditions are shown in illustrations (1) through (4) of Line B in [Figure QB-461.2](#). The brazing filler metal flows by capillary action with the aid of gravity downward into the joint. The maximum permitted angular deviation from the specified flow plane is ± 15 deg.

QB-123 VERTICAL-UPFLOW POSITION

The test coupon joints in position suitable for applying brazing filler metal in rod, strip, or other suitable form under the vertical-upflow conditions are shown in illustrations (1) through (4) of Line C in [Figure QB-461.2](#). The brazing filler metal flows by capillary action through the joint. The maximum permitted angular deviation from the specified flow plane is ± 15 deg.

QB-124 HORIZONTAL-FLOW POSITION

The test coupon joints in a position suitable for applying brazing filler metal in rod, strip, or other suitable form under the horizontal-flow conditions are shown in illustrations (1) and (2) of Line D of [Figure QB-461.2](#). The brazing filler metal flows horizontally by capillary action through the joint. The maximum permitted angular deviation from the specified flow plane is ± 15 deg.

QB-140 TYPES AND PURPOSES OF TESTS AND EXAMINATIONS**QB-141 TESTS**

Tests used in brazing procedure and performance qualifications are specified in [QB-141.1](#) through [QB-141.6](#).

QB-141.1 Tension Tests. Tension tests, as described in [QB-150](#), are used to determine the ultimate strength of brazed butt, scarf, lap, and rabbit joints.

QB-141.2 Guided-Bend Tests. Guided-bend tests, as described in [QB-160](#), are used to determine the degree of soundness and ductility of butt and scarf joints.

QB-141.3 Peel Tests. Peel tests, as described in [QB-170](#), are used to determine the quality of the bond and the amount of defects in lap joints.

- (13) **QB-141.4 Sectioning Tests.** Sectioning tests, i.e., the sectioning of test coupons, as described in [QB-180](#), are used to determine the soundness of workmanship coupons or test specimens. Sectioning tests are also a substitute for the peel test when the peel test is impractical to perform.

QB-141.5 Workmanship Coupons. Workmanship coupons, as described in [QB-182](#), are used to determine the soundness of joints other than the standard butt, scarf, lap, and rabbit joints.

QB-141.6 Visual Examination. Visual examination of brazed joints is used for estimating the soundness by external appearance, such as continuity of the brazing filler metal, size, contour, and wetting of fillet along the joint and, where appropriate, to determine if filler metal flowed through the joint from the side of application to the opposite side.

QB-150 TENSION TESTS**QB-151 SPECIMENS**

Tension test specimens shall conform to one of the types illustrated in [Figures QB-462.1\(a\)](#) through [QB-462.1\(f\)](#), and shall meet the requirements of [QB-153](#).

QB-151.1 Reduced Section — Plate. Reduced-section specimens conforming to the requirements given in [Figures QB-462.1\(a\)](#) and [QB-462.1\(c\)](#) may be used for

tension tests on all thicknesses of plate. The specimens may be tested in a support fixture in substantial accordance with [Figure QB-462.1\(f\)](#).

(a) For thicknesses up to and including 1 in. (25 mm), a full thickness specimen shall be used for each required tension test.

(b) For plate thicknesses greater than 1 in. (25 mm), full thickness specimens or multiple specimens may be used, provided (c) and (d) are complied with.

(c) When multiple specimens are used in lieu of full thickness specimens, each set shall represent a single tension test of the full plate thickness. Collectively, all of the specimens required to represent the full thickness of the brazed joint at one location shall comprise a set.

(d) When multiple specimens are necessary, the entire thickness shall be mechanically cut into a minimum number of approximately equal strips of a size that can be tested in the available equipment. Each specimen of the set shall be tested and meet the requirements of [QB-153](#).

QB-151.2 Reduced Section — Pipe. Reduced-section specimens conforming to the requirements given in [Figure QB-462.1\(b\)](#) may be used for tension tests on all thicknesses of pipe or tube having an outside diameter greater than 3 in. (75 mm). The specimens may be tested in a support fixture in substantial accordance with [Figure QB-462.1\(f\)](#).

(a) For thicknesses up to and including 1 in. (25 mm), a full thickness specimen shall be used for each required tension test.

(b) For pipe thicknesses greater than 1 in. (25 mm), full thickness specimens or multiple specimens may be used, provided (c) and (d) are complied with.

(c) When multiple specimens are used in lieu of full thickness specimens, each set shall represent a single tension test of the full pipe thickness. Collectively, all of the specimens required to represent the full thickness of the brazed joint at one location shall comprise a set.

(d) When multiple specimens are necessary, the entire thickness shall be mechanically cut into a minimum number of approximately equal strips of a size that can be tested in the available equipment. Each specimen of the set shall be tested and meet the requirements of [QB-153](#).

QB-151.3 Full-Section Specimens for Pipe. Tension specimens conforming to the dimensions given in [Figure QB-462.1\(e\)](#) may be used for testing pipe with an outside diameter of 3 in. (75 mm) or less.

QB-152 TENSION TEST PROCEDURE

The tension test specimen shall be ruptured under tensile load. The tensile strength shall be computed by dividing the ultimate total load by the least cross-sectional area of the specimen as measured before the load is applied.

QB-153 ACCEPTANCE CRITERIA — TENSION TESTS

QB-153.1 Tensile Strength. Minimum values for procedure qualification are provided under the column heading “Minimum Specified Tensile” of Table QW/QB-422. In order to pass the tension test, the specimen shall have a tensile strength that is not less than

(a) the specified minimum tensile strength of the base metal in the annealed condition; or

(b) the specified minimum tensile strength of the weaker of the two in the annealed condition, if base metals of different specified minimum tensile strengths are used; or

(c) if the specimen breaks in the base metal outside of the braze, the test shall be accepted as meeting the requirements, provided the strength is not more than 5% below the minimum specified tensile strength of the base metal in the annealed condition.

(d) the specified minimum tensile strength is for full thickness specimens including cladding for Aluminum Alclad materials (P-No. 104 and P-No. 105) less than $\frac{1}{2}$ in. (13 mm). For Aluminum Alclad materials $\frac{1}{2}$ in. (13 mm) and greater, the specified minimum tensile strength is for both full thickness specimens that include cladding and specimens taken from the core.

QB-160 GUIDED-BEND TESTS

QB-161 SPECIMENS

Guided-bend test specimens shall be prepared by cutting the test plate or pipe to form specimens of approximately rectangular cross section. The cut surfaces shall be designated the sides of the specimen. The other two surfaces shall be designated the first and second surfaces. The specimen thickness and bend radius are shown in Figures QB-466.1, QB-466.2, and QB-466.3. Guided-bend specimens are of five types, depending on whether the axis of the joint is transverse or parallel to the longitudinal axis of the specimen, and which surface (first or second) is on the convex (outer) side of the bent specimen. The five types are defined as follows (QB-161.1 through QB-161.6).

QB-161.1 Transverse First Surface Bend. The joint is transverse to the longitudinal axis of the specimen, which is bent so that the first surface becomes the convex surface of the bent specimen. In general, the *first surface* is defined as that surface from which the brazing filler metal is applied and is fed by capillary attraction into the joint. Transverse first surface bend specimens shall conform to the dimensions shown in Figure QB-462.2(a). For subsize first surface bends, see QB-161.3.

QB-161.2 Transverse Second Surface Bend. The joint is transverse to the longitudinal axis of the specimen, which is bent so that the second surface becomes the convex surface of the bent specimen. In general, the *second surface* is defined as the surface opposite to that from

which the brazing filler metal is placed or fed, but definitely is the surface opposite to that designated as the first surface, irrespective of how the brazing filler metal is fed. Transverse second surface bend specimens shall conform to the dimensions shown in Figure QB-462.2(a). For subsize first surface bends, see QB-161.3.

QB-161.3 Subsize Transverse Bend. In those cases where the wall thickness of the tube or pipe is less than $\frac{3}{8}$ in. (10 mm) and the diameter-to-thickness ratio does not permit the preparation of full-size rectangular guided-bend specimens, the $1\frac{1}{2}$ in. (38 mm) wide standard guided-bend specimen shown in Figure QB-462.2(a) may be replaced by three subsize specimens having a width of $\frac{3}{8}$ in. (10 mm) or $4t$, whichever is less.

QB-161.4 Longitudinal-Bend Tests. Longitudinal-bend tests may be used in lieu of the transverse-bend tests for testing braze metal or base metal combinations, which differ markedly in bending properties between

(a) the two base metals; or

(b) the braze metal and the base metal.

QB-161.5 Longitudinal First Surface Bend. The joint is parallel to the longitudinal axis of the specimen, which is bent so that the first surface becomes the convex surface of the bent specimen. The definition of first surface is as given in QB-161.1. Longitudinal first surface bend specimens shall conform to the dimensions given in Figure QB-462.2(b).

QB-161.6 Longitudinal Second Surface Bend. The joint is parallel to the longitudinal axis of the specimen, which is bent so that the second surface becomes the convex surface of the specimen. The definition of the second surface is given in QB-161.2. Longitudinal second surface bend specimens shall conform to the dimensions given in Figure QB-462.2(b).

QB-162 GUIDED-BEND TEST PROCEDURE

QB-162.1 Jigs. Guided-bend specimens shall be bent in test jigs that are in substantial accordance with QB-466. When using the jigs in accordance with Figure QB-466.1 or Figure QB-466.2, the side of the specimen turned toward the gap of the jig shall be the first surface for first surface bend specimens (defined in QB-161.1), and the second surface for second surface bend specimens (defined in QB-161.2). The specimen shall be forced into the die by applying load on the plunger until the curvature of the specimen is such that a $\frac{1}{8}$ in. (3 mm) diameter wire cannot be inserted between the specimen and the die of Figure QB-466.1, or the specimen is bottom ejected, if the roller type of jig (Figure QB-466.2) is used.

When using the wrap around jig (Figure QB-466.3) the side of the specimen turned toward the roller shall be the first surface for first surface bend specimens, and the second surface for second surface bend specimens.

QB-163 ACCEPTANCE CRITERIA — BEND TESTS

The joint of a transverse-bend specimen shall be completely within the bent portion of the specimen after testing.

The guided-bend specimens shall have no open discontinuities exceeding $\frac{1}{8}$ in. (3 mm), measured in any direction on the convex surface of the specimen after bending. Cracks occurring on the corners of the specimen during testing shall not be considered, unless there is definite evidence that they result from flux inclusions, voids, or other internal discontinuities.

QB-170 PEEL TESTS**QB-171 SPECIMENS**

The dimensions and preparation of the peel test specimen shall conform to the requirements of [Figure QB-462.3](#).

QB-172 ACCEPTANCE CRITERIA — PEEL TEST

In order to pass the peel test, the specimens shall show evidence of brazing filler metal along each edge of the joint. Specimens shall be separated or peeled either by clamping Section A and striking Section B with a suitable tool such that the bending occurs at the fulcrum point (see [Figure QB-462.3](#)), or by clamping Section A and Section B in a machine suitable for separating the sections under tension. The separated faying surfaces of joints shall meet the following criteria:

(a) The total area of discontinuities (unbrazed areas, flux inclusions, etc.) shall not exceed 25% of the total area of any individual faying surface.

(b) The sum of the lengths of the discontinuities measured on any one line in the direction of the lap shall not exceed 25% of the lap.

(c) No discontinuity shall extend continuously from one edge of the joint to the other edge, irrespective of its direction.

QB-180 SECTIONING TESTS AND WORKMANSHIP COUPONS**QB-181 SECTIONING TEST SPECIMENS**

The dimensions and configuration of the sectioning test specimens shall conform to the requirements of [Figure QB-462.4](#). Each side of the specimen shall be polished and examined with at least a four-power magnifying glass. The sum of the length of unbrazed areas on either side, considered individually, shall not exceed 20% of the length of the joint overlap.

QB-182 WORKMANSHIP COUPONS

The dimensions and configuration of the workmanship coupon shall conform to the nearest approximation of the actual application. Some typical workmanship coupons are shown in [Figure QB-462.5](#). Each side of the specimen shall be polished and examined with at least a four-power magnifying glass. The sum of the length of unbrazed areas on either side, considered individually, shall not exceed 20% of the length of the joint overlap.

ARTICLE XII

BRAZING PROCEDURE QUALIFICATIONS

(13) QB-200 GENERAL

QB-200.1 Each organization shall prepare written Brazing Procedure Specifications, which are defined as follows.

(a) *Brazing Procedure Specification (BPS)*. A BPS is a written qualified brazing procedure prepared to provide direction for making production brazes to Code requirements. The BPS or other documents [see (e)] may be used to provide direction to the brazer or brazing operator to assure compliance with the Code requirements.

(b) *Contents of the BPS*. The completed BPS shall describe all of the essential and nonessential variables for each brazing process used in the BPS. These variables are listed in QB-250 and are defined in Article XIV, Brazing Data.

The BPS shall reference the supporting Procedure Qualification Record(s) (PQR) described in QB-200.2. The organization may include any other information in the BPS that may be helpful in making a Code braze.

(c) *Changes to the BPS*. Changes may be made in the nonessential variables of a BPS to suit production requirements without requalification provided such changes are documented with respect to the essential and nonessential variables for each process. This may be by amendment to the BPS or by use of a new BPS.

Changes in essential variables require requalification of the BPS [new or additional PQRs to support the change in essential variable(s)].

(d) *Format of the BPS*. The information required to be in the BPS may be in any format, written or tabular, to fit the needs of each organization, as long as every essential and nonessential variable outlined in QB-250 is included or referenced.

Form QB-482 (see Nonmandatory Appendix B) has been provided as a guide for the BPS. It is only a guide and does not list all required data for all brazing processes.

(e) *Availability of the BPS*. A BPS used for Code production brazing shall be available for reference and review by the Authorized Inspector (AI) at the fabrication site.

QB-200.2 Each organization shall be required to prepare a procedure qualification record, which is defined as follows.

(a) *Procedure Qualification Record (PQR)*. The PQR is a record of variables recorded during the brazing of the test coupons. It also contains the test results of the tested

specimens. Recorded variables normally fall within a small range of the actual variables that will be used in production brazing.

(b) *Contents of the PQR*. The completed PQR shall document all essential variables of QB-250 for each brazing process used during the brazing of the test coupon. Nonessential or other variables used during the brazing of the test coupon may be recorded at the organization's option. All variables, if recorded, shall be the actual variables (including ranges) used during the brazing of the test coupon. If variables are not monitored during brazing, they shall not be recorded. It is not intended that the full range or the extreme of a given range of variables to be used in production be used during qualification unless required due to a specific essential variable.

The PQR shall be certified accurate by the organization. The organization may not subcontract the certification function. This certification is intended to be the organization's verification that the information in the PQR is a true record of the variables that were used during the brazing of the test coupon and that the resulting tensile, bend, peel, or section (as required) test results are in compliance with Section IX.

(c) *Changes to the PQR*. Changes to the PQR are not permitted, except as described below. It is a record of what happened during a particular brazing test. Editorial corrections or addenda to the PQR are permitted. An example of an editorial correction is an incorrect P-Number or F-Number that was assigned to a particular base material or filler metal. An example of an addendum would be a change resulting from a Code change. For example, Section IX may assign a new F-Number to a filler material or adopt a new filler material under an established F-Number. This may permit, depending on the particular construction Code requirements, an organization to use other filler metals that fall within that particular F-Number where, prior to the Code revision, the organization was limited to the particular filler metal classification that was used during qualification. Additional information can be incorporated into a PQR at a later date provided the information is substantiated as having been part of the original qualification condition by lab record or similar data.

All changes to a PQR require recertification (including date) by the organization.

(d) *Format of the PQR*. Form QB-483 (see Nonmandatory Appendix B) has been provided as a guide for the PQR. The information required to be in the PQR may be in any format, to fit the needs of each organization,

as long as every essential variable, required by [QB-250](#), is included. Also the type of tests, number of tests, and test results shall be listed in the PQR. Additional sketches or information may be attached or referenced to record the required variables.

(e) *Availability of the PQR.* PQRs used to support BPSs shall be available, upon request, for review by the Authorized Inspector (AI). The PQR need not be available to the brazer or brazing operator.

(f) *Multiple BPSs With One PQR/Multiple PQRs With One BPS.* Several BPSs may be prepared from the data on a single PQR (e.g., a vertical-upflow pipe PQR may support BPSs for the vertical-upflow and downflow positions on pipe within all other essential variables). A single BPS may cover several essential variable changes as long as a supporting PQR exists for each essential variable.

QB-200.3 To reduce the number of brazing procedure qualifications required, P-Numbers are assigned to base metals dependent on characteristics such as composition, brazability, and mechanical properties, where this can logically be done, and for ferrous and nonferrous metals.

The assignments do not imply that base metals may be indiscriminately substituted for a base metal which was used in the qualification test without consideration of the compatibility from the standpoint of metallurgical properties, postbrazing heat treatment, design, mechanical properties, and service requirements.

QB-200.4 Dissimilar Base Metal Thicknesses. A BPS qualified on test coupons of equal thickness shall be applicable for production brazements between dissimilar base metal thicknesses provided the thickness of both base metals are within the qualified thickness range permitted by [QB-451](#). A BPS qualified on test coupons of different thicknesses shall be applicable for production brazements between dissimilar base metal thicknesses provided the thickness of each base metal is within the qualified range of thickness (based on each test coupon thickness) permitted by [QB-451](#).

QB-201 ORGANIZATIONAL RESPONSIBILITY

The organization shall certify that they have qualified each Brazing Procedure Specification, performed the procedure qualification test, and documented it with the necessary Procedure Qualification Record (PQR).

QB-202 TYPE OF TESTS REQUIRED

QB-202.1 Tests. The type and number of test specimens which shall be tested to qualify a brazing procedure are given in [QB-451](#), and shall be removed in a manner similar to that shown in [QB-463](#). If any test specimen required by [QB-451](#) fails to meet the applicable acceptance criteria, the test coupon shall be considered as failed.

When it can be determined that the cause of failure is not related to brazing parameters, another test coupon may be brazed using identical brazing parameters. Alternatively, if adequate material of the original test coupon

exists, additional test specimens may be removed as close as practicable to the original specimen location to replace the failed test specimens.

When it has been determined that the test failure was caused by an essential variable, a new test coupon may be brazed with appropriate changes to the variable(s) that were determined to cause the test failure. If the new test passes, the essential variables shall be documented on the PQR.

When it is determined that the test failure was caused by one or more brazing related factors other than essential variables, a new test coupon may be brazed with the appropriate changes to brazing related factors that were determined to cause the test failure. If the new test passes, the brazing related factors that were determined to cause the previous test failure shall be addressed by the organization to assure that the required properties are achieved in the production brazement.

QB-202.2 Base Metals. The procedure qualification shall encompass the thickness ranges to be used in production for the base metals to be joined or repaired. The range of thickness qualified is given in [QB-451](#).

QB-203 LIMITS OF QUALIFIED FLOW POSITIONS FOR PROCEDURES (SEE FIGURES [QB-461.1](#) AND [QB-461.2](#))

QB-203.1 For plate, qualification in the flat-flow, vertical-upflow, or horizontal-flow position shall qualify for the vertical-downflow position. For pipe, qualification in the horizontal-flow or vertical-upflow position shall qualify for the vertical-downflow position.

Qualification in pipe shall qualify for plate, but not vice versa. Horizontal-flow in pipe shall also qualify for flat-flow in plate.

QB-203.2 Special Flow Positions. An organization who does production brazing in a special orientation may make the tests for procedure qualification in this specific orientation. Such qualifications are valid only for the flow positions actually tested, except that an angular deviation of ± 15 deg is permitted in the inclination of the braze plane, as defined in [Figures \[QB-461.1\]\(#\) and \[QB-461.2\]\(#\)](#).

QB-203.3 The brazing process must be compatible, and the brazing filler metals, such as defined in the specifications of Section II, Part C, must be suitable for their use in specific flow positions. A brazer or brazing operator making and passing the BPS qualification test is thereby qualified for the flow position tested (see [QB-301.2](#)).

QB-210 PREPARATION OF TEST COUPON

QB-211 BASE METAL AND FILLER METAL

The base metals and filler metals shall be one or more of those listed in the BPS. The dimensions of the test assembly shall be sufficient to provide the required test specimens.

The base metals may consist of either plate, pipe, or other product forms. Qualification in pipe also qualifies for plate brazing, but not vice versa.

QB-212 TYPE AND DIMENSION OF JOINTS

The test coupon shall be brazed using a type of joint design proposed in the BPS for use in construction.

QB-250 BRAZING VARIABLES

QB-251 GENERAL

QB-251.1 Types of Variables for Brazing Procedure Specification (BPS). Brazing variables (listed for each brazing process in [Tables QB-252](#) through [QB-257](#)) are subdivided into essential and nonessential variables ([QB-401](#)).

QB-251.2 Essential Variables. Essential variables are those in which a change, as described in the specific variables, is considered to affect the mechanical properties of the brazement, and shall require requalification of the BPS.

QB-251.3 Nonessential Variables. Nonessential variables are those in which a change, as described in the specific variables, may be made in the BPS without requalification.

**Table QB-252
Torch Brazing (TB)**

Paragraph	252.1 Essential Variables	252.2 Nonessential Variables
QB-402 Base Metal	QB-402.1	...
	QB-402.3	...
QB-403 Brazing Filler Metal	QB-403.1	...
	QB-403.2	...
QB-406 Brazing Flux, Gas, or Atmosphere	QB-406.1	QB-406.3
QB-407 Flow Position	QB-407.1	...
QB-408 Joint Design	QB-408.2	...
	QB-408.4	...
QB-409 Postbrazing Heat Treatment	QB-409.1	...
	QB-409.2	...
	QB-409.3	...
QB-410 Technique	...	QB-410.1
	...	QB-410.2
	...	QB-410.3
	...	QB-410.4
	...	QB-410.5

**Table QB-253
Furnace Brazing (FB)**

Paragraph	253.1 Essential Variables	253.2 Nonessential Variables
QB-402 Base Metal	QB-402.1	...
	QB-402.3	...
QB-403 Brazing Filler Metal	QB-403.1	...
	QB-403.2	...
QB-404 Brazing Temperature	QB-404.1	...
QB-406 Brazing Flux, Gas, or Atmosphere	QB-406.1	...
	QB-406.2	...
QB-407 Flow Position	QB-407.1	...
QB-408 Joint Design	QB-408.2	...
	QB-408.4	...
QB-409 Postbrazing Heat Treatment	QB-409.1	...
	QB-409.2	...
	QB-409.3	...
QB-410 Technique	...	QB-410.1
	...	QB-410.2

**Table QB-254
Induction Brazing (IB)**

Paragraph	254.1 Essential Variables	254.2 Nonessential Variables
QB-402 Base Metal	QB-402.1	...
	QB-402.3	...
QB-403 Brazing Filler Metal	QB-403.1	...
	QB-403.2	...
QB-404 Brazing Temperature	QB-404.1	...
QB-406 Brazing Flux, Gas, or Atmosphere	QB-406.1	...
QB-407 Flow Position	QB-407.1	...
QB-408 Joint Design	QB-408.2	...
	QB-408.4	...
QB-409 Postbrazing Heat Treatment	QB-409.1	...
	QB-409.2	...
	QB-409.3	...
QB-410 Technique	...	QB-410.1
	...	QB-410.2

Table QB-255
Resistance Brazing (RB)

Paragraph	255.1 Essential Variables	255.2 Nonessential Variables
QB-402 Base Metal	QB-402.1	...
	QB-402.3	...
QB-403 Brazing Filler Metal	QB-403.1	...
	QB-403.2	...
QB-404 Brazing Temperature	QB-404.1	...
QB-406 Brazing Flux, Gas, or Atmosphere	QB-406.1	...
QB-407 Flow Position	QB-407.1	...
QB-408 Joint Design	QB-408.2	...
	QB-408.4	...
QB-409 Postbrazing Heat Treatment	QB-409.1	...
	QB-409.2	...
	QB-409.3	...
QB-410 Technique	...	QB-410.1
	...	QB-410.2

Table QB-256
Dip Brazing — Salt or Flux Bath (DB)

Paragraph	256.1 Essential Variables	256.2 Nonessential Variables
QB-402 Base Metal	QB-402.1	...
	QB-402.3	...
QB-403 Brazing Filler Metal	QB-403.1	...
	QB-403.2	...
QB-404 Brazing Temperature	QB-404.1	...
QB-406 Brazing Flux, Gas, or Atmosphere	QB-406.1	...
QB-407 Flow Position	QB-407.1	...
QB-408 Joint Design	QB-408.2	...
	QB-408.4	...
QB-409 Postbrazing Heat Treatment	QB-409.1	...
	QB-409.2	...
	QB-409.3	...
QB-410 Technique	...	QB-410.1
	...	QB-410.2

Table QB-257
Dip Brazing — Molten Metal Bath (DB)

Paragraph	257.1 Essential Variables	257.2 Nonessential Variables
QB-402 Base Metal	QB-402.1	...
	QB-402.3	...
QB-403 Brazing Filler Metal	QB-403.1	...
	QB-403.2	...
QB-404 Brazing Temperature	QB-404.1	...
QB-406 Brazing Flux, Gas, or Atmosphere	QB-406.1	...
QB-407 Flow Position	QB-407.1	...
QB-408 Joint Design	QB-408.2	...
	QB-408.4	...
QB-409 Postbrazing Heat Treatment	QB-409.1	...
	QB-409.2	...
	QB-409.3	...
QB-410 Technique	...	QB-410.1
	...	QB-410.2

ARTICLE XIII

BRAZING PERFORMANCE QUALIFICATIONS

(13) QB-300 GENERAL

QB-300.1 This Article lists the brazing processes separately, with the essential variables which apply to brazer and brazing operator performance qualifications.

The brazer qualification is limited by the essential variables given for each brazing process. These variables are listed in [QB-350](#), and are defined in [Article XIV](#), Brazing Data. The brazing operator qualification is limited by the essential variables given in [QB-350](#) for each brazing process.

QB-301 TESTS

QB-301.1 Intent of Tests. The performance qualification tests are intended to determine the ability of brazers and brazing operators to make sound braze joints.

QB-301.2 Qualification Tests. Each organization shall qualify each brazer or brazing operator for each brazing process to be used in production brazing. The performance qualification test shall be brazed in accordance with one of any of his qualified Brazing Procedure Specifications (BPS).

The brazer or brazing operator who prepares the BPS qualification test coupons is also qualified within the limits of the performance qualifications, listed in [QB-304](#) for brazers and in [QB-305](#) for brazing operators. He is qualified only for the positions tested in the procedure qualification in accordance with [QB-407](#).

QB-301.3 Identification of Brazers and Brazing Operators. Each qualified brazer and brazing operator shall be assigned an identifying number, letter, or symbol by the organization, which shall be used to identify the work of that brazer or brazing operator.

QB-301.4 Record of Tests. The record of Brazer or Brazing Operator Performance Qualification (BPQ) tests shall include the essential variables ([QB-350](#)), the type of tests and the test results, and the ranges qualified in accordance with [QB-452](#) for each brazer and brazing operator. A suggested form for these records is given in [Form QB-484](#) (see [Nonmandatory Appendix B](#)).

QB-302 TYPE OF TEST REQUIRED

QB-302.1 Test Specimens. The type and number of test specimens required shall be in accordance with [QB-452](#), and shall be removed in a manner similar to that shown in [QB-463](#).

All test specimens shall meet the requirements prescribed in [QB-170](#) or [QB-180](#), as applicable. Tests for brazing operators shall meet the requirements of [QB-305](#).

QB-302.2 Test Coupons in Pipe. For test coupons made in pipe, specimens shall be removed as shown in [Figure QB-463.2\(c\)](#) at approximately 180 deg apart.

QB-302.3 Combination of Base Metal Thicknesses. When joints are brazed between two base metals of different thicknesses, a performance qualification shall be made for the applicable combination of thicknesses, even though qualification tests have been made for each of the individual base metals brazed to itself. The range of thickness of each of the base metals shall be determined individually per [QB-452](#).

QB-303 LIMITS OF QUALIFIED POSITIONS

(See [Figures QB-461.1](#) and [QB-461.2](#))

QB-303.1 For plate, qualification in the flat-flow, vertical-upflow, or horizontal-flow positions shall qualify for the vertical-downflow position.

QB-303.2 For pipe, qualification in either the horizontal-flow or vertical-upflow position shall qualify for the vertical-downflow position.

QB-303.3 Qualification in pipe shall qualify for plate, but not vice versa. Horizontal-flow in pipe shall qualify for flat-flow in plate.

QB-303.4 Special Positions. An organization who does production brazing in a special orientation may make the tests for performance qualification in this specific orientation. Such qualifications are valid only for the flow positions actually tested, except that an angular deviation of ± 15 deg is permitted in the inclination of the braze plane, as defined in [Figures QB-461.1](#) and [QB-461.2](#).

QB-304 BRAZERS

Each brazer who brazes under the rules of this Code shall have passed the tests prescribed in [QB-302](#) for performance qualifications.

A brazer qualified to braze in accordance with one qualified BPS is also qualified to braze in accordance with other qualified BPSs, using the same brazing process, within the limits of the essential variables of [QB-350](#).

QB-305 BRAZING OPERATORS

The brazing operator who prepares brazing procedure qualification test specimens meeting requirements of [QB-451](#) is thereby qualified. Alternatively, each brazing operator who brazes on vessels constructed under the rules of this Code shall be qualified for each combination of essential variables under which brazing is performed using semiautomatic or automatic processes (such as the resistance, induction, or furnace processes) as follows:

(a) A typical joint or workmanship coupon embodying the requirements of a qualified brazing procedure shall be brazed and sectioned. Typical joints are shown in [Figure QB-462.5](#).

(b) In order to ensure that the operator can carry out the provisions of the brazing procedure, the test sections required in (a) shall meet the requirements of [QB-452](#).

QB-310 QUALIFICATION TEST COUPONS

QB-310.1 Test Coupons. The test coupons may be plate, pipe, or other product forms. The dimensions of the test coupon and length of braze shall be sufficient to provide the required test specimens.

QB-310.2 Braze Joint. The dimensions of the braze joint at the test coupon used in making qualification tests shall be the same as those in the Brazing Procedure Specification (BPS).

QB-310.3 Base Metals. When a brazer or brazing operator is to be qualified, the test coupon shall be base metal of the P-Number or P-Numbers to be joined in production brazing.

QB-320 RETESTS AND RENEWAL OF QUALIFICATION**QB-321 RETESTS**

A brazer or brazing operator who fails to meet the requirements for one or more of the test specimens prescribed in [QB-452](#) may be retested under the following conditions.

QB-321.1 Immediate Retest. When an immediate retest is made, the brazer or brazing operator shall make two consecutive test coupons for each position which he has failed, all of which shall pass the test requirements.

QB-321.2 Further Training. When the brazer or brazing operator has had further training or practice, a complete retest shall be made for each position on which he failed to meet the requirements.

QB-322 RENEWAL OF QUALIFICATION

Renewal of qualification of a performance qualification is required

(a) when a brazer or brazing operator has not used the specific brazing process for a period of 6 months or more, or

(b) when there is a specific reason to question his ability to make brazes that meet the specification. Renewal of qualification for a specific brazing process under (a) may be made with specific brazing process by making only one test joint (plate or pipe) with all the essential variables used on any one of the brazer's or brazing operator's previous qualification test joints. This will reestablish the brazer's or brazing operator's qualification for all variables for which he had previously qualified with the specific brazing process.

QB-350 BRAZING VARIABLES FOR BRAZERS AND BRAZING OPERATORS**QB-351 GENERAL**

A brazer or brazing operator shall be requalified whenever a change is made in one or more of the essential variables for each brazing process, as follows:

- (a) Torch Brazing (TB)
- (b) Furnace Brazing (FB)
- (c) Induction Brazing (IB)
- (d) Resistance Brazing (RB)
- (e) Dip Brazing (DB)

QB-351.1 Essential Variables — Manual, Semiautomatic, and Machine Brazing.

- (a) [QB-402](#) Base Metal
 - (1) [QB-402.2](#)
 - (2) [QB-402.3](#)
- (b) [QB-403](#) Brazing Filler Metal
 - (1) [QB-403.1](#)
 - (2) [QB-403.2](#)
- (c) [QB-407](#) Flow Position
 - (1) [QB-407.1](#)
- (d) [QB-408](#) Joint Design
 - (1) [QB-408.1](#)
 - (2) [QB-408.3](#)
- (e) [QB-410](#) Technique
 - (1) [QB-410.5](#)

QB-351.2 Essential Variables — Automatic.

- (a) A change from automatic to machine brazing.
- (b) A change in brazing process.

ARTICLE XIV BRAZING DATA

QB-400 VARIABLES

QB-401 GENERAL

QB-401.1 Each brazing variable described in this Article is applicable as an essential or nonessential variable for procedure qualification when referenced in [QB-250](#) for each specific process. Essential variables for performance qualification are referenced in [QB-350](#) for each specific brazing process. A change from one brazing process to another brazing process is an essential variable and requires requalification.

QB-402 BASE METAL

QB-402.1 A change from a base metal listed under one P-Number in [Table QW/QB-422](#) to any of the following:

- (a) a metal listed under another P-Number
- (b) any other base metal not listed in [Table QW/QB-422](#)

The brazing of dissimilar metals need not be requalified if each base metal involved is qualified individually for the same brazing filler metal, flux, atmosphere, and process. Similarly, the brazing of dissimilar metals qualifies for the individual base metal brazed to itself and for the same brazing filler metal, flux, atmosphere, and process, provided the requirements of [QB-153.1\(a\)](#) are met.

QB-402.2 A change from a base metal listed under one P-Number in [Table QW/QB-422](#) to any of the following:

- (a) a metal listed under another P-Number
- (b) any other metal not listed in [Table QW/QB-422](#)

The brazing of dissimilar metals need not be requalified if each base metal involved is qualified individually for the same brazing filler metal, flux, atmosphere, and process. Similarly, the brazing of dissimilar metals qualifies for the individual base metal brazed to itself and for the same brazing filler metal, flux, atmosphere, and process.

QB-402.3 A change in base metal thickness beyond the range qualified in [QB-451](#) for procedure qualification, or [QB-452](#) for performance qualification.

QB-403 BRAZING FILLER METAL

QB-403.1 A change from one F-Number in [Table QB-432](#) to any other F-Number, or to any other filler metal not listed in [Table QB-432](#).

QB-403.2 A change in filler metal from one product form to another (for example, from preformed ring to paste).

QB-404 BRAZING TEMPERATURE

QB-404.1 A change in brazing temperature to a value outside the range specified in the BPS.

QB-406 BRAZING FLUX, FUEL GAS, OR ATMOSPHERE

QB-406.1 The addition or deletion of brazing flux or a change in AWS classification of the flux. Nominal chemical composition or the trade name of the flux may be used as an alternative to the AWS classification.

QB-406.2 A change in the furnace atmosphere from one basic type to another type. For example

- (a) reducing to inert
- (b) carburizing to decarburizing
- (c) hydrogen to disassociated ammonia

QB-406.3 A change in the type of fuel gas(es).

QB-407 FLOW POSITION

QB-407.1 The addition of other brazing positions than those already qualified (see [QB-120](#) through [QB-124](#), [QB-203](#) for procedure, and [QB-303](#) for performance).

(a) If the brazing filler metal is preplaced or faced from outside the joint, then requalification is required in accordance with the positions defined in [Figures QB-461.1](#) and [QB-461.2](#) under the conditions of [QB-120](#) through [QB-124](#).

(b) If the brazing filler metal is preplaced in a joint in a manner that major flow does occur, then requalification is required in accordance with the positions defined in [Figures QB-461.1](#) and [QB-461.2](#) under the conditions of [QB-120](#) through [QB-124](#).

(c) If the brazing filler metal is preplaced in a joint so that there is no major flow, then the joint may be brazed in any position without requalification.

QB-408 JOINT DESIGN

QB-408.1 A change in the joint type, i.e., from a butt to a lap or socket, from that qualified. For lap or socket joints, an increase in lap length of more than 25% from the overlap used on the brazer performance qualification test coupon (a decrease in overlap is permitted without requalification).

QB-408.2 A change in the joint clearances to a value outside the range specified in the BPS and as recorded in the PQR.

QB-408.3 A change in the joint clearances to a value outside the range specified in the BPS.

QB-408.4 A change in the joint type, e.g., from a butt to a lap or socket, from that qualified. For lap and socket joints, a decrease in overlap length from the overlap used on the procedure qualification test coupon (an increase in overlap is permitted without requalification).

QB-409 POSTBRAZE HEAT TREATMENT

QB-409.1 A separate procedure qualification is required for each of the following:

(a) For P-Nos. 101 and 102 materials, the following postbrazing heat treatment conditions apply:

- (1) no postbrazing heat treatment
- (2) postbrazing heat treatment below the lower transformation temperature
- (3) postbrazing heat treatment above the upper transformation temperature (e.g., normalizing)
- (4) postbrazing heat treatment above the upper transformation temperature followed by heat treatment below the lower transformation temperature (e.g., normalizing or quenching followed by tempering)
- (5) postbrazing heat treatment between the upper and lower transformation temperatures

(b) For all other materials, the following post weld heat treatment conditions apply:

- (1) no postbrazing heat treatment
- (2) postbrazing heat treatment within a specified temperature range

QB-409.2 A change in the postbrazing heat treatment (see [QB-409.1](#)) temperature and time range requires a PQR.

The procedure qualification test shall be subjected to postbrazing heat treatment essentially equivalent to that encountered in the fabrication of production brazements, including at least 80% of the aggregate time at temperature (s). The postbrazing heat treatment total time(s) at temperature(s) may be applied in one heating cycle.

QB-409.3 For a procedure qualification test coupon receiving a postbrazing heat treatment in which the upper transformation temperature is exceeded, the maximum qualified thickness for production brazements is 1.1 times the thickness of the test coupon.

QB-410 TECHNIQUE

QB-410.1 A change in the method of preparing the base metal, i.e., method of precleaning the joints (for example, from chemical cleaning to cleaning by abrasive or mechanical means).

QB-410.2 A change in the method of postbrazing cleaning (for example, from chemical cleaning to cleaning by wire brushing or wiping with a wet rag).

QB-410.3 A change in the nature of the flame (for example, a change from neutral or slightly reducing).

QB-410.4 A change in the brazing tip sizes.

QB-410.5 A change from manual to machine or semi-automatic torch brazing, and vice versa. (13)

QB-420 P-NUMBERS

(See [Part QW](#), Welding — [QW-420](#))

QB-430 F-NUMBERS

QB-431 GENERAL

The following F-Number grouping of brazing filler metals in [Table QB-432](#) is based essentially on their usability characteristics, which fundamentally determine the ability of brazers and brazing operators to make satisfactory brazements with a given filler metal. This grouping is made to reduce the number of brazing procedure and performance qualifications, where this can logically be done. The grouping does not imply that filler metals within a group may be indiscriminately substituted for a filler metal which was used in the qualification test without consideration of the compatibility from the standpoint of metallurgical properties, design, mechanical properties, postbrazing heat treatment, and service requirements.

Table QB-432
F-Numbers
Grouping of Brazing Filler Metals for Procedure and Performance Qualification SFA-5.8

QB	F.No.	AWS Classification No.
432.1	101	BAG-1
		BAG-1a
		BAG-8
		BAG-8a
		BAG-22
		BAG-23
		BVAG-0
		BVAG-8
		BVAG-8b
		BVAG-30
432.2	102	BAG-2
		BAG-2a
		BAG-3
		BAG-4
		BAG-5
		BAG-6
		BAG-7
		BAG-9
		BAG-10
		BAG-13
		BAG-13a
		BAG-18
		BAG-19
		BAG-20
		BAG-21
		BAG-24
		BAG-26
		BAG-27
		BAG-28
		BAG-33
		BAG-34
		BAG-35
		BAG-36
		BAG-37
		BVAG-6b
		BVAG-8
		BVAG-8a
		BVAG-18
		BVAG-29
		BVAG-31
		BVAG-32
432.3	103	BCuP-2
		BCuP-3
		BCuP-4
		BCuP-5
		BCuP-6
		BCuP-7
		BCuP-8
		BCuP-9
432.4	104	BAlSi-2
		BAlSi-3
		BAlSi-4
		BAlSi-5
		BAlSi-7
		BAlSi-9
		BAlSi-11

Table QB-432
F-Numbers
Grouping of Brazing Filler Metals for Procedure and Performance Qualification SFA-5.8 (Cont'd)

QB	F-No.	AWS Classification No.
432.5	105	BCu-1 BCu-1a BCu-2 BCu-3 BVCu-1a BVCu-1b
432.6	106	RBCuZn-A RBCuZn-B RBCuZn-C RBCuZn-D
432.7	107	BNi-1 BNi-1a BNi-2 BNi-3 BNi-4 BNi-5 BNi-5a BNi-5b BNi-6 BNi-7 BNi-8 BNi-9 BNi-10 BNi-11 BNi-12 BNi-13
432.8	108	BAu-1 BAu-2 BAu-3 BAu-4 BAu-5 BAu-6 BVAu-2 BVAu-3 BVAu-4 BVAu-7 BVAu-8 BVAu-9 BVAu-10
432.9	109	BMg-1
432.10	110	BCo-1
432.11	111	BVPd-1

QB-450 SPECIMENS**QB-451 PROCEDURE QUALIFICATION SPECIMENS**

Table QB-451.1
Tension Tests and Transverse-Bend Tests — Butt and Scarf Joints

Thickness <i>T</i> of Test Coupon as Braze, in. (mm)	Range of Thickness of Materials Qualified by Test Plate or Pipe, in. (mm)		Type and Number of Test Specimens Required		
	Min.	Max.	Tension [Note (1)]	First Surface Bend [Note (2)]	Second Surface Bend [Note (2)]
Less than $\frac{1}{8}$ (3)	$0.5T$	$2T$	2	2	2
$\frac{1}{8}$ to $\frac{3}{8}$ (3 to 10), incl.	$\frac{1}{16}$ (1.5)	$2T$	2	2	2
Over $\frac{3}{8}$ (10)	$\frac{3}{16}$ (5)	$2T$	2 [Note (3)]	2	2

NOTES:

- (1) For specimen dimensions, see Figure QB-462.1(a) for plate specimens, or Figure QB-462.1(b) for pipe specimens. For pipe specimens not greater than NPS 3 (DN 75), full section testing may be substituted; see Figure QB-462.1(e).
- (2) For specimen dimensions, see Figure QB-462.2(a). For specimen removal, see Figure QB-463.1(a) for plate coupons, or Figure QB-463.1(e) for pipe coupons.
- (3) See QB-151 for details on multiple specimens when coupon thicknesses are over 1 in. (25 mm).

Table QB-451.2
Tension Tests and Longitudinal Bend Tests — Butt and Scarf Joints

Thickness <i>T</i> of Test Coupon as Braze, in. (mm)	Range of Thickness of Materials Qualified by Test Plate or Pipe, in. (mm)		Type and Number of Test Specimens Required		
	Min.	Max.	Tension [Note (1)]	First Surface Bend [Note (2)]	Second Surface Bend [Note (2)]
Less than $\frac{1}{8}$ (3)	$0.5T$	$2T$	2	2	2
$\frac{1}{8}$ to $\frac{3}{8}$ (3 to 10), incl.	$\frac{1}{16}$ (1.5)	$2T$	2	2	2
Over $\frac{3}{8}$ (10)	$\frac{3}{16}$ (5)	$2T$	2 [Note (3)]	2	2

NOTES:

- (1) For specimen dimensions, see Figure QB-462.1(a) for plate specimens, or Figure QB-462.1(b) for pipe specimens. For pipe specimens not greater than NPS 3 (DN 75), full section testing may be substituted; see Figure QB-462.1(e).
- (2) For specimen dimensions, see Figures QB-462.2(b) and QB-463.1(b) for specimen removal.
- (3) See QB-151 for details on multiple specimens when coupon thicknesses are over 1 in. (25 mm).

Table QB-451.3
Tension Tests and Peel Tests — LAP Joints

Thickness <i>T</i> of Test Coupon as Brazed, in. (mm)	Range of Thickness of Materials Qualified by Test Plate or Pipe, in. (mm)		Type and Number of Test Specimens Required [Note (1)]	
	Min.	Max.	Tension [Note (2)]	Peel [Note (3)] and [Note (4)]
Less than $\frac{1}{8}$ (3)	$0.5T$	$2T$	2	2
$\frac{1}{8}$ to $\frac{3}{8}$ (3 to 10), incl.	$\frac{1}{16}$ (1.5)	$2T$	2	2
Over $\frac{3}{8}$ (10)	$\frac{3}{16}$ (5)	$2T$	2	2

NOTES:

- (1) When materials of a representative geometry and thickness are not available to prepare butt or lap joint test coupons, workmanship coupons may be prepared and examined per QB-451.5 to establish the range of thickness of base metal qualified. When this is done, the properties of the joint shall be validated using butt or lap joint test coupons of any thickness.
- (2) For specimen dimensions, see Figure QB-462.1(c). For pipe specimens not greater than NPS 3 (DN 75), full section testing may be substituted; see Figure QB-462.1(e).
- (3) For peel specimens, see Figure QB-462.3 for specimen dimensions, and Figure QB-463.1(d) for specimen removal.
- (4) Sectioning tests may be substituted for peel tests. For section specimens, see Figure QB-462.4 for specimen dimensions, and Figure QB-463.1(c) for specimen removal.

Table QB-451.4
Tension Tests and Section Tests — Rabbet Joints

Thickness <i>T</i> of Test Coupon as Brazed, in. (mm)	Range of Thickness of Materials Qualified by Test Plate or Pipe, in. (mm)		Type and Number of Test Specimens Required	
	Min.	Max.	Tension [Note (1)]	Tension [Note (2)]
Less than $\frac{1}{8}$ (3)	$0.5T$	$2T$	2	2
$\frac{1}{8}$ to $\frac{3}{8}$ (3 to 10), incl.	$\frac{1}{16}$ (1.5)	$2T$	2	2
Over $\frac{3}{8}$ (10)	$\frac{3}{16}$ (5)	$2T$	2	2

NOTES:

- (1) For specimen dimensions, see Figure QB-462.1(c). For pipe specimens not greater than NPS 3 (DN 75), full section testing may be substituted; see Figure QB-462.1(e).
- (2) For specimen dimensions, see Figures QB-462.4 and QB-463.1(c) for specimen removal.

Table QB-451.5
Section Tests — Workmanship Coupon Joints

Thickness <i>T</i> of Test Coupon as Brazed, in. (mm)	Range of Thickness of Materials Qualified by Test Plate or Pipe, in. (mm)		Type and Number of Test Specimens Required
	Min.	Max.	Section, QB-462.5 [Note (1)]
Less than $\frac{1}{8}$ (3)	$0.5T$	$2T$	2
$\frac{1}{8}$ to $\frac{3}{8}$ (3 to 10), incl.	$\frac{1}{16}$ (1.5)	$2T$	2
Over $\frac{3}{8}$ (10)	$\frac{3}{16}$ (5)	$2T$	2

NOTE:

- (1) This test in itself does not constitute procedure qualification but must be validated by conductance of tests of butt or lap joints as appropriate. For joints connecting tension members, such as the stay or partition type in QB-462.5, the validation data may be based upon butt joints; for joints connecting members in shear, such as saddle or spud joints, the validation data may be based on lap joints.

QB-452 PERFORMANCE QUALIFICATION SPECIMENS

Table QB-452.1
Peel or Section Tests — Butt, Scarf, Lap, Rabbet Joints

Thickness <i>T</i> of Test Coupon as Brazed, in. (mm)	Range of Thickness of Materials Qualified by Test Plate or Pipe, in. (mm)		Type and Number of Test Specimens Required
	Min.	Max.	Peel, QB-462.3 or section, QB-462.4 [Note (1)], [Note (2)], and [Note (3)]
Less than $\frac{1}{8}$ (3)	$0.5T$	$2T$	2
$\frac{1}{8}$ to $\frac{3}{8}$ (3 to 10), incl.	$\frac{1}{16}$ (1.5)	$2T$	2
Over $\frac{3}{8}$ (10)	$\frac{3}{16}$ (5)	$2T$	2


NOTES:

- (1) Sectioning tests may be substituted for the peel test when the peel test is impractical to perform (e.g., when the strength of the brazing filler metal is equal to or greater than the strength of the base metals).
- (2) For specimen dimensions, see Figure QB-462.3 for peel test specimens or Figure QB-462.4 for section specimens.
- (3) For specimen removal, see Figure QB-463.2(a) for section specimens or Figure QB-463.2(b) for peel specimens from plate coupons, or Figure QB-463.2(c) for pipe coupons.

Table QB-452.2
Section Tests — Workmanship Specimen Joints

Thickness <i>T</i> of Test Coupon as Brazed, in. (mm)	Range of Thickness of Materials Qualified by Test Plate or Pipe, in. (mm)		Type and Number of Test Specimens Required
	Min.	Max.	Section, QB-462.5
Less than $\frac{1}{8}$ (3)	$0.5T$	$2T$	1
$\frac{1}{8}$ to $\frac{3}{8}$ (3 to 10), incl.	$\frac{1}{16}$ (1.5)	$2T$	1
Over $\frac{3}{8}$ (10)	$\frac{3}{16}$ (5)	$2T$	1


QB-460 GRAPHICS

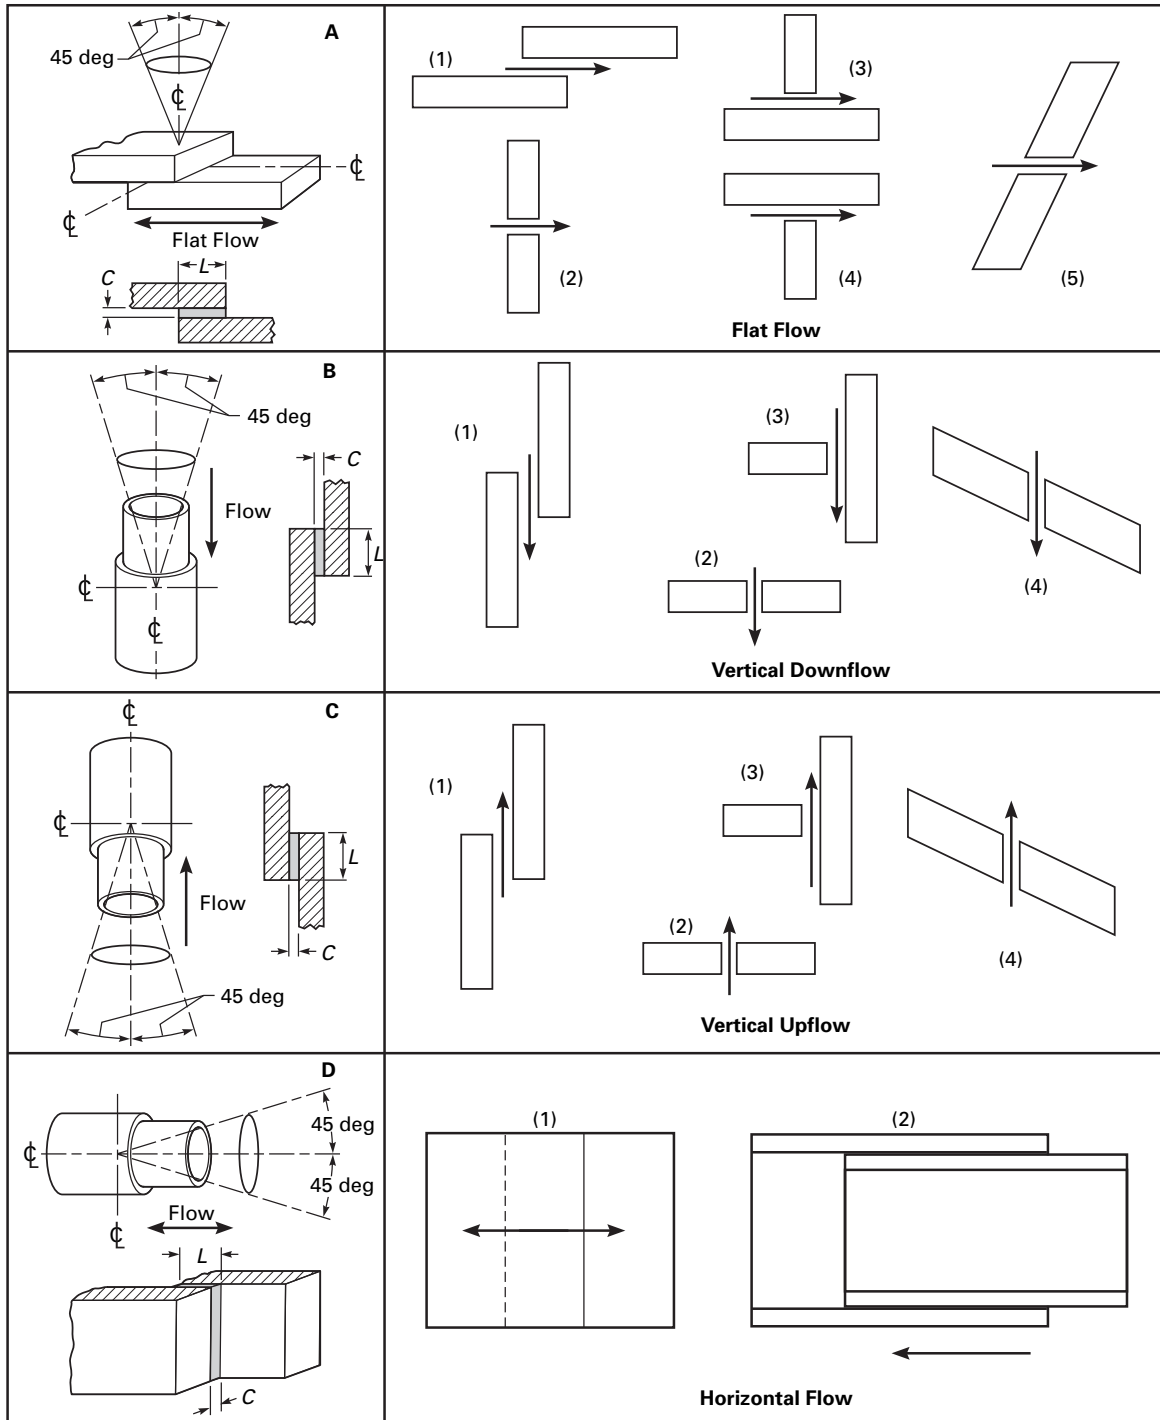Figure QB-461.1
Flow Positions

GENERAL NOTES:

- (a) C = joint clearance
 (b) L = length of lap or thickness

Figure QB-461.2
Test Flow Positions


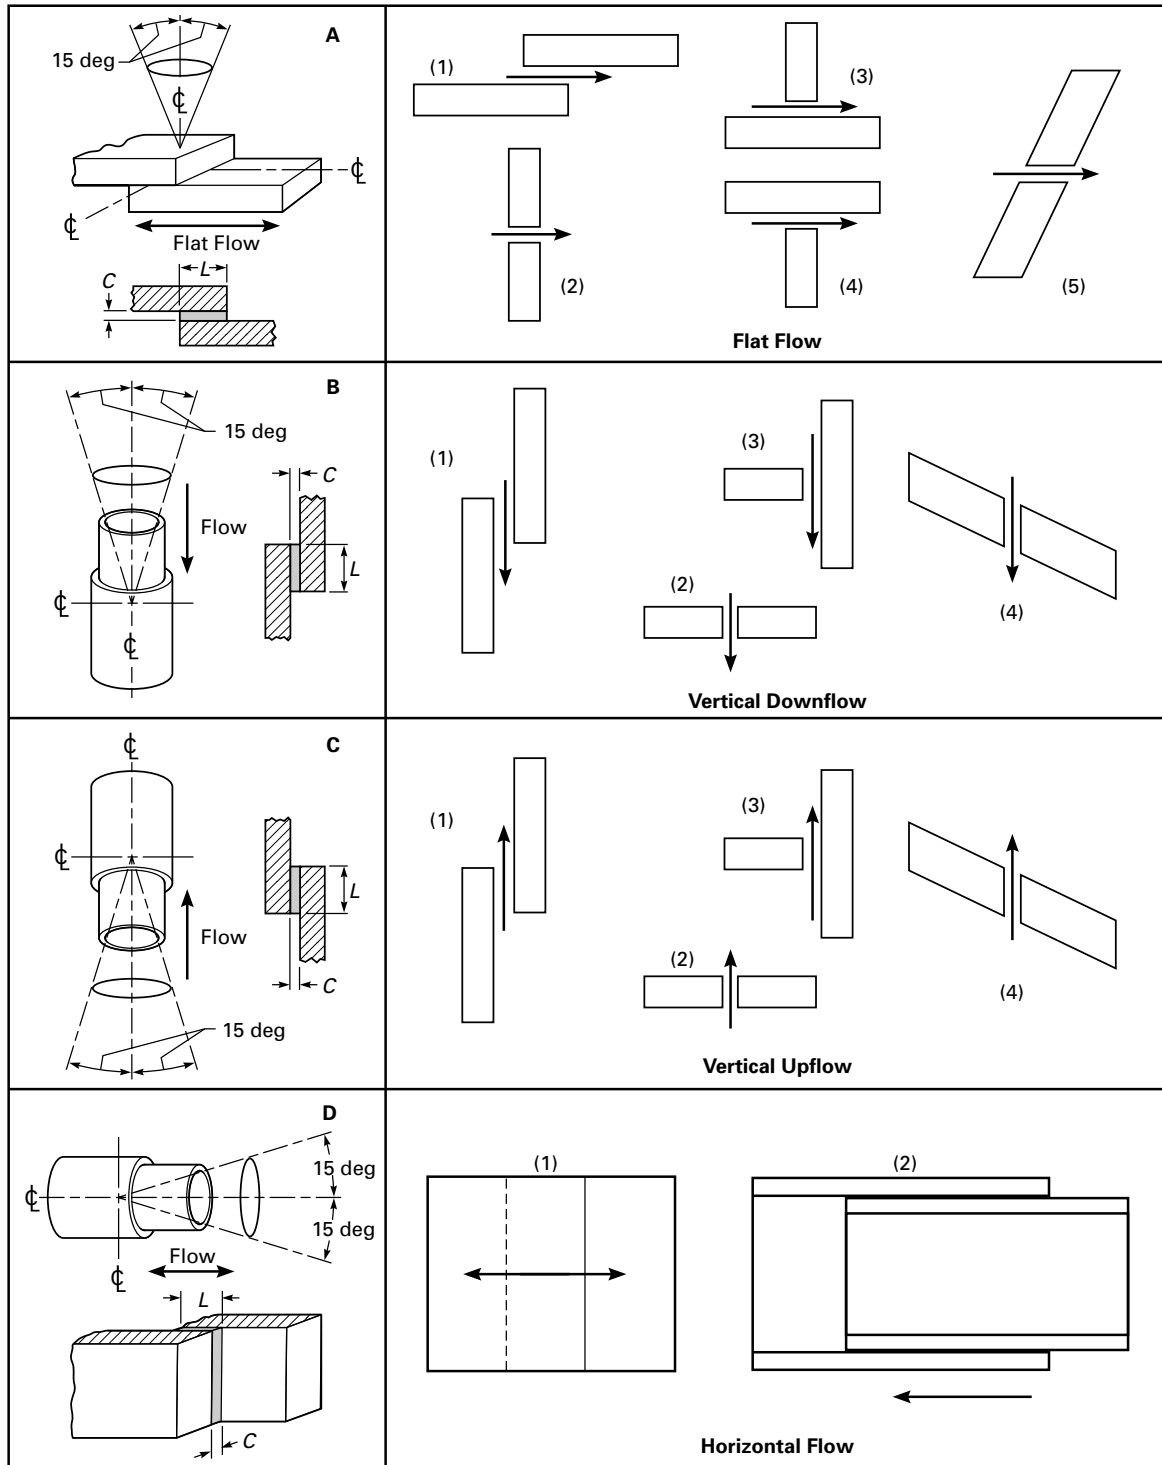


GENERAL NOTES:

(a) C = joint clearance

(b) L = length of lap or thickness

Figure QB-462.1(a)
Tension — Reduced Section for Butt and Scarf Joints — Plate

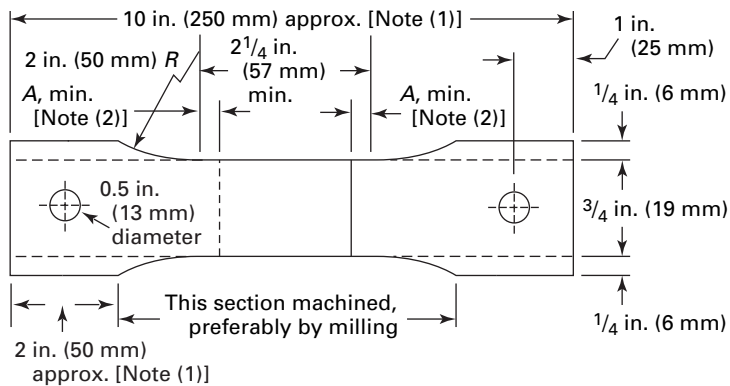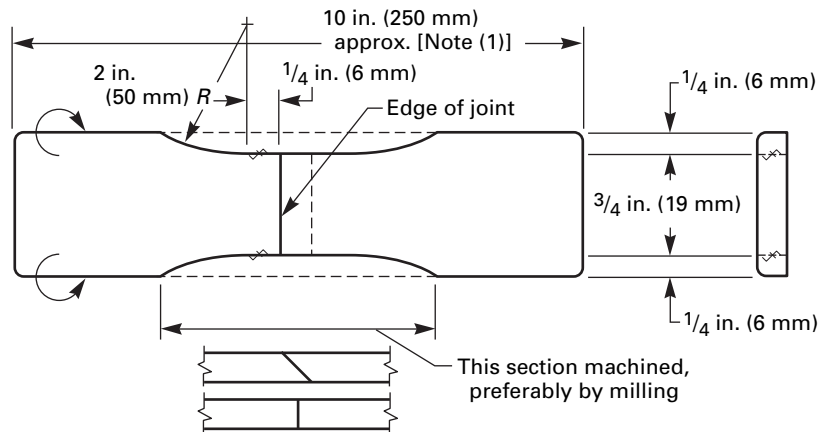



Alternate Pin-Loaded Specimen

NOTES:


(1) Length may vary to fit testing machine.

(2) A = greater of $\frac{1}{4}$ in. (6 mm) or $2T$

Figure QB-462.1(b)
Tension — Reduced Section for Butt, Lap, and Scarf Joints — Pipe

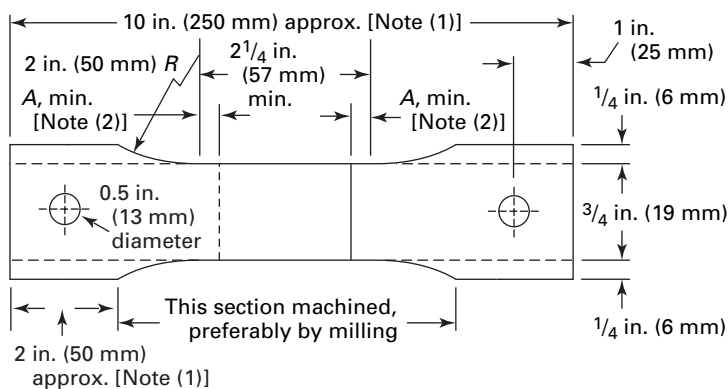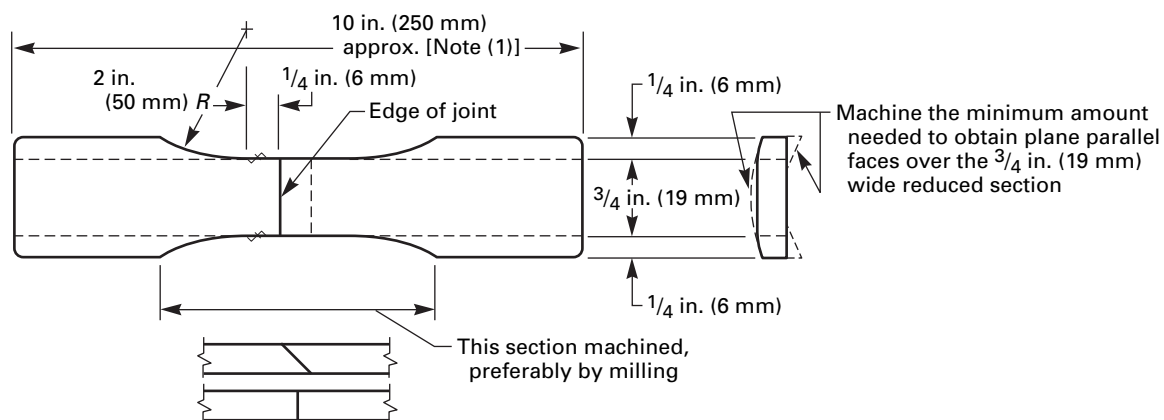

Alternate Pin-Loaded Specimen


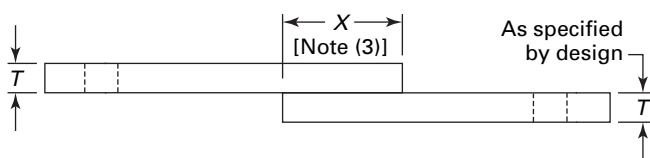


For Lap Joints


NOTES:

- (1) Length may vary to fit testing machine.
- (2) A = greater of $\frac{1}{4}$ in. (6 mm) or $2T$
- (3) X = test specimen overlap


Figure QB-462.1(c)
Tension — Reduced Section for Lap and Rabbet Joints — Plate

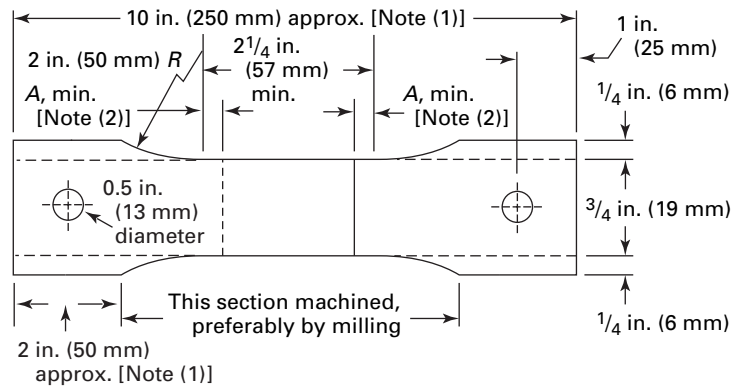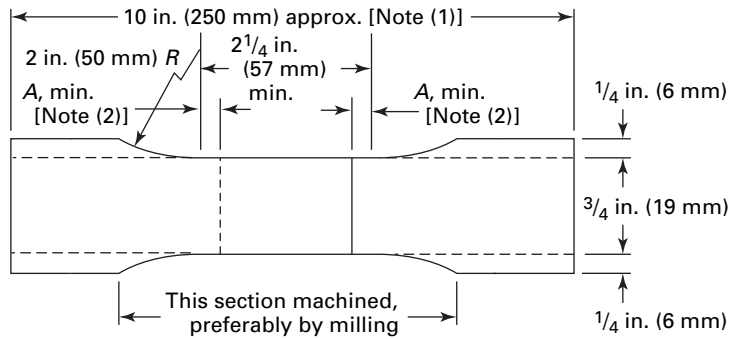

Alternate Pin-Loaded Specimen

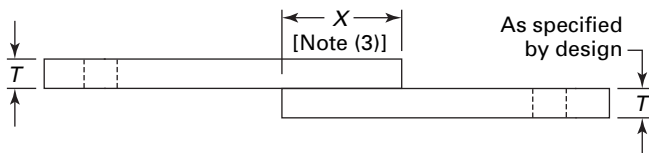

For Lap Joints

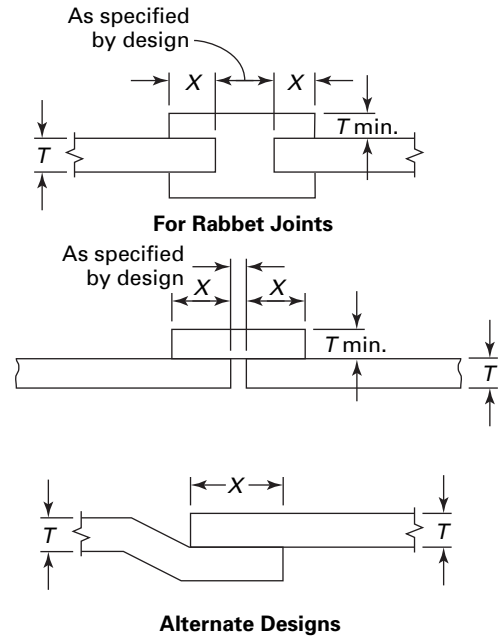

Alternate Designs

NOTES:

- (1) Length may vary to fit testing machine.
- (2) A = greater of $1/4$ in. (6 mm) or $2T$
- (3) X = test specimen overlap

Figure QB-462.1(e)
Tension — Full Section for Lap, Scarf, and Butt Joints — Small Diameter Pipe



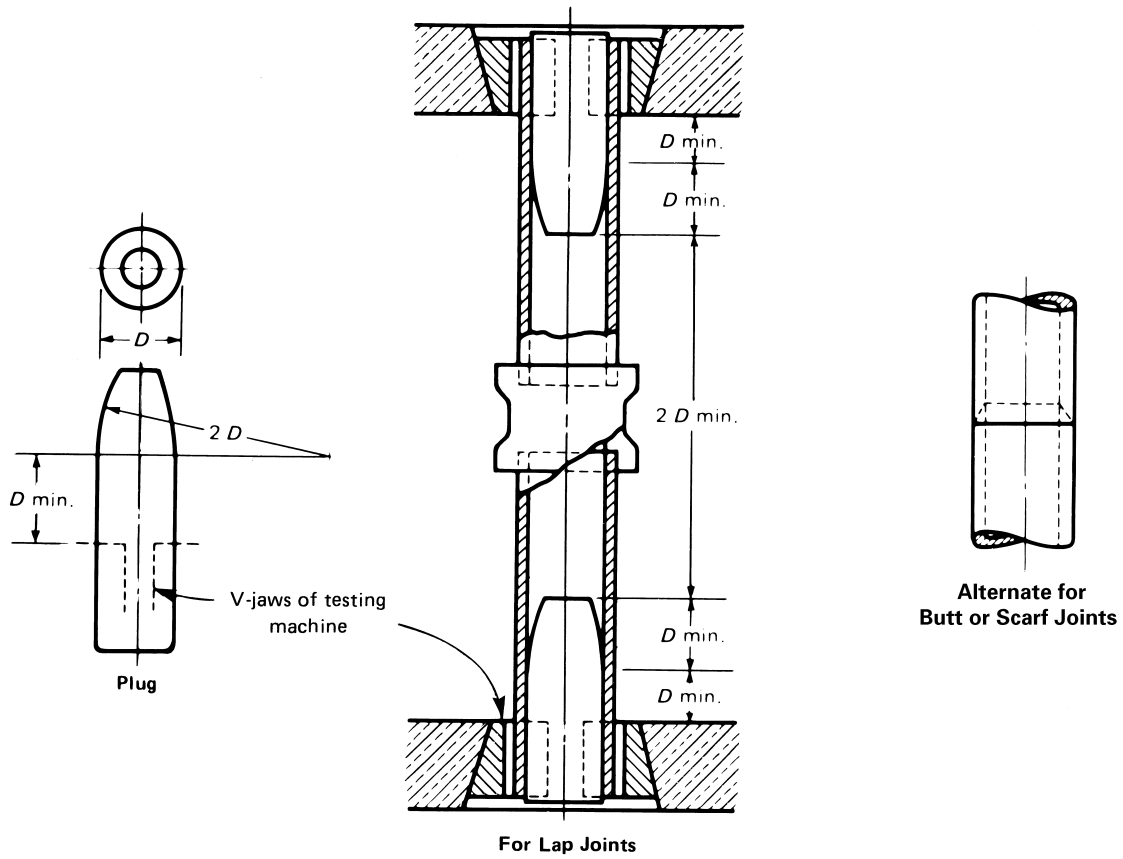


Figure QB-462.1(f)
Support Fixture for Reduced-Section Tension Specimens

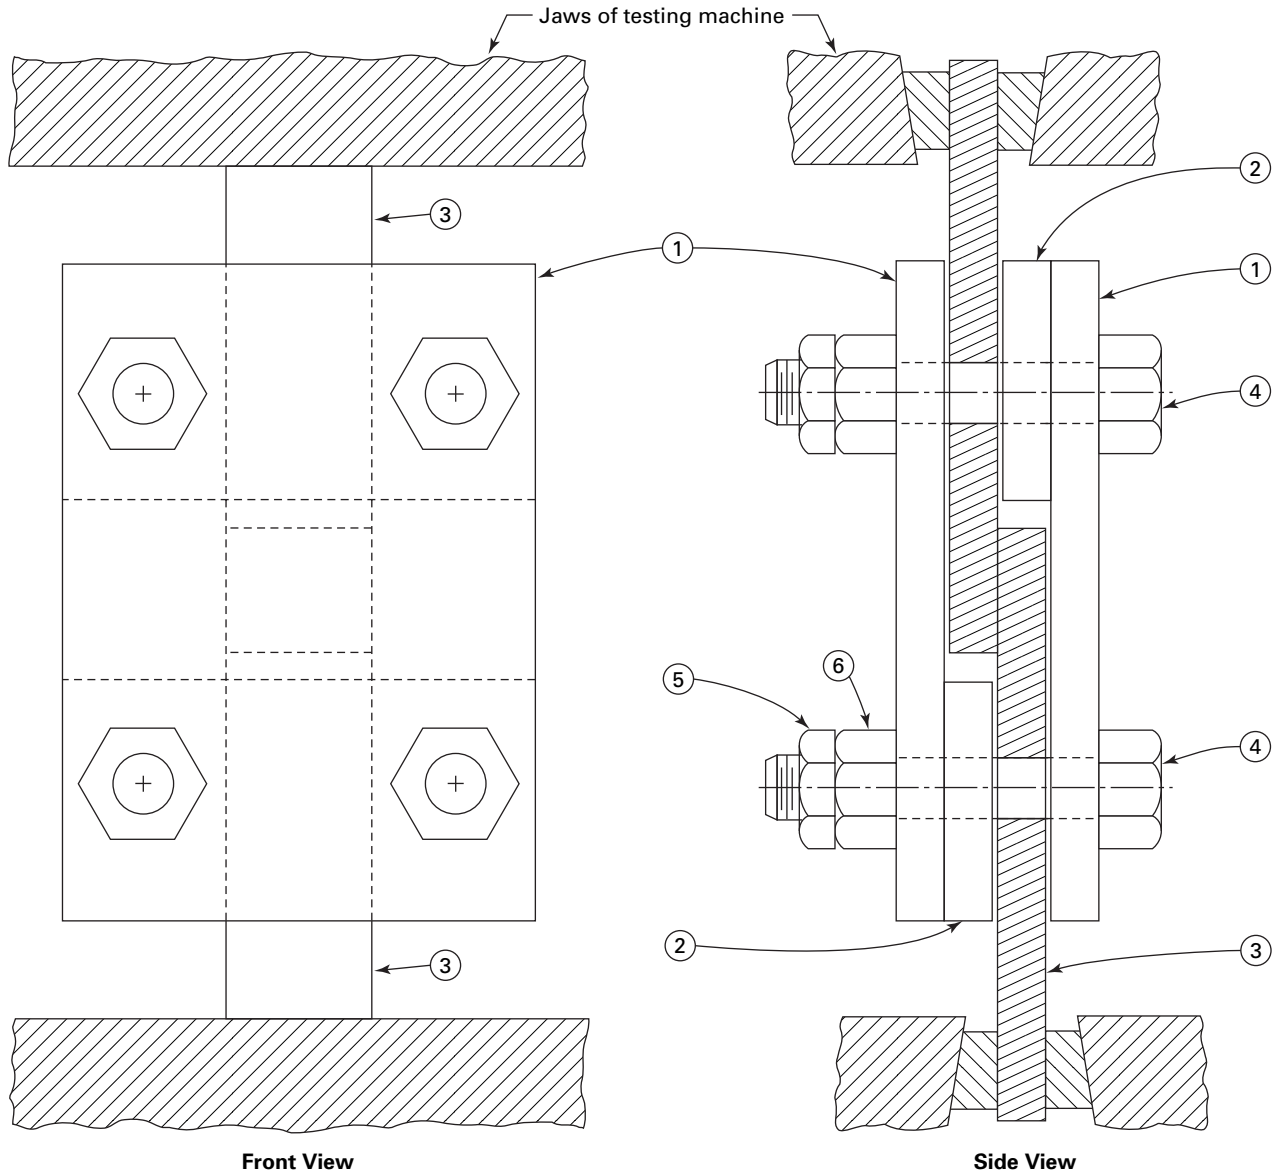

GENERAL NOTE: The restraining fixture is intended to provide a snug fit between the fixture and the contour of the tension specimen. The fixture shall be tightened, but only to the point where a minimum of 0.001 in. (0.03 mm) clearance exists between the sides of the fixture and the tension specimen.


Figure QB-462.2(a)
Transverse First and Second Surface Bends — Plate and Pipe

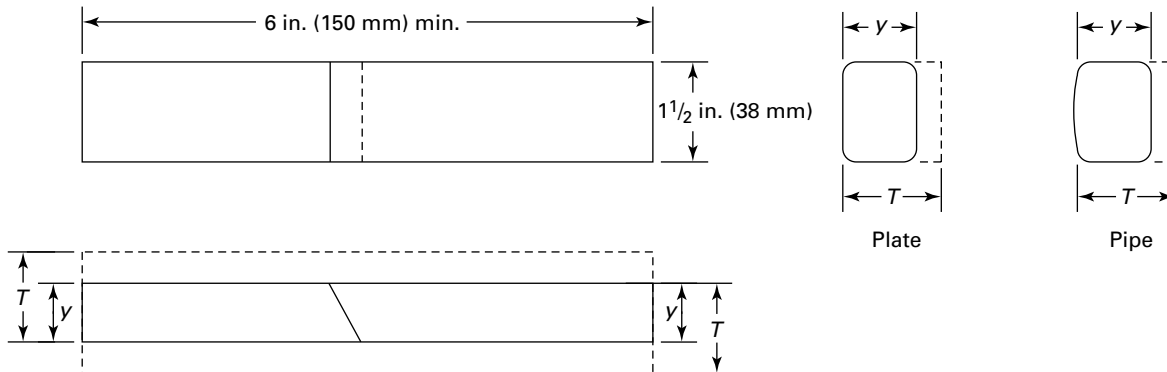

T , in. (mm)	y , in. (mm)
	All ferrous and nonferrous materials
$1/16 - 3/8$ (1.5–10)	T
$> 3/8$ (>10)	$3/8$ (10)

GENERAL NOTE: For the first surface bend specimens, machine from the second surface as necessary until the required thickness is obtained. For second surface bend specimens, machine from the first surface as necessary until the required thickness is obtained.


Figure QB-462.2(b)
Longitudinal First and Second Surface Bends — Plate

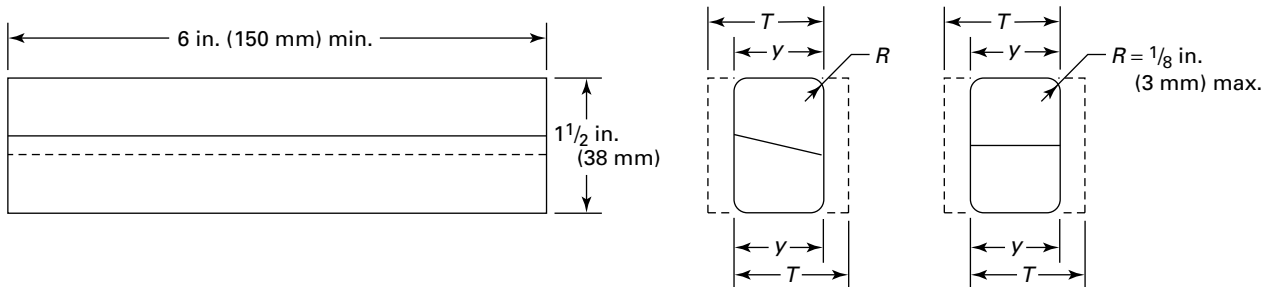

T , in. (mm)	y , in. (mm)
	All ferrous and nonferrous materials
$1/16 - 3/8$ (1.5–10)	T
$> 3/8$ (>10)	$3/8$ (10)

GENERAL NOTE: For the first surface bend specimens, machine from the second surface as necessary until the required thickness is obtained. For second surface bend specimens, machine from the first surface as necessary until the required thickness is obtained.

Figure QB-462.3
Lap Joint Peel Specimen

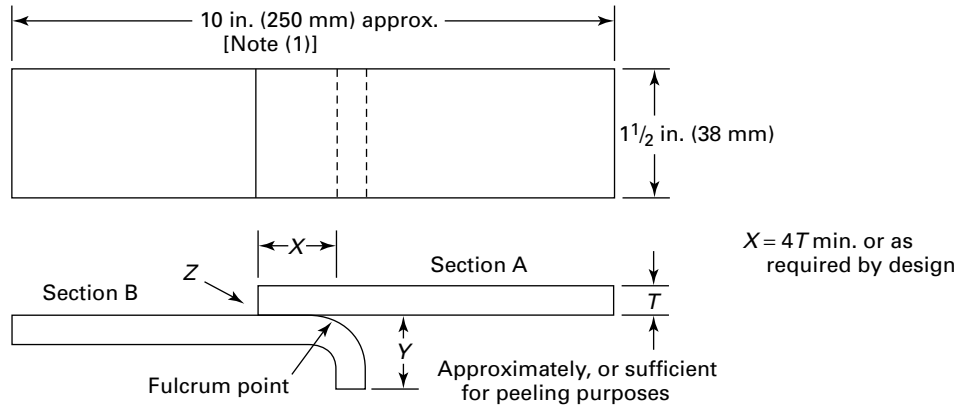

GENERAL NOTES:


- (a) Flange Y may be omitted from Section B when "peeling" is to be accomplished in a suitable tension machine.
(b) Specimen shall be brazed from side marked Z.

NOTE:

- (1) Length may vary to fit testing machine.


(13)

Figure QB-462.4
Lap Joint Section Specimen (see QB-181)

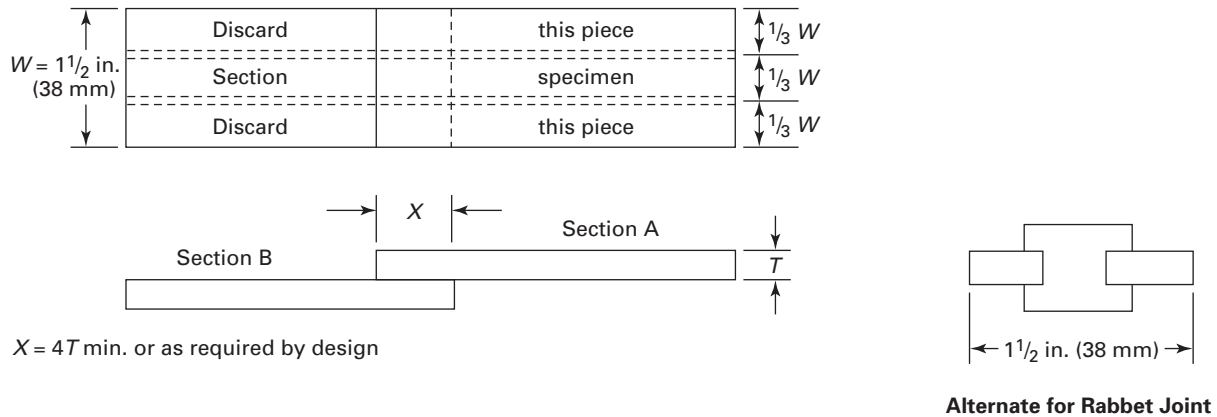


GENERAL NOTE: Lap or socket joint specimens in the pipe and tube shall be sectioned by cutting the pipe or tube specimen in half lengthwise, and the cut edges of at least one-half prepared and examined.

Figure QB-462.5
Workmanship Coupons

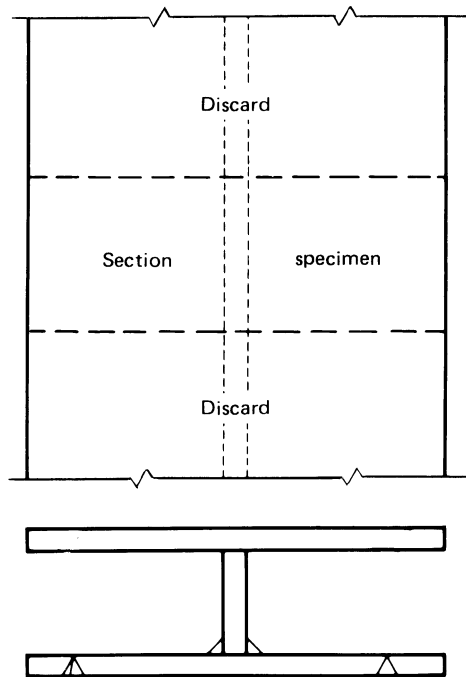


(a) Typical Stay or Partition Joint

[Note (1)]

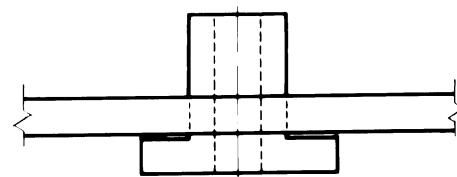

(b) Typical Spud Joint

[Note (2)]

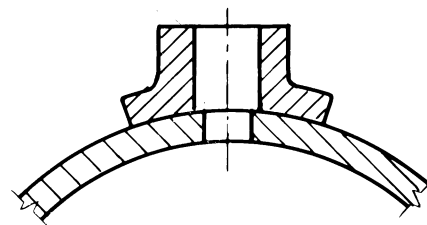

(c) Typical Saddle Joint Sectioned

[Note (2)]

NOTES:

- (1) Workmanship coupons shall be 10 in. (250 mm) in length or represent one-half the typical joint, whichever is less.
- (2) Circular coupons shall be sectioned in half, and one-half shall be used as the test specimen.

QB-463 ORDER OF REMOVAL**Figure QB-463.1(a)
Plates Procedure Qualification**

Discard	this piece
Reduced-section	tensile specimen
First surface	bend specimen
Second surface	bend specimen
Reduced-section	tensile specimen
First surface	bend specimen
Second surface	bend specimen
Discard	this piece

**Scarf Joint****Alternate Butt Joint****Figure QB-463.1(b)
Plates Procedure Qualification**

Discard	this piece
Reduced-section	tensile specimen
Reduced-section	tensile specimen
Reduced-section	tensile specimen
Reduced-section	tensile specimen
Discard	this piece

Longitudinal
first surface
bend specimen

Longitudinal
second surface
bend specimen



Longitudinal
first surface
bend specimen

Longitudinal
second surface
bend specimen

**Scarf Joint****Alternate Butt Joint**

Figure QB-463.1(c)
Plates Procedure Qualification

Discard				this piece
Reduced section tensile				specimen
Sectioning				specimen
Reduced section tensile				specimen
Sectioning				specimen
Discard				this piece

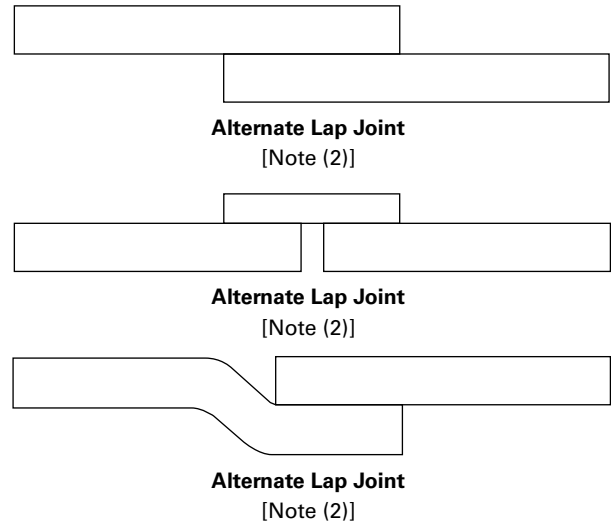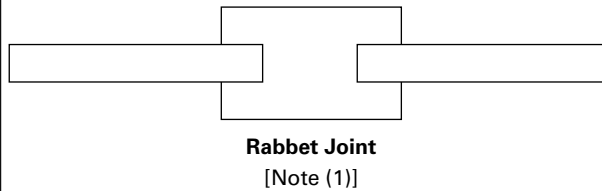

NOTES:

- (1) Required for rabbet joints.
- (2) The sectioning specimen in this view may be used as an alternate to sectioning the peel test specimens of QB-463.1(d) when the peel test cannot be used. This section test specimen should be approximately 1/2 in. (13 mm) wide.

Figure QB-463.1(d)
Plates Procedure Qualification

Discard		this piece
Peel test		specimen
Spare		section
Peel test		specimen
Discard		this piece




Lap Joint

[Note (1)]

NOTE:

(1) Required when peel test can be used.

Figure QB-463.1(e)
Pipe — Procedure Qualification






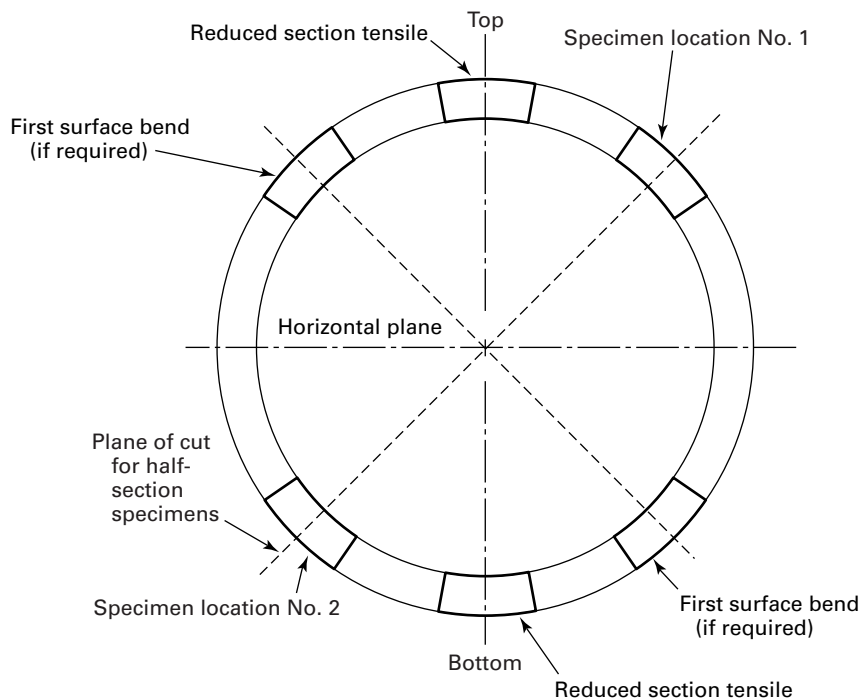


GENERAL NOTES:

- (a) Figure shown is for coupons over 3 in. (75 mm) O.D. Locations No. 1 and 2 are for:
 - (1) second surface specimens for butt and scarf joints
 - (2) peel or section specimens for lap joints
 - (3) section specimens for rabbet joints
- (b) For coupons 3 in. (75 mm) O.D. and smaller, two coupons shall be brazed and one specimen shall be removed from each coupon. If brazed in the horizontal flow position, the specimen shall be taken at specimen location No. 1. Alternatively, each coupon shall be cut longitudinally and the specimen shall consist of both sides of one half-section of each coupon.
- (c) When coupon is brazed in the horizontal flow position, specimens locations shall be as shown relative to the horizontal plane of the coupon, and for half-section specimens, plane of cut shall be oriented as shown relative to the horizontal plane of the coupon.
- (d) When both ends of a coupling are brazed, each end is considered a separate test coupon.

Figure QB-463.2(a)
Plates Performance Qualification

Discard		this piece
Sectioning		specimen
Discard		this piece
Sectioning		specimen
Discard		this piece

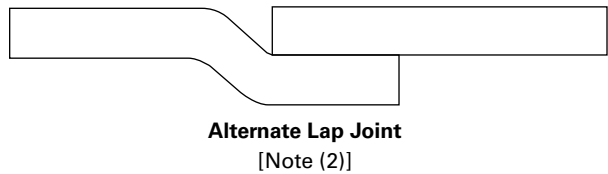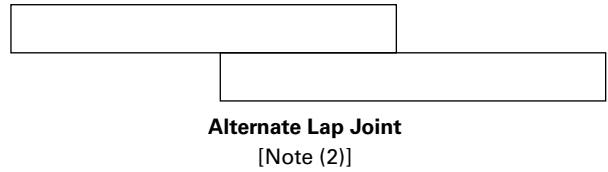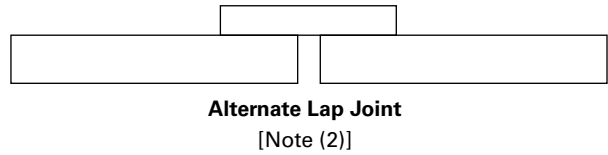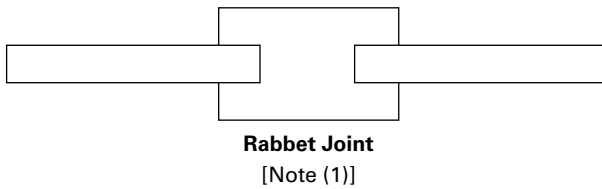

NOTES:

- (1) Required for rabbet joints.
- (2) The sectioning specimen in this view may be used as an alternate to sectioning the peel test specimens of QB-463.2 (b) when the peel test cannot be used. This section test specimen should be approximately $\frac{1}{2}$ in. (13 mm) wide.

Figure QB-463.2(b)
Plates Performance Qualification

Discard		this piece
Peel test		specimen
Spare		section
Peel test		specimen
Discard		this piece




Lap Joint

[Note (1)]

NOTE:

(1) Required when peel test can be used.

Figure QB-463.2(c)
Pipe Performance Qualification

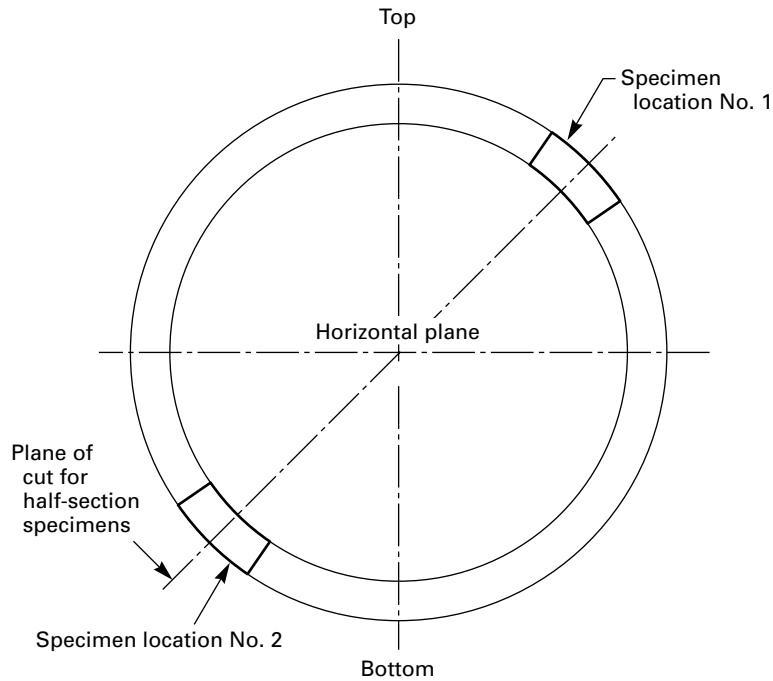


GENERAL NOTES:

- (a) For coupons over 3 in. (75 mm) O.D., one specimen shall be removed from each location shown.
- (b) For coupons 3 in. (75 mm) O.D. and smaller, two coupons shall be brazed and one specimen shall be removed from each coupon. If brazed in the horizontal flow position, the specimen shall be taken at specimen location No. 1. Alternatively, each coupon shall be cut longitudinally and the specimen shall be both sides of one half-section of each coupon.
- (c) When the coupon is brazed in the horizontal flow position, specimen locations shall be as shown relative to the horizontal plane of the coupon. For half-section specimens, plane of cut shall be oriented as shown relative to the horizontal plane of the coupon.
- (d) When both ends of a coupling are brazed, each end is considered a separate test coupon.


QB-466 TEST JIGS

Figure QB-466.1
Guided-Bend Jig

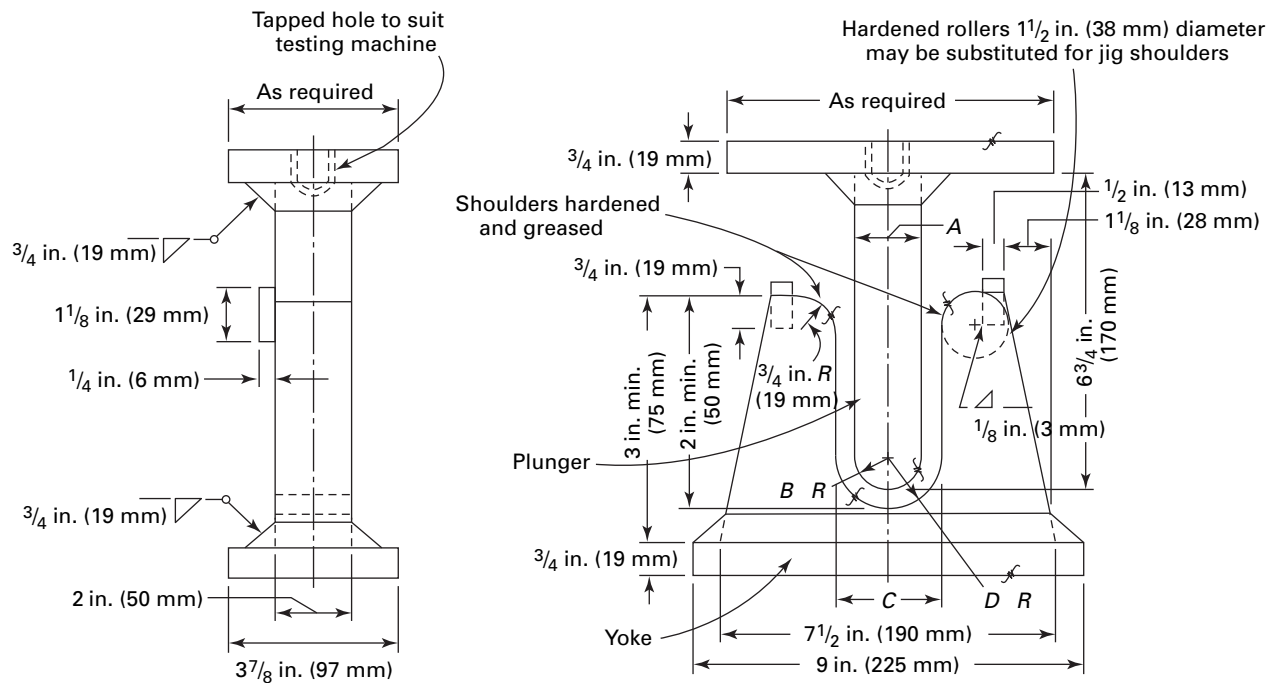

Thickness of Specimen, in. (mm)	A, in. (mm)	B, in. (mm)	C, in. (mm)	D, in. (mm)
$\frac{3}{8}$ (10)	$1\frac{1}{2}$ (38)	$\frac{3}{4}$ (19)	$2\frac{3}{8}$ (60)	$1\frac{3}{16}$ (30)
t	4t	2t	6t + 3.2	3t + 1.6

Figure QB-466.2
Guided-Bend Roller Jig

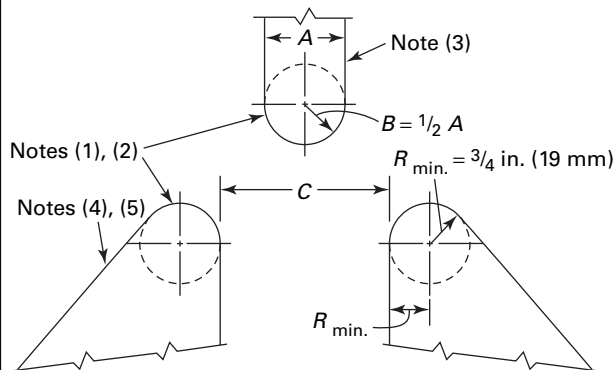


Thickness of Specimen, in. (mm)	A, in. (mm)	B, in. (mm)	C, in. (mm)
$\frac{3}{8}$ (10)	$1\frac{1}{2}$ (38)	$\frac{3}{4}$ (19)	$2\frac{3}{8}$ (60)
t	4t	2t	$6t + \frac{1}{8}$ (3)

GENERAL NOTE: The braze joint in the case of a transverse bend specimen shall be completely within the bend portion of the specimen after testing.

NOTES:

- (1) Either hardened and greased shoulders or hardened rollers free to rotate shall be used.
- (2) The shoulders of rollers shall have a minimum bearing surface of 2 in. (50 mm) for placement of the specimen. The rollers shall be high enough above the bottom of the jig so that the specimens will clear the rollers when the ram is in the low position.
- (3) The ram shall be fitted with an appropriate base and provision made for attachment to the testing machine, and shall be of a sufficiently rigid design to prevent deflection and misalignment while making the bend test. The body of the ram may be less than the dimensions shown in column A.
- (4) If desired, either the rollers or the roller supports may be made adjustable in the horizontal direction so that specimens of t thickness may be tested on the same jig.
- (5) The roller supports shall be fitted with an appropriate base designed to safeguard against deflection or misalignment and equipped with means for maintaining the rollers centered midpoint and aligned with respect to the ram.

Figure QB-466.3
Guided-Bend Wrap Around Jig

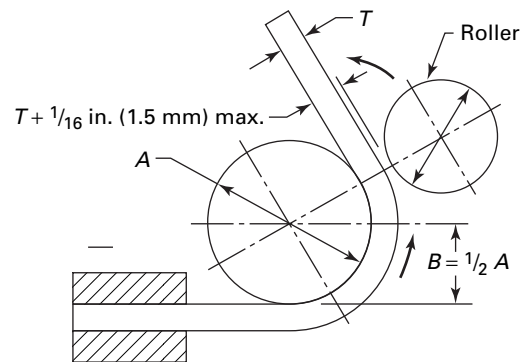

Thickness of Specimen, in. (mm)	A, in. (mm)	B, in. (mm)
$\frac{3}{8}$ (10)	$1\frac{1}{2}$ (38)	$\frac{3}{4}$ (19)
t	4t	2t

GENERAL NOTES:

- (a) Dimensions not shown are the option of the designer. The essential consideration is to have adequate rigidity so that the jig parts will not spring.
- (b) The specimen shall be firmly clamped on one end so that there is no sliding of the specimen during the bending operation.
- (c) Test specimens shall be removed from the jig when the outer roll has been removed 180 deg from the starting point.

(13)

PART QF PLASTIC FUSING

ARTICLE XXI PLASTIC FUSING GENERAL REQUIREMENTS

QF-100 SCOPE

The rules in this Part apply to the preparation and qualification of the fusing procedure specification (FPS), and the performance qualification of fusing machine operators.

QF-101 FUSING PROCEDURE SPECIFICATION (FPS)

A fusing procedure specification (FPS) used by an organization that will have responsible operational control of production fusing shall be an FPS that has been qualified by that organization in accordance with [Article XXII](#), or it shall be a standard fusing procedure specification (SFPS) as defined in [QF-201.2](#).

The FPS or SFPS specify the “variables” (including ranges, if any) under which fusing must be performed. The FPS prepared by the organization and the SFPS shall address the applicable fusing process variables, both essential and nonessential, as provided in [Article XXII](#) for production fusing.

QF-102 FUSING PERFORMANCE QUALIFICATION (FPQ)

Fusing machine operator performance qualification is intended to verify the ability of the fusing machine operator to produce a soundly fused joint when following a qualified FPS. The fusing machine operator performance qualification record (FPQ) documents the performance test of the fusing machine operator, and the results of the required mechanical tests.

QF-103 RESPONSIBILITY

QF-103.1 Fusing. Each organization shall conduct the tests required in this Section to qualify the FPS and the performance of the fusing machine operators who apply these procedures. Alternatively, an organization may use an SFPS under the provisions of [QF-201.2](#). The

organization shall perform and document the tests required by this Article to qualify the performance of fusing machine operators for fusing operations.

QF-103.2 Records. Each organization shall maintain a record of the results of the mechanical testing performed to satisfy the requirements for FPS and fusing machine operator performance qualifications.

QF-110 FUSED JOINT ORIENTATION

Orientation categories for fused joints are illustrated in [Figure QF-461.1](#).

QF-120 TEST POSITIONS

Fused joints may be made in test coupons oriented in any of the positions shown in [Figure QF-461.2](#).

QF-130 DATA ACQUISITION AND EVALUATION

QF-131 DATA ACQUISITION RECORD REQUIREMENTS

The following fusing variables shall be recorded for each fused test joint:

- (a) heater surface temperature immediately before inserting the heater plate
- (b) gauge pressure during the initial heat cycle
- (c) gauge pressure and elapsed time during the heat-soak cycle
- (d) heater removal (dwell) time
- (e) gauge pressure and elapsed time during the fusing/cool cycle
- (f) drag pressure
- (g) joint configuration
- (h) pipe diameter and wall thickness
- (i) type of HDPE material (specification and classification) and manufacturer

(j) FPS used, operator identification, time, date, and fusing machine identification

QF-132 DATA ACQUISITION RECORD REVIEW

The data acquisition record for each fused test joint shall be compared to the FPS after completion. QF-485 provides a suggested format to document the data acquisition record review. The reviewer shall verify the following:

- (a) all data required by QF-131 was recorded
- (b) interfacial fusing pressure was within the FPS range
- (c) heater surface temperature recorded was within the FPS range
- (d) butt-fusing pressure applied during the fusing/cool cycle was correctly calculated to include the drag pressure, fell within the FPS range for the applicable size (e.g., pipe diameter), and agrees with the recorded hydraulic fusing pressure
- (e) butt-fusing pressure was reduced to a value less than or equal to the drag pressure at the beginning of the heat soak cycle
- (f) fusing machine was opened at the end of the heat soak cycle, the heater was removed, and the ends brought together at the fusing pressure within the time frame specified by the FPS
- (g) cooling time at butt-fusing pressure met the minimum time specified by the FPS

If the recorded data is outside the limits of the FPS, the joint is unacceptable.

QF-140 EXAMINATIONS AND TESTS

QF-141 VISUAL EXAMINATION

(a) All fused joints shall receive a visual examination of all accessible surfaces of the fused joint.

(b) *Acceptance Criteria* (see Figure QF-462 for evaluation examples)

(1) There shall be no evidence of cracks or incomplete fusing.

(2) Joints shall exhibit proper fused bead configuration.

(3) Variations in upset bead heights on opposite sides of the cleavage and around the circumference of fused pipe joints are acceptable.

(4) The apex of the cleavage between the upset beads of the fused joint shall remain above the base material surface.

(5) The data record for the FPS or fusing machine operator performance qualification test shall be reviewed and compared to the FPS to verify observance of the specified variables applied when completing the fused test joint.

(6) Fused joints shall not display visible angular misalignment, and outside diameter mismatch shall be less than 10% of the nominal wall thickness.

(c) Visual examination results shall be recorded on the PQR or FPQ.

QF-142 ELEVATED TEMPERATURE SUSTAINED PRESSURE TESTS FOR PIPE

Elevated temperature sustained pressure tests shall be performed in accordance with ASTM D3035-08.

QF-143 BEND TESTS

These tests are designed to impart bending stresses to a butt-fused plastic specimen to evaluate the soundness of the fused joint.

QF-143.1 Reverse-Bend Test (RBT)

(a) Reverse-bend test specimens shall be cut to a minimum width of 1.5 times the test coupon thickness for testing and removed as shown in Figure QF-463(a).

(b) One test specimen shall be bent to place the inside surface of the joint in tension, and the other test specimen shall be bent to place the outside surface of the joint in tension.

(c) The bending process shall ensure the ends of the specimens are brought into contact with one another.

(d) Testing shall be in accordance with ASTM F2620-09, Appendix X4.

(e) Test results shall be recorded on the PQR.

QF-143.2 Guided Side-Bend Test (GSBT)

QF-143.2.1 Significance and Use. This test is designed to impart a bending load on a specimen from a butt fusion joint to evaluate its soundness. It is intended for butt fusion joints of HDPE pipe with a wall thickness greater than 1.0 in. (25 mm).

QF-143.2.2 Test Specimens

(a) Test specimens shall be removed from the fused test coupon with the upset bead remaining on the outside and inside surfaces. A strip having the full thickness of the test coupon and measuring approximately 1 in. (25 mm) wide and 18 in. (450 mm) long shall be removed along the longitudinal axis of the test coupon, with the joint located in the approximate center of the strip. See Figure QF-463(b).

(b) Plane or machine the width down to 0.50 in. \pm 0.03 in. (13 mm \pm 0.75 mm) with a smooth finish on both sides. See Figure QF-463(c).

QF-143.2.3 Test Conditions

(a) *Test Temperature.* Conduct the GSBT at a temperature 60°F to 80°F (16°C to 27°C).

(b) *Test speed.* The elapsed time of the test shall be between 30 sec and 60 sec.

QF-143.2.4 Guided Side-Bend Test Procedure

QF-143.2.4.1 Jigs. Test specimens shall be bent in a test jig consisting of a fixed member with two cross bars to support the specimen while force is applied. The

hydraulic ram, used to supply the bending force, is also attached to the jig and has a ram attached to the end of the cylinder. See Figure QF-463(d).

QF-143.2.4.2 Bend Procedure. Position the side-bend test specimen with the butt fusion joint in the center of the jig between the support mandrels. Position the ram in the center of the fusion bead on the test specimen. Move the ram slowly until it makes contact with the test specimen and is positioned in line with the fusion bead. Begin to apply the bending force and deflect the side-bend test specimen. The test is complete when the test specimen is bent to an angle of $60 \text{ deg} \pm 10 \text{ deg}$ between the inside surfaces of the specimen or until failure occurs. See Figure QF-463(d).

QF-143.3 Acceptance Criteria. The test specimen shall not break or exhibit cracking or fractures on the convex (outer) surface at the fusion interface during this test.

QF-144 HIGH-SPEED TENSILE IMPACT TEST (HSTIT)

This test method is designed to impart tensile impact energy to a butt-fused PE pipe specimen to evaluate its ductility.

QF-144.1 Test Specimens

(a) Test specimens shall be removed from the fused test coupon with the upset bead remaining on the outside diameter and inside diameter surfaces. Specimens for test coupon thicknesses less than or equal to 2 in. (50 mm) shall include the full wall thickness of the fused joint. Specimens for test coupon thicknesses 2 in. (50 mm) and greater may be cut into approximately equal strips between 1 in. (25 mm) and 2.5 in. (64 mm) wide for testing with each segment tested individually such that the full cross section is tested.

(b) Test specimens shall be prepared by machining to achieve the dimensions given in Figure QF-464, with the upset beads remaining intact.

(c) A smooth surface free of visible flaws, scratches, or imperfections shall remain on all faces of the reduced area with no notches, gouges, or undercuts exceeding the dimensional tolerances given in ASTM F2634-07. Marks left by coarse machining operations shall be removed, and the surfaces shall be smoothed with abrasive paper (600 grit or finer) with the sanding strokes applied parallel to the longitudinal axis of the test specimen.

(d) Mark the test specimens in the area outside the hole with the applicable specimen identification using a permanent indelible marker of a contrasting color, or an etching tool.

(e) Condition the test specimens at $73^{\circ}\text{F} \pm 4^{\circ}\text{F}$ ($23^{\circ}\text{C} \pm 2^{\circ}\text{C}$) for not less than 1 hr just prior to conducting the test.

QF-144.2 Test Conditions

(a) *Test Temperature.* Conduct the high speed impact test at a temperature of $73^{\circ}\text{F} \pm 4^{\circ}\text{F}$ ($23^{\circ}\text{C} \pm 2^{\circ}\text{C}$) unless otherwise specified.

(b) *Test Speed.* The speed of testing shall be in accordance with Table QF-144.2 with a testing speed tolerance of $+0.5 \text{ in./sec}$ to -1 in./sec ($+13 \text{ mm/sec}$ to -25 mm/sec).

Table QF-144.2
Testing Speed Requirements

Wall Thickness	Testing Speed
$\leq 1.25 \text{ in. (32 mm)}$	6 in./sec (150 mm/sec)
$> 1.25 \text{ in. (32 mm)}$	4 in./sec (100 mm/sec)

QF-144.3 Test Procedure

(a) Set up the machine and set the speed of testing to the rate specified in QF-144.2(b).

(b) Pin each specimen in the clevis tooling of the testing machine, aligning the long axis of the specimen and the tooling with the pulling direction of the test machine.

(c) Testing shall be performed in accordance with ASTM F2634.

(d) Evaluate the test specimen fracture to determine the mode of failure, and note the results in the test record and on the PQR.

QF-144.4 Test Record. The HSTIT shall be documented by preparing a test record that includes the following information:

- (a) testing speed applied
- (b) testing temperature observed
- (c) specimen dimension verification
- (d) test machine calibration data
- (e) test specimen identification
- (f) test date
- (g) test operator identification
- (h) testing failure mode and acceptance/rejection
- (i) test equipment identification

QF-144.5 Acceptance Criteria. Failure mode shall be ductile, with no evidence of brittle failure at the fusion interface. See Figure QF-465, illustrations (a) through (d), for evaluation examples.

ARTICLE XXII

FUSING PROCEDURE QUALIFICATIONS

QF-200 GENERAL

Each organization shall prepare a written FPS as defined in [QF-201.1](#), or assume responsibility for an SFPS as defined in [QF-201.2](#).

QF-201 PROCEDURE QUALIFICATION

QF-201.1 Fusing Procedure Specification (FPS)

(a) *Fusing Procedure Specification (FPS)*. A FPS is a written qualified fusing procedure prepared to provide direction to the fusing machine operator for making production fused joints.

(b) *Contents of the FPS*. The completed FPS shall address all of the essential and nonessential variables for each fusing process used in the FPS. The essential and nonessential variables for fusing are listed in [Table QF-254](#). The organization may include any other information in the FPS that may be helpful in making a fused joint.

(c) Changes in the documented essential variables require requalification of the FPS.

QF-201.2 Standard Fusing Procedure Specification (SFPS)

(a) *Standard Fusing Procedure Specification (SFPS)*. A fusing procedure specification that contains acceptable polyethylene fusing variables based on standard industry practice and testing as reported in the Plastic Pipe Institute (PPI), Report TR-33-06, or ASTM F2620-09, Standard Practice for Heat Fusion Joining of Polyethylene Pipe and Fittings. A SFPS may be used for production fusing by organizations without further qualification.

(b) *Contents of the SFPS*. The SFPS shall address all of the essential and nonessential variables listed in [QF-220](#). The organization may include any additional information in the SFPS that may be helpful in making a fused joint.

(c) Changes in the documented parameters of a SFPS beyond the limits specified in [QF-220](#) shall require the qualification of an FPS.

QF-201.3 Format of the FPS or SFPS. The information required to be included in the FPS or SFPS may be in any format, written or tabular, to fit the needs of each organization, provided all essential and nonessential variables outlined in [QF-250](#), or the parameters specified in [QF-220](#) as applicable, are addressed. [Form QF-482](#) has been provided as a guide for preparing the FPS or SFPS.

QF-201.4 Availability of the FPS or SFPS. The FPS or SFPS used for production fusing shall be available for reference and reviewed by the Inspector when fused joints are made.

QF-201.5 Each organization who qualifies a FPS shall prepare a procedure qualification record (PQR) that is defined as follows:

(a) *Procedure Qualification Record (PQR)*. A record of the range of essential variables documented during the fusing of the test coupon(s) and the results of the required visual and mechanical tests performed.

(b) *Contents of the PQR*. The completed PQR shall document the ranges for all essential variables listed in [QF-250](#) during the fusing of the test coupon(s). Nonessential variables observed during the fusing of the test coupon may be recorded at the organization's option.

The PQR shall be certified by the organization to be a true and accurate record of the variables recorded during the fusing of the test coupon(s) and the required examinations and tests specified in [QF-140](#).

(c) *Changes to the PQR*. Changes to the PQR are not permitted except for documented editorial corrections or those utilizing addenda. An organization may be permitted to fuse materials other than those used in the FPS qualification, when the alternative materials are assigned to a material grouping in [QF-420](#) whose fusing properties are considered essentially identical. Additional information may be incorporated into a PQR at a later date, provided the information is substantiated as having been associated with the original qualification conditions by lab records or similar documented evidence. All changes to a PQR require recertification (including date) by the organization.

(d) *Format of the PQR*. The information required to be in the PQR may be in any format, written or tabular, to fit the needs of each organization, provided all essential variables outlined in [QF-250](#) are included. The types and number of tests, and their results shall be reported on the PQR. [Form QF-483](#) has been provided as a guide for preparing the PQR. When required, additional sketches or information may be attached or referenced to record the required variables.

(e) *Availability of the PQR*. PQRs supporting an FPS to be used in production fusing operations shall be available for review by the inspector.

(f) *Multiple FPSs with One PQR/Multiple PQRs with One FPS*. Several FPSs may be prepared from the qualification test data recorded on a single PQR. A single FPS may

encompass the range of qualified essential variables represented by multiple PQRs supporting the qualified combination and range of essential variables.

QF-202 TYPE OF TESTS REQUIRED

QF-202.1 Mechanical Tests

QF-202.1.1 High-speed tensile impact test specimens (HSTIT) shall be prepared in accordance with [Figure QF-464](#) and tested in accordance with [QF-144.1](#). The minimum number of specimens required to be tested shall be as follows:

(a) for pipe specimens less than 4 NPS (100 mm): not less than two specimens removed from fused pipe test coupons at intervals of approximately 180 deg apart

(b) for pipe specimens 4 NPS (100 mm) and greater: not less than four specimens removed from fused pipe test coupons at intervals approximately 90 deg apart

(c) other product forms: not less than two specimens removed from fused test coupons

QF-202.1.2 Elevated temperature sustained pressure tests shall be conducted in accordance with [QF-142](#).

QF-202.1.3 If any test specimen required by [QF-202.1](#) fails to meet the applicable acceptance criteria, the test coupon shall be considered unacceptable.

(a) When it can be determined that the cause of failure is not related to incorrectly selected or applied fusing variables, additional test specimens may be removed as close as practicable to the original specimen location to replace the failed test specimens. If sufficient material is not available, another test coupon may be fused utilizing the original fusing parameters.

(b) When it has been determined that the test failure was caused by one or more incorrectly selected or applied essential variable(s), a new test coupon may be fused with appropriate changes to the variable(s) that were determined to be the cause for test failure.

(c) When it is determined that the test failure was caused by one or more fusing conditions other than essential variables, a new set of test coupons may be fused with the appropriate changes to the fusing conditions that were determined to be the cause for test failure. If the new test passes, the fusing conditions that were determined to be the cause for the previous test failure shall be addressed by the organization to ensure that the required properties are achieved in all fused production joints.

QF-202.2 Testing Procedure to Qualify the FPS

QF-202.2.1 Polyethylene Pipe Butt Fusing

(a) For pipe having a wall thickness less than or equal to 2 in. (50 mm), one set of test coupons shall be prepared using any thickness of pipe less than or equal to 2 in. (50 mm) but not less than one-half the thickness of the pipe to be fused in production.

(b) For pipe having wall thickness greater than 2 in. (50 mm), one set of test coupons shall be prepared using pipe of at least 2 in. (50 mm) thickness but not less than one-half the maximum thickness to be fused in production.

(c) Butt-fusing joint coupons shall be prepared in accordance with the FPS using the following combinations of heater temperature ranges and interfacial pressure ranges:

(1) high heater surface temperature and high interfacial pressure, five joints

(2) high heater surface temperature and low interfacial pressure, five joints

(3) low heater surface temperature and high interfacial pressure, five joints

(4) low heater surface temperature and low interfacial pressure, five joints

(d) Each fused joint shall be subject to visual examination per [QF-141](#).

(e) Two fused joints of each combination shall be evaluated using the elevated temperature sustained pressure tests for pipe specified in [QF-142](#).

(f) Three fused joints of each combination described in (c) shall be evaluated using the high speed tensile impact test (HSTIT) specified in [QF-144](#).

QF-203 LIMITS OF QUALIFIED POSITIONS FOR PROCEDURES

Unless otherwise specified by the fusing variables ([QF-250](#)), a procedure qualified in any position shown in [Figure QF-461.2](#) qualifies for all positions. A fusing machine operator making and passing the FPS qualification test is qualified only for the position tested (See [QF-301.2](#)).

QF-220 STANDARD FUSING PROCEDURE SPECIFICATION (SFPS)

QF-221 SFPS FOR POLYETHYLENE FUSING

QF-221.1 Pipe Butt Fusing of Polyethylene. When the fusing procedure is limited to the following parameters, procedure qualification testing is not required. If the organization deviates from the conditions listed below, procedure qualification testing in accordance with [QF-202.2](#) is required.

(a) The pipe material is limited to PE 2708, PE 3608, and PE 4710.

(b) The axis of the pipe is limited to the horizontal position ± 45 deg.

(c) The pipe ends shall be faced to establish clean, parallel mating surfaces that are perpendicular to the pipe centerline on each pipe end, except for mitered joints. When the ends are brought together at the drag pressure, there shall be no visible gap.

(d) For mitered butt fusion joints, the pipe faces shall be at the specific angle to produce the mitered joint. When the ends are brought together at the drag pressure, there shall be no visible gap.

(e) The external surfaces of the pipe are aligned to within 10% of the pipe wall thickness.

(f) The drag pressure shall be measured and recorded. The theoretical fusing pressure shall be calculated so that an interfacial pressure of 60 psi to 90 psi (0.41 MPa to 0.62 MPa) is applied to the pipe ends. The butt-fusing gauge pressure set on the fusing machine shall be the theoretical fusing pressure plus drag pressure.

(g) The heater surface temperature shall be 400°F to 450°F (200°C to 230°C).

(h) The initial heating shall begin by inserting the heater into the gap between the pipe ends and applying the butt-fusing pressure until an indication of melt is observed around the circumference of the pipe. When observed, the pressure shall be reduced to drag pressure and the fixture shall be locked in position so that no outside force is applied to the joint during the heat soak cycle.


(i) The ends shall be held in place until the minimum bead size is formed between the heater faces and the pipe ends, as shown in Figure QF-221.1. For 14 NPS (350 mm) and larger pipe sizes, the minimum heat soak time of 4.5 min per inch (25 mm) of pipe wall thickness shall be obtained.

(j) After the proper bead size is formed, the machine shall be opened and the heater removed. The pipe end surfaces shall be smooth, flat, and free of contamination. The pipe ends shall be brought together and the butt-fusing pressure reapplied.

(k) The maximum time from separating the pipe ends from the heater until the pipe ends are pushed together shall not exceed the time given in Table QF-221.2.

(l) The butt-fusing pressure shall be maintained until the joint has cooled, after which the pipe may be removed from the joining machine. The minimum cool time at the butt-fusing pressure shall be 11 min per inch (26 sec per millimeter) of pipe wall thickness of the thicker member.

Figure QF-221.1
Required Minimum Melt Bead Size

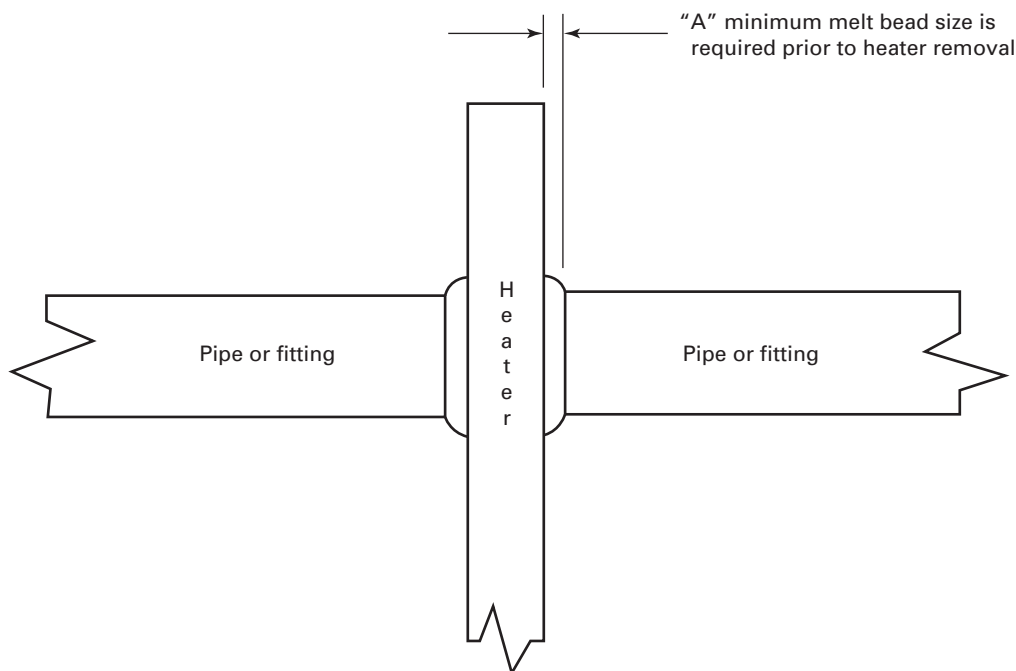

Pipe (O.D.), in. (mm)	"A" Minimum Melt Bead Size, in. (mm)
< 2.37 (60)	$\frac{1}{32}$ (1)
≥ 2.37 (60) to ≤ 3.5 (89)	$\frac{1}{16}$ (1.5)
> 3.5 (89) to ≤ 8.63 (219)	$\frac{3}{16}$ (5)
> 8.63 (219) to ≤ 12.75 (324)	$\frac{1}{4}$ (6)
> 12.75 (324) to ≤ 24 (610)	$\frac{3}{8}$ (10)
> 24 (610) to ≤ 36 (900)	$\frac{7}{16}$ (11)
> 36 (900) to ≤ 65 (1625)	$\frac{9}{16}$ (14)

Table QF-221.2
Maximum Heater Plate Removal Time for Pipe-to-Pipe Fusing

Field Applications	
Pipe Wall Thickness, in. (mm)	Maximum Heater Plate Removal Time, sec
0.17 to 0.36 (4 to 9)	8
> 0.36 to 0.55 (> 9 to 14)	10
> 0.55 to 1.18 (> 14 to 30)	15
> 1.18 to 2.5 (> 30 to 64)	20
> 2.5 to 4.5 (> 64 to 114)	25
> 4.5 (> 114)	30
Fabrication Shop	
1.18 to 2.5 (30 to 64)	40
> 2.5 to 4.5 (> 64 to 114)	50
> 4.5 (> 114)	60

QF-250 FUSING VARIABLES

QF-251 TYPES OF VARIABLES FOR FUSING PROCEDURE SPECIFICATIONS (FPS)

These variables (listed for each fusing process starting in [Table QF-254](#)) are categorized as essential or nonessential variables. The "Brief of Variables" listed in the tables are for reference only. See the complete variable description in [Article XXIV, QF-400](#).

QF-252 ESSENTIAL VARIABLES

Essential variables are those that will affect the mechanical properties of the fused joint, if changed, and require

requalification of the FPS when any change exceeds the specified limits of the values recorded in the FPS for that variable.

QF-253 NONESSENTIAL VARIABLES

Nonessential variables are those that will not affect the mechanical properties of the fused joint, if changed, and do not require requalification of the FPS when changed.

Table QF-254
Fusing Variables Procedure Specification
Polyethylene Pipe Butt Fusing

Paragraph		Brief of Variables	Essential	Nonessential
QF-402 Joints	.1	ϕ Joint type	X	
	.2	ϕ Pipe surface alignment	X	
QF-403 Material	.1	ϕ PE	X	
	.3	ϕ Wall thickness	X	
	.4	ϕ Cross-sectional area		X
QF-404 Position	.1	ϕ Position	X	
QF-405 Thermal Conditions	.1	ϕ Heater surface temperature	X	
	.2	ϕ Interfacial pressure	X	
	.3	Decrease in melt bead width	X	
	.4	Increase in heater removal time	X	
	.5	Decrease in cool-down time	X	
QF-406 Equipment	.1	ϕ Fusing machine manufacturer		X
QF-407 Technique	.1	ϕ Shop to field, or vice versa		X

GENERAL NOTE: Table QF-254 is applicable to fusing procedure specifications (FPSs) only.

ARTICLE XXIII

PLASTIC FUSING PERFORMANCE QUALIFICATIONS

QF-300 GENERAL

This Article lists the essential variables that apply to fusing machine operator performance qualifications. The fusing machine operator qualification is limited by the essential variables given for the fusing process. These variables are listed in [Table QF-362](#).

QF-301 TESTS

QF-301.1 Intent of Tests. The fusing machine operator performance qualification tests are intended to determine the ability of fusing machine operators to make sound fused joints when following a qualified FPS or SFPS.

QF-301.2 Qualification Tests. Each organization shall qualify each fusing machine operator for the fusing process(es) to be used in production. The performance qualification tests shall be completed using a qualified FPS. A fusing machine operator qualified for fusing in accordance with one qualified FPS or SFPS is also qualified for fusing in accordance with other qualified FPSs or SFPSs within the limits of the fusing operator essential performance variables given in [Table QF-362](#). Visual and mechanical examination requirements are described in [QF-302](#). Retests and renewal of qualification are given in [QF-320](#).

The fusing machine operator responsible for fusing FPS qualification test coupons successfully qualifying the FPS is also qualified as a fusing machine operator within the limits of the essential performance qualification variables given in [Table QF-362](#).

QF-301.3 Identification of Fusing Machine Operators. Each qualified fusing machine operator shall be assigned an identifying number, letter, or symbol by the organization, which shall be used to identify production fused joints completed by the fusing machine operator.

QF-301.4 Record of Tests. The record of fusing machine operator performance qualification (FPQ) tests shall include the qualified ranges of essential performance variables, the type of tests performed, and test results for each fusing machine operator. Suggested forms for these records are given in [Form QF-484](#).

QF-302 TYPE OF TEST REQUIRED

QF-302.1 Visual Examination. For pipe coupons, all surfaces shall be examined visually per [QF-141](#) before cutting specimens. Pipe test coupons shall be visually examined per [QF-141](#) over the entire circumference.

QF-302.2 Mechanical Tests. For pipe coupons, two bend test specimens shall be removed from the fused test joint at intervals of approximately 180 deg. Each specimen shall be tested by one of the following methods:

(a) *Reverse-Bend Test.* The specimens shall be removed as shown in [Figure QF-463](#), illustration (a), and tested in accordance with [QF-143.1](#).

(b) *Guided Side-Bend Test.* Each specimen shall be removed as shown in [Figure QF-463](#), illustration (b), and prepared and tested in accordance with [QF-143.2](#).

QF-303 LIMITS OF QUALIFIED POSITIONS AND DIAMETERS (SEE [QF-461](#))

QF-303.1 Pipe Positions. Fusing machine operators who pass the required tests for fusing in the test positions shown in [Figures QF-461.1](#) and [QF-461.2](#) shall be qualified for fusing within the following limits:

(a) The 5G test position qualifies for the horizontal position ± 45 deg.

(b) Test positions other than 5G qualify for the orientation tested ± 20 deg.

QF-303.2 Pipe Diameters. Pipe sizes within the ranges listed in [Table QF-452.3](#) shall be used for test coupons to qualify within the ranges listed in [Table QF-452.3](#).

QF-305 FUSING MACHINE OPERATORS

Each fusing machine operator shall have passed the mechanical and visual examinations prescribed in [QF-301](#) and [QF-302](#).

QF-305.1 Testing. Qualification testing shall be performed on test coupons in accordance with [QF-311](#) and the following requirements:

(a) The data required by [QF-130](#) shall be recorded for each fusing machine operator.

(b) The supervisor conducting the test shall observe the making of the fused joint and verify that the FPS or SFPS was followed.

QF-305.2 Examination. Test coupons fused in accordance with [QF-305.1](#) shall be evaluated as follows:

(a) The completed joint shall be visually examined in accordance with [QF-302.1](#).

(b) After the joint is complete, the data required by [QF-130](#) shall be reviewed for compliance with the requirements of the FPS or SFPS used for the qualification test.

(c) Bend test specimens shall be removed and tested and in accordance with [QF-302.2](#).

QF-310 QUALIFICATION TEST COUPONS**QF-311 TEST COUPONS**

The test coupons shall consist of fusing one pipe joint assembly in at least one of the positions shown in Figure QF-461.2.

QF-320 RETESTS AND RENEWAL OF QUALIFICATION**QF-321 RETESTS**

A fusing machine operator who fails one or more of the tests prescribed in QF-302, as applicable, may be retested under the following conditions.

QF-321.1 Immediate Retest Using Visual Examination. When the qualification coupon has failed the visual examination of QF-302.1, retests shall be accepted by visual examination before conducting the mechanical testing.

When an immediate retest is made, the fusing machine operator shall make two consecutive test coupons. If both additional coupons pass the visual examination requirements, the examiner shall select one of the acceptable test coupons for specimen removal to facilitate conducting the required mechanical testing.

QF-321.2 Immediate Retest Using Mechanical Testing. When the qualification coupon has failed the mechanical testing of QF-302.2, and an immediate retest is conducted, the fusing machine operator shall make two consecutive test coupons. If both additional coupons pass the mechanical test requirements, the fusing machine operator is qualified.

QF-321.3 Further Training. When the fusing machine operator has undergone additional training or completed additional fusing practice joints, a new test shall be made for each fusion test joint that failed to meet the requirements.

QF-322 EXPIRATION AND RENEWAL OF QUALIFICATION

QF-322.1 Expiration of Qualification. The performance qualification of a fusing machine operator shall be affected when one of the following conditions occurs:

(a) When a fusing machine operator has not completed a fused joint using a qualified FPS or SFPS for a time period of 6 months or more, their qualification shall expire.

(b) When there is a specific reason to question the ability of the fusing machine operator to make fused joints meeting the requirements of this Section, the qualifications of the fusing machine operator shall be revoked.

QF-322.2 Renewal of Qualification

(a) Performance qualifications that have expired under the provisions of QF-322.1(a) may be renewed by having the fusing machine operator fuse a single test coupon and subjecting the test coupon to the testing required by QF-302. A successful test shall renew all of the fusing machine operator's previous qualifications.

(b) Fusing machine operators whose qualifications have been revoked under the provisions of QF-322.1(b) may be requalified by fusing a test coupon representative of the planned production work. The fused test coupon shall be tested as required by QF-302. A successful test shall restore the fusing machine operator's qualification within the qualified range of essential performance variables listed in Table QF-362.

QF-360 ESSENTIAL VARIABLES FOR PERFORMANCE QUALIFICATION OF FUSING MACHINE OPERATORS**QF-361 GENERAL**

A fusing machine operator shall be requalified whenever a change is made in one or more of the essential variables listed in Table QF-362.

Table QF-362
Essential Variables Applicable to Fusing Machine Operators

Paragraph		Brief of Variables
QF-403 Material	.1	φ Pipe material
	.2	φ Pipe diameter
QF-404 Position	.1	+ Position
QF-406 Equipment	.1	φ Equipment manufacturer

ARTICLE XXIV PLASTIC FUSING DATA

QF-400 VARIABLES

QF-401 GENERAL

Each fusing variable described in this Article is applicable for procedure qualification when referenced in [QF-250](#) for each specific fusing process. Essential variables for performance qualification are referenced in [QF-360](#) for each specific fusing process. A change from one fusing process to another fusing process requires re-qualification (e.g., a change from butt-fusing to electro-fusing).

QF-401.1 Essential Variable (Procedure). A fusing condition that, if changed, will affect the mechanical properties of the joint (e.g., a change in pipe wall thickness).

QF-401.2 Essential Variable (Performance). A fusing condition that, if changed, will affect the ability of a fusing machine operator to make a sound fused joint [e.g., a change in pipe size (diameter) or pipe position].

QF-401.3 Nonessential Variable (Procedure). A fusing condition that, if changed, will *not* affect the mechanical properties of a fused joint [e.g., a change in pipe size (diameter)].

QF-401.4 Fusing Data. The fusing data includes the fusing variables grouped as joints, pipe material, position, thermal conditions, equipment, and technique.

QF-402 JOINTS

QF-402.1 A change in the type of joint from that qualified, except that a square butt joint qualifies a mitered joint.

QF-402.2 A change in the pipe O.D. surface misalignment of more than 10% of the wall thickness of the thinner member to be fused.

QF-403 MATERIAL

QF-403.1 A change to any pipe material other than those listed in [Table QF-422](#).

QF-403.2 A change in the pipe diameter beyond the range qualified in [Table QF-452.3](#).

QF-403.3 A change in the pipe wall thickness beyond the range qualified. See [QF-202.2.1](#).

QF-403.4 A change in the cross-sectional area to be fused beyond the range specified.

QF-404 POSITION

QF-404.1 The addition of other fusing positions beyond that qualified. See [QF-303.1](#).

QF-405 THERMAL CONDITIONS

QF-405.1 A change in the heater surface temperature to a value beyond the range qualified.

QF-405.2 A change in the interfacial pressure to a value beyond the range qualified.

QF-405.3 A decrease in melt bead size from that qualified.

QF-405.4 An increase in heater plate removal time from that qualified.

QF-405.5 A decrease in the cool time at butt-fusing pressure from that qualified.

QF-406 EQUIPMENT

QF-406.1 A change in the fusing machine manufacturer.

QF-407 TECHNIQUE

QF-407.1 A change in fabrication location from the fabrication shop to field applications or vice versa.

QF-420 MATERIAL GROUPINGS

High-density polyethylene pipe listed in [Table QF-422](#) may be fused in accordance with Section IX.

**Table QF-422
Material Grouping**

Specification	Classification	Product Form
D3035	PE 2708	Pipe
	PE 3608	
F714	PE 4710	
D3261	PE 2708	Fittings
	PE 3608	
	PE 4710	

QF-450 PIPE FUSING LIMITS

Table QF-452.3
Pipe Fusing Diameter Limits

Size of Test Coupon — IPS [in. (mm)]	Size Qualified — IPS [in. (mm)]	
	Minimum	Maximum
Less than 6 [6.625 (168)]	None	Size tested
6 to less than 8 [6.625 (168) to less than 8.625 (219)]	None	Less than 8 [less than 8.625 (219)]
8 to 20 [8.625 (219) to 20 (508)]	8 [8.625 (219)]	20 [20 (508)]
Greater than 20 [greater than 20 (508)]	Greater than 20 [greater than 20 (508)]	Unlimited

QF-460 GRAPHICS**QF-461 POSITIONS**

Figure QF-461.1
Fusing Positions

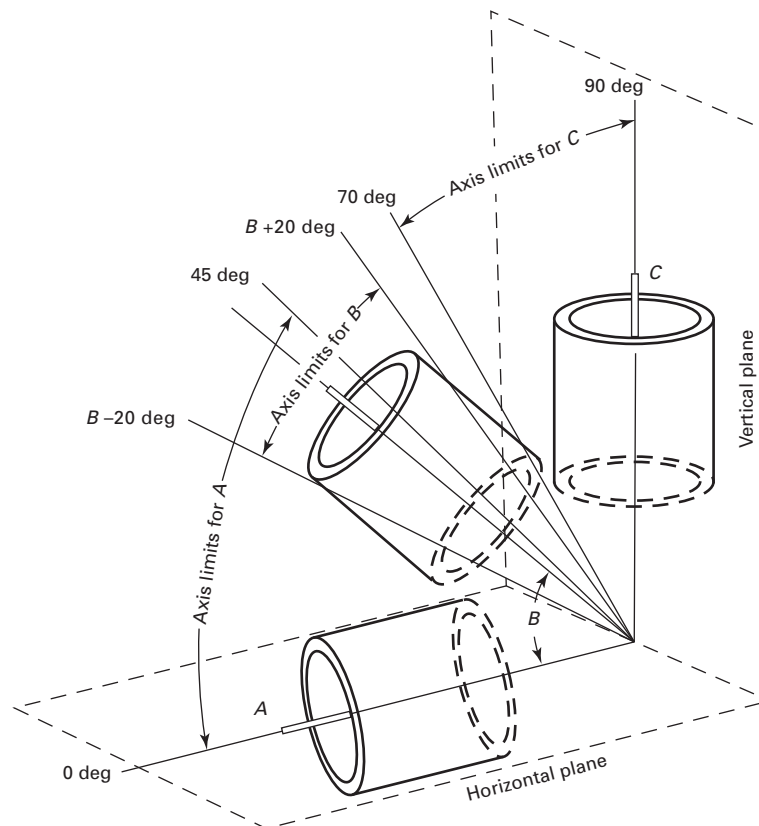


Figure QF-461.1
Fusing Positions (Cont'd)

Table continued

Tabulation of Positions in Joints		
Position	Diagram Reference	Inclination of Axis, deg
Horizontal	A	0 ± 45
Intermediate	B	$B \pm 20$
Vertical	C	90 ± 20

GENERAL NOTE: Inclination of the axis is measured from the horizontal reference plane toward the vertical.

Figure QF-461.2
Fusing Test Positions



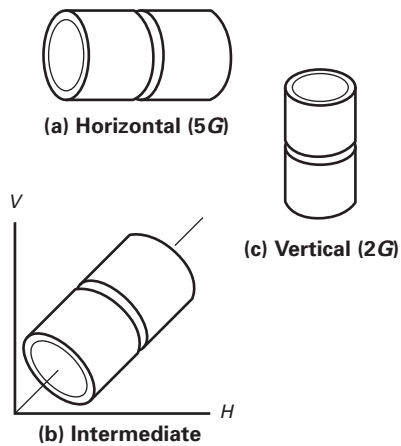



Figure QF-462
Cross Section of Upset Beads for Butt-Fused PE Pipe

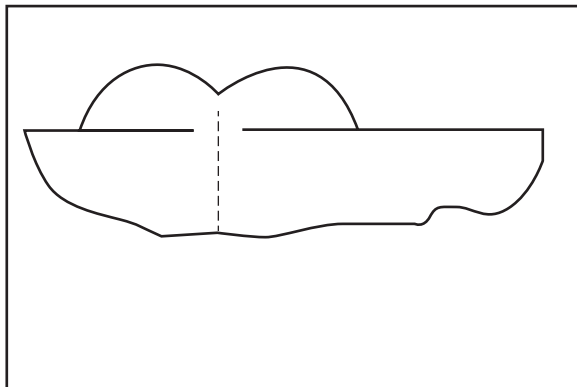

(a) Visually Acceptable — Uniform Bead Around Pipe

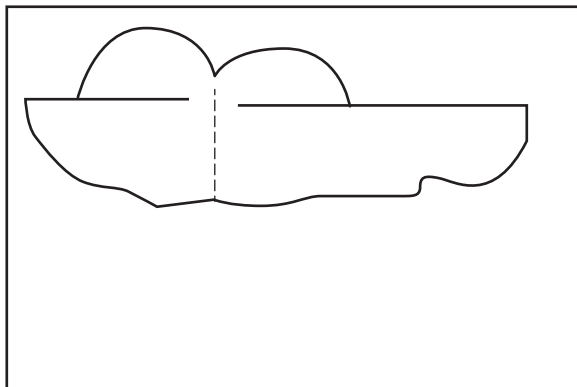


**(b) Visually Acceptable — Non-Uniform Bead Around Pipe,
 But Localized Diameter Mismatch Less Than 10%
 of the Nominal Wall Thickness**

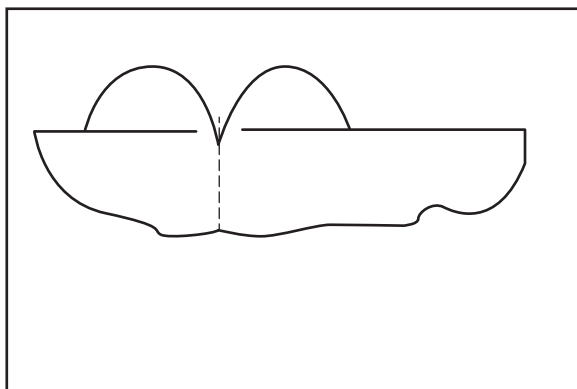


**(c) Visually Unacceptable — V-Groove Too Deep at Pipe Tangent
 for Both Uniform and Non-Uniform Beads**

Figure QF-463
Bend Test Specimen Removal, Configuration, and Testing

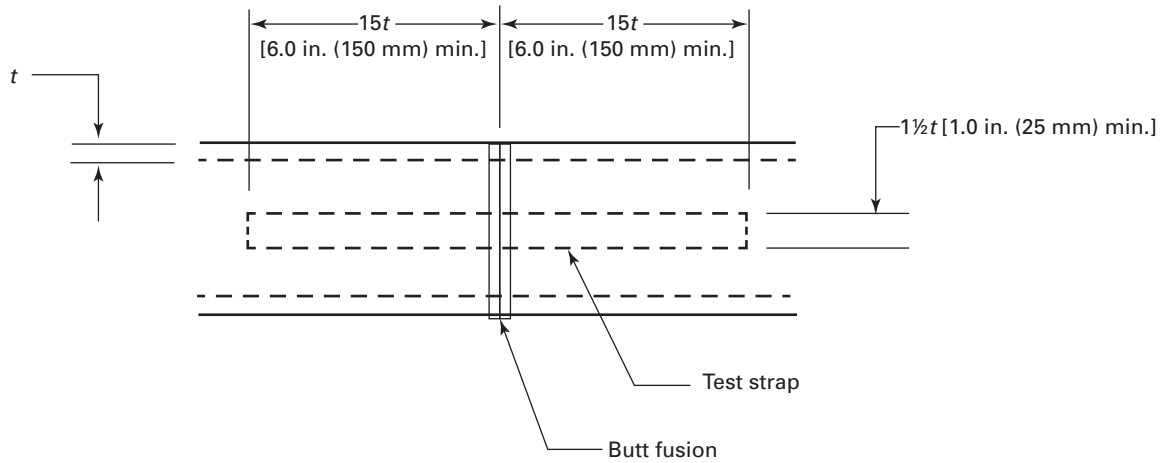


(a) Reverse-Bend Test Specimen Removal [for $t_{\text{max}} \leq 1 \text{ in. (25 mm)}$]

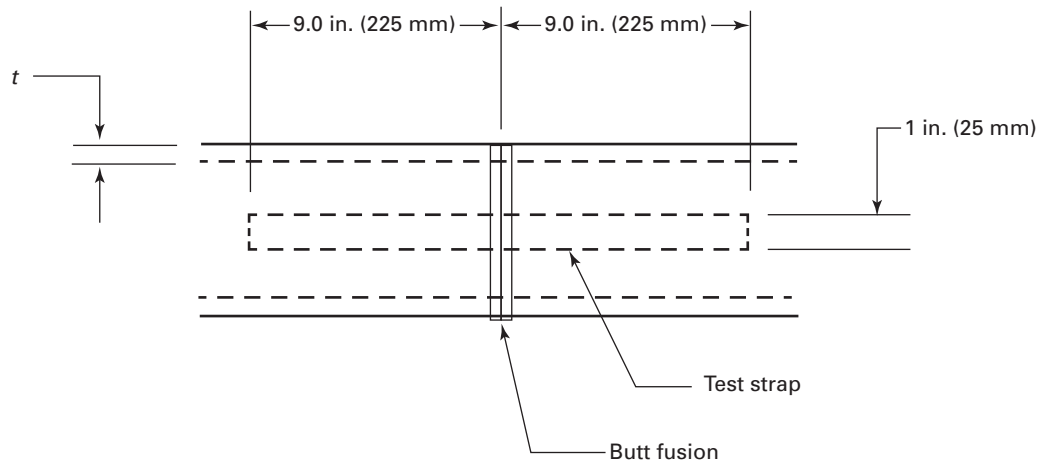


(b) Guided Side-Bend Test Specimen Removal [for $t_{\text{max}} > 1 \text{ in. (25 mm)}$]

Figure QF-463
Bend Test Specimen Removal, Configuration, and Testing (Cont'd)

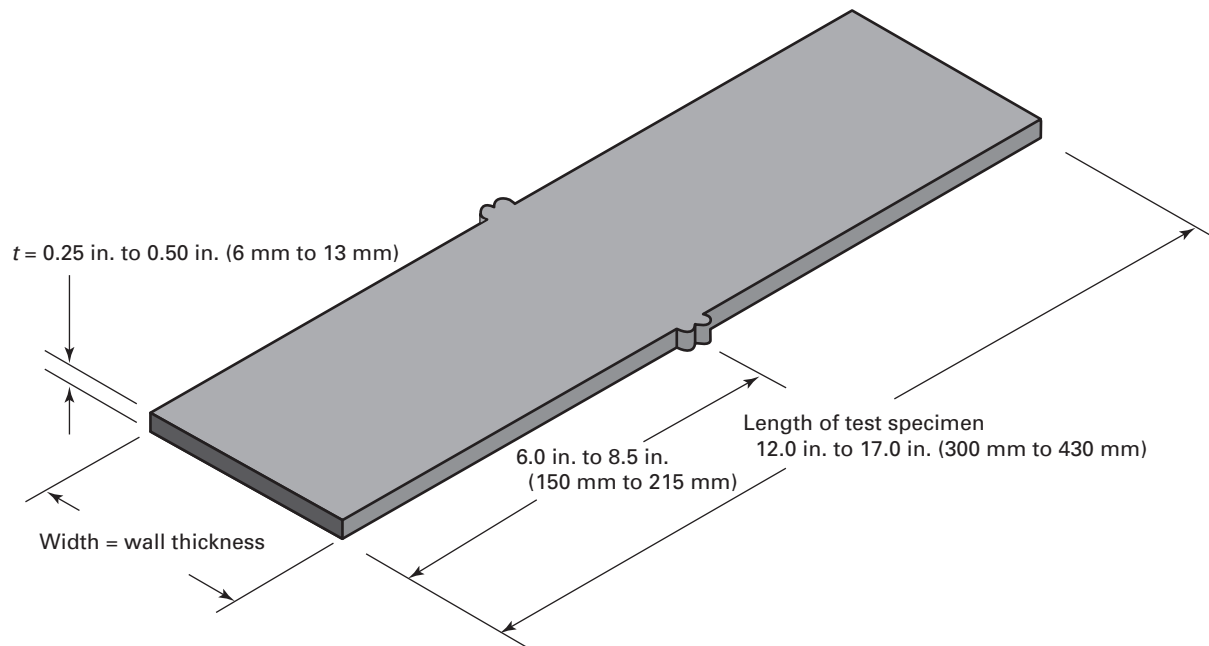


(c) Guided Side-Bend Test Specimen

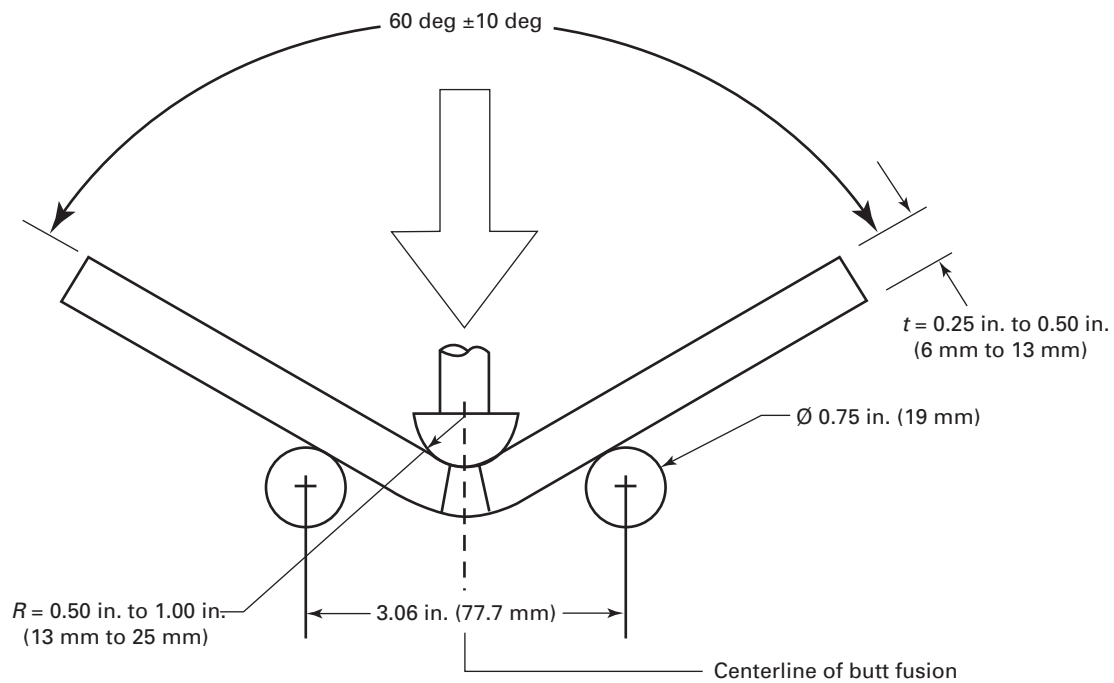

(d) Guided Side-Bend Test Machine Dimensions


Figure QF-464
HSTIT Specimen Configuration and Dimensions

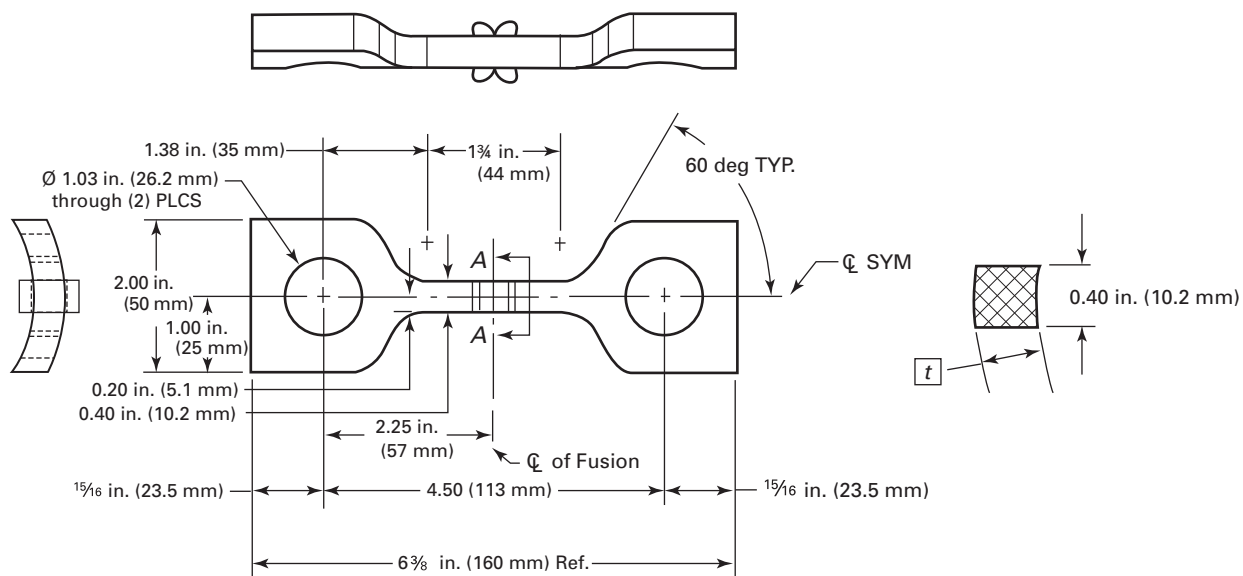

GENERAL NOTES:

- (a) All machined surfaces 125 RMS or better.
- (b) 3 place dimensions ± 0.005 in. (± 0.13 mm).
- (c) 2 place dimensions ± 0.010 in. (± 0.25 mm).
- (d) Fractional dimensions $\pm 1/32$ in. (± 0.80 mm).
- (e) All internal radii $R1/2$ in. (± 0.13 mm).
- (f) All external radii $R3/8$ in. (10 mm).
- (g) Bead remains on after machining.


Figure QF-465
HSTIT Specimen Failure Examples

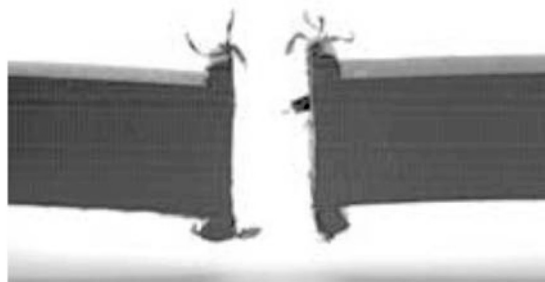


(a) Brittle Rupture



(b) Ductile Rupture Outside Fusion Interface

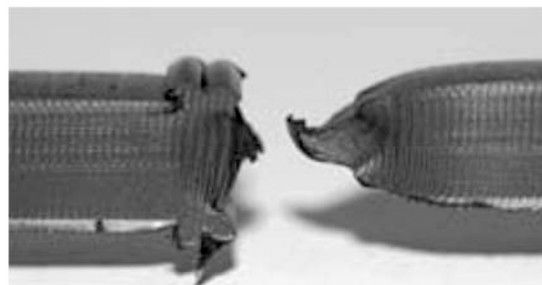

**(c) Ductile Rupture Adjacent to
Fusion Interface**

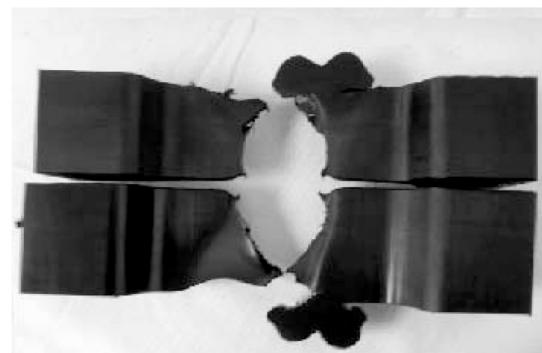

(d) Ductile Ruptures of Split Specimens

QF-480 FORMS

FORM QF-482 Suggested Format for Fusing Procedure Specifications (FPS) (See QF-201.3, Section IX, ASME Boiler and Pressure Vessel Code)	
Company Name _____ By _____	
Fusing Procedure Specification No. _____ Date _____	
Revision No. _____ Date _____	
FPS Qualification <input type="checkbox"/> By testing <input type="checkbox"/> SFPS If qualified by testing, supporting PQR No.(s) _____	
Fusing Process Type _____	
Joints (QF-402) Joint Type _____ Pipe End Preparation _____ Miter Joint Angle _____ Pipe Surface Alignment _____ Sketches, production drawings, weld symbols, or written description should show the general arrangement of the parts to be fused. Where applicable, the details of the joint groove may be specified. Sketches may be attached to illustrate joint design.	Details
Materials (QF-403) Specification _____ Classification _____ to Specification _____ Classification _____ Pipe Size (Diameter) _____ Pipe Wall Thickness _____ Other _____	
Position (QF-404) Pipe Position _____ Other _____	
Thermal Conditions (QF-405) Heater Surface Temperature Range _____ Fusing Interfacial Pressure Range _____ Drag Pressure Range _____ Butt-Fusing Pressure Range _____ Melt Bead Size Range _____ Heater Plate Removal Time Range _____ Cool-Down Time at Butt-Fusing Pressure Range _____	
Equipment (QF-406) Fusing Machine Manufacturer _____ Data Acquisition Used <input type="checkbox"/> Yes <input type="checkbox"/> No Data Acquisition Machine Manufacturer _____ Hydraulic Hose Length _____	
Technique (QF-407) Location <input type="checkbox"/> Fabrication Shop <input type="checkbox"/> Field _____	

FORM QF-483 Suggested Format for Fusing Procedure Qualification Records (PQR)
(See QF-201.5(d), Section IX, ASME Boiler and Pressure Vessel Code)

Company Name _____

Procedure Qualification Record No. _____ Date _____

FPS No. _____

Fusing Process(es) _____

Joints (QF-402)

Pipe Surface Alignment _____

Pipe End Preparation of Test Coupon

Material (QF-403)

Specification _____ Classification _____

to Specification _____ Classification _____

Pipe Size (Diameter) _____

Pipe Wall Thickness _____

Other _____

Equipment (QF-406)

Fusing Machine Manufacturer _____

Data Acquisition Used ☐ Yes ☐ No

Data Acquisition System Manufacturer _____

Hydraulic Hose Length _____

Position (QF-404)

Position of Pipe _____

Other _____

Technique (QF-407)

Location ☐ Fabrication Shop ☐ Field

Thermal Conditions (QF-405)

Heater Surface Temperature _____

Fusing Interfacial Pressure _____

Drag Pressure _____

Butt-Fusing Pressure _____

Melt Bead Size _____

Heater Plate Removal Time _____

Cool-Down Time at Butt-Fusing Pressure _____

Other _____

Other

FORM QF-483 (Back)

PQR No. _____

Visual Examination (QF-141)

Elevated Temperature Sustained Pressure Tests (QF-142)

Joint No.	Heater Temperature	Interfacial Pressure	Result

Joint No.	Heater Temperature	Interfacial Pressure	Result

High-Speed Tensile Impact Tests (QF-144)

Joint No.	Spec. No.	Heater Temperature	Interfacial Pressure	Type of Failure	Location of Failure

Joint No.	Spec. No.	Heater Temperature	Interfacial Pressure	Type of Failure	Location of Failure

Attach additional sheet(s) for high-speed tensile test impact test data for pipe larger than NPS 4 (DN 100).

Fusing Machine Operator's Name _____ Identification No. _____ Stamp No. _____

Tests Conducted By _____ Laboratory Test No. _____

We certify that the statements in this record are correct and that the test joints were prepared, fused, and tested in accordance with the requirements of Section IX of the ASME Boiler and Pressure Vessel Code.

Organization _____

Date _____ Certified By _____

(Detail of record of tests are illustrative only and may be modified to conform to the type and number of tests required by the Code.)

FORM QF-484 Suggested Format for Fusing Machine Operator Performance Qualifications (FPQ)
(See QF-301.4, Section IX, ASME Boiler and Pressure Vessel Code)

Fusing Machine Operator's Name _____ Identification No. _____

Test Description (Information Only)

Type of Test: ☐ Original qualification ☐ Requalification

Identification of FPS Followed _____

Pipe Specification _____ Classification _____ to Specification _____ Classification _____

Pipe Size (Diameter) _____ Pipe Wall Thickness _____

Testing Conditions and Qualification Limits

Fusing Variables (QF-360)	Actual Values	Range Qualified
Pipe Material	_____	_____
Pipe Size (Diameter)	_____	_____
Pipe Position	_____	_____
Fusing Machine Manufacturer	_____	_____

RESULTS

Visual Examination of Completed Joint [QF-305.2(a)] _____

Examination of Data Acquisition Output [QF-305.2(b)] _____

Bend Tests (QF-302.2)

Specimen No.	Type of Bend	Result	Specimen No.	Type of Bend	Result

Bend Specimens Evaluated By _____ Company _____

Mechanical Tests Conducted By _____ Laboratory Test No. _____

Fusing Supervised By _____

Data Acquisition Output Examined By _____

We certify that the statements in this record are correct and that the test coupons were prepared, fused, and tested in accordance with the requirements of Section IX of the ASME Boiler and Pressure Vessel Code.

Organization _____

Date _____

Certified by _____

FORM QF-485 Suggested Format for Plastic Pipe Fusing Data Acquisition Log Review
(See QF-131 Section IX, ASME Boiler and Pressure Vessel Code)

Job Information _____ Job Number _____
 Fusing Machine Operator Name _____ Fusing Machine Operator Identification _____
 FPS or SFPS Used _____ Date _____ Time _____
 Fusing Machine Identification _____ Fusing Machine Manufacturer _____ Joint Number _____
 Pipe Specification _____ Classification _____ to Specification _____ Classification _____
 Pipe Size (Diameter) _____ Pipe Wall Thickness _____ Joint Configuration _____

FUSING VARIABLES

Heater Surface Temperature _____ Within Qualification Range ☐ Yes ☐ No
 Interfacial Fusing Pressure _____ Within Qualification Range ☐ Yes ☐ No
 Drag Pressure _____
 Butt-Fusing Pressure: _____ Within Qualification Range ☐ Yes ☐ No
 Calculated Value _____ Recorded Hydraulic-Fusing Pressure _____ Acceptable ☐ Yes ☐ No
 Butt-Fusing Pressure Drop to Less Than Drag Pressure? ☐ Yes ☐ No
 Gauge Pressure During Initial Heat Cycle _____ Elapsed Time During Initial Heat Cycle _____
 Gauge Pressure During Heat-Soak Cycle _____ Elapsed Time During Heat-Soak Cycle _____
 Gauge Pressure During Fusing/Cool Cycle _____
 Elapsed Time During Fusing/Cool Cycle _____ Within Qualification Range ☐ Yes ☐ No
 Melt Bead Size _____ Within Qualification Range ☐ Yes ☐ No
 Heater Plate Removal Time _____ Within Qualification Range ☐ Yes ☐ No
 Data Logger Probe _____ External Probe _____
 Data Acquisition System Manufacturer _____

Review of the Recorded Pressure/Time Diagram

Acceptable ☐ Yes ☐ No

Data Acquisition Acceptable ☐ Yes ☐ No

Examiner name _____ Examiner signature _____

Date _____

QF-490 DEFINITIONS

QF-491 GENERAL

Terms relating to fusing used in Section IX are listed in [QG-109](#). Other common terms relating to fusing are defined in ASTM F 412, Standard Terminology Relating to Plastic Piping Systems.

QF-492 DEFINITIONS

Definitions relocated to [QG-109](#).

(13)

MANDATORY APPENDIX A

DELETED

NONMANDATORY APPENDIX B WELDING AND BRAZING FORMS

B-100 FORMS

This Nonmandatory Appendix illustrates sample formats for Welding and Brazing Procedure Specifications, Procedure Qualification Records, and Performance Qualification.

B-101 WELDING

Form QW-482 is a suggested format for Welding Procedure Specifications (WPS); Form QW-483 is a suggested format for Procedure Qualification Records (PQR). These forms are for the shielded metal-arc (SMAW), submerged-arc (SAW), gas metal-arc (GMAW), and gas tungsten-arc (GTAW) welding processes, or a combination of these processes.

Forms for other welding processes may follow the general format of Forms QW-482 and QW-483, as applicable.

Form QW-484 is a suggested format for Welder/Welding Operator/Performance Qualification (WPQ) for groove or fillet welds.

Form QW-485 is a suggested format for Demonstration of Standard Welding Procedure Specifications.

B-102 BRAZING

Form QB-482 is a suggested format for Brazing Procedure Specifications (BPS); Form QB-483 is a suggested format for Procedure Qualifications Records (PQR). These forms are for torch brazing (TB), furnace brazing (FB), induction brazing (IB), resistance brazing (RB), and dip brazing (DB) processes.

Forms for other brazing processes may follow the general format of Forms QB-482 and QB-483, as applicable.

Form QB-484 is a suggested format for Brazer/Brazing Operator/Performance Qualification (BPQ).

(13)

FORM QW-482 SUGGESTED FORMAT FOR WELDING PROCEDURE SPECIFICATIONS (WPS)
(See QW-200.1, Section IX, ASME Boiler and Pressure Vessel Code)

Organization Name _____ By _____
 Welding Procedure Specification No. _____ Date _____ Supporting PQR No.(s) _____
 Revision No. _____ Date _____

Welding Process(es) _____ Type(s) _____
 (Automatic, Manual, Machine, or Semi-Automatic)

JOINTS (QW-402)**Details**

Joint Design _____
 Root Spacing _____
 Backing: Yes _____ No _____
 Backing Material (Type) _____
 (Refer to both backing and retainers)

☐ Metal ☐ Nonfusing Metal

☐ Nonmetallic ☐ Other

Sketches, Production Drawings, Weld Symbols, or Written Description should show the general arrangement of the parts to be welded. Where applicable, the details of weld groove may be specified.

Sketches may be attached to illustrate joint design, weld layers, and bead sequence (e.g., for notch toughness procedures, for multiple process procedures, etc.)

***BASE METALS (QW-403)**

P-No. _____ Group No. _____ to P-No. _____ Group No. _____

OR

Specification and type/grade or UNS Number _____

to Specification and type/grade or UNS Number _____

OR

Chem. Analysis and Mech. Prop. _____

to Chem. Analysis and Mech. Prop. _____

Thickness Range:

Base Metal: _____ Groove _____ Fillet _____

Maximum Pass Thickness $\leq 1/2$ in. (13 mm) (Yes) _____ (No) _____

Other _____

***FILLER METALS (QW-404)**

1

2

Spec. No. (SFA) _____

AWS No. (Class) _____

F-No. _____

A-No. _____

Size of Filler Metals _____

Filler Metal Product Form _____

Supplemental Filler Metal _____

Weld Metal _____

Deposited Thickness:

Groove _____

Fillet _____

Electrode-Flux (Class) _____

Flux Type _____

Flux Trade Name _____

Consumable Insert _____

Other _____

*Each base metal-filler metal combination should be recorded individually.

(07/13)

2013 SECTION IX

FORM QW-482 (Back)

WPS No. _____ Rev. _____

POSITIONS (QW-405) Position(s) of Groove _____ Welding Progression: Up _____ Down _____ Position(s) of Fillet _____ Other _____					POSTWELD HEAT TREATMENT (QW-407) Temperature Range _____ Time Range _____ Other _____																											
PREHEAT (QW-406) Preheat Temperature, Minimum _____ Interpass Temperature, Maximum _____ Preheat Maintenance _____ Other _____ (Continuous or special heating, where applicable, should be recorded)					GAS (QW-408) <table style="width: 100%; border-collapse: collapse;"> <thead> <tr> <th rowspan="2"></th> <th colspan="3" style="text-align: center; border-bottom: 1px solid black;">Percent Composition</th> </tr> <tr> <th style="text-align: center; border-bottom: 1px solid black;">Gas(es)</th> <th style="text-align: center; border-bottom: 1px solid black;">(Mixture)</th> <th style="text-align: center; border-bottom: 1px solid black;">Flow Rate</th> </tr> </thead> <tbody> <tr> <td>Shielding</td> <td>_____</td> <td>_____</td> <td>_____</td> </tr> <tr> <td>Trailing</td> <td>_____</td> <td>_____</td> <td>_____</td> </tr> <tr> <td>Backing</td> <td>_____</td> <td>_____</td> <td>_____</td> </tr> <tr> <td>Other</td> <td>_____</td> <td>_____</td> <td>_____</td> </tr> </tbody> </table>						Percent Composition			Gas(es)	(Mixture)	Flow Rate	Shielding	_____	_____	_____	Trailing	_____	_____	_____	Backing	_____	_____	_____	Other	_____	_____	_____
	Percent Composition																															
	Gas(es)	(Mixture)	Flow Rate																													
Shielding	_____	_____	_____																													
Trailing	_____	_____	_____																													
Backing	_____	_____	_____																													
Other	_____	_____	_____																													
ELECTRICAL CHARACTERISTICS (QW-409)																																
Weld Pass(es)	Process	Filler Metal		Current Type and Polarity	Amps (Range)	Wire Feed Speed (Range)	Energy or Power (Range)	Volts (Range)	Travel Speed (Range)	Other (e.g., Remarks, Com- ments, Hot Wire Addition, Technique, Torch Angle, etc.)																						
		Classifi- cation	Diameter																													
<p>Amps and volts, or power or energy range, should be recorded for each electrode size, position, and thickness, etc.</p> <p>Pulsing Current _____ Heat Input (max.) _____</p> <p>Tungsten Electrode Size and Type _____ <small>(Pure Tungsten, 2% Thoriated, etc.)</small></p> <p>Mode of Metal Transfer for GMAW (FCAW) _____ <small>(Spray Arc, Short Circuiting Arc, etc.)</small></p> <p>Other _____</p>																																
TECHNIQUE (QW-410) String or Weave Bead _____ Orifice, Nozzle, or Gas Cup Size _____ Initial and Interpass Cleaning (Brushing, Grinding, etc.) _____ _____ Method of Back Gouging _____ Oscillation _____ Contact Tube to Work Distance _____ Multiple or Single Pass (Per Side) _____ Multiple or Single Electrodes _____ Electrode Spacing _____ Peening _____ Other _____ _____ _____																																

(07/10)

(13)

FORM QW-483 SUGGESTED FORMAT FOR PROCEDURE QUALIFICATION RECORDS (PQR)
(See QW-200.2, Section IX, ASME Boiler and Pressure Vessel Code)
Record Actual Variables Used to Weld Test Coupon

Organization Name _____
 Procedure Qualification Record No. _____ Date _____
 WPS No. _____
 Welding Process(es) _____
 Types (Manual, Automatic, Semi-Automatic) _____

JOINTS (QW-402)

Groove Design of Test Coupon
 (For combination qualifications, the deposited weld metal thickness shall be recorded for each filler metal and process used.)

BASE METALS (QW-403) Material Spec. _____ Type/Grade, or UNS Number _____ P-No. _____ Group No. _____ to P-No. _____ Group No. _____ Thickness of Test Coupon _____ Diameter of Test Coupon _____ Maximum Pass Thickness _____ Other _____ _____ _____		POSTWELD HEAT TREATMENT (QW-407) Temperature _____ Time _____ Other _____ _____ _____																																																		
FILLER METALS (QW-404) <table border="1"> <tr> <td>1</td> <td>2</td> </tr> <tr> <td>SFA Specification _____</td> <td>_____</td> </tr> <tr> <td>AWS Classification _____</td> <td>_____</td> </tr> <tr> <td>Filler Metal F-No. _____</td> <td>_____</td> </tr> <tr> <td>Weld Metal Analysis A-No. _____</td> <td>_____</td> </tr> <tr> <td>Size of Filler Metal _____</td> <td>_____</td> </tr> <tr> <td>Filler Metal Product Form _____</td> <td>_____</td> </tr> <tr> <td>Supplemental Filler Metal _____</td> <td>_____</td> </tr> <tr> <td>Electrode Flux Classification _____</td> <td>_____</td> </tr> <tr> <td>Flux Type _____</td> <td>_____</td> </tr> <tr> <td>Flux Trade Name _____</td> <td>_____</td> </tr> <tr> <td>Weld Metal Thickness _____</td> <td>_____</td> </tr> <tr> <td>Other _____</td> <td>_____</td> </tr> </table>		1	2	SFA Specification _____	_____	AWS Classification _____	_____	Filler Metal F-No. _____	_____	Weld Metal Analysis A-No. _____	_____	Size of Filler Metal _____	_____	Filler Metal Product Form _____	_____	Supplemental Filler Metal _____	_____	Electrode Flux Classification _____	_____	Flux Type _____	_____	Flux Trade Name _____	_____	Weld Metal Thickness _____	_____	Other _____	_____	GAS (QW-408) <table border="1"> <tr> <th rowspan="2"></th> <th colspan="3">Percent Composition</th> </tr> <tr> <th>Gas(es)</th> <th>(Mixture)</th> <th>Flow Rate</th> </tr> <tr> <td>Shielding</td> <td>_____</td> <td>_____</td> <td>_____</td> </tr> <tr> <td>Trailing</td> <td>_____</td> <td>_____</td> <td>_____</td> </tr> <tr> <td>Backing</td> <td>_____</td> <td>_____</td> <td>_____</td> </tr> <tr> <td>Other</td> <td>_____</td> <td>_____</td> <td>_____</td> </tr> </table>			Percent Composition			Gas(es)	(Mixture)	Flow Rate	Shielding	_____	_____	_____	Trailing	_____	_____	_____	Backing	_____	_____	_____	Other	_____	_____	_____
1	2																																																			
SFA Specification _____	_____																																																			
AWS Classification _____	_____																																																			
Filler Metal F-No. _____	_____																																																			
Weld Metal Analysis A-No. _____	_____																																																			
Size of Filler Metal _____	_____																																																			
Filler Metal Product Form _____	_____																																																			
Supplemental Filler Metal _____	_____																																																			
Electrode Flux Classification _____	_____																																																			
Flux Type _____	_____																																																			
Flux Trade Name _____	_____																																																			
Weld Metal Thickness _____	_____																																																			
Other _____	_____																																																			
	Percent Composition																																																			
	Gas(es)	(Mixture)	Flow Rate																																																	
Shielding	_____	_____	_____																																																	
Trailing	_____	_____	_____																																																	
Backing	_____	_____	_____																																																	
Other	_____	_____	_____																																																	
POSITION (QW-405) Position of Groove _____ Weld Progression (Uphill, Downhill) _____ Other _____ _____		ELECTRICAL CHARACTERISTICS (QW-409) Current _____ Polarity _____ Amps. _____ Volts _____ Tungsten Electrode Size _____ Mode of Metal Transfer for GMAW (FCAW) _____ Heat Input _____ Other _____ _____																																																		
PREHEAT (QW-406) Preheat Temperature _____ Interpass Temperature _____ Other _____ _____		TECHNIQUE (QW-410) Travel Speed _____ String or Weave Bead _____ Oscillation _____ Multipass or Single Pass (Per Side) _____ Single or Multiple Electrodes _____ Other _____ _____																																																		

(07/13)

2013 SECTION IX

FORM QW-483 (Back)

Tensile Test (QW-150)

PQR No. _____

Specimen No.	Width	Thickness	Area	Ultimate Total Load	Ultimate Unit Stress, (psi or MPa)	Type of Failure and Location

Guided-Bend Tests (QW-160)

Type and Figure No.	Result

Toughness Tests (QW-170)

Specimen No.	Notch Location	Specimen Size	Test Temperature	Impact Values			Drop Weight Break (Y/N)
				ft-lb or J	% Shear	Mils (in.) or mm	

Comments _____

Fillet-Weld Test (QW-180)

Result — Satisfactory: Yes _____ No _____ Penetration into Parent Metal: Yes _____ No _____

Macro — Results _____

Other Tests

Type of Test _____

Deposit Analysis _____

Other _____

Welder's Name _____ Clock No. _____ Stamp No. _____

Tests Conducted by _____ Laboratory Test No. _____

We certify that the statements in this record are correct and that the test welds were prepared, welded, and tested in accordance with the requirements of Section IX of the ASME Boiler and Pressure Vessel Code.

Organization _____

Date _____ Certified by _____

(Detail of record of tests are illustrative only and may be modified to conform to the type and number of tests required by the Code.)

(07/13)

(13)

FORM QW-484A SUGGESTED FORMAT A FOR WELDER PERFORMANCE QUALIFICATIONS (WPQ)
(See QW-301, Section IX, ASME Boiler and Pressure Vessel Code)

Welder's name _____ Identification no. _____

Test Description

Identification of WPS followed _____ ☐ Test coupon ☐ Production weld

Specification and type/grade or UNS Number of base metal(s) _____ Thickness _____

Testing Variables and Qualification Limits

Welding Variables (QW-350)	Actual Values	Range Qualified
Welding process(es)	_____	_____
Type (i.e., manual, semi-automatic) used	_____	_____
Backing (with/without)	_____	_____
<input type="checkbox"/> Plate <input type="checkbox"/> Pipe (enter diameter if pipe or tube)	_____	_____
Base metal P-Number to P-Number	_____	_____
Filler metal or electrode specification(s) (SFA) (info. only)	_____	_____
Filler metal or electrode classification(s) (info. only)	_____	_____
Filler metal F-Number(s)	_____	_____
Consumable insert (GTAW or PAW)	_____	_____
Filler Metal Product Form (solid/metal or flux cored/powder) (GTAW or PAW)	_____	_____
Deposit thickness for each process	_____	_____
Process 1 _____ 3 layers minimum <input type="checkbox"/> Yes <input type="checkbox"/> No	_____	_____
Process 2 _____ 3 layers minimum <input type="checkbox"/> Yes <input type="checkbox"/> No	_____	_____
Position qualified (2G, 6G, 3F, etc.)	_____	_____
Vertical progression (uphill or downhill)	_____	_____
Type of fuel gas (OFW)	_____	_____
Inert gas backing (GTAW, PAW, GMAW)	_____	_____
Transfer mode (spray/globular or pulse to short circuit-GMAW)	_____	_____
GTAW current type/polarity (AC, DCEP, DCEN)	_____	_____

RESULTS

Visual examination of completed weld (QW-302.4) _____

☐ Transverse face and root bends [QW-462.3(a)] ☐ Longitudinal bends [QW-462.3(b)] ☐ Side bends (QW-462.2)

☐ Pipe bend specimen, corrosion-resistant weld metal overlay [QW-462.5(c)]

☐ Plate bend specimen, corrosion-resistant weld metal overlay [QW-462.5(d)]

☐ Pipe specimen, macro test for fusion [QW-462.5(b)] ☐ Plate specimen, macro test for fusion [QW-462.5(e)]

Type	Result	Type	Result	Type	Result

Alternative Volumetric Examination Results (QW-191): _____ RT ☐ or UT ☐ (check one)

Fillet weld — fracture test (QW-181.2) _____ Length and percent of defects _____

☐ Fillet welds in plate [QW-462.4(b)] ☐ Fillet welds in pipe [QW-462.4(c)]

Macro examination (QW-184) _____ Fillet size (in.) _____ × _____ Concavity/convexity (in.) _____

Other tests _____

Film or specimens evaluated by _____ Company _____

Mechanical tests conducted by _____ Laboratory test no. _____

Welding supervised by _____

We certify that the statements in this record are correct and that the test coupons were prepared, welded, and tested in accordance with the requirements of Section IX of the ASME BOILER AND PRESSURE VESSEL CODE.

Organization _____

Date _____ Certified by _____

FORM QW-484B SUGGESTED FORMAT B FOR WELDING OPERATOR PERFORMANCE QUALIFICATIONS (WOPQ)
(See QW-301, Section IX, ASME Boiler and Pressure Vessel Code)

Welding operator's name _____ Identification no. _____

Test Description (Information Only)

Identification of WPS followed _____ ☐ Test coupon ☐ Production weld

Specification and type/grade or UNS Number of base metal(s) _____ Thickness _____

Base metal P-Number _____ to P-Number _____ Position (2G, 6G, 3F, etc.) _____

☐ Plate ☐ Pipe (enter diameter, if pipe or tube) _____

Filler metal (SFA) specification _____ Filler metal or electrode classification _____

Testing Variables and Qualification Limits When Using Automatic Welding Equipment

Welding Variables (QW-361.1)	Actual Values	Range Qualified
Type of welding (automatic)	_____	_____
Welding process	_____	_____
Filler metal used (Yes/No) (EBW or LBW)	_____	_____
Type of laser for LBW (CO ₂ to YAG, etc.)	_____	_____
Continuous drive or inertia welding (FW)	_____	_____
Vacuum or out of vacuum (EBW)	_____	_____

Testing Variables and Qualification Limits When Using Machine Welding Equipment

Welding Variables (QW-361.2)	Actual Values	Range Qualified
Type of welding (Machine)	_____	_____
Welding process	_____	_____
Direct or remote visual control	_____	_____
Automatic arc voltage control (GTAW)	_____	_____
Automatic joint tracking	_____	_____
Position qualified (2G, 6G, 3F, etc.)	_____	_____
Consumable inserts (GTAW or PAW)	_____	_____
Backing (with/without)	_____	_____
Single or multiple passes per side	_____	_____

RESULTS

Visual examination of completed weld (QW-302.4) _____

☐ Transverse face and root bends [QW-462.3(a)] ☐ Longitudinal bends [QW-462.3(b)] ☐ Side bends [QW-462.2]

☐ Pipe bend specimen, corrosion-resistant weld metal overlay [QW-462.5(c)]

☐ Plate bend specimen, corrosion-resistant weld metal overlay [QW-462.5(d)]

☐ Pipe specimen, macro test for fusion [QW-462.5(b)] ☐ Plate specimen, macro test for fusion [QW-462.5(e)]

Type	Result	Type	Result	Type	Result

Alternative Volumetric Examination Results (QW-191): _____ RT ☐ or UT ☐ (check one)

Fillet weld — fracture test (QW-181.2) _____ Length and percent of defects _____

☐ Fillet welds in plate [QW-462.4(b)] ☐ Fillet welds in pipe [QW-462.4(c)]

Macro examination (QW-184) _____ Fillet size (in.) _____ × _____ Concavity/convexity (in.) _____

Other tests _____

Film or specimens evaluated by _____ Company _____

Mechanical tests conducted by _____ Laboratory test no. _____

Welding supervised by _____

We certify that the statements in this record are correct and that the test coupons were prepared, welded, and tested in accordance with the requirements of Section IX of the ASME Boiler and Pressure Vessel Code.

Organization _____

Date _____

Certified by _____

(07/13)

(13)

**FORM QW-485 SUGGESTED FORMAT FOR DEMONSTRATION OF STANDARD WELDING
PROCEDURE SPECIFICATIONS (SWPS)
(See Article V)**

Identification of Standard Welding Procedure Specification Demonstrated _____

Demonstration Welding Variables

Specification and type/grade or UNS Number of Base Metal(s) _____
to Specification and type/grade or UNS Number of Base Metal(s) _____

Base Metal P-Number _____ to Base Metal P-Number _____ Thickness _____

Welding Process(es) used _____

☐ Plate ☐ Pipe (Enter Diameter of Pipe or Tube) _____

Groove Design (Single V, Double V, Single U, etc.) _____

Initial Cleaning Method _____

Backing (with/without) _____

Filler Metal Specification _____

Filler Metal or Electrode Classification _____

Filler Metal or Electrode Trade Name _____

Size of Consumable Electrode or Filler Metal _____

Tungsten Electrode Classification and Size for GTAW _____

Consumable Insert Class and Size for GTAW _____

Shielding Gas Composition and Flow Rate for GTAW or GMAW (FCAW) _____

Preheat Temperature _____

Position (1G, 2G, etc.) of Weld _____

Progression (Uphill or Downhill) _____

Interpass Cleaning Method _____

Measured Maximum Interpass Temperature _____

Approximate Deposit Thickness for Each Process or Electrode Type _____

Current Type/Polarity (AC, DCEP, DCEN) _____

Postweld Heat Treatment Time and Temperature _____

Visual Examination of Completed Weld (QW-302.4) _____ Date of Test _____

Bend Test (QW-302.1)

☐ Transverse Face and Root [QW-462.3(a)]

☐ Side (QW-462.2)

Type	Result	Type	Result	Type	Result

Alternative Radiographic Examination Results (QW-302.2) _____

Specimens Evaluated By _____ Title _____ Company _____

Welding Supervised By _____ Title _____ Company _____

Welder's Name _____ Stamp No. _____

We certify that the statements in this record are correct and that the weld described above was prepared, welded, and tested in accordance with the requirements of Section IX of the ASME BOILER AND PRESSURE VESSEL CODE.

Organization _____

Signature _____ Date _____ Demonstration Number _____

(07/13)

2013 SECTION IX

FORM QB-482 SUGGESTED FORMAT FOR A BRAZING PROCEDURE SPECIFICATION (BPS)
(See QB-200.1, Section IX, ASME Boiler and Pressure Vessel Code)

Organization Name _____ By _____
BPS Number _____ Revision _____ Date Issued _____
Supporting PQRs _____
Brazing Process(es) _____ Type(s) _____
(Automatic, Manual, Machine, or Semi-Automatic)

Joint Design (QB-408)

Joint Design: Type _____ Joint Clearance _____
Overlap: Minimum _____ Maximum _____

Base Metal (QB-402)

P-Number _____
to P-Number _____
Other _____

Base Metal Thickness
Minimum _____
Maximum _____

Brazing Filler Metal (QB-403)

Specification Number _____
AWS Classification _____
F-Number _____
Filler Metal Product Form _____

Brazing Temperature (QB-404)

Brazing Temperature Range _____

Postbrazing Heat Treatment (QB-409)

Temperature Range _____
Time Range _____

Brazing Flux, Fuel Gas, or Atmosphere (QB-406)

Flux (AWS Class, Composition, or Trade Name) _____
Fuel Gas _____
Furnace Temperature _____
Atmosphere Type _____
Other _____

Flow Position (QB-407)

Positions Permitted _____
Flow Direction _____

Technique (QB-410) and Other Information

Initial Cleaning _____

Flux Application _____
Nature of Flame (Oxidizing, Neutral, Reducing) _____
Torch Tip Sizes _____
Postbrazing Cleaning _____
Inspection _____

(13)

FORM QB-483 SUGGESTED FORMAT FOR A BRAZING PROCEDURE QUALIFICATION RECORD (PQR)
(See QB-200.2, Section IX, ASME Boiler and Pressure Vessel Code)
Record of Actual Variables Used to Braze Test Coupon

Organization Name _____
 BPS Followed During Brazing of Test Coupon _____ PQR No. _____
 Brazing Process(es) Used _____ Date Coupon Was Brazed _____

Base Metal (QB-402)

Base Metal Specification _____ to Base Metal Specification _____
 P-Number _____ to P-Number _____
 Base Metal Thickness _____ to Base Metal Thickness _____
 Plate or Pipe/Tube _____

Brazing Filler Metal (QB-403)

Filler Metal Specification: AWS Classification _____ F-No. _____ Filler Metal Product Form _____

Joint Design (QB-408)

Overlap _____ Joint Type _____ Joint Clearance _____

Brazing Temperature (QB-404)

Brazing Temperature Range _____

Brazing Flux, Fuel Gas, or Atmosphere (QB-406)

Flux (AWS Class., Composition, Trade Name, or None) _____ Atmosphere Type _____
 Fuel Gas _____ Furnace Temperature _____ Other _____

Flow Position (QB-407)

Position _____ Flow Direction _____

Postbrazing Heat Treatment (QB-409)

Temperature _____ Time _____

Technique (QB-410)

Cleaning Prior to Brazing _____
 Postbrazing Cleaning _____
 Nature of Flame (Oxidizing, Neutral, Reducing) _____
 Other _____

Tensile Tests (QB-150)

Specimen	Width/ Diameter	Thickness	Area	Ultimate Load	UTS (psi or MPa)	Failure Location

Bend Tests (QB-160)

Type	Results	Type	Results

Peel Tests (QB-170) or Section Tests (QB-180)

Type	Results	Type	Results

Other Tests

Brazer's/Brazing Operator's Name _____ ID No. _____
 Brazing of Test Coupon Supervised by _____
 Test Specimens Evaluated by _____ Company _____
 Laboratory Test Number _____

We hereby certify that the statements in this record are correct and that the test coupons were prepared, brazed, and tested in accordance with the requirements of Section IX of the ASME BOILER AND PRESSURE VESSEL CODE.

Organization _____

Certified by _____ Date _____

(07/13)

**FORM QB-484 SUGGESTED FORMAT FOR A BRAZER/BRAZING OPERATOR PERFORMANCE
QUALIFICATION (BPQ)
(See QB-301, Section IX, ASME Boiler and Pressure Vessel Code)**

Brazer's/Brazing Operator's Name _____ Identification No. _____

Testing Variables and Ranges Qualified

Identification of BPS Followed During Brazing of Test Coupon _____

Specification of First Test Coupon Base Metal _____

Specification of Second Test Coupon Base Metal _____

Brazing Variables (QB-350)	Actual Values	Range Qualified
Brazing Process(es)	_____	_____
Type of Brazing (Manual, Semi-Automatic, Automatic, Machine)	_____	_____
Torch Brazing: Manual or Mechanical	_____	_____
Base Metal P-Number _____ to P-Number _____	_____	_____
<input type="checkbox"/> Plate <input type="checkbox"/> Pipe (enter diameter if pipe or tube)	_____	_____
Base Metal Thickness _____	_____	_____
to Base Metal Thickness _____	_____	_____
Joint Type (Butt, Lap, Scarf, Socket, etc.)	_____	_____
If Lap or Socket, Overlap Length _____	_____	_____
Joint Clearance _____	_____	_____
Filler Metal (SFA) Specification(s) (info. only)	_____	_____
Filler Metal Classification(s) (info. only)	_____	_____
Filler Metal/F-Number _____	_____	_____
Filler Metal Product Form _____	_____	_____
Brazing Flow Positions _____	_____	_____

Testing and Results

Visual Examination of Completed Joint (QB-141.6) _____ Date of Test _____

Mechanical Test

☐ Peel (QB-462.3)

☐ Section (QB-462.4)

☐ Tension (QB-462.1)

☐ Transverse Bends [QB-462.2(a)]

☐ Longitudinal Bends [QB-462.2(b)]

Position	Result	Position	Result	Position	Result

Mechanical Tests Conducted by _____ Company _____

Specimens Evaluated by _____ Company _____

Lab Test No. _____

We certify that the statements in this record are correct and that the test coupons were prepared, brazed, and tested in accordance with the requirements of Section IX of the ASME BOILER AND PRESSURE VESSEL CODE.

Organization _____

Certified by _____ Date _____

(13)

NONMANDATORY APPENDIX D P-NUMBER LISTING

P-No.	Grp. No.	Spec. No.	Type, Grade, or UNS No.	P-No.	Grp. No.	Spec. No.	Type, Grade, or UNS No.
Steel and Steel Alloys				Steel and Steel Alloys (Cont'd)			
1	1	A/SA-36	...	1	1	A/SA-369	FPA
1	1	A/SA-53	Type E, Gr. A	1	1	A/SA-369	FPB
1	1	A/SA-53	Type E, Gr. B	1	1	A/SA-372	A
1	1	A/SA-53	Type F	1	1	A381	Y35
1	1	A/SA-53	Type S, Gr. A	1	1	A381	Y42
1	1	A/SA-53	Type S, Gr. B	1	1	A381	Y46
1	1	A/SA-106	A	1	1	A381	Y48
1	1	A/SA-106	B	1	1	A381	Y50
1	1	A108	1015CW	1	1	A/SA-414	A
1	1	A108	1018CW	1	1	A/SA-414	B
1	1	A108	1020CW	1	1	A/SA-414	C
1	1	A/SA-134	...	1	1	A/SA-414	D
1	1	A/SA-135	A	1	1	A/SA-414	E
1	1	A/SA-135	B	1	1	A/SA-420	WPL6
1	1	A139	A	1	1	A500	B
1	1	A139	B	1	1	A500	C
1	1	A139	C	1	1	A501	A
1	1	A139	D	1	1	A/SA-513	1008
1	1	A139	E	1	1	A/SA-513	1010
1	1	A/SA-178	A	1	1	A/SA-513	1015
1	1	A/SA-178	C	1	1	A513	1015CW
1	1	A/SA-179	...	1	1	A/SA-515	60
1	1	A/SA-181	Cl. 60	1	1	A/SA-515	65
1	1	A/SA-192	...	1	1	A/SA-516	55
1	1	A/SA-210	A-1	1	1	A/SA-516	60
1	1	A211	A570-30	1	1	A/SA-516	65
1	1	A211	A570-33	1	1	A519	1018 HR
1	1	A211	A570-40	1	1	A519	1020 HR
1	1	A/SA-214	...	1	1	A519	1022 HR
1	1	A/SA-216	WCA	1	1	A519	1025 HR
1	1	A/SA-234	WPB	1	1	A519	1026 HR
1	1	A/SA-266	1	1	1	A/SA-524	I
1	1	A/SA-283	A	1	1	A/SA-524	II
1	1	A/SA-283	B	1	1	A/SA-556	A2
1	1	A/SA-283	C	1	1	A/SA-556	B2
1	1	A/SA-283	D	1	1	A/SA-557	A2
1	1	A/SA-285	A	1	1	A/SA-557	B2
1	1	A/SA-285	B	1	1	A/SA-562	...
1	1	A/SA-285	C	1	1	A/SA-572	42
1	1	A/SA-333	1	1	1	A/SA-572	50
1	1	A/SA-333	6	1	1	A573	58
1	1	A/SA-334	1	1	1	A573	65
1	1	A/SA-334	6	1	1	A575	M1008
1	1	A/SA-350	LF1				
1	1	A/SA-352	LCA				
1	1	A/SA-352	LCB				

2013 SECTION IX

P-No.	Grp. No.	Spec. No.	Type, Grade, or UNS No.
Steel and Steel Alloys (Cont'd)			
1	1	A575	M1010
1	1	A575	M1012
1	1	A575	M1015
1	1	A575	M1017
1	1	A575	M1020
1	1	A575	M1023
1	1	A575	M1025
1	1	A576	G10080
1	1	A576	G10100
1	1	A576	G10120
1	1	A576	G10150
1	1	A576	G10160
1	1	A576	G10170
1	1	A576	G10180
1	1	A576	G10190
1	1	A576	G10200
1	1	A576	G10210
1	1	A576	G10220
1	1	A576	G10230
1	1	A576	G10250
1	1	A/SA-587	...
1	1	A/SA-618	III
1	1	A633	A
1	1	A633	C
1	1	A633	D
1	1	A/SA-656	Type 3, Gr. 50
1	1	A/SA-656	Type 7, Gr. 50
1	1	A/SA-660	WCA
1	1	A/SA-662	A
1	1	A/SA-662	B
1	1	A/SA-663	...
1	1	A/SA-668	Cl. B
1	1	A/SA-668	Cl. C
1	1	A/SA-671	CA55
1	1	A/SA-671	CB60
1	1	A/SA-671	CB65
1	1	A/SA-671	CC60
1	1	A/SA-671	CC65
1	1	A/SA-671	CE55
1	1	A/SA-671	CE60
1	1	A/SA-672	A45
1	1	A/SA-672	A50
1	1	A/SA-672	A55
1	1	A/SA-672	B55
1	1	A/SA-672	B60
1	1	A/SA-672	B65
1	1	A/SA-672	C55
1	1	A/SA-672	C60
1	1	A/SA-672	C65
1	1	A/SA-672	E55
1	1	A/SA-672	E60
1	1	A/SA-675	45
1	1	A/SA-675	50
1	1	A/SA-675	55
1	1	A/SA-675	60

P-No.	Grp. No.	Spec. No.	Type, Grade, or UNS No.
Steel and Steel Alloys (Cont'd)			
1	1	A/SA-675	65
1	1	A694	F42
1	1	A694	F46
1	1	A694	F52
1	1	A/SA-696	B
1	1	A707	L1, Cl. 1
1	1	A707	L1, Cl. 2
1	1	A707	L2, Cl. 1
1	1	A707	L2, Cl. 2
1	1	A707	L3, Cl. 1
1	1	A707	L3, Cl. 2
1	1	A/SA-727	...
1	1	A/SA-765	I
1	1	A/SA-836	...
1	1	A992	...
1	1	A/SA-1008	CS Type A
1	1	A/SA-1008	CS Type B
1	1	A/SA-1008	DS Type B
1	1	A/SA-1011	CS Type B
1	1	A/SA-1011	DS Type B
1	1	API 5L	A (all grades)
1	1	API 5L	A25 (all grades)
1	1	API 5L	A25P (all grades)
1	1	API 5L	B (all grades)
1	1	API 5L	X42 (all grades)
1	1	API 5L	X46 (all grades)
1	1	API 5L	X52 (all grades)
1	1	MSS SP-75	WPHY-42
1	1	MSS SP-75	WPHY-46
1	1	MSS SP-75	WPHY-52
1	1	SA/AS 1548	PT430
1	1	SA/AS 1548	PT460
1	1	SA/CSA G40.21	Gr. 38W
1	1	SA/CSA G40.21	Gr. 44W
1	1	SA/CSA G40.21	Gr. 50W
1	1	SA/EN 10028-2	P235GH
1	1	SA/EN 10028-2	P265GH
1	1	SA/EN 10028-2	P295GH
1	1	SA/EN 10028-3	P275NH
1	1	SA/EN 10216-2	P235GH
1	1	SA/EN 10216-2	P265GH
1	1	SA/EN 10222-2	P280GH
1	1	SA/EN 10025-2	S235JR
1	1	SA/EN 10217-1	P235TR2
1	1	SA/GB 713	Q345R
1	1	SA/IS 2062	E250 A
1	1	SA/IS 2062	E250 B
1	1	SA/IS 2062	E250 C
1	2	A/SA-105	...
1	2	A/SA-106	C
1	2	A/SA-178	D
1	2	A/SA-181	Cl. 70
1	2	A/SA-210	C
1	2	A/SA-216	WCB
1	2	A/SA-216	WCC

2013 SECTION IX

P-No.	Grp. No.	Spec. No.	Type, Grade, or UNS No.
Steel and Steel Alloys (Cont'd)			
1	2	A/SA-234	WPC
1	2	A/SA-266	2
1	2	A/SA-266	3
1	2	A/SA-266	4
1	2	A/SA-299	A
1	2	A/SA-350	LF2
1	2	A/SA-352	LCC
1	2	A356	1
1	2	A/SA-372	B
1	2	A381	Y52
1	2	A381	Y56
1	2	A381	Y60
1	2	A/SA-414	F
1	2	A/SA-414	G
1	2	A/SA-455	...
1	2	A/SA-487	Gr. 16, Cl. A
1	2	A501	B
1	2	A/SA-508	1
1	2	A/SA-508	1A
1	2	A513	1020 CW
1	2	A513	1025 CW
1	2	A/SA-515	70
1	2	A/SA-516	70
1	2	A519	1018 CW
1	2	A519	1020 CW
1	2	A519	1022 CW
1	2	A519	1025 CW
1	2	A519	1026 CW
1	2	A521	Cl. CE
1	2	A/SA-537	Cl. 1
1	2	A/SA-541	1
1	2	A/SA-541	1A
1	2	A/SA-556	C2
1	2	A/SA-557	C2
1	2	A/SA-572	60
1	2	A573	70
1	2	A618	11
1	2	A633	C
1	2	A633	D
1	2	A/SA-656	Type 3, Gr. 60
1	2	A/SA-656	Type 7, Gr. 60
1	2	A/SA-660	WCB
1	2	A/SA-660	WCC
1	2	A/SA-662	C
1	2	A/SA-671	CB70
1	2	A/SA-671	CC70
1	2	A/SA-671	CD70
1	2	A/SA-671	CK75
1	2	A/SA-672	B70
1	2	A/SA-672	C70
1	2	A/SA-672	D70
1	2	A/SA-672	N75
1	2	A/SA-675	70

P-No.	Grp. No.	Spec. No.	Type, Grade, or UNS No.
Steel and Steel Alloys (Cont'd)			
1	2	A/SA-691	CMS-75
1	2	A/SA-691	CMSH-70
1	2	A694	F56
1	2	A694	F60
1	2	A694	F65
1	2	A/SA-696	C
1	2	A707	L2, Cl. 3
1	2	A707	L3, Cl. 3
1	2	A/SA-737	B
1	2	A/SA-738	A
1	2	A/SA-765	II
1	2	API 5L	X56 (all grades)
1	2	API 5L	X60 (all grades)
1	2	API 5L	X65 (all grades)
1	2	MSS SP-75	WPHY-56
1	2	MSS SP-75	WPHY-60
1	2	MSS SP-75	WPHY-65
1	2	SA/AS 1548	PT490
1	2	SA/EN 10028-2	P355GH
1	2	SA/EN 10222-2	P305GH
1	2	SA/GB 713	Q345R
1	2	SA/GB 713	Q370R
1	2	SA/JIS G3118	SGV480
1	2	A/SA-841	A, Cl. 1
1	3	A/SA-299	B
1	3	A/SA-333	10
1	3	A/SA-350	LF6, Cl. 2
1	3	A513	1026 CW
1	3	A/SA-537	Cl. 2
1	3	A/SA-537	Cl. 3
1	3	A633	E
1	3	A/SA-656	Type 3, Gr. 70
1	3	A/SA-656	Type 7, Gr. 70
1	3	A/SA-671	CD80
1	3	A/SA-672	D80
1	3	A/SA-691	CMSH-80
1	3	A694	F70
1	3	A/SA-737	C
1	3	A/SA-738	B
1	3	A/SA-738	C
1	3	A/SA-765	IV
1	3	A/SA-812	65
1	3	A/SA-841	B, Cl. 2
1	3	API 5L	X70 (all grades)
1	3	MSS SP-75	WPHY-70
1	4	A/SA-656	Type 3, Gr. 80
1	4	A/SA-656	Type 7, Gr. 80
1	4	A/SA-724	A
1	4	A/SA-724	B
1	4	A/SA-724	C
1	4	A/SA-812	80
1	4	API 5L	X80 (all grades)
3	1	A/SA-204	A
3	1	A/SA-209	T1

2013 SECTION IX

P-No.	Grp. No.	Spec. No.	Type, Grade, or UNS No.
Steel and Steel Alloys (Cont'd)			
3	1	A/SA-209	T1a
3	1	A/SA-209	T1b
3	1	A/SA-213	T2
3	1	A/SA-217	WC1
3	1	A/SA-234	WP1
3	1	A/SA-250	T1
3	1	A/SA-250	T1a
3	1	A/SA-250	T1b
3	1	A/SA-250	T2
3	1	A/SA-335	P1
3	1	A/SA-335	P2
3	1	A/SA-335	P15
3	1	A/SA-352	LC1
3	1	A356	2
3	1	A/SA-369	FP1
3	1	A/SA-369	FP2
3	1	A/SA-387	Gr. 2, Cl. 1
3	1	A/SA-426	CP1
3	1	A/SA-426	CP2
3	1	A/SA-426	CP15
3	1	A588	K11430
3	1	A588	K12043
3	1	A/SA-672	L65
3	1	A/SA-691	1/2CR
3	1	A/SA-691	CM-65
3	1	SA/EN 10216-2	16Mo3
3	2	A/SA-182	F1
3	2	A/SA-182	F2
3	2	A/SA-204	B
3	2	A/SA-204	C
3	2	A/SA-302	A
3	2	A/SA-336	F1
3	2	A/SA-387	Gr. 2, Cl. 2
3	2	A/SA-672	H75
3	2	A/SA-672	L70
3	2	A/SA-672	L75
3	2	A/SA-691	1/2CR, Cl. 2
3	2	A/SA-691	CM-70
3	2	A/SA-691	CM-75
3	3	A108	8620 CW
3	3	A/SA-302	B
3	3	A/SA-302	C
3	3	A/SA-302	D
3	3	A/SA-487	Gr. 2, Cl. A
3	3	A/SA-487	Gr. 2, Cl. B
3	3	A/SA-487	Gr. 4, Cl. A
3	3	A/SA-508	2, Cl. 1
3	3	A/SA-508	2, Cl. 2
3	3	A/SA-508	3, Cl. 1
3	3	A/SA-508	3, Cl. 2
3	3	A/SA-508	4N, Cl. 3
3	3	A/SA-533	Type A, Cl. 1
3	3	A/SA-533	Type A, Cl. 2
3	3	A/SA-533	Type B, Cl. 1
3	3	A/SA-533	Type B, Cl. 2

P-No.	Grp. No.	Spec. No.	Type, Grade, or UNS No.
Steel and Steel Alloys (Cont'd)			
3	3	A/SA-533	Type C, Cl. 1
3	3	A/SA-533	Type C, Cl. 2
3	3	A/SA-533	Type D, Cl. 1
3	3	A/SA-533	Type D, Cl. 2
3	3	A/SA-533	Type E, Cl. 1
3	3	A/SA-533	Type E, Cl. 2
3	3	A/SA-541	2, Cl. 1
3	3	A/SA-541	2, Cl. 2
3	3	A/SA-541	3, Cl. 1
3	3	A/SA-541	3, Cl. 2
3	3	A/SA-543	B Cl. 3
3	3	A/SA-543	C Cl. 3
3	3	A/SA-672	H80
3	3	A/SA-672	J80
3	3	A/SA-672	J90
4	1	A/SA-182	F11, Cl. 1
4	1	A/SA-182	F11, Cl. 2
4	1	A/SA-182	F11, Cl. 3
4	1	A/SA-182	F12, Cl. 1
4	1	A/SA-182	F12, Cl. 2
4	1	A199	T11
4	1	A/SA-202	A
4	1	A/SA-202	B
4	1	A/SA-213	T11
4	1	A/SA-213	T12
4	1	A/SA-217	WC4
4	1	A/SA-217	WC5
4	1	A/SA-217	WC6
4	1	A/SA-234	WP11, Cl. 1
4	1	A/SA-234	WP12, Cl. 1
4	1	A/SA-234	WP11, Cl. 3
4	1	A/SA-234	WP12, Cl. 2
4	1	A/SA-250	T11
4	1	A/SA-250	T12
4	1	A/SA-335	P11
4	1	A/SA-335	P12
4	1	A/SA-336	F11, Cl. 2
4	1	A/SA-336	F11, Cl. 3
4	1	A/SA-336	F11, Cl. 1
4	1	A/SA-336	F12
4	1	A356	6
4	1	A356	8
4	1	A356	9
4	1	A/SA-369	FP11
4	1	A/SA-369	FP12
4	1	A/SA-387	11, Cl. 1
4	1	A/SA-387	11, Cl. 2
4	1	A/SA-387	12, Cl. 1
4	1	A/SA-387	12, Cl. 2
4	1	A/SA-426	CP11
4	1	A/SA-426	CP12
4	1	A/SA-541	11, Cl. 4
4	1	A/SA-691	1CR
4	1	A/SA-691	1 1/4 CR

2013 SECTION IX

P-No.	Grp. No.	Spec. No.	Type, Grade, or UNS No.
Steel and Steel Alloys (Cont'd)			
4	1	A/SA-739	B11
4	1	SA/EN 10028-2	13CrMo4-5
4	1	SA/EN 10028-2	13CrMoSi5-5+QT
4	1	SA/EN 10216-2	13CrMo4-5
4	1	SA/EN 10222-2	13CrMo4-5
4	1	SA/GB 713	15CrMoR
4	2	A/SA-333	4
4	2	A/SA-423	1
4	2	A/SA-423	2
5A	1	A/SA-182	F21
5A	1	A/SA-182	F22, Cl. 1
5A	1	A/SA-182	F22, Cl. 3
5A	1	A199	T21
5A	1	A199	T22
5A	1	A/SA-213	T21
5A	1	A/SA-213	T22
5A	1	A/SA-217	WC9
5A	1	A/SA-234	WP22, Cl. 1
5A	1	A/SA-234	WP22, Cl. 3
5A	1	A/SA-250	T22
5A	1	A/SA-335	P21
5A	1	A/SA-335	P22
5A	1	A/SA-336	F21, Cl. 3
5A	1	A/SA-336	F21, Cl. 1
5A	1	A/SA-336	F22, Cl. 3
5A	1	A/SA-336	F22, Cl. 1
5A	1	A356	10
5A	1	A/SA-369	FP21
5A	1	A/SA-369	FP22
5A	1	A/SA-387	21, Cl. 1
5A	1	A/SA-387	21, Cl. 2
5A	1	A/SA-387	22, Cl. 1
5A	1	A/SA-387	22, Cl. 2
5A	1	A/SA-426	CP21
5A	1	A/SA-426	CP22
5A	1	A/SA-691	2 $\frac{1}{4}$ CR
5A	1	A/SA-691	3CR
5A	1	A/SA-739	B22
5A	1	SA/EN 10028-2	10CrMo9-10
5A	1	SA/EN 10216-2	10CrMo9-10
5A	1	SA/EN 10222-2	11CrMo9-10
5B	1	A/SA-182	F5
5B	1	A/SA-182	F5a
5B	1	A/SA-182	F9
5B	1	A199	T5
5B	1	A199	T9
5B	1	A/SA-213	T5
5B	1	A/SA-213	T5b
5B	1	A/SA-213	T5c
5B	1	A/SA-213	T9
5B	1	A/SA-217	C5
5B	1	A/SA-217	C12
5B	1	A/SA-234	WP5

P-No.	Grp. No.	Spec. No.	Type, Grade, or UNS No.
Steel and Steel Alloys (Cont'd)			
5B	1	A/SA-234	WP9
5B	1	A/SA-234	WP5, cl.3
5B	1	A/SA-234	WP9, cl.3
5B	1	A/SA-335	P5
5B	1	A/SA-335	P5b
5B	1	A/SA-335	P5c
5B	1	A/SA-335	P9
5B	1	A/SA-336	F5
5B	1	A/SA-336	F5A
5B	1	A/SA-336	F9
5B	1	A/SA-369	FP5
5B	1	A/SA-369	FP9
5B	1	A/SA-387	5, Cl. 1
5B	1	A/SA-387	5, Cl. 2
5B	1	A/SA-387	9, Cl. 1
5B	1	A/SA-387	9, Cl. 2
5B	1	A/SA-426	CP5
5B	1	A/SA-426	CP5b
5B	1	A/SA-426	CP9
5B	1	A/SA-691	5CR
5C	1	A/SA-182	F3V
5C	1	A/SA-182	F3VCb
5C	1	A/SA-182	F22V
5C	1	A/SA-336	F3V
5C	1	A/SA-336	F3VCb
5C	1	A/SA-336	F22V
5C	1	A/SA-487	Gr. 8 Cl. A
5C	1	A/SA-508	3V
5C	1	A/SA-508	3VCb
5C	1	A/SA-508	22, Cl. 3
5C	1	A/SA-541	3V
5C	1	A/SA-541	3VCb
5C	1	A/SA-541	22V
5C	1	A/SA-541	22, Cl. 3
5C	1	A/SA-542	A, Cl. 4
5C	1	A/SA-542	A, Cl. 4a
5C	1	A/SA-542	B, Cl. 4
5C	1	A/SA-542	B, Cl. 4a
5C	1	A/SA-542	C, Cl. 4
5C	1	A/SA-542	C, Cl. 4a
5C	1	A/SA-542	D, Cl. 4a
5C	1	A/SA-542	E, Cl. 4a
5C	1	A/SA-832	21V
5C	1	A/SA-832	22V
5C	1	A/SA-832	23V
5C	3	A/SA-542	A, Cl. 3
5C	3	A/SA-542	B, Cl. 3
5C	3	A/SA-542	C, Cl. 3
5C	4	A/SA-487	Gr. 8 Cl. B
5C	4	A/SA-487	Gr. 8 Cl. C
5C	4	A/SA-541	22, Cl. 4
5C	4	A/SA-542	A, Cl. 1
5C	4	A/SA-542	B, Cl. 1
5C	4	A/SA-542	C, Cl. 1
5C	5	A/SA-541	22, Cl. 5
5C	5	A/SA-542	A, Cl. 2

2013 SECTION IX

P-No.	Grp. No.	Spec. No.	Type, Grade, or UNS No.
Steel and Steel Alloys (Cont'd)			
5C	5	A/SA-542	B, Cl. 2
5C	5	A/SA-542	C, Cl. 2
6	1	A/SA-182	F6a, Cl. 1
6	1	A/SA-240	410
6	1	A/SA-268	TP410
6	1	A/SA-276	TP410
6	1	A/SA-479	403
6	1	A/SA-479	410
6	2	A/SA-182	F429
6	2	A/SA-240	429
6	2	A/SA-268	TP429
6	3	A/SA-182	F6a, Cl. 2
6	3	A/SA-182	F6b
6	3	A/SA-182	F6a, Cl. 3
6	3	A/SA-182	F6a, Cl. 4
6	3	A/SA-217	CA15
6	3	A/SA-336	F6
6	3	A/SA-426	CPCA15
6	3	A/SA-487	CA15 Cl. B
6	3	A/SA-487	CA15 Cl. C
6	3	A/SA-487	CA15 Cl. D
6	3	A/SA-487	CA15M Cl. A
6	4	A/SA-182	F6NM
6	4	A/SA-240	S41500
6	4	A/SA-268	S41500
6	4	A/SA-352	CA6NM
6	4	A/SA-479	414
6	4	A/SA-479	S41500
6	4	A/SA-487	CA6NM Cl. A
6	4	A/SA-487	CA6NM Cl. B
6	4	A/SA-731	S41500
6	4	A/SA-815	S41500
7	1	A/SA-240	Type 405
7	1	A/SA-240	Type 409
7	1	A/SA-240	Type 410S
7	1	A/SA-268	S40800
7	1	A/SA-268	TP405
7	1	A/SA-268	TP409
7	1	A/SA-479	405
7	1	A/SA-1010	40
7	1	A/SA-1010	50
7	1	SA/JIS G4303	SUS405
7	2	A/SA-182	F430
7	2	A/SA-240	S44400
7	2	A/SA-240	Type 430
7	2	A/SA-240	Type 439
7	2	A/SA-240	S43932
7	2	A/SA-268	18Cr-2Mo
7	2	A/SA-268	TP430Ti
7	2	A/SA-268	TP430
7	2	A/SA-268	TP439
7	2	A/SA-479	430
7	2	A/SA-479	439
7	2	A/SA-479	S44400
7	2	A/SA-731	18Cr-2Mo

P-No.	Grp. No.	Spec. No.	Type, Grade, or UNS No.
Steel and Steel Alloys (Cont'd)			
7	2	A/SA-731	TP439
7	2	A/SA-803	TP439
8	1	A167	Type 302B
8	1	A/SA-182	S30600
8	1	A/SA-182	F304
8	1	A/SA-182	F304H
8	1	A/SA-182	F304L
8	1	A/SA-182	F304LN
8	1	A/SA-182	F304N
8	1	A/SA-182	F316
8	1	A/SA-182	F316H
8	1	A/SA-182	F316L
8	1	A/SA-182	F316LN
8	1	A/SA-182	F316N
8	1	A/SA-182	F317
8	1	A/SA-182	F317L
8	1	A/SA-182	F321
8	1	A/SA-182	F321H
8	1	A/SA-182	F347
8	1	A/SA-182	F347H
8	1	A/SA-182	F348
8	1	A/SA-182	F348H
8	1	A/SA-213	TP304
8	1	A/SA-213	TP304H
8	1	A/SA-213	TP304L
8	1	A/SA-213	TP304LN
8	1	A/SA-213	TP304N
8	1	A/SA-213	S32615
8	1	A/SA-213	TP316
8	1	A/SA-213	TP316H
8	1	A/SA-213	TP316Ti
8	1	A/SA-213	TP316L
8	1	A/SA-213	TP316LN
8	1	A/SA-213	TP316N
8	1	A/SA-213	TP321
8	1	A/SA-213	TP321H
8	1	A/SA-213	TP347
8	1	A/SA-213	TP347H
8	1	A/SA-213	TP347HFG
8	1	A/SA-213	TP347LN
8	1	A/SA-213	TP317
8	1	A/SA-213	TP317L
8	1	A/SA-213	TP348
8	1	A/SA-213	TP348H
8	1	A/SA-213	XM-15
8	1	A269	TP304
8	1	A269	TP304L
8	1	A269	TP316
8	1	A269	TP316L
8	1	A/SA-276	TP304
8	1	A/SA-276	TP304L
8	1	A/SA-276	TP316
8	1	A/SA-276	TP316L
8	1	A/SA-240	S30500
8	1	A/SA-240	S30600

2013 SECTION IX

P-No.	Grp. No.	Spec. No.	Type, Grade, or UNS No.
Steel and Steel Alloys (<i>Cont'd</i>)			
8	1	A/SA-240	S30601
8	1	A/SA-240	S31753
8	1	A/SA-240	S32615
8	1	A/SA-240	Type 301
8	1	A/SA-240	Type 302
8	1	A/SA-240	Type 304
8	1	A/SA-240	Type 304H
8	1	A/SA-240	Type 304L
8	1	A/SA-240	Type 304LN
8	1	A/SA-240	Type 304N
8	1	A/SA-240	Type 316
8	1	A/SA-240	Type 316Cb
8	1	A/SA-240	Type 316H
8	1	A/SA-240	Type 316L
8	1	A/SA-240	Type 316LN
8	1	A/SA-240	Type 316N
8	1	A/SA-240	Type 316Ti
8	1	A/SA-240	Type 317
8	1	A/SA-240	Type 317L
8	1	A/SA-240	Type 321
8	1	A/SA-240	Type 321H
8	1	A/SA-240	Type 347
8	1	A/SA-240	Type 347H
8	1	A/SA-240	Type 348
8	1	A/SA-240	Type 348H
8	1	A/SA-240	Type XM-15
8	1	A/SA-240	Type XM-21
8	1	A/SA-249	TP304
8	1	A/SA-249	TP304H
8	1	A/SA-249	TP304L
8	1	A/SA-249	TP304LN
8	1	A/SA-249	TP304N
8	1	A/SA-249	TP316
8	1	A/SA-249	TP316H
8	1	A/SA-249	TP316L
8	1	A/SA-249	TP316LN
8	1	A/SA-249	TP316N
8	1	A/SA-249	TP317
8	1	A/SA-249	TP317L
8	1	A/SA-249	TP321
8	1	A/SA-249	TP321H
8	1	A/SA-249	TP347
8	1	A/SA-249	TP347H
8	1	A/SA-249	TP348
8	1	A/SA-249	TP348H
8	1	A/SA-249	TP XM-15
8	1	A269	TP304
8	1	A269	TP304L
8	1	A269	TP316
8	1	A269	TP316L
8	1	A276	TP304
8	1	A276	TP304L
8	1	A276	TP316
8	1	A276	TP316L
8	1	A/SA-312	S30600

P-No.	Grp. No.	Spec. No.	Type, Grade, or UNS No.
Steel and Steel Alloys (<i>Cont'd</i>)			
8	1	A/SA-312	S32615
8	1	A/SA-312	TP304
8	1	A/SA-312	TP304H
8	1	A/SA-312	TP304L
8	1	A/SA-312	TP304LN
8	1	A/SA-312	TP304N
8	1	A/SA-312	TP316
8	1	A/SA-312	TP316H
8	1	A312	S31635
8	1	A/SA-312	TP316L
8	1	A/SA-312	TP316LN
8	1	A/SA-312	TP316N
8	1	A/SA-312	TP317
8	1	A/SA-312	TP317L
8	1	A/SA-312	TP321
8	1	A/SA-312	TP321H
8	1	A/SA-312	TP347
8	1	A/SA-312	TP347H
8	1	A/SA-312	TP347LN
8	1	A/SA-312	TP348
8	1	A/SA-312	TP348H
8	1	A/SA-312	TP XM-15
8	1	A/SA-351	CF3
8	1	A/SA-351	CF3A
8	1	A/SA-351	CF3M
8	1	A/SA-351	CF8
8	1	A/SA-351	CF8A
8	1	A/SA-351	CF8C
8	1	A/SA-351	CF8M
8	1	A/SA-351	CF10
8	1	A/SA-351	CF10M
8	1	A/SA-351	CG8M
8	1	A/SA-351	CF10MC
8	1	A/SA-358	304
8	1	A/SA-358	304H
8	1	A/SA-358	304L
8	1	A/SA-358	304LN
8	1	A/SA-358	304N
8	1	A/SA-358	316
8	1	A/SA-358	316H
8	1	A/SA-358	316L
8	1	A/SA-358	316LN
8	1	A/SA-358	316N
8	1	A/SA-358	321
8	1	A/SA-358	347
8	1	A/SA-358	348
8	1	A/SA-376	16-8-2H
8	1	A/SA-376	TP304
8	1	A/SA-376	TP304H
8	1	A/SA-376	TP304LN
8	1	A/SA-376	TP304N
8	1	A/SA-376	TP316
8	1	A/SA-376	TP316H
8	1	A/SA-376	TP316LN
8	1	A/SA-376	TP316N

2013 SECTION IX

P-No.	Grp. No.	Spec. No.	Type, Grade, or UNS No.
Steel and Steel Alloys (Cont'd)			
8	1	A/SA-376	TP321
8	1	A/SA-376	TP321H
8	1	A/SA-376	TP347
8	1	A/SA-376	TP347H
8	1	A/SA-376	TP348
8	1	A/SA-376	16-8-2H
8	1	A/SA-403	WP304
8	1	A/SA-403	WP304H
8	1	A/SA-403	WP304L
8	1	A/SA-403	WP304LN
8	1	A/SA-403	WP304N
8	1	A/SA-403	WP316
8	1	A/SA-403	WP316H
8	1	A/SA-403	WP316L
8	1	A/SA-403	WP316LN
8	1	A/SA-403	WP316N
8	1	A/SA-403	WP317
8	1	A/SA-403	WP317L
8	1	A/SA-403	WP321
8	1	A/SA-403	WP321H
8	1	A/SA-403	WP347
8	1	A/SA-403	WP347H
8	1	A/SA-403	WP348
8	1	A/SA-403	WP348H
8	1	A/SA-409	TP304
8	1	A/SA-409	TP304L
8	1	A/SA-409	TP316
8	1	A/SA-409	TP316L
8	1	A/SA-409	TP317
8	1	A/SA-409	TP321
8	1	A/SA-409	TP347
8	1	A/SA-409	TP348
8	1	A/SA-451	CPF3
8	1	A/SA-451	CPF3A
8	1	A/SA-451	CPF3M
8	1	A/SA-451	CPF8
8	1	A/SA-451	CPF8A
8	1	A/SA-451	CPF8C
8	1	A/SA-451	CPF8M
8	1	A/SA-451	CPF10MC
8	1	A/SA-479	302
8	1	A/SA-479	304
8	1	A/SA-479	304H
8	1	A/SA-479	304L
8	1	A/SA-479	304LN
8	1	A/SA-479	304N
8	1	A/SA-479	316
8	1	A/SA-479	316Cb
8	1	A/SA-479	316H
8	1	A/SA-479	316L
8	1	A/SA-479	316LN
8	1	A/SA-479	316N
8	1	A/SA-479	316Ti
8	1	A/SA-479	321
8	1	A/SA-479	321H
8	1	A/SA-479	347
8	1	A/SA-479	347H
8	1	A/SA-479	348

P-No.	Grp. No.	Spec. No.	Type, Grade, or UNS No.
Steel and Steel Alloys (Cont'd)			
8	1	A/SA-479	348H
8	1	A/SA-479	S30600
8	1	A/SA-479	S32615
8	1	A/SA-666	302
8	1	A/SA-666	304
8	1	A/SA-666	304L
8	1	A/SA-666	304LN
8	1	A/SA-666	304N
8	1	A/SA-666	316
8	1	A/SA-666	316L
8	1	A/SA-666	316N
8	1	A/SA-688	TP304
8	1	A/SA-688	TP304L
8	1	A/SA-688	TP304LN
8	1	A/SA-688	TP304N
8	1	A/SA-688	TP316
8	1	A/SA-688	TP316L
8	1	A/SA-688	TP316LN
8	1	A/SA-688	TP316N
8	1	A/SA-813	TP304
8	1	A/SA-813	TP304H
8	1	A/SA-813	TP304L
8	1	A/SA-813	TP304LN
8	1	A/SA-813	TP304N
8	1	A/SA-813	TP316
8	1	A/SA-813	TP316H
8	1	A/SA-813	TP316L
8	1	A/SA-813	TP316LN
8	1	A/SA-813	TP316N
8	1	A/SA-813	TP317
8	1	A/SA-813	TP317L
8	1	A/SA-813	TP321
8	1	A/SA-813	TP321H
8	1	A/SA-813	TP347
8	1	A/SA-813	TP347H
8	1	A/SA-813	TP348
8	1	A/SA-813	TP348H
8	1	A/SA-813	TPXM-15
8	1	A/SA-814	TP304
8	1	A/SA-814	TP304H
8	1	A/SA-814	TP304L
8	1	A/SA-814	TP304LN
8	1	A/SA-814	TP304N
8	1	A/SA-814	TP316
8	1	A/SA-814	TP316H
8	1	A/SA-814	TP316L
8	1	A/SA-814	TP316LN
8	1	A/SA-814	TP316N
8	1	A/SA-814	TP317
8	1	A/SA-814	TP317L
8	1	A/SA-814	TP321
8	1	A/SA-814	TP321H
8	1	A/SA-814	TP347
8	1	A/SA-814	TP347H
8	1	A/SA-814	TP348
8	1	A/SA-814	TP348H
8	1	A/SA-814	TPXM-15

2013 SECTION IX

P-No.	Grp. No.	Spec. No.	Type, Grade, or UNS No.
Steel and Steel Alloys (<i>Cont'd</i>)			
8	1	A/SA-965	F304
8	1	A/SA-965	F304H
8	1	A/SA-965	F304L
8	1	A/SA-965	F304LN
8	1	A/SA-965	F304N
8	1	A/SA-965	F316
8	1	A/SA-965	F316H
8	1	A/SA-965	F316L
8	1	A/SA-965	F316LN
8	1	A/SA-965	F316N
8	1	A/SA-965	F321
8	1	A/SA-965	F321H
8	1	A/SA-965	F347
8	1	A/SA-965	F347H
8	1	A/SA-965	F348
8	1	A/SA-965	F348H
8	1	SA/EN 10028-7	X5CrNi18-10
8	1	SA/EN 10028-7	X5CrNiMo17-12-2
8	1	SA/EN 10028-7	X2CrNi18-9
8	1	SA/EN 10028-7	X5CrNiN19-9
8	1	SA/EN 10028-7	X2CrNiN18-10
8	1	SA/EN 10028-7	X2CrNiMo17-12-2
8	1	SA/EN 10028-7	X2CrNiMoN17-11-2
8	1	SA/EN 10028-7	X2CrNiMoN17-13-3
8	1	SA/EN 10028-7	X6CrNiTi18-10
8	1	SA/EN 10088-2	X6CrNiMoTi17-12-2
8	1	SA/JIS G4303	SUS302
8	1	SA/JIS G4303	SUS304
8	1	SA/JIS G4303	SUS304L
8	1	SA/JIS G4303	SUS316
8	1	SA/JIS G4303	SUS316L
8	1	SA/JIS G4303	SUS321
8	1	SA/JIS G4303	SUS347
8	2	A167	Type 308
8	2	A167	Type 309
8	2	A167	Type 310
8	2	A/SA-182	F10
8	2	A/SA-182	F45
8	2	A/SA-182	F310
8	2	A/SA-182	F310MoLN
8	2	A/SA-213	S30815
8	2	A/SA-213	TP309Cb
8	2	A/SA-213	TP309H
8	2	A/SA-213	TP309S
8	2	A/SA-213	TP310Cb
8	2	A/SA-213	TP310S
8	2	A/SA-213	TP309HCb
8	2	A/SA-213	TP310H
8	2	A/SA-213	TP310MoLN
8	2	A/SA-213	TP310HCb
8	2	A/SA-240	S30815
8	2	A/SA-240	Type 309Cb
8	2	A/SA-240	Type 309H
8	2	A/SA-240	Type 309HCb
8	2	A/SA-240	Type 309S

P-No.	Grp. No.	Spec. No.	Type, Grade, or UNS No.
Steel and Steel Alloys (<i>Cont'd</i>)			
8	2	A/SA-240	Type 310Cb
8	2	A/SA-240	Type 310HCb
8	2	A/SA-240	Type 310MoLN
8	2	A/SA-240	Type 310S
8	2	A/SA-249	S30815
8	2	A/SA-249	TP309Cb
8	2	A/SA-249	TP309H
8	2	A/SA-249	TP309HCb
8	2	A/SA-249	TP309S
8	2	A/SA-249	TP310Cb
8	2	A/SA-249	TP310H
8	2	A/SA-249	TP310S
8	2	A/SA-249	TP310MoLN
8	2	A/SA-312	S30815
8	2	A/SA-312	TP309Cb
8	2	A/SA-312	TP309H
8	2	A/SA-312	TP309HCb
8	2	A/SA-312	TP309S
8	2	A/SA-312	TP310Cb
8	2	A/SA-312	TP310H
8	2	A/SA-312	TP310HCb
8	2	A/SA-312	TP310S
8	2	A/SA-312	TP310MoLN
8	2	A/SA-351	CH8
8	2	A/SA-351	CH20
8	2	A/SA-351	CK20
8	2	A/SA-351	CE20N
8	2	A/SA-351	CH10
8	2	A/SA-351	HK30
8	2	A/SA-351	HK40
8	2	A/SA-358	309
8	2	A/SA-358	309Cb
8	2	A/SA-358	309S
8	2	A/SA-358	310Cb
8	2	A/SA-358	310S
8	2	A/SA-358	S30815
8	2	A/SA-403	WP309
8	2	A/SA-403	WP310S
8	2	A/SA-409	S30815
8	2	A/SA-409	TP309Cb
8	2	A/SA-409	TP309S
8	2	A/SA-409	TP310Cb
8	2	A/SA-409	TP310S
8	2	A/SA-451	CPH8
8	2	A/SA-451	CPH20
8	2	A/SA-451	CPK20
8	2	A/SA-451	CPE20N
8	2	SA-479	309Cb
8	2	A/SA-479	309S
8	2	SA/JIS G4303	SUS309S
8	2	A/SA-479	310Cb
8	2	A/SA-479	310S
8	2	SA/JIS G4303	SUS310S
8	2	A/SA-479	S30815
8	2	A/SA-813	S30815

2013 SECTION IX

P-No.	Grp. No.	Spec. No.	Type, Grade, or UNS No.
Steel and Steel Alloys (Cont'd)			
8	2	A/SA-813	TP309Cb
8	2	A/SA-813	TP309S
8	2	A/SA-813	TP310Cb
8	2	A/SA-813	TP310S
8	2	A/SA-814	S30815
8	2	A/SA-814	TP309Cb
8	2	A/SA-814	TP309S
8	2	A/SA-814	TP310Cb
8	2	A/SA-814	TP310S
8	2	A/SA-965	F310
8	3	A/SA-182	FXM-11
8	3	A/SA-182	FXM-19
8	3	A/SA-213	TP201
8	3	A/SA-213	TP202
8	3	A/SA-213	XM-19
8	3	A/SA-213	S31042
8	3	A/SA-240	S20100
8	3	A/SA-240	S21800
8	3	A/SA-240	S20153
8	3	A/SA-240	Type 202
8	3	A/SA-240	S20400
8	3	A/SA-240	Type XM-17
8	3	A/SA-240	Type XM-18
8	3	A/SA-240	Type XM-19
8	3	A/SA-240	Type XM-29
8	3	A/SA-249	TP201
8	3	A/SA-249	TP202
8	3	A/SA-249	TPXM-19
8	3	A/SA-249	TPXM-29
8	3	A/SA-312	TPXM-11
8	3	A/SA-312	TPXM-19
8	3	A/SA-312	TPXM-29
8	3	A/SA-351	CG6MMN
8	3	A/SA-358	XM-19
8	3	A/SA-358	XM-29
8	3	A/SA-403	WPXM-19
8	3	A/SA-479	S21800
8	3	A/SA-479	XM-11
8	3	A/SA-479	XM-17
8	3	A/SA-479	XM-18
8	3	A/SA-479	XM-19
8	3	A/SA-479	XM-29
8	3	A/SA-666	201
8	3	A/SA-666	XM-11
8	3	A/SA-688	XM-29
8	3	A/SA-813	TPXM-11
8	3	A/SA-813	TPXM-19
8	3	A/SA-813	TPXM-29
8	3	A/SA-814	TPXM-11
8	3	A/SA-814	TPXM-19
8	3	A/SA-814	TPXM-29
8	3	A/SA-965	FXM-11
8	3	A/SA-965	FXM-19
8	4	A/SA-182	F44
8	4	A/SA-182	S32053

P-No.	Grp. No.	Spec. No.	Type, Grade, or UNS No.
Steel and Steel Alloys (Cont'd)			
8	4	A/SA-182	S34565
8	4	A/SA-213	S31725
8	4	A/SA-213	S31726
8	4	A/SA-213	S34565
8	4	A/SA-240	S31254
8	4	A/SA-240	S31725
8	4	A/SA-240	S31726
8	4	A/SA-240	S32053
8	4	A/SA-240	S34565
8	4	A/SA-249	S31254
8	4	A/SA-249	S31725
8	4	A/SA-249	S31726
8	4	A/SA-249	S32053
8	4	A/SA-249	S34565
8	4	A/SA-312	S31254
8	4	A/SA-312	S31725
8	4	A/SA-312	S31726
8	4	A/SA-312	S32053
8	4	A/SA-312	S34565
8	4	A/SA-351	J93254
8	4	A/SA-358	S31254
8	4	A/SA-358	S31725
8	4	A/SA-358	S31726
8	4	A/SA-358	S32053
8	4	A/SA-376	S31725
8	4	A/SA-376	S31726
8	4	A/SA-376	S34565
8	4	A/SA-403	S31254
8	4	A/SA-403	S32053
8	4	A/SA-403	S34565
8	4	A/SA-409	S31254
8	4	A/SA-409	S31725
8	4	A/SA-409	S31726
8	4	A/SA-409	S32053
8	4	A/SA-409	S34565
8	4	A/SA-479	S31254
8	4	A/SA-479	S31725
8	4	A/SA-479	S31726
8	4	A/SA-479	S32053
8	4	A/SA-479	S34565
8	4	A/SA-813	S31254
8	4	A/SA-813	S32053
8	4	A/SA-814	S31254
8	4	A/SA-814	S32053
8	4	SA-965	F46
9A	1	A/SA-182	FR
9A	1	A/SA-203	A
9A	1	A/SA-203	B
9A	1	A/SA-234	WPR
9A	1	A/SA-333	7
9A	1	A/SA-333	9
9A	1	A/SA-334	7
9A	1	A/SA-334	9

2013 SECTION IX

P-No.	Grp. No.	Spec. No.	Type, Grade, or UNS No.
Steel and Steel Alloys (<i>Cont'd</i>)			
9A	1	A/SA-350	LF5, Cl. 1
9A	1	A/SA-350	LF5, Cl. 2
9A	1	A/SA-350	LF9
9A	1	A/SA-352	LC2
9A	1	A/SA-420	WPL9
9A	1	A714	Gr. V
9A	1	A714	Gr. V, Tp. E
9B	1	A/SA-203	D
9B	1	A/SA-203	E
9B	1	A/SA-203	F
9B	1	A/SA-333	3
9B	1	A/SA-334	3
9B	1	A/SA-350	LF3, Cl. 2
9B	1	A/SA-352	LC3
9B	1	A/SA-420	WPL3
9B	1	A/SA-765	III
9C	1	A/SA-352	LC4
10A	1	A/SA-225	C
10A	1	A/SA-225	D
10A	1	A/SA-487	Gr. 1, Cl. A
10A	1	A/SA-487	Gr. 1, Cl. B
10A	1	SA/NF A 36-215	NJ4
10B	1	A/SA-213	T17
10C	1	A/SA-612	...
10H	1	A/SA-182	F53
10H	1	A/SA-182	F50
10H	1	A/SA-182	F51
10H	1	A/SA-182	F54
10H	1	A/SA-182	F55
10H	1	A/SA-182	S32202
10H	1	A/SA-182	F60
10H	1	A/SA-240	S31200
10H	1	A/SA-240	S31260
10H	1	A/SA-240	S31803
10H	1	A/SA-240	S32003
10H	1	A/SA-240	S32101
10H	1	A/SA-240	S32202
10H	1	A/SA-240	S32205
10H	1	A/SA-240	S32550
10H	1	A/SA-240	S32750
10H	1	A/SA-240	S32760
10H	1	A/SA-240	S32906
10H	1	A/SA-240	S32950
10H	1	A/SA-240	Type 329
10H	1	A/SA-276	S32205
10H	1	A/SA-351	CD3MWCuN
10H	1	A/SA-479	S31803
10H	1	A/SA-479	S32202
10H	1	A/SA-479	S32101
10H	1	A/SA-479	S32205
10H	1	A/SA-479	S32550
10H	1	A/SA-479	S32750
10H	1	A/SA-479	S32906
10H	1	A/SA-789	S31200

P-No.	Grp. No.	Spec. No.	Type, Grade, or UNS No.
Steel and Steel Alloys (<i>Cont'd</i>)			
10H	1	A/SA-789	S31260
10H	1	A/SA-789	S31500
10H	1	A/SA-789	S31803
10H	1	A/SA-789	S32003
10H	1	A/SA-789	S32101
10H	1	A/SA-789	S32202
10H	1	A/SA-789	S32205
10H	1	A/SA-789	S32304
10H	1	A/SA-789	S32550
10H	1	A/SA-789	S32750
10H	1	A/SA-789	S32760
10H	1	A/SA-789	S32900
10H	1	A/SA-789	S32906
10H	1	A/SA-789	S32950
10H	1	A/SA-789	S39274
10H	1	A/SA-790	S31200
10H	1	A/SA-790	S31260
10H	1	A/SA-790	S31500
10H	1	A/SA-790	S31803
10H	1	A/SA-790	S32003
10H	1	A/SA-790	S32101
10H	1	A/SA-790	S32202
10H	1	A/SA-790	S32205
10H	1	A/SA-790	S32304
10H	1	A/SA-790	S32550
10H	1	A/SA-790	S32750
10H	1	A/SA-790	S32760
10H	1	A/SA-790	S32900
10H	1	A/SA-790	S32906
10H	1	A/SA-790	S32950
10H	1	A/SA-790	S39274
10H	1	A/SA-815	S31803
10H	1	A/SA-815	S32202
10H	1	A/SA-815	S32101
10H	1	A/SA-815	S32205
10H	1	A815	S32750
10H	1	A/SA-815	S32760
10H	1	A890	J93380
10H	1	A890	J92205
10H	1	A928	S32760
10H	1	A928	S32205
10H	1	A/SA-995	J93345
10H	1	A/SA-995	J93372
10H	1	A/SA-995	J93380
10H	1	A/SA-995	J92205
10I	1	A/SA-182	FXM-27Cb
10I	1	A/SA-240	S44635
10I	1	A/SA-240	Type XM-27
10I	1	A/SA-240	Type XM-33
10I	1	A/SA-268	25-4-4
10I	1	A/SA-268	TP446-1
10I	1	A/SA-268	TP446-2
10I	1	A/SA-268	TPXM-27
10I	1	A/SA-268	TPXM-33
10I	1	A/SA-336	FXM-27Cb
10I	1	A/SA-479	XM-27
10I	1	A/SA-731	TPXM-27

2013 SECTION IX

P-No.	Grp. No.	Spec. No.	Type, Grade, or UNS No.
Steel and Steel Alloys (Cont'd)			
10I	1	A/SA-731	TPXM-33
10J	1	A/SA-240	S44700
10J	1	A/SA-268	S44700
10J	1	A/SA-268	S44735
10J	1	A/SA-479	S44700
10J	1	A/SA-731	S44700
10K	1	A/SA-240	S44660
10K	1	A/SA-240	S44800
10K	1	A/SA-268	S44660
10K	1	A/SA-268	S44800
10K	1	A/SA-479	S44800
10K	1	A/SA-731	S44660
10K	1	A/SA-731	S44800
10K	1	A/SA-803	S44660
11A	1	A/SA-333	8
11A	1	A/SA-334	8
11A	1	A/SA-353	...
11A	1	A/SA-420	WPL8
11A	1	A/SA-522	Type I
11A	1	A/SA-522	Type II
11A	1	A/SA-553	Type I
11A	1	A/SA-553	Type II
11A	2	A/SA-645	A
11A	3	A/SA-487	Gr. 4, Cl. B
11A	3	A/SA-487	Gr. 4, Cl. E
11A	4	A/SA-533	Type A, Cl. 3
11A	4	A/SA-533	Type B, Cl. 3
11A	4	A/SA-533	Type C, Cl. 3
11A	4	A/SA-533	Type D, Cl. 3
11A	4	A/SA-672	J100
11A	5	A/SA-352	LC2-1
11A	5	A/SA-508	4N, Cl. 1
11A	5	A/SA-508	5, Cl. 1
11A	5	A/SA-543	B Cl. 1
11A	5	A/SA-543	C Cl. 1
11A	1	SA/EN 10028-4	X8Ni9
11A	1	SA/EN 10028-4	X7Ni9
11B	1	A514	A
11B	1	A/SA-517	A
11B	1	A/SA-592	A
11B	2	A514	E
11B	2	A/SA-517	E
11B	2	A/SA-592	E
11B	3	A514	F
11B	3	A/SA-517	F
11B	3	A/SA-592	F
11B	4	A514	B
11B	4	A/SA-517	B
11B	8	A514	P
11B	8	A/SA-517	P
11B	9	A514	Q
11B	10	A/SA-508	4N, Cl. 2

P-No.	Grp. No.	Spec. No.	Type, Grade, or UNS No.
Steel and Steel Alloys (Cont'd)			
11B	10	A/SA-508	5, Cl. 2
11B	10	A/SA-543	B Cl. 2
11B	10	A/SA-543	C Cl. 2
11C	1	A/SA-859	A
15E	1	A/SA-182	F91
15E	1	A/SA-182	F92
15E	1	A/SA-213	T91
15E	1	A/SA-213	T92
15E	1	A/SA-217	C12A
15E	1	A/SA-234	WP91
15E	1	A/SA-335	P91
15E	1	A/SA-335	P92
15E	1	A/SA-336	F91
15E	1	A356	12A
15E	1	A/SA-369	FP91
15E	1	A/SA-369	FP92
15E	1	A/SA-691	91
15E	1	A/SA-387	Gr. 91, Cl. 2
15E	1	SA/EN 10222-2	X10CrMoVNb9-1
15E	1	SA/EN 10216-2	X10CrMoVNb9-1
Aluminum and Aluminum-Base Alloys			
21	...	B/SB-26	A03560
21	...	B/SB-26	A24430
21	...	B/SB-209	A91060
21	...	B/SB-209	A91100
21	...	B/SB-209	A93003
21	...	B/SB-209	A95050
21	...	B/SB-210	A91060
21	...	B/SB-210	A93003
21	...	B/SB-221	A91060
21	...	B/SB-221	A91100
21	...	B/SB-221	A93003
21	...	B/SB-234	A91060
21	...	B/SB-234	A93003
21	...	B/SB-241	A91060
21	...	B/SB-241	A91100
21	...	B/SB-241	A93003
21	...	B/SB-247	A93003
21	...	B345	A91060
21	...	B345	A93003
21	...	B361	A83003
21	...	B361	A91060
21	...	B361	A91100
21	...	B361	A93003
21	...	B491	A93003
21	...	B547	A93003
21	...	B547	A83003
22	...	B/SB-209	A93004
22	...	B/SB-209	A95052
22	...	B/SB-209	A95154
22	...	B/SB-209	A95254
22	...	B/SB-209	A95454
22	...	B/SB-209	A95652
22	...	B/SB-210	A95052
22	...	B/SB-210	A95154

2013 SECTION IX

P-No.	Grp. No.	Spec. No.	Type, Grade, or UNS No.
-------	----------	-----------	-------------------------

Aluminum and Aluminum-Base Alloys (Cont'd)

22	...	B/SB-221	A95154
22	...	B/SB-221	A95454
22	...	B/SB-234	A95052
22	...	B/SB-234	A95454
22	...	B/SB-241	A95052
22	...	B/SB-241	A95454
22	...	B361	A95154
22	...	B547	A95454
23	...	B/SB-209	A96061
23	...	B/SB-210	A96061
23	...	B/SB-210	A96063
23	...	B/SB-211	A96061
23	...	B/SB-221	A96061
23	...	B/SB-221	A96063
23	...	B/SB-234	A96061
23	...	B/SB-241	A96061
23	...	B/SB-241	A96063
23	...	B/SB-247	A96061
23	...	B/SB-308	A96061
23	...	B345	A96061
23	...	B345	A96063
23	...	B361	A96061
23	...	B361	A96063
23	...	B547	A96061
25	...	B/SB-209	A95083
25	...	B/SB-209	A95086
25	...	B/SB-209	A95456
25	...	B210	A95083
25	...	B210	A95086
25	...	B210	A95456
25	...	B/SB-221	A95083
25	...	B/SB-221	A95456
25	...	B/SB-241	A95083
25	...	B/SB-241	A95086
25	...	B/SB-241	A95456
25	...	B/SB-247	A95083
25	...	B345	A95083
25	...	B345	A95086
25	...	B361	A95083
25	...	B547	A95083
25	...	B/SB-928	A95083
25	...	B/SB-928	A95086
25	...	B/SB-928	A95456
26	...	B/SB-26	A24430
26	...	B/SB-26	A03560
26	...	SB/EN 1706	EN AC 43000

Copper and Copper-Base Alloys

31	...	B/SB-42	C10200
31	...	B/SB-42	C12000
31	...	B/SB-42	C12200
31	...	B68	C10200
31	...	B68	C12000

P-No.	Grp. No.	Spec. No.	Type, Grade, or UNS No.
-------	----------	-----------	-------------------------

Copper and Copper-Base Alloys (Cont'd)

31	...	B68	C12200
31	...	B/SB-75	C10200
31	...	B/SB-75	C12000
31	...	B/SB-75	C12200
31	...	B/SB-75	C14200
31	...	B88	C10200
31	...	B88	C12000
31	...	B88	C12200
31	...	B/SB-111	C10200
31	...	B/SB-111	C12000
31	...	B/SB-111	C12200
31	...	B/SB-111	C14200
31	...	B/SB-111	C19200
31	...	B/SB-152	C10200
31	...	B/SB-152	C10400
31	...	B/SB-152	C10500
31	...	B/SB-152	C10700
31	...	B/SB-152	C11000
31	...	B/SB-152	C12200
31	...	B/SB-152	C12300
31	...	B/SB-152	C14200
31	...	B/SB-187	C10200
31	...	B/SB-187	C11000
31	...	B280	C10200
31	...	B280	C12000
31	...	B280	C12200
31	...	B/SB-283	C11000
31	...	B302	C12000
31	...	B/SB-359	C10200
31	...	B/SB-359	C12000
31	...	B/SB-359	C12200
31	...	B/SB-359	C14200
31	...	B/SB-359	C19200
31	...	B/SB-395	C10200
31	...	B/SB-395	C12000
31	...	B/SB-395	C12200
31	...	B/SB-395	C14200
31	...	B/SB-395	C19200
31	...	B/SB-543	C12200
31	...	B/SB-543	C19400
32	...	B/SB-43	C23000
32	...	B/SB-111	C23000
32	...	B/SB-111	C28000
32	...	B/SB-111	C44300
32	...	B/SB-111	C44400
32	...	B/SB-111	C44500
32	...	B/SB-111	C68700
32	...	B/SB-135	C23000
32	...	B/SB-171	C36500
32	...	B/SB-171	C44300
32	...	B/SB-171	C44400
32	...	B/SB-171	C44500
32	...	B/SB-171	C46400
32	...	B/SB-171	C46500

2013 SECTION IX

P-No.	Grp. No.	Spec. No.	Type, Grade, or UNS No.
Copper and Copper-Base Alloys (Cont'd)			
32	...	B/SB-283	C67500
32	...	B/SB-283	C46400
32	...	B/SB-359	C23000
32	...	B/SB-359	C44300
32	...	B/SB-359	C44400
32	...	B/SB-359	C44500
32	...	B/SB-359	C68700
32	...	B/SB-395	C23000
32	...	B/SB-395	C44300
32	...	B/SB-395	C44400
32	...	B/SB-395	C44500
32	...	B/SB-395	C68700
32	...	B/SB-543	C23000
32	...	B/SB-543	C44300
32	...	B/SB-543	C44400
32	...	B/SB-543	C44500
32	...	B/SB-543	C68700
33	...	B/SB-96	C65500
33	...	B/SB-98	C65100
33	...	B/SB-98	C65500
33	...	B/SB-98	C66100
33	...	B/SB-283	C65500
33	...	B/SB-315	C65500
34	...	B/SB-111	C70400
34	...	B/SB-111	C70600
34	...	B/SB-111	C71000
34	...	B/SB-111	C71500
34	...	B/SB-111	C71640
34	...	B/SB-111	C72200
34	...	B/SB-151	C70600
34	...	B/SB-171	C70600
34	...	B/SB-171	C71500
34	...	B/SB-359	C70400
34	...	B/SB-359	C70600
34	...	B/SB-359	C71000
34	...	B/SB-359	C71500
34	...	B/SB-359	C71640
34	...	B/SB-359	C72200
34	...	B/SB-359	C73000
34	...	B/SB-359	C73500
34	...	B/SB-359	C74000
34	...	B/SB-359	C74500
34	...	B/SB-359	C75000
34	...	B/SB-359	C75500
34	...	B/SB-359	C76000
34	...	B/SB-359	C76500
34	...	B/SB-359	C77000
34	...	B/SB-359	C77500
34	...	B/SB-359	C78000
34	...	B/SB-359	C78500
34	...	B/SB-359	C79000
34	...	B/SB-359	C79500
34	...	B/SB-359	C80000
34	...	B/SB-359	C80500
34	...	B/SB-359	C81000
34	...	B/SB-359	C81500
34	...	B/SB-359	C82000
34	...	B/SB-359	C82500
34	...	B/SB-359	C83000
34	...	B/SB-359	C83500
34	...	B/SB-359	C84000
34	...	B/SB-359	C84500
34	...	B/SB-359	C85000
34	...	B/SB-359	C85500
34	...	B/SB-359	C86000
34	...	B/SB-359	C86500
34	...	B/SB-359	C87000
34	...	B/SB-359	C87500
34	...	B/SB-359	C88000
34	...	B/SB-359	C88500
34	...	B/SB-359	C89000
34	...	B/SB-359	C89500
34	...	B/SB-359	C90000
34	...	B/SB-359	C90500
34	...	B/SB-359	C91000
34	...	B/SB-359	C91500
34	...	B/SB-359	C92000
34	...	B/SB-359	C92500
34	...	B/SB-359	C93000
34	...	B/SB-359	C93500
34	...	B/SB-359	C94000
34	...	B/SB-359	C94500
34	...	B/SB-359	C95000
34	...	B/SB-359	C95500
34	...	B/SB-359	C96000
34	...	B/SB-359	C96500
34	...	B/SB-359	C97000
34	...	B/SB-359	C97500
34	...	B/SB-359	C98000
34	...	B/SB-359	C98500
34	...	B/SB-359	C99000
34	...	B/SB-359	C99500
34	...	B/SB-359	C100000

P-No.	Grp. No.	Spec. No.	Type, Grade, or UNS No.
Copper and Copper-Base Alloys (Cont'd)			
35	...	B/SB-148	C95400
35	...	B/SB-148	C95300
35	...	B/SB-148	C95500
35	...	B/SB-148	C95600
35	...	B/SB-150	C61400
35	...	B/SB-150	C62300
35	...	B/SB-150	C63000
35	...	B/SB-150	C64200
35	...	B/SB-169	C61400
35	...	B/SB-171	C61400
35	...	B/SB-171	C63000
35	...	B/SB-271	C95200
35	...	B/SB-271	C95400
35	...	B/SB-359	C60800
35	...	B/SB-395	C60800
35	...	B/SB-505	C95200
Nickel and Nickel-Base Alloys			
41	...	B/SB-160	N02200
41	...	B/SB-160	N02201
41	...	B/SB-161	N02200
41	...	B/SB-161	N02201
41	...	B/SB-162	N02200
41	...	B/SB-162	N02201
41	...	B/SB-163	N02200
41	...	B/SB-163	N02201
41	...	B/SB-366	N02200
41	...	B/SB-366	N02201
41	...	B725	N02200
42	...	B/SB-127	N04400
42	...	B/SB-163	N04400
42	...	B/SB-164	N04400
42	...	B/SB-164	N04405
42	...	B/SB-165	N04400
42	...	B/SB-366	N04400
42	...	A/SA-494	N04020
42	...	A/SA-494	N24130
42	...	A/SA-494	N24135
42	...	B/SB-564	N04400
43	...	B/SB-163	N06600
43	...	B/SB-163	N06601
43	...	B/SB-163	N06690
43	...	B/SB-166	N06600
43	...	B/SB-166	N06601
43	...	B/SB-166	N06617
43	...	B/SB-166	N06690
43	...	B/SB-167	N06600
43	...	B/SB-167	N06601
43	...	B/SB-167	N06617
43	...	B/SB-167	N06690
43	...	B/SB-168	N06600
43	...	B/SB-168	N06601
43	...	B/SB-168	N06617
43	...	B/SB-168	N06690
43	...	B/SB-366	N06002

2013 SECTION IX

P-No.	Grp. No.	Spec. No.	Type, Grade, or UNS No.
Nickel and Nickel-Base Alloys (Cont'd)			
43	...	B/SB-366	N06022
43	...	B/SB-366	N06035
43	...	B/SB-366	N06059
43	...	B/SB-366	N06200
43	...	B/SB-366	N06210
43	...	B/SB-366	N06230
43	...	B/SB-366	N06455
43	...	B/SB-366	N06600
43	...	B/SB-366	N06625
43	...	B/SB-366	N10276
43	...	B/SB-435	N06002
43	...	B/SB-435	N06230
43	...	B/SB-443	N06625
43	...	B/SB-444	N06625
43	...	B/SB-446	N06625
43	...	B/SB-462	N06022
43	...	B/SB-462	N06035
43	...	B/SB-462	N06059
43	...	B/SB-462	N06200
43	...	B/SB-462	N06686
43	...	B/SB-462	N10276
43	...	A/SA-494	N06040
43	...	A/SA-494	N26022
43	...	A/SA-494	N26455
43	...	A/SA-494	N26625
43	...	B/SB-516	N06600
43	...	B/SB-517	N06600
43	...	B/SB-564	N06022
43	...	B/SB-564	N06035
43	...	B/SB-564	N06059
43	...	B/SB-564	N06200
43	...	B/SB-564	N06210
43	...	B/SB-564	N06230
43	...	B/SB-564	N06600
43	...	B/SB-564	N06617
43	...	B/SB-564	N06625
43	...	B/SB-564	N06686
43	...	B/SB-564	N06690
43	...	B/SB-564	N10276
43	...	B/SB-572	N06002
43	...	B/SB-572	N06230
43	...	B/SB-574	N06022
43	...	B/SB-574	N06035
43	...	B/SB-574	N06059
43	...	B/SB-574	N06200
43	...	B/SB-574	N06210
43	...	B/SB-574	N06455
43	...	B/SB-574	N06686
43	...	B/SB-574	N10276
43	...	B/SB-575	N06022
43	...	B/SB-575	N06035
43	...	B/SB-575	N06059
43	...	B/SB-575	N06200
43	...	B/SB-575	N06210
43	...	B/SB-575	N06455

P-No.	Grp. No.	Spec. No.	Type, Grade, or UNS No.
Nickel and Nickel-Base Alloys (Cont'd)			
43	...	B/SB-575	N06686
43	...	B/SB-575	N10276
43	...	B/SB-619	N06002
43	...	B/SB-619	N06022
43	...	B/SB-619	N06035
43	...	B/SB-619	N06059
43	...	B/SB-619	N06200
43	...	B/SB-619	N06210
43	...	B/SB-619	N06230
43	...	B/SB-619	N06455
43	...	B/SB-619	N06686
43	...	B/SB-619	N10276
43	...	B/SB-622	N06002
43	...	B/SB-622	N06022
43	...	B/SB-622	N06035
43	...	B/SB-622	N06059
43	...	B/SB-622	N06200
43	...	B/SB-622	N06210
43	...	B/SB-622	N06230
43	...	B/SB-622	N06455
43	...	B/SB-622	N06686
43	...	B/SB-622	N10276
43	...	B/SB-626	N06002
43	...	B/SB-626	N06022
43	...	B/SB-626	N06035
43	...	B/SB-626	N06059
43	...	B/SB-626	N06200
43	...	B/SB-626	N06210
43	...	B/SB-626	N06230
43	...	B/SB-626	N06455
43	...	B/SB-626	N06686
43	...	B/SB-626	N10276
43	...	B/SB-704	N06625
43	...	B/SB-705	N06625
44	...	B/SB-333	N10001
44	...	B/SB-333	N10629
44	...	B/SB-333	N10665
44	...	B/SB-333	N10675
44	...	B/SB-335	N10001
44	...	B/SB-335	N10629
44	...	B/SB-335	N10665
44	...	B/SB-335	N10675
44	...	B/SB-366	N10001
44	...	B/SB-366	N10003
44	...	B/SB-366	N10242
44	...	B/SB-366	N10629
44	...	B/SB-366	N10665
44	...	B/SB-366	N10675
44	...	B/SB-434	N10003
44	...	B/SB-434	N10242
44	...	B/SB-462	N10629
44	...	B/SB-462	N10665
44	...	B/SB-462	N10675
44	...	A/SA-494	N30007

2013 SECTION IX

P-No.	Grp. No.	Spec. No.	Type, Grade, or UNS No.
Nickel and Nickel-Base Alloys (Cont'd)			
44	...	A/SA-494	N30107
44	...	B/SB-564	N10242
44	...	B/SB-564	N10629
44	...	B/SB-564	N10665
44	...	B/SB-564	N10675
44	...	B/SB-573	N10003
44	...	B/SB-573	N10242
44	...	B/SB-619	N10001
44	...	B/SB-619	N10242
44	...	B/SB-619	N10629
44	...	B/SB-619	N10665
44	...	B/SB-619	N10675
44	...	B/SB-622	N10001
44	...	B/SB-622	N10242
44	...	B/SB-622	N10629
44	...	B/SB-622	N10665
44	...	B/SB-622	N10675
44	...	B/SB-626	N10001
44	...	B/SB-626	N10242
44	...	B/SB-626	N10629
44	...	B/SB-626	N10665
44	...	B/SB-626	N10675
45	...	A/SA-240	S31277
45	...	A/SA-249	N08904
45	...	B/SB-163	N08120
45	...	B/SB-163	N08800
45	...	B/SB-163	N08801
45	...	B/SB-163	N08810
45	...	B/SB-163	N08811
45	...	B/SB-163	N08825
45	...	A/SA-351	CN3MN
45	...	A/SA-351	N08007
45	...	A/SA-351	N08151
45	...	A/SA-351	N08603
45	...	B/SB-366	N06007
45	...	B/SB-366	N06030
45	...	B/SB-366	N06985
45	...	B/SB-366	N08020
45	...	B/SB-366	N08031
45	...	B/SB-366	N08120
45	...	B/SB-366	N08367
45	...	B/SB-366	N08800
45	...	B/SB-366	N08825
45	...	B/SB-366	N08925
45	...	B/SB-366	R20033
45	...	B/SB-366	R30556
45	...	B/SB-366	N08926
45	...	B/SB-407	N08120
45	...	B/SB-407	N08800
45	...	B/SB-407	N08801
45	...	B/SB-407	N08810
45	...	B/SB-407	N08811
45	...	B/SB-408	N08120

P-No.	Grp. No.	Spec. No.	Type, Grade, or UNS No.
Nickel and Nickel-Base Alloys (Cont'd)			
45	...	B/SB-408	N08800
45	...	B/SB-408	N08810
45	...	B/SB-408	N08811
45	...	B/SB-409	N08120
45	...	B/SB-409	N08800
45	...	B/SB-409	N08810
45	...	B/SB-409	N08811
45	...	B/SB-423	N08825
45	...	B/SB-424	N08825
45	...	B/SB-425	N08825
45	...	B/SB-435	R30556
45	...	B/SB-462	N06030
45	...	B/SB-462	N08020
45	...	B/SB-462	N08031
45	...	A/SA-182	N08904
45	...	A/SA-240	N08367
45	...	A/SA-240	N08904
45	...	A/SA-249	N08367
45	...	A/SA-312	N08367
45	...	A/SA-312	N08904
45	...	A/SA-358	N08367
45	...	A479	N08904
45	...	A/SA-813	N08367
45	...	A/SA-814	N08367
45	...	B/SB-462	N08367
45	...	B/SB-462	R20033
45	...	B/SB-463	N08020
45	...	B/SB-463	N08024
45	...	B/SB-463	N08026
45	...	B/SB-464	N08020
45	...	B/SB-464	N08024
45	...	B/SB-464	N08026
45	...	B/SB-468	N08020
45	...	B/SB-468	N08024
45	...	B/SB-468	N08026
45	...	B/SB-473	N08020
45	...	A/SA-494	N08826
45	...	B/SB-514	N08120
45	...	B/SB-514	N08800
45	...	B/SB-514	N08810
45	...	B/SB-515	N08120
45	...	B/SB-515	N08800
45	...	B/SB-515	N08810
45	...	B/SB-515	N08811
45	...	B/SB-564	N08031
45	...	B/SB-564	N08120
45	...	B/SB-564	N08367
45	...	B/SB-564	N08800
45	...	B/SB-564	N08810
45	...	B/SB-564	N08811
45	...	B/SB-564	N08825
45	...	B/SB-564	R20033
45	...	B/SB-572	R30556
45	...	B/SB-581	N06007

2013 SECTION IX

P-No.	Grp. No.	Spec. No.	Type, Grade, or UNS No.
Nickel and Nickel-Base Alloys (Cont'd)			
45	...	B/SB-581	N06030
45	...	B/SB-581	N06975
45	...	B/SB-581	N06985
45	...	B/SB-581	N08031
45	...	B/SB-582	N06007
45	...	B/SB-582	N06030
45	...	B/SB-582	N06975
45	...	B/SB-582	N06985
45	...	B/SB-599	N08700
45	...	B/SB-619	N06007
45	...	B/SB-619	N06030
45	...	B/SB-619	N06975
45	...	B/SB-619	N06985
45	...	B/SB-619	N08031
45	...	B/SB-619	N08320
45	...	B/SB-619	R20033
45	...	B/SB-619	R30556
45	...	B/SB-620	N08320
45	...	B/SB-621	N08320
45	...	B/SB-622	N06007
45	...	B/SB-622	N06030
45	...	B/SB-622	N06975
45	...	B/SB-622	N06985
45	...	B/SB-622	N08031
45	...	B/SB-622	N08320
45	...	B/SB-622	R20033
45	...	B/SB-622	R30556
45	...	B/SB-625	N08031
45	...	B/SB-625	N08904
45	...	B/SB-625	N08925
45	...	B/SB-625	R20033
45	...	B/SB-625	N08926
45	...	B/SB-626	N06007
45	...	B/SB-626	N06030
45	...	B/SB-626	N06975
45	...	B/SB-626	N06985
45	...	B/SB-626	N08031
45	...	B/SB-626	N08320
45	...	B/SB-626	R20033
45	...	B/SB-626	R30556
45	...	B/SB-649	N08904
45	...	B/SB-649	N08925
45	...	B/SB-649	R20033
45	...	B/SB-649	N08926
45	...	B/SB-668	N08028
45	...	B/SB-672	N08700
45	...	B/SB-673	N08904
45	...	B/SB-673	N08925
45	...	B/SB-673	N08926
45	...	B/SB-674	N08904
45	...	B/SB-674	N08925
45	...	B/SB-674	N08926
45	...	B/SB-675	N08367
45	...	B/SB-676	N08367

P-No.	Grp. No.	Spec. No.	Type, Grade, or UNS No.
Nickel and Nickel-Base Alloys (Cont'd)			
45	...	B/SB-677	N08904
45	...	B/SB-677	N08925
45	...	B/SB-677	N08926
45	...	B/SB-688	N08367
45	...	B/SB-690	N08367
45	...	B/SB-691	N08367
45	...	B/SB-704	N08825
45	...	B/SB-705	N08825
45	...	B/SB-709	N08028
45	...	B/SB-729	N08020
46	...	B/SB-166	N06045
46	...	B/SB-167	N06045
46	...	B/SB-168	N06045
46	...	B/SB-366	N06045
46	...	B/SB-366	N08330
46	...	B/SB-366	N12160
46	...	B/SB-435	N12160
46	...	B/SB-462	N06045
46	...	B/SB-511	N08330
46	...	B/SB-516	N06045
46	...	B/SB-517	N06045
46	...	B/SB-535	N08330
46	...	B/SB-536	N08330
46	...	B/SB-564	N06045
46	...	B/SB-564	N12160
46	...	B/SB-572	N12160
46	...	B/SB-619	N12160
46	...	B/SB-622	N12160
46	...	B/SB-626	N12160
46	...	B/SB-710	N08330
49	...	B/SB-815	R31233
49	...	B/SB-818	R31233
Titanium and -Base Alloys			
51	...	B/SB-265	R50250
51	...	B/SB-265	R50400
51	...	B/SB-265	R52250
51	...	B/SB-265	R52252
51	...	B/SB-265	R52254
51	...	B/SB-265	R52400
51	...	B/SB-265	R52402
51	...	B/SB-265	R52404
51	...	B/SB-338	R50250
51	...	B/SB-338	R50400
51	...	B/SB-338	R52400
51	...	B/SB-338	R52402
51	...	B/SB-338	R52404
51	...	B/SB-348	R50250
51	...	B/SB-348	R50400
51	...	B/SB-348	R50402
51	...	B/SB-348	R52400
51	...	B/SB-348	R52404
51	...	B/SB-363	R50250
51	...	B/SB-363	R50400

2013 SECTION IX

P-No.	Grp. No.	Spec. No.	Type, Grade, or UNS No.
Titanium and -Base Alloys (<i>Cont'd</i>)			
51	...	B/SB-363	R52400
51	...	B/SB-363	R52404
51	...	B/SB-367	R50400
51	...	B/SB-381	R50250
51	...	B/SB-381	R50400
51	...	B/SB-381	R50402
51	...	B/SB-381	R52400
51	...	B/SB-381	R52404
51	...	B/SB-861	R50250
51	...	B/SB-861	R50400
51	...	B/SB-861	R52400
51	...	B/SB-861	R52404
51	...	B/SB-862	R50250
51	...	B/SB-862	R50400
51	...	B/SB-862	R52400
51	...	B/SB-862	R52404
52	...	B/SB-265	R50550
52	...	B/SB-265	R53400
52	...	B/SB-338	R50550
52	...	B/SB-338	R53400
52	...	B/SB-348	R50550
52	...	B/SB-348	R53400
52	...	B/SB-363	R50550
52	...	B/SB-363	R53400
52	...	B/SB-367	R50550
52	...	B/SB-381	R50550
52	...	B/SB-381	R53400
52	...	B/SB-861	R50550
52	...	B/SB-861	R53400

P-No.	Grp. No.	Spec. No.	Type, Grade, or UNS No.
Titanium and -Base Alloys (<i>Cont'd</i>)			
52	...	B/SB-862	R50550
52	...	B/SB-862	R53400
53	...	B/SB-265	R56320
53	...	B/SB-338	R56320
53	...	B/SB-348	R56320
53	...	B/SB-363	R56320
53	...	B/SB-381	R56320
53	...	B/SB-861	R56320
53	...	B/SB-862	R56320
53	...	B/SB-265	R56323
53	...	B/SB-338	R56323
53	...	B/SB-348	R56323
53	...	B/SB-363	R56323
53	...	B/SB-381	R56323
53	...	B/SB-861	R56323
53	...	B/SB-862	R56323
Zirconium and Zirconium-Base Alloys			
61	...	B/SB-493	R60702
61	...	B/SB-523	R60702
61	...	B/SB-550	R60702
61	...	B/SB-551	R60702
61	...	B/SB-653	R60702
61	...	B/SB-658	R60702
62	...	B/SB-493	R60705
62	...	B/SB-523	R60705
62	...	B/SB-550	R60705
62	...	B/SB-551	R60705
62	...	B/SB-658	R60705

(13)

MANDATORY APPENDIX E PERMITTED SWPSS

The following AWS Standard Welding Procedure Specifications may be used under the requirements given in Article V.

Specification	Designation
Carbon Steel	
Shielded Metal Arc Welding	
Standard Welding Procedure Specification for Shielded Metal Arc Welding of Carbon Steel (M-1/P-1/S-1, Group 1 or 2), $\frac{1}{8}$ through $1\frac{1}{2}$ inch Thick, E7018, As-Welded or PWHT Condition	B2.1-1-016-94 (R05)
Standard Welding Procedure Specification for Shielded Metal Arc Welding of Carbon Steel (M-1/P-1/S-1, Group 1 or 2), $\frac{1}{8}$ through $1\frac{1}{2}$ inch Thick, E6010, As-Welded or PWHT Condition	B2.1-1-017-94 (R05)
Standard Welding Procedure Specification for Shielded Metal Arc Welding of Carbon Steel (M-1/P-1/S-1, Group 1 or 2), $\frac{1}{8}$ through $1\frac{1}{2}$ inch Thick, E6010 (Vertical Uphill) Followed by E7018, As-Welded or PWHT Condition	B2.1-1-022-94 (R05)
Standard Welding Procedure Specification for Shielded Metal Arc Welding of Carbon Steel (M-1/P-1/S-1, Group 1 or 2), $\frac{1}{8}$ through $1\frac{1}{2}$ inch Thick, E6010 (Vertical Downhill) Followed by E7018, As-Welded or PWHT Condition	B2.1-1-026-94 (R05)
Combination GTAW and SMAW	
Standard Welding Procedure Specification for Gas Tungsten Arc Welding Followed by Shielded Metal Arc Welding of Carbon Steel (M-1/P-1/S-1, Group 1 or 2), $\frac{1}{8}$ through $1\frac{1}{2}$ inch Thick, ER70S-2 and E7018, As-Welded or PWHT Condition	B2.1-1-021-94 (R05)
Flux Cored Arc Welding	
Standard Welding Procedure Specification (WPS) for CO ₂ Shielded Flux Cored Arc Welding of Carbon Steel (M-1/P-1/S-1, Group 1 or 2), $\frac{1}{8}$ through $1\frac{1}{2}$ inch Thick, E70T-1 and E71T-1, As-Welded Condition	B2.1-1-019-94 (R05)
Standard Welding Procedure Specification (WPS) for 75% Ar/25% CO ₂ Shielded Flux Cored Arc Welding of Carbon Steel (M-1/P-1/S-1, Group 1 or 2), $\frac{1}{8}$ through $1\frac{1}{2}$ inch Thick, E70T-1 and E71T-1, As-Welded or PWHT Condition	B2.1-1-020-94 (R05)
Carbon Steel — Primarily Pipe Applications	
Shielded Metal Arc Welding	
Standard Welding Procedure Specification (SWPS) for Shielded Metal Arc Welding of Carbon Steel (M-1/P-1/S-1, Group 1 or 2), $\frac{1}{8}$ through $\frac{3}{4}$ inch Thick, E6010 (Vertical Uphill) Followed by E7018 (Vertical Uphill), As- Welded Condition, Primarily Pipe Applications	B2.1-1-201-96 (R07)
Standard Welding Procedure Specification (SWPS) for Shielded Metal Arc Welding of Carbon Steel (M-1/P-1/S-1, Group 1 or 2), $\frac{1}{8}$ through $\frac{3}{4}$ inch Thick, E6010 (Vertical Downhill) Followed by E7018 (Vertical Uphill), As- Welded Condition, Primarily Pipe Applications	B2.1-1-202-96 (R07)
Standard Welding Procedure Specification (SWPS) for Shielded Metal Arc Welding of Carbon Steel (M-1/P-1/S-1, Group 1 or 2), $\frac{1}{8}$ through $\frac{3}{4}$ inch Thick, E6010 (Vertical Uphill), As-Welded Condition, Primarily Pipe Applications	B2.1-1-203-96 (R07)
Standard Welding Procedure Specification (SWPS) for Shielded Metal Arc Welding of Carbon Steel (M-1/P-1/S-1, Group 1 or 2), $\frac{1}{8}$ through $\frac{3}{4}$ inch Thick, E6010 (Vertical Downhill Root with the Balance Vertical Uphill), As- Welded Condition, Primarily Pipe Applications	B2.1-1-204-96 (R07)
Standard Welding Procedure Specification (SWPS) for Shielded Metal Arc Welding of Carbon Steel (M-1/P-1/S-1, Group 1 or 2), $\frac{1}{8}$ through $1\frac{1}{2}$ inch Thick, E6010 (Vertical Uphill) Followed by E7018 (Vertical Uphill), As- Welded or PWHT Condition, Primarily Pipe Applications	B2.1-1-205-96 (R07)
Standard Welding Procedure Specification (SWPS) for Shielded Metal Arc Welding of Carbon Steel (M-1/P-1/S-1, Group 1 or 2), $\frac{1}{8}$ through $1\frac{1}{2}$ inch Thick, E6010 (Vertical Downhill) Followed by E7018 (Vertical Uphill), As- Welded or PWHT Condition, Primarily Pipe Applications	B2.1-1-206-96 (R07)
Standard Welding Procedure Specification (SWPS) for Shielded Metal Arc Welding of Carbon Steel (M-1/P-1/S-1, Group 1 or 2), $\frac{1}{8}$ through $1\frac{1}{2}$ inch Thick, E7018, As-Welded or PWHT Condition, Primarily Pipe Applications	B2.1-1-208-96 (R07)
Gas Tungsten Arc Welding	
Standard Welding Procedure Specification (SWPS) for Gas Tungsten Arc Welding of Carbon Steel (M-1/P-1/S-1, Group 1 or 2), $\frac{1}{8}$ through $1\frac{1}{2}$ inch Thick, ER70S-2, As-Welded or PWHT Condition, Primarily Pipe Applications	B2.1-1-207-96 (R07)
Standard Welding Procedure Specification (SWPS) for Gas Tungsten Arc Welding with Consumable Insert Root of Carbon Steel (M-1/P-1/S-1, Group 1 or 2), $\frac{1}{8}$ through $1\frac{1}{2}$ inch Thick, INMs-1 and ER70S-2, As-Welded or PWHT Condition, Primarily Pipe Applications	B2.1-1-210: 2001 (R11)

Table continued	
Specification	Designation
Carbon Steel — Primarily Pipe Applications (Cont'd)	
Flux Cored Arc Welding	
Standard Welding Procedure Specification (SWPS) for Argon plus 25% Carbon Dioxide Shielded Flux Cored Arc Welding of Carbon Steel (M-1/P-1/S-1, Groups 1 and 2), $\frac{1}{8}$ through $1\frac{1}{2}$ inch Thick, E7XT-X, As-Welded or PWHT Condition, Primarily Pipe Applications	B2.1-1-234: 2006
Gas Metal Arc Welding — Spray Transfer	
Standard Welding Procedure Specification (SWPS) for Argon plus 2% Oxygen Shielded Gas Metal Arc Welding (Spray Transfer Mode) of Carbon Steel (M-1/P-1/S-1, Groups 1 and 2), $\frac{1}{8}$ through $1\frac{1}{2}$ inch Thick, E70S-3, Flat Position Only, As-Welded or PWHT Condition, Primarily Pipe Applications	B2.1-1-235: 2006
Combination GTAW and SMAW	
Standard Welding Procedure Specification (SWPS) for Gas Tungsten Arc Welding Followed by Shielded Metal Arc Welding of Carbon Steel (M-1/P-1/S-1, Group 1 or 2), $\frac{1}{8}$ through $1\frac{1}{2}$ inch Thick, ER70S-2 and E7018, As-Welded or PWHT Condition, Primarily Pipe Applications	B2.1-1-209-96 (R07)
Standard Welding Procedure Specification (SWPS) for Gas Tungsten Arc Welding with Consumable Insert Root followed by Shielded Metal Arc Welding of Carbon Steel (M-1/P-1/S-1, Group 1 or 2), $\frac{1}{8}$ through $1\frac{1}{2}$ inch Thick, INMs-1, ER70S-2, and E7018, As-Welded or PWHT Condition, Primarily Pipe Applications	B2.1-1-211: 2001 (R11)
Austenitic Stainless Steel Plate and Pipe	
Shielded Metal Arc Welding	
Standard Welding Procedure Specification (SWPS) for Shielded Metal Arc Welding of Austenitic Stainless Steel (M-8/P-8/S-8, Group 1), $\frac{1}{8}$ through $1\frac{1}{2}$ inch Thick, As-Welded Condition	B2.1-8-023-94 (R05)
Gas Tungsten Arc Welding	
Standard Welding Procedure Specification (SWPS) for Gas Tungsten Arc Welding of Austenitic Stainless Steel (M-8/P-8/S-8, Group 1), $\frac{1}{16}$ through $1\frac{1}{2}$ inch Thick, ER3XX, As-Welded Condition, Primarily Plate and Structural Applications	B2.1-8-024: 2001 (R11)
Combination GTAW and SMAW	
Standard Welding Procedure Specification (SWPS) for Gas Tungsten Arc Welding Followed by Shielded Metal Arc Welding of Austenitic Stainless Steel (M-8/P-8/S-8, Group 1), $\frac{1}{8}$ through $1\frac{1}{2}$ inch Thick, ER3XX and 3XX-XX, As-Welded Condition, Primarily Plate and Structural Applications	B2.1-8-025: 2001 (R11)
Austenitic Stainless Steel Primarily Pipe Applications	
Shielded Metal Arc Welding	
Standard Welding Procedure Specification (SWPS) for Shielded Metal Arc Welding of Austenitic Stainless Steel (M-8/P-8/S-8, Group 1), $\frac{1}{8}$ through $1\frac{1}{2}$ inch Thick, E3XX-XX, As-Welded Condition, Primarily Pipe Applications	B2.1-8-213-97 (R11)
Gas Tungsten Arc Welding	
Standard Welding Procedure Specification (SWPS) for Gas Tungsten Arc Welding of Austenitic Stainless Steel (M-8/P-8/S-8, Group 1), $\frac{1}{16}$ through $1\frac{1}{2}$ inch Thick, ER3XX, As-Welded Condition, Primarily Pipe Applications	B2.1-8-212: 2001 (R11)
Standard Welding Procedure Specification (SWPS) for Gas Tungsten Arc Welding with Consumable Insert of Austenitic Stainless Steel (M-8/P-8/S-8, Group 1), $\frac{1}{8}$ through $1\frac{1}{2}$ inch Thick, IN3XX and ER3XX, As-Welded Condition, Primarily Pipe Applications	B2.1-8-215: 2001 (R11)
Combination GTAW and SMAW	
Standard Welding Procedure Specification (SWPS) for Gas Tungsten Arc Welding Followed by Shielded Metal Arc Welding of Austenitic Stainless Steel (M-8/P-8/S-8, Group 1), $\frac{1}{8}$ through $1\frac{1}{2}$ inch Thick, ER3XX and E3XX-XX, As-Welded Condition, Primarily Pipe Applications	B2.1-8-214: 2001 (R11)
Standard Welding Procedure Specification (SWPS) for Gas Tungsten Arc Welding with Consumable Insert Root followed by Shielded Metal Arc Welding of Austenitic Stainless Steel (M-8/P-8/S-8, Group 1), $\frac{1}{8}$ through $1\frac{1}{2}$ inch Thick, IN3XX, ER3XXX, and E3XX-XX, As-Welded Condition, Primarily Pipe Applications	B2.1-8-216: 2001 (R11)
Carbon Steel to Austenitic Stainless Steel	
Gas Tungsten Arc Welding	
Standard Welding Procedure Specification (SWPS) for Gas Tungsten Arc Welding of Carbon Steel to Austenitic Stainless Steel (M-1/P-1/S-1, Groups 1 and 2 Welded to M-8/P-8/S-8, Group 1), $\frac{1}{16}$ through $1\frac{1}{2}$ inch Thick, ER309(L), As-Welded Condition, Primarily Pipe Applications	B2.1-1/8- 227: 2002

2013 SECTION IX

Table continued	
Specification	Designation
Carbon Steel to Austenitic Stainless Steel (Cont'd)	
Gas Tungsten Arc Welding (Cont'd)	
Standard Welding Procedure Specification (SWPS) for Gas Tungsten Arc Welding with Consumable Insert Root of Carbon Steel to Austenitic Stainless Steel (M-1/P-1/S-1, Groups 1 and 2 Welded to M-8/P-8/S-8, Group 1), $\frac{1}{16}$ through $1\frac{1}{2}$ inch Thick, IN309 and R309(L), As-Welded Condition, Primarily Pipe Applications	B2.1-1/8- 230: 2002
Shielded Metal Arc Welding	
Standard Welding Procedure Specification (SWPS) for Shielded Metal Arc Welding of Carbon Steel to Austenitic Stainless Steel (M-1/P-1/S-1, Groups 1 and 2 Welded to M-8/P-8/S-8, Group 1), $\frac{1}{8}$ through $1\frac{1}{2}$ inch Thick, E309(L)-15, -16, or -17, As-Welded Condition, Primarily Pipe Applications	B2.1-1/8- 228: 2002
Combination GTAW and SMAW	
Standard Welding Procedure Specification (SWPS) for Gas Tungsten Arc Welding Followed by Shielded Metal Arc Welding of Carbon Steel to Austenitic Stainless Steel (M-1/P-1/S-1 Groups 1 and 2 Welded to M-8/P-8/S-8, Group 1), $\frac{1}{8}$ through $1\frac{1}{2}$ inch Thick, ER309(L) and E309(L)-15, -16, or -17, As-Welded Condition, Primarily Pipe Applications	B2.1-1/8- 229: 2002
Standard Welding Procedure Specification (SWPS) for Gas Tungsten Arc Welding with Consumable Insert Root, Followed by Shielded Metal Arc Welding of Carbon Steel to Austenitic Stainless Steel (M-1/P-1/S-1 Groups 1 and 2 Welded to M-8/P-8/S-8, Group 1) $\frac{1}{8}$ through $1\frac{1}{2}$ inch Thick, IN309, ER309(L), and E309(L)-15, -16, -17, As-Welded Condition, Primarily Pipe Applications	B2.1-1/8- 231: 2002

MANDATORY APPENDIX F

STANDARD UNITS FOR USE IN EQUATIONS

Table F-100
Standard Units for Use in Equations

Quantity	U.S. Customary Units	SI Units
Linear dimensions (e.g., length, height, thickness, radius, diameter)	inches (in.)	millimeters (mm)
Area	square inches (in. ²)	square millimeters (mm ²)
Volume	cubic inches (in. ³)	cubic millimeters (mm ³)
Section modulus	cubic inches (in. ³)	cubic millimeters (mm ³)
Moment of inertia of section	inches ⁴ (in. ⁴)	millimeters ⁴ (mm ⁴)
Mass (weight)	pounds mass (lbm)	kilograms (kg)
Force (load)	pounds force (lbf)	newtons (N)
Bending moment	inch-pounds (in.-lb)	newton-millimeters (N·mm)
Pressure, stress, stress intensity, and modulus of elasticity	pounds per square inch (psi)	megapascals (MPa)
Energy (e.g., Charpy impact values)	foot-pounds (ft-lb)	joules (J)
Temperature	degrees Fahrenheit (°F)	degrees Celsius (°C)
Absolute temperature	Rankine (R)	kelvin (K)
Fracture toughness	ksi square root inches (ksi√in.)	MPa square root meters (MPa√m)
Angle	degrees or radians	degrees or radians
Boiler capacity	Btu/hr	watts (W)

NONMANDATORY APPENDIX G

GUIDANCE FOR THE USE OF U.S. CUSTOMARY AND SI UNITS IN THE ASME BOILER AND PRESSURE VESSEL CODE

G-100 USE OF UNITS IN EQUATIONS

The equations in this Nonmandatory Appendix are suitable for use with either the U.S. Customary or the SI units provided in [Mandatory Appendix F](#), or with the units provided in the nomenclature associated with that equation. It is the responsibility of the individual and organization performing the calculations to ensure that appropriate units are used. Either U.S. Customary or SI units may be used as a consistent set. When necessary to convert from one system of units to another, the units shall be converted to at least three significant figures for use in calculations and other aspects of construction.

G-200 GUIDELINES USED TO DEVELOP SI EQUIVALENTS

The following guidelines were used to develop SI equivalents:

(a) SI units are placed in parentheses after the U.S. Customary units in the text.

(b) In general, separate SI tables are provided if interpolation is expected. The table designation (e.g., table number) is the same for both the U.S. Customary and SI tables, with the addition of suffix "M" to the designator for the SI table, if a separate table is provided. In the text, references to a table use only the primary table number (i.e., without the "M"). For some small tables, where interpolation is not required, SI units are placed in parentheses after the U.S. Customary unit.

(c) Separate SI versions of graphical information (charts) are provided, except that if both axes are dimensionless, a single figure (chart) is used.

(d) In most cases, conversions of units in the text were done using hard SI conversion practices, with some soft conversions on a case-by-case basis, as appropriate. This was implemented by rounding the SI values to the number of significant figures of implied precision in the existing U.S. Customary units. For example, 3,000 psi has an implied precision of one significant figure. Therefore, the conversion to SI units would typically be to 20 000 kPa. This is a difference of about 3% from the "exact" or soft conversion of 20 684.27 kPa. However, the precision of the conversion was determined by the Committee on a case-by-case basis. More significant digits were included

in the SI equivalent if there was any question. The values of allowable stress in Section II, Part D generally include three significant figures.

(e) Minimum thickness and radius values that are expressed in fractions of an inch were generally converted according to the following table:

Fraction, in.	Proposed SI Conversion, mm	Difference, %
$\frac{1}{32}$	0.8	- 0.8
$\frac{3}{64}$	1.2	- 0.8
$\frac{1}{16}$	1.5	5.5
$\frac{3}{32}$	2.5	- 5.0
$\frac{1}{8}$	3	5.5
$\frac{5}{32}$	4	- 0.8
$\frac{3}{16}$	5	- 5.0
$\frac{7}{32}$	5.5	1.0
$\frac{1}{4}$	6	5.5
$\frac{5}{16}$	8	- 0.8
$\frac{3}{8}$	10	- 5.0
$\frac{7}{16}$	11	1.0
$\frac{1}{2}$	13	- 2.4
$\frac{9}{16}$	14	2.0
$\frac{5}{8}$	16	- 0.8
$\frac{11}{16}$	17	2.6
$\frac{3}{4}$	19	0.3
$\frac{7}{8}$	22	1.0
1	25	1.6

(f) For nominal sizes that are in even increments of inches, even multiples of 25 mm were generally used. Intermediate values were interpolated rather than converting and rounding to the nearest mm. See examples in the following table. [Note that this table does not apply to nominal pipe sizes (NPS), which are covered below.]

Size, in.	Size, mm
1	25
$1\frac{1}{8}$	29
$1\frac{1}{4}$	32
$1\frac{1}{2}$	38
2	50
$2\frac{1}{4}$	57
$2\frac{1}{2}$	64
3	75
$3\frac{1}{2}$	89
4	100
$4\frac{1}{2}$	114
5	125
6	150
8	200

Table continued

Size, in.	Size, mm
12	300
18	450
20	500
24	600
36	900
40	1 000
54	1 350
60	1 500
72	1 800

Size or Length, ft	Size or Length, m
3	1
5	1.5
200	60

(g) For nominal pipe sizes, the following relationships were used:

U.S. Customary Practice	SI Practice	U.S. Customary Practice	SI Practice
NPS $\frac{1}{8}$	DN 6	NPS 20	DN 500
NPS $\frac{1}{4}$	DN 8	NPS 22	DN 550
NPS $\frac{3}{8}$	DN 10	NPS 24	DN 600
NPS $\frac{1}{2}$	DN 15	NPS 26	DN 650
NPS $\frac{3}{4}$	DN 20	NPS 28	DN 700
NPS 1	DN 25	NPS 30	DN 750
NPS $1\frac{1}{4}$	DN 32	NPS 32	DN 800
NPS $1\frac{1}{2}$	DN 40	NPS 34	DN 850
NPS 2	DN 50	NPS 36	DN 900
NPS $2\frac{1}{2}$	DN 65	NPS 38	DN 950
NPS 3	DN 80	NPS 40	DN 1000
NPS $3\frac{1}{2}$	DN 90	NPS 42	DN 1050
NPS 4	DN 100	NPS 44	DN 1100
NPS 5	DN 125	NPS 46	DN 1150
NPS 6	DN 150	NPS 48	DN 1200
NPS 8	DN 200	NPS 50	DN 1250
NPS 10	DN 250	NPS 52	DN 1300
NPS 12	DN 300	NPS 54	DN 1350
NPS 14	DN 350	NPS 56	DN 1400
NPS 16	DN 400	NPS 58	DN 1450
NPS 18	DN 450	NPS 60	DN 1500

(h) Areas in square inches (in.^2) were converted to square mm (mm^2) and areas in square feet (ft^2) were converted to square meters (m^2). See examples in the following table:

Area (U.S. Customary)	Area (SI)
1 in.^2	650 mm^2
6 in.^2	4 000 mm^2
10 in.^2	6 500 mm^2
5 ft^2	0.5 m^2

(i) Volumes in cubic inches (in.^3) were converted to cubic mm (mm^3) and volumes in cubic feet (ft^3) were converted to cubic meters (m^3). See examples in the following table:

Volume (U.S. Customary)	Volume (SI)
1 in.^3	16 000 mm^3
6 in.^3	100 000 mm^3
10 in.^3	160 000 mm^3
5 ft^3	0.14 m^3

(j) Although the pressure should always be in MPa for calculations, there are cases where other units are used in the text. For example, kPa is used for small pressures. Also, rounding was to one significant figure (two at the most) in most cases. See examples in the following table. (Note that 14.7 psi converts to 101 kPa, while 15 psi converts to 100 kPa. While this may seem at first glance to be an anomaly, it is consistent with the rounding philosophy.)

Pressure (U.S. Customary)	Pressure (SI)
0.5 psi	3 kPa
2 psi	15 kPa
3 psi	20 kPa
10 psi	70 kPa
14.7 psi	101 kPa
15 psi	100 kPa
30 psi	200 kPa
50 psi	350 kPa
100 psi	700 kPa
150 psi	1 MPa
200 psi	1.5 MPa
250 psi	1.7 MPa
300 psi	2 MPa
350 psi	2.5 MPa
400 psi	3 MPa
500 psi	3.5 MPa
600 psi	4 MPa
1,200 psi	8 MPa
1,500 psi	10 MPa

(k) Material properties that are expressed in psi or ksi (e.g., allowable stress, yield and tensile strength, elastic modulus) were generally converted to MPa to three significant figures. See example in the following table:

Strength (U.S. Customary)	Strength (SI)
95,000 psi	655 MPa

(l) In most cases, temperatures (e.g., for PWHT) were rounded to the nearest 5°C. Depending on the implied precision of the temperature, some were rounded to the nearest 1°C or 10°C or even 25°C. Temperatures colder than

0°F (negative values) were generally rounded to the nearest 1°C. The examples in the table below were created by rounding to the nearest 5°C, with one exception:

Temperature, °F	Temperature, °C
70	20
100	38
120	50
150	65
200	95
250	120
300	150
350	175
400	205
450	230
500	260
550	290
600	315
650	345
700	370
750	400
800	425
850	455
900	480
925	495
950	510
1,000	540
1,050	565
1,100	595
1,150	620
1,200	650
1,250	675
1,800	980
1,900	1 040
2,000	1 095
2,050	1 120

G-300 SOFT CONVERSION FACTORS

The following table of “soft” conversion factors is provided for convenience. Multiply the U.S. Customary value by the factor given to obtain the SI value. Similarly, divide

the SI value by the factor given to obtain the U.S. Customary value. In most cases it is appropriate to round the answer to three significant figures.

U.S.		Factor	Notes
Customary	SI		
in.	mm	25.4	...
ft	m	0.3048	...
in. ²	mm ²	645.16	...
ft ²	m ²	0.09290304	...
in. ³	mm ³	16,387.064	...
ft ³	m ³	0.02831685	...
U.S. gal	m ³	0.003785412	...
U.S. gal	liters	3.785412	...
psi	MPa (N/mm ²)	0.0068948	Used exclusively in equations
psi	kPa	6.894757	Used only in text and for nameplate
psi	bar	0.06894757	...
ft-lb	J	1.355818	...
°F	°C	$\frac{5}{9} \times (°F - 32)$	Not for temperature difference
°F	°C	$\frac{5}{9}$	For temperature differences only
R	K	$\frac{5}{9}$	Absolute temperature
lbm	kg	0.4535924	...
lbf	N	4.448222	...
in.-lb	N·mm	112.98484	Use exclusively in equations
ft-lb	N·m	1.3558181	Use only in text
ksi√in.	MPa√m	1.0988434	...
Btu/hr	W	0.2930711	Use for boiler rating and heat transfer
lb/ft ³	kg/m ³	16.018463	...

NONMANDATORY APPENDIX H WAVEFORM CONTROLLED WELDING

H-100 BACKGROUND

Advances in microprocessor controls and welding power source technology have resulted in the ability to develop waveforms for welding that improve the control of droplet shape, penetration, bead shape and wetting. Some welding characteristics that were previously controlled by the welder or welding operator are controlled by software or firmware internal to the power source. It is recognized that the use of controlled waveforms in welding can result in improvements in productivity and quality. The intention of this Code is to enable their use with both new and existing procedure qualifications.

The ASME Section IX heat input measurement methods in QW-409.1(a) and QW-409.1(b), were developed at a time when welding power source output was relatively constant. The heat input of welds made using waveform controlled power sources is not accurately represented by QW-409.1(a) due to the rapidly-changing outputs, phase shifts, and synergic changes, but is correctly represented by QW-409.1(b) or QW-409.1(c). During waveform controlled welding, current and voltage and values observed on the equipment meters no longer are valid for heat input determination, and must be replaced by instantaneous energy (joules) or power (joules/second or watts) to correctly calculate heat input. QW-409.1(c) more accurately reflects heat input changes when performing waveform controlled welding, but is also suitable for nonwaveform controlled (conventional) welding.

H-200 WAVEFORM CONTROLLED WELDING AND HEAT INPUT DETERMINATION

Power sources that support rapidly pulsing processes (e.g., GMAW-P) are the most common waveform controlled power sources. Power sources that are marketed as synergic, programmable, or microprocessor controlled are generally capable of waveform controlled welding. In these cases, heat input is calculated by the methods outlined in either QW-409.1(b) or QW-409.1(c) when performing procedure qualification or to determine compliance with a qualified procedure. If any doubt exists on whether waveform controlled welding is being performed, the welding equipment manufacturer should be consulted. It is recognized that waveform controls may not be active for all of the welding processes or equipment settings for a particular power source. When the

waveform control features of the equipment are not used, the heat input determination methods of either QW-409.1(a), QW-409.1(b), or QW-409.1(c) are used.

When the welding equipment does not display instantaneous energy or power, an external meter with high frequency sampling capable of displaying instantaneous energy or power is typically used, or the welding equipment is upgraded or modified to display instantaneous energy or power.

The equation shown in QW-409.1(c)(1) uses the unit of joules (J) for energy. Other conveniently obtained units of energy such as calories or British thermal units (Btu) may be used with the appropriate conversion factors. The equation shown in QW-409.1(c)(2) uses the unit of joules/second (J/s) or watts (W) for power. One J/s is equal to 1 W. Other conveniently obtained units of power, such as horsepower (HP or kilowatts (kW) may be used with the appropriate conversion factors.

H-300 NEW PROCEDURES QUALIFICATIONS

When qualifying a new procedure using waveform controlled welding, the instantaneous energy or power range is used in lieu of the current (amperage) and voltage ranges to determine the heat input per QW-409.1(c).

When qualifying a new procedure using nonwaveform controlled welding, either the current and voltage is recorded and heat input determined using the methods of QW-409.1(a) or QW-409.1(b), as previously required, or the instantaneous energy or power is recorded and the heat input determined by the method in QW-409.1(c).

H-400 EXISTING QUALIFIED PROCEDURES

Welding procedures previously qualified using nonwaveform controlled welding and heat input determined by QW-409.1(a) may continue to be used for waveform controlled welding, provided they are amended to require heat input determination for production welds using the methods of QW-409.1(c). Welding procedures previously qualified using nonwaveform controlled welding and heat input determined by QW-409.1(b) continue to be applicable for waveform controlled welding without changes to the heat input determination method.

(a) To determine if the heat input of a waveform controlled production weld meets the heat input range of a welding procedure qualified with nonwaveform controlled welding with heat input determined using QW-409.1(a)

(1) the heat input of the production weld is determined using instantaneous power or energy per the method of QW-409.1(c)

(2) the heat input of the production weld is compared to the heat input range of the welding procedure specification

(b) to determine if the heat input of a nonwaveform controlled production weld meets the heat input range of a welding procedure qualified with waveform controlled welding with heat input determined using QW-409.1(c)

(1) the heat input of the production weld is determined using QW-409.1(a) or QW-409.1(c)

(2) the heat input of the production weld is compared to the heat input range of the welding procedure specification

H-500 PERFORMANCE QUALIFICATIONS

(13)

Separate performance qualifications are not required for waveform controlled welding. However, it is recognized that a welder or welding operator may require instruction on proper use of the equipment. The extent of such instruction is best determined by the organization, as needed to understand how to properly set up and adjust the equipment for welding and conformance to the WPS requirements.

Power sources capable of waveform controlled welding often have additional operator settings that are typically not used during nonwaveform controlled welding. It is important for a welder to be familiar with other equipment parameters that can influence the overall welding performance. These can include the mode, arc control, program, cable length, wire feed speed, trim, and other machine and software settings.

MANDATORY APPENDIX J

GUIDELINE FOR REQUESTING P-NUMBER ASSIGNMENTS FOR BASE METALS NOT LISTED IN **TABLE QW/QB-422**

J-100 INTRODUCTION

This Mandatory Appendix provides requirements to Code users for submitting requests for P-Number assignments to base metals not listed in [Table QW/QB-422](#). Such requests shall be limited to base metals that are listed in ASME Code Section II, Parts A or B; ASTM; or other recognized national or international specifications. [QW-420](#) should be referenced before requesting a P-Number, to see if the base metal can be considered a P-Number under existing rules. For new materials, users shall reference the Submittal of Technical Inquiries to the Boiler and Pressure Vessel Committee in this Section and the Guideline on the Approval of New Materials, under ASME Boiler and Pressure Vessel Code in Section II, Part D. P-Number assignment does not constitute approval of a base metal for ASME Code construction. The applicable Construction Code shall be consulted for base metals that are acceptable for use.

J-200 REQUEST FORMAT

A request for a P-Number shall include the following:

- (a) product application or use
- (b) the material specification, grade, class, and type as applicable
- (c) the mechanical properties and chemical analysis requirements

(d) welding or brazing data, such as comparable P-Numbers; published welding or brazing data; welding procedure specifications and procedure qualification data; or brazing procedure specifications and procedure qualification data

(e) properties of welded or brazed base metal joints, if less than the minimum specified in the applicable specification

J-300 SUBMITTALS

Submittals to and responses from the Committee shall meet the following:

(a) *Submittal*. Requests for P-Number assignments shall be in English and preferably in the type-written form. However, legible handwritten requests will also be considered. They shall include the name, address, telephone number, fax number, and e-mail address, if available, of the requester and be mailed to The American Society of Mechanical Engineers, Attn: Secretary, BPV IX Committee, Three Park Avenue, New York, NY 10016-5990. As an alternative, requests may be submitted via e-mail to secretaryBPV@asme.org.

(b) *Response*. The Secretary of the ASME BPV IX Committee shall acknowledge receipt of each properly prepared request and shall provide written response to the requester upon completion of the requested action by the Code Committee.

(13)

NONMANDATORY APPENDIX K

GUIDANCE ON INVOKING SECTION IX REQUIREMENTS IN OTHER CODES, STANDARDS, SPECIFICATIONS, AND CONTRACT DOCUMENTS

K-100 BACKGROUND AND PURPOSE

ASME Section IX provides rules for the qualification of welding, brazing, and fusing personnel and the procedures that they follow in welding, brazing and fusing. While the historical application of Section IX has been in service to the ASME Boiler and Pressure Vessel Code and the ASME B31 Codes for Pressure Piping, Section IX is invoked by many other standards without the benefit of members of the Section IX Committee participating in those committees. In addition, Section IX is invoked in specifications and related contract documents. The purpose of this Non-mandatory Appendix is to provide guidance on invoking Section IX in other documents in a clear, concise, and accurate manner.

K-200 SCOPE OF SECTION IX AND WHAT REFERENCING DOCUMENTS MUST ADDRESS

Section IX addresses only the mandatory content of welding, brazing, and fusing procedures; the qualification of those procedures; and the qualification of personnel who follow those procedures in the manufacture, fabrication, assembly, and installation of welded and fused products. Accordingly, to ensure construction of suitable products, the requirements for the service conditions, materials used, the design of welds, preheating, postweld heat treatment, and metallurgical effects of welding; and the acceptance criteria for weld quality matters such as penetration, undercut, reinforcement, porosity, surface condition, and related examinations must be addressed in the codes, standards, specifications, or contract documents that invoke Section IX since Section IX is not a fabrication code and it does not contain requirements for welded, brazed, or fused products.

Further, construction codes may specify different requirements than those specified by Section IX; for example, ASME Section III has requirements for PWHT of procedure qualification test coupons that are more restrictive than those of Section IX, and ASME B31.1 allows fabricators and contractors to use WPSs qualified by a technically competent group or agency, whereas Section IX requires each fabricator or contractor to qualify WPSs themselves. When such requirements are specified in the

referencing construction Codes that invoke Section IX, these requirements take precedence over those of Section IX, and the manufacturer or contractor is required to comply with them.

Specifications or contract documents that are required to follow Section IX may add additional requirements, and the manufacturer or contractor shall comply with both sets of requirements.

When the reference to Section IX is not the result of mandatory requirements, such as laws, but is a matter of choice, the specification or contract document may impose additional or different requirements than those in Section IX, and the manufacturer or contractor shall comply with them. Material specifications are an example of this.

Most standards that refer to Section IX consider the requirements of Section IX to be adequate to cover the basic needs for the content of welding, brazing, and fusing procedures and for qualification of those WPSs, as well as for the qualification of the personnel who use them. However, for some applications, additional information may be required from the invoking party, as noted in [K-300](#).

K-300 RECOMMENDED WORDING — GENERAL

When invoking Section IX in general, the following wording is recommended:

“Welding, brazing, and fusing shall be performed using procedures and personnel qualified in accordance with the requirements of ASME BPVC Section IX.”

When the above is specified, qualification for the following are automatically included:

(a) all welding processes that are listed in [QW-250](#) for groove and fillet welding

(b) use of standard welding procedures specifications (SWPSs) listed in [Mandatory Appendix E](#)

(c) application of hard-facing weld metal overlay (hardness values shall be a matter of agreement between the supplier and the purchaser)

(d) application of corrosion-resistant weld metal overlay (chemical composition of the weld overlay surface shall be a matter of agreement between the supplier and the purchaser)

(e) laser beam lap joints

- (f) joining of composite (clad) materials
- (g) attachment of applied linings

K-301 RECOMMENDED WORDING FOR TOUGHNESS — QUALIFIED APPLICATIONS

When invoking Section IX and qualification of the WPS for toughness applications is required, the following wording is recommended:

“Welding procedures shall be qualified for toughness, and the supplementary essential variables of Section IX shall apply.”

The referencing construction code shall also be specified.

K-302 RECOMMENDED WORDING — TUBE-TO-TUBESHEET WELDING

When invoking Section IX for qualification of tube-to-tubesheet welding procedures and personnel, and qualification by use of mock-ups is desired, the following wording is recommended:

“Welding procedures, welders, and welding operators shall be qualified using mock-ups in accordance with Section IX.”

Note that if qualification using mock-ups is not specified but qualification to Section IX is, tube-to-tubesheet welding procedures and personnel may also be qualified following the standard groove welding rules.

K-303 RECOMMENDED WORDING — TEMPER BEAD WELDING

When invoking Section IX for qualification of temper bead welding procedures, the following wording is recommended:

“Welding procedures shall be prepared and qualified in accordance with Section IX.”

INDEX

PART QW

A-Numbers (listing), QW-442

Acceptance criteria

tension tests, QW-153

bend tests, QW-163

notch toughness, QW-171.2, QW-172.2

bend and hammer tests, QW-192.2

torque test, QW-192.3

Addenda (issuance of), QW-100.3

requalification of procedures, QW-100.3

Aluminum alloys, QW/QB-422

Austenitic stainless steels, QW/QB-422

AWS (reference to), QW-102

Backing (pertaining to performance qualification), QW-303.2, QW-303.3, QW-310.2, QW-310.3

Part IV — data, QW-402.2, QW-402.3, QW-402.4, QW-402.5, QW-402.7
definition, QW-492

Backing gas, QW-408.5, QW-408.8

Base metals (definition), QW-492

corrosion-resistance overlay cladding (pertaining to procedure qualification), QW-214.1

groove and fillet welds (pertaining to procedure qualification), QW-202.2, QW-211

stud welding, QW-202.3

variable, QW-403

Carbon steels, QW/QB-422

Combination of welding processes or procedures pertaining to performance qualification, QW-306

Consumable inserts, QW-404.22

Copper (copper-base alloys), QW/QB-422

Corrosion-resistant overlay cladding (pertaining to procedure qualification), QW-381

pertaining to performance qualification, QW-381

Definitions, QW-102, QW-490

Description of Section IX, QW-100

Dimensions

of welding groove with backing for performance qualification, QW-310.2

of welding groove without backing for performance qualification, QW-310.3

of tension test specimen, QW-462.1

of bend test specimen, QW-462.2

of test jigs, QW-466

of groove welds for procedure qualification, QW-212

Drawings (see Graphics)

Electrical characteristics, QW-409

Electrogas welding (definition), QW-492

variables for procedure qualifications, QW-259

Electron beaming (pertaining to procedure qualification), QW-215

definition, QW-492

variables for procedure qualification, QW-260

variables for performance qualification, QW-362

Electroslag welding (definition), QW-492

variables for procedure qualification, QW-258

Essential variables (performance), QW-401.2

procedure, QW-251.2, QW-401.1

Etching, QW-470

Filler metals (pertaining to procedure qualification), QW-211, QW-404

Fillet-weld tests, QW-180

Flat position (definition), QW-121.1, QW-122.1, QW-131.1, QW-132.1

Flux, QW-404.9

F-Numbers (listing), QW-430

Forms (suggested), Appendix B

Fracture tests, QW-182

Full-section specimens, QW-151.4

Gas, QW-408

Gas tungsten-arc welding (definition), QW-492

variables for procedure qualification, QW-256

variables for performance qualification, QW-356

Gas welding (definition), QW-492

variables for procedure qualification, QW-256

variables for performance qualification, QW-356

Graphics, QW-460

test positions, QW-461

groove welds in plate, QW-461.3

groove welds in pipe, QW-451.4

fillet welds in plate, QW-461.5

fillet welds in pipe, QW-461.6

stud welds, QW-461.7

test specimens, QW-462

tension — reduced section — plate, QW-462.1(a)

tension — reduced section — pipe, QW-462.1(b)

tension — reduced section — pipe alternate, QW-462.1(c)

tension — reduced section — turned specimen, QW-462.1(d)

tension — full section — small diameter pipe, QW-462.1(e)

side bend, QW-462.2

face and root bends transverse, QW-462.3(a)

face and root bends longitudinal, QW-462.3(b)

fillet welds — procedure, QW-462.4(a)

fillet welds — performance, QW-462.4(b)

fillet welds in pipe — performance, QW-462.4(c)

fillet welds in pipe — procedure, QW-462.4(d)

corrosion-resistant overlay, QW-462.5

composite test plates, QW-462.6

spot welds, QW-462.8-QW-462.11

order of removal, QW-463

plates — procedure qualification, QW-463.1(a)

plates — procedure qualification alternate, QW-463.1(b)

plates — procedure qualification longitudinal, QW-463.1(c)

pipe — procedure qualification, QW-463.1(d)

pipe — procedure qualification alternate, QW-463.1(e)

pipe — notch toughness specimen location, QW-463.1(f)

plate — procedure qualification, QW-463.2(a)

plate — procedure qualification alternate, QW-463.2(b)

plate — procedure qualification longitudinal, QW-463.2(c)

pipe — performance qualification, QW-463.2(d)

pipe — performance qualification alternate, QW-463.2(e)

pipe — performance qualification 10 in. diameter, QW-463.2(f)

pipe — performance qualification 6 in. or 8 in. diameter, QW-463.2(g)

- pipe — performance qualification fillet weld, QW-463.2(h)
- test jigs, QW-466
 - guided-bend, QW-466.1
 - guided-bend roller jig, QW-466.2
 - guided-bend wrap-around, QW-466.3
 - stud weld bend jig, QW-466.4
 - torque testing arrangement, QW-466.5
 - tensile test for studs, QW-466.6
- typical test joints, QW-469
 - butt joint, QW-469.1
 - alternative butt joint, QW-469.2
- Groove welds (pertaining to performance qualification), QW-303.1
 - with backing, QW-310.2
 - without backing, QW-310.3
- Guided-bend jig, QW-466.1
- Guided-bend roller jig, QW-466.2
- Guided-bend test (see Tests)
- Guided-bend wrap-around jig, QW-466.3
- Hard-facing overlay (pertaining to procedure qualification), QW-216
- Horizontal position, QW-121.2, QW-122.2, QW-131.2, QW-132.2
- Identification of welders and welding operators, QW-301.3
- Joints, QW-402
- Limits of qualified positions
 - procedures, QW-203
 - performance, QW-303, QW-461.9
- Longitudinal-bend tests, QW-161.5–QW-161.7
- Macro-examination, QW-183, QW-184
- Mechanical tests, QW-141, QW-202.1, QW-302.1
- Multiple positions, QW-122.3, QW-122.4, QW-132.4
- Nickel and nickel-base alloys, QW/QB-422
- Nonessential variables, QW-251.3
- Notch-toughness test, QW-170
- Order of removal, QW-463
- Orientation of welds, QW-110, QW-461.1
- Overhead position, QW-121.4, QW-131.4, QW-132.3
- Performance qualification, QW-300
- Performance qualification specimens, QW-452
- Performance variables, QW-405
- Pipe, test welds in, QW-302.3
- Pipe positions, QW-132
- Plasma-arc welding
 - variables for procedure, QW-257
 - variables for performance, QW-357
- Plate and pipe performance, QW-303.1–QW-303.4
- Plate and pipe procedure, QW-211
- P-Numbers, QW-200.3, QW/QB-422, Appendix D
- Positions of welds
 - plate and pipe groove welds
 - descriptions, QW-120–QW-123
 - sketches and graphics, QW-460–QW-461
 - plate and pipe fillet welds
 - descriptions, QW-130–QW-132
 - sketches and graphics, QW-460–QW-461
 - limits of qualified positions
 - for procedures, QW-203
 - for performance, QW-303
- Postweld heat treatment, QW-407
- PQR, QW-201.2
- Preheat, QW-406
- Procedure qualification, QW-200
- Procedure qualification record, QW-201, QW-483
- Procedure qualification specimens, QW-451
- Processes, combination of, QW-200.4, QW-306
- Processes, special, QW-251.4
- Radiography, QW-142, QW-143, QW-191
 - acceptance criteria, QW-191.1.2
 - for performance qualification, QW-302.2, QW-304
 - retests and renewal of qualification, QW-320
- Records, QW-103.2
- Record of welder or welding operator qualification tests, QW-301.4, QW-484
- Reduced-section specimens, QW-151.1, QW-151.2
- Renewal of qualification, QW-322
- Requalification, QW-350
- Responsibility of records, QW-103.2
- Responsibility of welding, QW-103.1, QW-201
- Retests, QW-321
- Scope of Section IX, QW-101
- Shielding gas, QW-408.1, QW-408.2, QW-408.3, QW-408.4, QW-408.6
- Shielded metal-arc welding
 - variables for procedure, QW-253
 - variables, QW-353
- Sketches (see Graphics)
- S-Numbers, QW-420
- Specimens, QW-450
- Stud-weld bend jig, QW-466.4
- Stud welding
 - performance qualification specimens, QW-193
 - positions, QW-123.1, QW-461.6, QW-461.7, QW-461.8
 - procedure qualification specimens, QW-192
 - variables for procedure, QW-261
 - variables for performance, QW-361
- Submerged-arc welding
 - variables for procedure, QW-254
 - variables for performance, QW-354
- Supplementary essential variables, QW-251.2, QW-401.3
- Tables
 - Welding variables, QW-415, QW-416
 - P-Numbers, QW/QB-422
 - F-Numbers, QW-432
 - A-Numbers, QW-442
 - Procedure qualification specimens, QW-451
 - Performance qualification specimens, QW-452
 - Performance qualification limitations, QW-461.9
- Technique, QW-410
- Tension test, QW-150
- Terms and definitions, QW-102, QW-492
- Test assemblies, QW-301.1
- Test jigs, QW-466
- Test joints, QW-469.1, QW-469.2
- Tests
 - acceptance criteria
 - bend and hammer, QW-192.2
 - fracture tests, QW-182
 - guided bend, QW-163
 - macro-examination, QW-183, QW-184, QW-192.1.4
 - notch-toughness tests
 - Charpy V-notch, QW-171.2
 - drop weight, QW-172.2
 - radiography, QW-191.1.2

- tension, QW-153
- torque test, QW-192.3
- ultrasonic, QW-191.2.3
- description and procedure
 - fillet weld, QW-180
 - guided bend, QW-160
 - notch toughness, QW-170
 - Charpy V-notch, QW-171
 - drop weight, QW-172
 - radiographic, QW-191
 - stud weld, QW-192
 - tension, QW-150, QW-152
 - tensile strength, QW-153.1
- for performance qualification, QW-100.2, QW-301
 - mechanical tests, QW-302.1
 - qualification tests, QW-301.2
- for procedure qualification, QW-100.1, QW-202
 - mechanical tests, QW-202.1
 - test-joint preparation, QW-210
 - test positions for groove welds, QW-120
 - test positions for fillet welds, QW-130
 - test positions for stud welds, QW-123
- types and purposes
 - fillet weld, QW-141.3
 - guided bend, QW-141.2, QW-160, QW-162, QW-451, QW-452, QW-462
 - mechanical, QW-141
 - notch toughness, QW-141.4
 - drop weight, QW-172.1
 - radiographic, QW-142, QW-143
 - special examination for welders, QW-142
 - stud weld, QW-141.5
 - tension, QW-141.1, QW-451, QW-462
 - visual, QW-302.4
- Thickness, QW-310.1, QW-351, QW-451, QW-452
- Titanium, QW/QB-422
- Torque testing for stud welds, QW-466.5
- Transverse bend tests, QW-161.1–QW-161.4
- Turned specimens, QW-151.3
- Variables, QW-250, QW-350
 - base metals, QW-403
 - electrical characteristics, QW-409
 - electrode gas welding (EGW), QW-259
 - electron beam welding (EBW), QW-260
 - electroslag welding (ESW), QW-258, QW-258.1
 - filler metals, QW-404
 - for welding operator, QW-360
 - gas, QW-408
 - gas metal-arc welding (GMAW) (MIG), QW-255, QW-255.1, QW-355
 - gas tungsten-arc welding (GTAW) (TIG), QW-256, QW-256.1, QW-356
 - general, QW-251, QW-351, QW-401
 - joints, QW-402
 - oxyfuel gas welding (OFW), QW-252, QW-252.1, QW-352
 - performance essential variable table, QW-416
 - plasma-arc welding (PAW), QW-257, QW-257.1, QW-359
 - positions, QW-405
 - postweld heat treatment (PWHT), QW-407
 - preheat, QW-406
 - procedure essential variable table, QW-415
 - shielded metal-arc welding (SMAW) (STICK), QW-253, QW-253.1, QW-353
 - stud welding, QW-261, QW-361
 - submerged-arc welding (SAW), QW-254, QW-254.1, QW-354
 - technique, QW-410
 - Vertical position, QW-121.3, QW-131.3
 - Welders and welding operators, QW-304, QW-305
 - Welding Procedure
 - Specification, QW-200.1(a), QW-482
 - WPS qualification tests, QW-202.2
- PART QB**
 - Acceptance criteria
 - tension test, QB-153
 - bend tests, QB-163
 - peel test, QB-172
 - Addenda (issuance of), QB-100.3
 - requalification of procedures, QB-100.3
 - AWS, QB-102
 - Base metal, QB-211
 - Base metal — variables, QB-402
 - BPS, QB-482
 - Brazers, QB-304
 - Brazing operators, QB-305
 - Definitions, QB-102, QB-490
 - F-Numbers, QB-430
 - Filler flow position, QB-121
 - Filler metal — variable, QB-403
 - Flow direction — variables, QB-407
 - Flow positions, QB-461
 - Flux and atmospheres (variables), QB-406
 - Forms, Appendix B
 - Graphics, QB-460
 - Guided bend test, QB-141.2, QB-160
 - Horizontal flow position, QB-124
 - Jigs, QB-162.1
 - Jigs — graphics, QB-466
 - Joint design — variables, QB-408
 - Joints, QB-210, QB-310
 - Longitudinal-bend test, QB-161.3, QB-161.4
 - Manufacturer's responsibility, QB-201
 - Order of removal — graphics, QB-463
 - Orientation, QB-110, QB-461
 - P-Numbers, QB-420
 - Peel test, QB-141.3, QB-170
 - Performance qualifications, Article XIII, QB-100.2
 - Performance qualification tests, QB-301.1
 - Position, QB-120
 - Position — graphics, QB-460
 - PQR, QB-201.2, QB-483
 - Preparation of test joints, QB-210
 - Procedure qualifications, Article XII, QB-100.1
 - Records, QB-103.2, QB-301.4
 - Reduced section, QB-151.1, QB-151.2, QB-151.3
 - Renewal of qualification, QB-322
 - Responsibility, QB-103, QB-201
 - Scope, QB-101

Sectioning test, QB-141.4, QB-181

Shear test, QB-141.1

Specimens

tension test, QB-151

guided-bend test, QB-161

peel test, QB-171

sectioning test, QB-181

workmanship sample, QB-182

for procedure qualification, QB-451

for performance qualification, QB-452

graphics, QB-462, QB-463

Temperature — variable, QB-404

Tension test, QB-141.1, QB-150

Test, QB-141

for procedure qualification, QB-202.1, QB-451

for performance qualification, QB-2-2.1, QB-451

positions, QB-120

flat-flow positions, QB-121

horizontal-flow positions, QB-124

vertical-downflow, QB-122

vertical-upflow, QB-123

Transverse bend tests, QB-161.1, QB-161.2

Variables

base metal, QB-402

brazing filler metal, QB-403

brazing flux, fuel gas or atmosphere, QB-406

brazing process, QB-405

brazing temperature, QB-404

data, QB-400

flow position, QB-407

joint design, QB-408

Vertical downfall position, QB-122

Vertical uphill position, QB-123

Workmanship samples, QB-141.5

INTENTIONALLY LEFT BLANK

ASME BOILER AND PRESSURE VESSEL CODE SECTION IX

INTERPRETATIONS Volume 62

Interpretations of the Code will be posted in January and July of 2014 and January of 2015 at <http://cstools.asme.org/interpretations.cfm>. Interpretations of Section III, Divisions 1 and 2, are part of the update service to Section III, Subsection NCA.

Interpretations Volumes 60 and 61 were included with the update service to the 2010 Edition of the Code; Volume 62 is the first Interpretations volume to be included with the update service to the 2013 Edition.

Section	Vol. 62
I	7/13
II-A	7/13
II-B	...
II-C	...
II-D (Customary)	7/13
II-D (Metric)	7/13
III-NCA	7/13
III-3	7/13
III-5	7/13
IV	7/13
V	7/13
VI	...
VII	...
VIII-1	7/13
VIII-2	7/13
VIII-3	7/13
IX	7/13
X	7/13
XI	7/13
XII	...

Copyright © 2013 by
THE AMERICAN SOCIETY OF MECHANICAL ENGINEERS
All rights reserved

www.iran-mavad.com

مرجع دانشجویان و مهندسين مواد

INTERPRETATIONS VOLUME 62 — SECTION IX

Replies to Technical Inquiries January 1, 2011 through December 31, 2012

FOREWORD

GENERAL INFORMATION

This publication includes all written interpretations issued between the indicated dates by the ASME Staff on behalf of the ASME Boiler and Pressure Vessel Committee in response to inquiries concerning interpretations of the ASME Boiler and Pressure Vessel Code. A contents is also included that lists subjects specific to the interpretations covered in the individual volume.

These interpretations are taken verbatim from the original letters, except for a few typographical and editorial corrections made for the purpose of improved clarity. In some instances, a review of the interpretation revealed a need for corrections of a technical nature. In these cases, a revised interpretation is presented bearing the original interpretation number with the suffix R and the original file number with an asterisk. Following these revised interpretations, new interpretations and revisions to them issued during the indicated dates are assigned interpretation numbers in chronological order. Interpretations applying to more than one Code Section appear with the interpretations for each affected Section.

ASME procedures provide for reconsideration of these interpretations when or if additional information is available that the inquirer believes might affect the interpretation. Further, persons aggrieved by an interpretation may appeal to the cognizant ASME committee or subcommittee. As stated in the Statement of Policy in the Code documents, ASME does not “approve,” “certify,” “rate,” or “endorse” any item, construction, proprietary device, or activity.

An interpretation applies either to the Edition and Addenda in effect on the date of issuance of the interpretation or the Edition and Addenda stated in the interpretation. Subsequent revisions to the Code may supersede the interpretation.

For detailed instructions, see “Submittal of Technical Inquiries to the ASME Boiler and Pressure Vessel Standards Committees” in the front matter.

SUBJECT AND NUMERICAL INDEXES

Subject and numerical indexes (if applicable) have been prepared to assist the user in locating interpretations by subject matter or by location in the Code. They cover interpretations issued from Volume 12 up to and including the present volume, and will be updated with each volume.

SECTION IX — INTERPRETATIONS VOL. 62

Subject	Interpretation	File No.
QW-103.2, Records	IX-13-06	12-7
QW-151.3, Tensile Tests — Turned Specimens	IX-10-37	11-2029
QW-181.2, Sectioning of Pipe-to-Pipe Quarter Sections	IX-13-04	12-120
QW-182, Fracture Tests	IX-10-32	11-939
QW-193, Macro Examination for the Mockup Test of Tube-to-Tubesheet Joint	IX-13-05	12-1563
QW-200.1(b)	IX-13-03	11-1476
QW-200.2, Use of Preliminary WPS	IX-10-22	10-1158
QW-200.4(b)	IX-10-34	10-1966
QW-201, Manufacturer's or Contractor's Responsibility	IX-10-25	11-44
QW-202.4, Dissimilar Base Metal Thicknesses	IX-13-09	12-1833
QW-250	IX-10-28	09-558
QW-288, Tube-to-Tubesheet Welder Qualification	IX-13-02	12-752
QW-300.3, Simultaneous Performance Qualifications	IX-10-29	10-339
QW-304, Volumetric Examination	IX-10-26	09-744
QW-361.2	IX-13-08	12-1501
QW-402 and QW-404 Through QW-410	IX-10-21	10-496
QW-403.6	IX-13-01	12-635
QW-404.23, Filler Metal Product Form	IX-10-38	12-47
QW-404.5, A-Number	IX-10-31	11-918
QW-404.5, A-Number Essential Variable for GMAW Weld Metal	IX-10-33	11-1339
QW-407.1(b)	IX-13-07	12-1230
QW-409.2, Combination of Processes	IX-10-24	11-216
QW-420, ASTM Materials' P-Number Assignment	IX-10-30	10-1189
QW-424.1, Base Metal Used for Procedure Qualification	IX-10-39	12-178
QW-433 and QW-452.1(b)	IX-10-23	10-1918
QW-452.1(b)	IX-10-35	11-2030
QW-452.5	IX-10-27	08-210
QW-462.4(a) and (b), Fillet Weld Test	IX-10-36	11-896

Interpretation: IX-10-21

Subject: QW-402 and QW-404 Through QW-410

Date Issued: March 11, 2011

File: 10-496

Question: When impacts are waived by a book section for the base metal (HAZ notch toughness is not required), but are required for the weld metal, do the supplementary essential variables of QW-402 and QW-404 through QW-410 apply per the applicable tables QW-252 through QW-265?

Reply: Yes.

Interpretation: IX-10-22

Subject: QW-200.2, Use of Preliminary WPS

Date Issued: March 14, 2011

File: 10-1158

Question: Does ASME Section IX require a preliminary WPS be used during procedure qualification testing, or that a WPS number be recorded on the PQR?

Reply: No.

Interpretation: IX-10-23

Subject: QW-433 and QW-452.1(b)

Date Issued: March 14, 2011

File: 10-1918

Background: A welder tests on an NPS 6 Sch. 80 (0.432 in. wall) coupon, depositing 0.100 in. of E6010 and the balance of 0.332 in. using E7018.

Question (1): Using E6010, is the welder qualified to deposit 0.864 in. maximum of weld metal?

Reply (1): Yes.

Question (2): Using E7018, is the welder qualified to deposit 0.664 in. maximum of weld metal?

Reply (2): Yes.

Question (3): Is the welder qualified to deposit 0.864 in. of weld metal using E6010 plus 0.664 in. of E7018 weld metal deposit thickness for a total of 1.528 in. in the same groove?

Reply (3): No. See QW-452.1(b).

Interpretation: IX-10-24

Subject: QW-409.2, Combination of Processes

Date Issued: March 14, 2011

File: 11-216

Background: A welder was tested on an SA-516 Gr. 70 plate, using the GMAW process. Short arc mode was used for depositing the root, and spray arc mode was used for depositing the balance of the weld in a single coupon.

Question: Is it permissible, according to ASME Section IX, QW-409.2, to use two modes of metal transfer in a single test coupon?

Reply: Yes; the deposit thickness for each transfer mode shall be recorded as required by QW-306.

Interpretation: IX-10-25

Subject: QW-201, Manufacturer's or Contractor's Responsibility

Date Issued: May 23, 2011

File: 11-44

Question: May an organization with more than one ASME Certificate of Authorization, under different names and in different locations, describe in its quality assurance programs the operational control of procedure qualifications and the use of welding procedures properly qualified under one certificate holder, under another certificate holder within the organization, but without separate qualification, as permitted by Section IX, QW-201?

Reply: Yes.

Interpretation: IX-10-26

Subject: QW-304, Volumetric Examination

Date Issued: June 13, 2011

File: 09-744

Question: Does Section IX require a welder to qualify for small diameter butt welds by preparing more than one small diameter pipe coupon to provide a minimum circumferential weld length when qualified by volumetric examination under the provisions of QW-304?

Reply: Yes.

Interpretation: IX-10-27

Subject: QW-452.5

Date Issued: August 1, 2011

File: 08-210

Question: Is it the intent of QW-452.5 to permit welder or welding operator fillet weld performance qualification testing to be conducted using test coupon thicknesses greater than $\frac{3}{8}$ in. thick?

Reply: Yes.

Interpretation: IX-10-28

Subject: QW-250
Date Issued: August 1, 2011
File: 09-558

Question (1): Is it the intent of the Code that Variables QW-403.6, QW-406.3, QW-409.1, QW-410.9, and QW-410.10 apply when specified in QW-250 for P-No. 10H materials?

Reply (1): No.

Question (2): Is it the intent of the Code that Variable QW-407.4 apply when specified in QW-250 for P-No. 10H materials?

Reply (2): Yes.

Interpretation: IX-10-29

Subject: QW-300.3, Simultaneous Performance Qualifications
Date Issued: August 1, 2011
File: 10-339

Question: Is it the intent of Section IX, QW-300.3 to permit an AWS standard welding procedure specification adopted by a contractor to be used in lieu of a PQR to support the range of variables for a single WPS proposed for use in conducting simultaneous welder performance qualification testing?

Reply: Yes.

Interpretation: IX-10-30

Subject: QW-420, ASTM Materials' P-Number Assignment
Date Issued: August 1, 2011
File: 10-1189

Question: Is it the intent that material produced under an ASTM specification shall be considered to have the same P-Number or P-Number plus Group Number as that of the P-Number or P-Number plus Group Number assigned to the same grade or type material in the corresponding ASME specification (e.g., SA-240 Type 304 is assigned P-No. 8, Group No. 1; therefore, A 240 Type 304 is considered P-No. 8, Group No. 1)?

Reply: Yes.

Interpretation: IX-10-31

Subject: QW-404.5, A-Number

Date Issued: August 25, 2011

File: 11-918

A procedure qualification test coupon was prepared and tested, which included a chemical analysis of the weld metal. The chemical analysis results were as follows: C: 0.08%, Cr: 0.044%, Mo: 0.14%, Ni: 1.48%, Mn: 1.45%, Si: 0.19%.

Question (1): Does this chemistry meet an A-1 classification?

Reply (1): No.

Question (2): Does this chemistry meet an A-10 classification?

Reply (2): Yes.

Interpretation: IX-10-32

Subject: QW-182, Fracture Tests

Date Issued: August 25, 2011

File: 11-939

Question (1): Is it required by QW-182 that the sum of all rounded indications (regardless of diameter) be considered in addition to the sum of the lengths of inclusions in determining the $\frac{3}{8}$ in. (10 mm) maximum allowed for acceptance?

Reply (1): Yes.

Question (2): Is it permissible to apply the porosity size limitation of $\frac{1}{32}$ in. or greater as specified in QW-191.1.2.2 (b) (3) to a $\frac{1}{2}$ in. (12 mm) welded coupon to the fracture test acceptance criteria of QW-182?

Reply (2): No.

Interpretation: IX-10-33

Subject: QW-404.5, A-Number Essential Variable for GMAW Weld Metal

Date Issued: November 14, 2011

File: 11-1339

Question (1): According to QW-404.5, may the A-Number of GMAW weld metal be established from the chemical analysis of a weld deposit prepared according to the filler metal specification when the shielding gas used for the chemical analysis was different from that used in the procedure qualification?

Reply (1): No.

Question (2): According to QW-404.5, may the A-Number of GMAW weld metal be established from the chemical analysis of a weld deposit prepared according to the filler metal specification provided the shielding gas used for the chemical analysis was the same as that used in the procedure qualification?

Reply (2): Yes.

Question (3): Are the GMAW rules in QW-404.5 for establishing A-Numbers also applicable to FCAW?

Reply (3): Yes.

Interpretation: IX-10-34

Subject: QW-200.4(b)

Date Issued: December 8, 2011

File: 10-1966

Background: PQR A is welded with SMAW to join $\frac{5}{8}$ in. (16 mm) thick plates with $\frac{5}{8}$ in. (16 mm) of SMAW deposit. PQR B is welded with GTAW and SMAW to join $\frac{5}{16}$ in. (8 mm) thick plates with $\frac{1}{8}$ in. (3 mm) of GTAW and $\frac{3}{16}$ in. (5 mm) of SMAW deposit. PQR C is welded with GTAW to join $\frac{3}{16}$ in. (5 mm) thick plates with $\frac{3}{16}$ in. (5 mm) of GTAW deposit.

Question (1): Do PQRs A and B qualify the combination WPS for a base metal thickness range of $\frac{1}{16}$ in. (1.5 mm) to $1\frac{1}{4}$ in. (32 mm) when impact testing is not required?

Reply (1): No.

Question (2): Do PQRs A and B qualify the combination WPS for a base metal thickness range of $\frac{1}{16}$ in. (5 mm) to $1\frac{1}{2}$ (38 mm) when impact testing is not required?

Reply (2): No.

Question (3): Do PQRs A and B qualify the combination WPS for a maximum deposit weld metal thickness range of $\frac{1}{4}$ in. (6 mm) for the GTAW process and $1\frac{1}{4}$ in. (32 mm) for the SMAW process?

Reply (3): No.

Question (4): Do PQRs A and C qualify the combination WPS for a maximum deposit weld metal thickness range of $\frac{3}{8}$ in. (10 mm) for the GTAW process and $1\frac{1}{4}$ in. (32 mm) for the SMAW process?

Reply (4): No.

Question (5): Do PQRs A and C qualify the combination WPS for a base metal thickness range of $\frac{1}{16}$ in. (1.5 mm) to $1\frac{1}{4}$ in. (32 mm) when impact testing is not required?

Reply (5): No.

Question (6): Do PQRs A and C qualify the combination WPS for a base metal thickness range of $\frac{1}{16}$ in. (1.5 mm) to $1\frac{1}{2}$ in. (38 mm) when impact testing is not required?

Reply (6): No.

Question (7): Do the provisions in QW-200.4(b) affect the responses to the above questions?

Reply (7): No.

Interpretation: IX-10-35

Subject: QW-452.1(b)

Date Issued: December 8, 2011

File: 11-2030

Question: Regarding QW-452.1(b) for performance qualification, is “Maximum to be welded” equivalent to “Unlimited”?

Reply: Yes.

Interpretation: IX-10-36

Subject: QW-462.4(a) and (b), Fillet Weld Test

Date Issued: February 16, 2012

File: 11-896

Question (1): May a WPS qualified with a fillet weld using a plate tee-joint configuration as shown in QW-462.4(a) be used to join a plate to a pipe with fillet welds made parallel to the axis of the pipe for nonpressure-retaining applications?

Reply (1): Yes.

Question (2): May a welder qualified with a fillet weld using a plate tee-joint configuration as shown in QW-462.4(b) be used to weld a plate to a pipe with fillet welds made parallel to the axis of the pipe?

Reply (2): Yes.

Interpretation: IX-10-37

Subject: QW-151.3, Tensile Tests — Turned Specimens

Date Issued: February 16, 2012

File: 11-2029

Question: For a 1-in. (25-mm) deep groove weld deposited in a 2-in. (50-mm) thick plate test coupon, may a single-turned 0.505-tensile specimen conforming to QW-462.1(d) be used for each tension test required by QW-451?

Reply: Yes.

Interpretation: IX-10-38

Subject: QW-404.23, Filler Metal Product Form

Date Issued: February 16, 2012

File: 12-47

Question: May stranded filler metal be considered the same as bare (solid or metal cored) filler metal in QW-404.23?

Reply: Yes.

Interpretation: IX-10-39

Subject: QW-424.1, Base Metal Used for Procedure Qualification

Date Issued: February 16, 2012

File: 12-178

Question: Does a PQR recording a P-No. 5B base metal welded to itself support a WPS for welding P-No. 5B metal to any metal assigned P-No. 4, 3, or 1?

Reply: No.

Interpretation: IX-13-01

Subject: QW-403.6
Date Issued: July 2, 2012
File: 12-635

Question: Does QW-403.6 apply when the HAZ is not subject to impact testing such as when qualifying a P-8 material?

Reply: Yes.

Interpretation: IX-13-02

Subject: QW-288, Tube-to-Tubesheet Welder Qualification
Date Issued: August 23, 2012
File: 12-752

Question: When a demonstration mock-up for tube-to-tubesheet welder or welding operator qualification is required, are all of the variables specified in QW-288 required to be followed during the performance qualification test?

Reply: Yes, see QW-193.2.

Interpretation: IX-13-03

Subject: QW-200.1(b)
Date Issued: September 13, 2012
File: 11-1476

Background: QW-200.1(b) says: "The completed WPS shall describe all of the essential, nonessential, and, when required, supplementary essential variables for each welding process used in the WPS."

Question (1): If a WPS is written and qualified for welding P-No.1 material to itself, is it necessary to specifically mention on the WPS or on the PQR anything regarding QW-410.64, which addresses the use of thermal processes for cutting or backgouging when welding on P-No.11A and P-No.11B materials?

Reply (1): No. The fact that the WPS and PQR are for welding on P-No.1 materials precludes the need to specifically describe the use of thermal cutting or backgouging for P-No.11A or P-No. 11B materials on either the WPS or the PQR.

Question (2): If a WPS specifies the use of ER70S-6 filler metal, is it necessary to specifically mention in the WPS anything regarding QW-404.23, which addresses filler metal product form by specifying that the filler metal has to be solid?

Reply (2): No. The designation ER70S-6 specifies that the filler metal be solid wire, and that is sufficient for describing the variable QW-404.23.

Question (3): If a WPS is written and qualified for welding P-No. 5A material to itself, is it necessary to specifically mention on a WPS or on the PQRs for submerged arc welding anything regarding QW-404.34 that addresses, when welding on P-No.1 materials, the use of active or neutral flux?

Reply (3): No. The use of active or neutral fluxes only needs to be specified on the WPS and documented on the PQR when the base metal is P-No.1.

Interpretation: IX-13-04

Subject: QW-181.2, Sectioning of Pipe-to-Pipe Quarter Sections

Date Issued: September 13, 2012

File: 12-120

Question: If the resultant size from a pipe-to-pipe quarter section, per QW-462.4(c), is too large to bend as specified in QW-181.2, can the fracture test quarter section specimen be cut into multiple specimens and tested in lieu of one full quarter specimen?

Reply: Yes.

Interpretation: IX-13-05

Subject: QW-193, Macro Examination for the Mockup Test of Tube-to-Tubesheet Joint

Date Issued: November 14, 2012

File: 12-1563

Question: When performing a tube-to-tubesheet test in accordance with QW-193, is it required to section a total of 10 tubes and perform a macroetch of the 40 surfaces exposed by sectioning?

Reply: Yes.

Interpretation: IX-13-06

Subject: QW-103.2, Records

Date Issued: December 6, 2012

File: 12-7

Background: In the 2006 Addenda to Section IX, it became mandatory to certify qualification records "by signature or other means as described in the manufacturer's or contractor's Quality Control System."

Question: Prior to the 2006 Addenda, is a typed signature or means other than a written signature on a procedure qualification or performance qualification record considered certified as required in QW/QB-103.2?

Reply: Prior to the 2006 Addenda, the method of certification for procedure and performance qualification records was not addressed by Section IX.

Interpretation: IX-13-07

Subject: QW-407.1(b)

Date Issued: December 6, 2012

File: 12-1230

Background:

(a) P-No. 8 plate is welded, heated to 780°C (1,436°F), then formed, followed by a solution heat treatment at 1 060°C (1,940°F).

(b) P-No. 8 plate is welded, then cold formed, followed by a solution heat treatment at 1 060°C (1,940°F).

Question: Is WPS supported by a PQR with 1 060°C (1,940°F) solution heat treatment qualified to weld P-No. 8 base material as described in (a) and (b) of the Background?

Reply: Yes.

Interpretation: IX-13-08

Subject: QW-361.2

Date Issued: December 6, 2012

File: 12-1501

Question: A welding operator (machine) successfully qualifies in accordance with QW-300, using an open root, single-welded, Vee-groove joint configuration, without backing and without a consumable insert. Is the welding operator (machine) qualified to perform machine welding with a consumable insert?

Reply: Yes.

Interpretation: IX-13-09

Subject: QW-202.4, Dissimilar Base Metal Thicknesses

Date Issued: December 6, 2012

File: 12-1833

Question: Does QW-202.4 allow a WPS qualified on groove weld, with specified P-No. 1 base metal thickness range of $\frac{1}{2}$ in. (13 mm) through 1 in. (25 mm), to be used in production to weld a $\frac{1}{2}$ in. (13 mm) thick base metal to a $\frac{3}{8}$ in. (10 mm) thick base metal?

Reply: No.

INTENTIONALLY LEFT BLANK

NUMERIC INDEX

Location	Interpreta- tion	File No.	Page No.	Location	Interpreta- tion	File No.	Page No.
Appendix C	IX-92-98	BC94-236	327	Part QB (Cont'd)			
Code Case 2141	IX-92-82	BC93-434	317	QB-484	IX-89-93	BC90-783	249
Code Case 2142-1	IX-01-16	BC01-338	433	Part QW			
Code Case 2143-1	IX-01-16	BC01-338	433	QW-100.1	IX-83-17	BC82-422	13
Q-11, 1971 Edition	IX-83-02	BC81-704	6		IX-89-03	BC88-166A	182
Q-11(b)(3), 1971 Edition,				QW-100.3	IX-83-99	BC83-472	63
Winter 1973 Addenda	IX-83-41	BC82-796	28		IX-92-86	BC93-658	318
Q-11(5), 1971 Edition, Winter					IX-01-22	BC01-679	440
1973 Addenda	IX-83-40	BC82-794	27		IX-01-22R	BC01-679*, BC04-600	481
Section II, Part C	IX-89-97	BC90-873	250		IX-01-26	BC01-826	441
	IX-92-27	BC91-471	273		IX-04-10	BC04-601	464
	IX-92-61	BC92-422	304		IX-07-05	BC04-600	482
	IX-92-94	BC93-754	326		IX-10-04	09-490	495
	IX-92-99	BC93-762,		QW-103	IX-92-09	BC91-260	265
		BC93-769	327		IX-92-80	BC93-584	316
	IX-01-25	BC01-815	441		IX-92-81	BC92-306	316
	IX-01-29	BC02-2692	445	QW-103.1	IX-92-16	BC91-314	268
	IX-01-38	BC03-274	452	QW-103.2	IX-92-55	BC92-307	295
Part QB					IX-13-06	12-7	516
Part QB	IX-86-73	BC86-332	159		IX-01-10	BC01-073	428
QB-121	IX-92-86	BC93-655	318	QW-144	IX-83-110	BC83-692	69
QB-123	IX-92-86	BC93-655	318	QW-150	IX-83-38	BC82-771	26
QB-141.4	IX-83-76	BC83-248	44	QW-151	IX-92-19	BC91-390	269
	IX-98-01	BC97-304	383		IX-92-37	BC92-097	282
QB-172	IX-89-74	BC90-429	234	QW-151.1	IX-89-25	BC89-099	197
QB-181	IX-83-76	BC83-248	44		IX-89-83	BC90-532	243
QB-200.4	IX-89-103	BC91-096	253		IX-89-90	BC90-532	247
QB-201.3	IX-86-21	BC86-058	126		IX-92-79	BC93-583	315
QB-203.1	IX-86-02	BC85-292	113	QW-151.1(d)	IX-83-119	BC84-253	79
	IX-01-34	BC02-3541	451		IX-01-21	BC01-035	439
QB-303.3	IX-01-34	BC02-3541	451	QW-151.2	IX-83-120	BC83-474	79
QB-402.1	IX-92-74	BC93-474	313	QW-151.2(d)	IX-83-95	BC83-301	61
	IX-92-93	BC93-752	325	QW-151.3	IX-92-29	BC91-473	279
QB-402.2	IX-83-136	BC84-398	87		IX-92-63	BC92-452	304
QB-402.3	IX-83-49	BC82-871	33		IX-04-01	BC02-3586	457
QB-406.1	IX-83-118	BC84-183	78		IX-04-25	BC05-1404	474
QB-406.3	IX-83-118	BC84-183	78		IX-10-37	11-2029	514
QB-408.1	IX-01-34	BC02-3541	451	QW-153.1	IX-89-04	BC88-167	182
QB-408.2	IX-86-11	BC85-420	116		IX-95-06	BC94-542	336
	IX-86-22	BC85-531	126		IX-01-18	BC01-772	435
QB-408.4	IX-01-34	BC02-3541	451	QW-153.1(d)	IX-95-09	BC94-570	344
QB-415	IX-92-83	BC93-527	317	QW-160	IX-83-156	BC84-697	98
QB-451.3	IX-04-06	BC03-1664	459		IX-92-10	BC91-261	265
	IX-10-09	09-883	501		IX-95-15	BC95-094	346
QB-451.3 [Note (1)]	IX-98-01	BC97-304	383	QW-162.1	IX-83-115	BC83-279	77
QB-451.5	IX-10-09	09-883	501		IX-86-37	BC86-297	139
QB-452.1 [Note (1)]	IX-83-76	BC83-248	44	QW-163	IX-83-60	BC82-749	38
QB-461	IX-86-02	BC85-292	113		IX-83-120	BC83-474	79
QB-462.1(a)	IX-89-49	BC89-372	218		IX-86-42	BC86-331	141
QB-462.1(b)	IX-89-49	BC89-372	218		IX-86-61	BC86-515	153
QB-462.1(c)	IX-89-81	BC90-537	237	QW-180	IX-10-10	09-2140	502
QB-462.1(e)	IX-04-06	BC03-1664	459	QW-181.1	IX-92-11	BC91-263	266
QB-463	IX-83-76	BC83-248	44		IX-86-40	BC86-329	141
QB-466.3	IX-86-38	BC86-298	140		IX-10-12	10-13	502
QB-482	IX-89-93	BC90-783	249				

(a)

www.iran-mavad.com

مرجع دانشجویان و مهندسين مواد

SECTION IX — CUMULATIVE INDEX — INTERPRETATIONS VOLS. 12-62

Location	Interpreta- tion	File No.	Page No.	Location	Interpreta- tion	File No.	Page No.
Part QW (Cont'd)				Part QW (Cont'd)			
QW-181.2	IX-13-04	12-120	516		IX-92-42	BC92-011	291
QW-181.2.1	IX-10-05	09-1956	495		IX-92-97	BC94-167	327
QW-182	IX-10-32	11-939	512	QW-200.4(a)(2)	IX-89-43	BC89-365	215
QW-183	IX-92-24	BC91-280	272	QW-200.4(b)	IX-92-75	BC93-490	313
QW-184	IX-92-24	BC91-280	272		IX-01-21	BC01-035	439
	IX-04-21	BC05-528	473		IX-01-32	BC02-3449	447
QW-191	IX-83-52	BC83-001	34		IX-04-18	BC05-25	472
	IX-83-142	BC84-548	89	QW-201	IX-10-34	10-1966	513
	IX-83-157	BC84-700	98		IX-83-03	BC82-056	7
	IX-83-174	BC84-557	107		IX-83-12	BC82-341	11
QW-191.2.2	IX-86-62	BC86-517	153		IX-83-25	BC81-160	16
QW-191.2.2(b)(1)	IX-83-173	BC85-013	106		IX-83-39	BC83-792	26
QW-191.2.2(b)(3)	IX-83-173	BC85-013	106		IX-83-68	BC83-040	41
QW-193	IX-13-05	12-1563	516		IX-83-151	BC84-620	96
QW-194	IX-01-03	BC00-519	420		IX-86-49	BC86-367	144
	IX-01-10	BC01-073	428		IX-89-73	BC90-319	234
QW-194.1	IX-86-18	BC85-585	125		IX-92-07	BC91-156	264
QW-195	IX-92-13	BC91-278	267		IX-92-66	BC93-377	305
QW-200	IX-86-42	BC86-331	141		IX-92-67	BC93-391	306
	IX-89-17	BC88-473	193		IX-92-80	BC93-584	316
	IX-92-38	BC91-630	283		IX-92-81	BC92-306	316
QW-200.1	IX-83-03	BC82-056	7		IX-92-92	BC93-678	325
	IX-89-03	BC88-166A	182		IX-95-25	BC95-252	359
	IX-92-30	BC91-587	279		IX-95-26	BC95-303	359
	IX-98-13	BC98-239	396		IX-95-27	BC95-482	360
QW-200.1(b)	IX-89-85	BC90-671	244		IX-95-29	BC95-302	360
	IX-95-01	BC94-104	333		IX-95-40	BC93-431,	
	IX-13-03	11-1476	515			BC95-222	376
QW-200.1(c)	IX-83-54	BC83-042	35		IX-98-02	BC97-309	383
	IX-83-111	BC84-001	70		IX-01-02	BC00-553	419
QW-200.2	IX-83-03	BC82-056	7		IX-01-40	BC03-740	453
	IX-83-72	BC83-269	43		IX-04-26	BC05-1196	477
	IX-86-70	BC87-089	157		IX-07-02	06-912	481
	IX-86-87	BC87-490A	175	QW-201.1	IX-10-25	11-44	510
	IX-92-78	BC93-561	318		IX-98-18	BC99-025	403
	IX-98-04	BC97-481	384		IX-01-40	BC03-740	453
	IX-01-05	BC00-654	420		IX-07-10	08-1002	488
	IX-04-10	BC04-601	464	QW-202	IX-92-17	BC91-315	268
	IX-04-14	BC04-1592	466	QW-202.2	IX-83-103	BC83-237	65
	IX-10-22	10-1158	509		IX-86-74	BC87-134	165
QW-200.2(b)	IX-83-164	BC85-023	103		IX-92-11	BC91-263	266
	IX-92-16	BC91-314	268	QW-202.2(b)	IX-95-03	BC94-235	334
	IX-92-25	BC91-415	272		IX-01-17	BC01-615	434
QW-200.2(c)	IX-83-171	BC85-132	105	QW-202.2(c)	IX-89-87	BC90-745	245
	IX-07-08	08-209	488		IX-89-100	BC90-663	252
QW-200.2(f)	IX-86-06	BC85-328	115		IX-89-100R	BC90-663*	261
	IX-04-05	BC03-1583	458	QW-202.3	IX-83-93	BC83-531	56
QW-200.3	IX-83-115	BC83-279	77		IX-83-114	BC84-070	71
	IX-89-37	BC89-358	212		IX-83-160	BC84-219	100
	IX-89-66	BC90-281	226		IX-86-56	BC86-429	146
QW-200.4	IX-83-80	BC83-388	50		IX-89-12	BC88-401	187
	IX-83-83	BC83-394	53		IX-95-34	BC96-060	368
	IX-86-06	BC85-328	115		IX-10-15	10-359	503
	IX-86-08	BC85-134	116	QW-202.3(b)	IX-01-17	BC01-615	434
	IX-86-23	BC85-553	127	QW-202.4	IX-83-123	BC84-092	80
	IX-86-33	BC86-262	138		IX-86-36	BC86-280	139
	IX-92-77	BC93-518	314		IX-86-43	BC86-337	142
	IX-95-10	BC94-662	344		IX-86-89	BC88-089	176
	IX-01-24	BC01-814	440		IX-92-11	BC91-263	266
	IX-04-08	BC03-1770	464		IX-95-12	BC95-027	345
	IX-10-14	09-2144	503		IX-01-23	BC01-789	440
QW-200.4(a)	IX-86-01	BC85-036	113		IX-04-11	BC04-599	465

(b)

www.iran-mavad.com

مرجع دانشجویان و مهندسين مواد

SECTION IX — CUMULATIVE INDEX — INTERPRETATIONS VOLS. 12-62

Location	Interpreta- tion	File No.	Page No.	Location	Interpreta- tion	File No.	Page No.
Part QW (Cont'd)				Part QW (Cont'd)			
	IX-13-09	12-1833	517		IX-98-14	BC98-447	397
QW-202.4(b)	IX-98-20R	BC99-539*	426	QW-300.1	IX-86-05	BC85-306	114
	IX-01-19	BC01-811	435		IX-86-24	BC86-001	128
QW-203	IX-95-13	BC94-035	345		IX-86-25	BC86-018	128
QW-204	IX-89-67	BC90-335	226		IX-95-35	BC96-287	368
QW-211	IX-83-15	BC82-388	13	QW-300.2	IX-83-133	BC84-370	86
	IX-89-105	BC91-119	254		IX-83-151	BC84-620	96
	IX-04-23	BC05-784	474		IX-86-64	BC86-395	154
QW-214	IX-86-71	BC87-090	157		IX-89-10	BC88-398	186
	IX-92-06	BC91-054	264		IX-92-25	BC91-415	272
	IX-92-60	BC92-421	303		IX-95-32	BC95-302	367
	IX-95-34	BC96-060	368		IX-01-08	BC01-030	427
	IX-10-19	09-2143	506		IX-01-15	BC01-641	433
QW-214.1	IX-83-48	BC82-870	32		IX-10-02	09-747	493
QW-214.3	IX-89-77	BC90-492	236	QW-300.3	IX-92-39	BC92-121	283
	IX-92-54	BC92-305	295		IX-95-14	BC95-040	345
QW-216	IX-89-29	BC89-178	204		IX-95-19	BC95-221	352
	IX-92-03	BC90-523	262		IX-10-29	10-339	511
	IX-95-34	BC96-060	368	QW-301	IX-83-103	BC83-237	65
QW-216.1	IX-89-32	BC89-287	205		IX-86-69	BC87-088	156
QW-216.2(d)	IX-89-39	BC89-361	213		IX-89-79	BC90-531	237
	IX-89-77	BC90-492	236		IX-92-17	BC91-315	268
QW-218	IX-89-31	BC89-178	204		IX-92-23	BC90-494	271
	IX-92-20	BC91-396	270	QW-301.1	IX-83-153	BC84-664	97
QW-250	IX-89-11	BC88-399	186	QW-301.2	IX-83-31	BC82-395	19
	IX-89-85	BC90-671	244		IX-83-149	BC84-558	95
	IX-10-07	09-588	496		IX-07-11	08-1607	489
	IX-10-28	09-558	511	QW-301.4	IX-83-32	BC82-598	19
QW-251.2	IX-83-79	BC83-358	50		IX-83-163	BC85-022	102
QW-251.4	IX-92-44	BC92-168	291		IX-86-13	BC85-507	118
QW-253	IX-92-57	BC92-354	296		IX-86-90	BC88-091	176
QW-254	IX-83-27	BC82-713	17		IX-89-30	BC89-177	204
QW-255	IX-95-16	BC95-095	346		IX-01-36	BC02-4198	452
	IX-07-03	07-1041	481	QW-302.1	IX-10-01	09-567	493
QW-256	IX-86-26	BC86-059	129	QW-302.2	IX-86-34	BC86-265	138
	IX-92-57	BC92-354	296		IX-86-79	BC87-140	167
	IX-04-17	BC05-24	471		IX-10-01	09-567	493
QW-256.1	IX-10-18	09-994	505	QW-302.3	IX-89-64	BC90-297	225
QW-258.1	IX-04-02	BC03-1029	457	QW-302.4	IX-92-71	BC93-365	312
QW-280	IX-89-92	BC90-681	248		IX-95-17	BC95-035	351
	IX-92-44	BC92-168,		QW-303	IX-89-98	BC91-003	251
		BC90-691	291		IX-92-15	BC91-293	267
QW-281.2(b)	IX-89-70	BC90-430	227	QW-303.1	IX-83-98	BC83-450	63
QW-281.2(c)	IX-86-59	BC86-458	152		IX-83-155	BC84-692	98
QW-281.2(e)	IX-83-129	BC84-251	84		IX-86-74	BC87-134	165
QW-281.5(a)	IX-89-44	BC89-366	215	QW-303.2	IX-92-45	BC92-238	292
QW-282	IX-83-125	BC84-151	81	QW-303.3	IX-92-46	BC92-265	292
	IX-89-54	BC89-367	220	QW-304	IX-83-19	BC82-440	14
QW-282.4(h)	IX-89-59	BC90-250	222		IX-83-57	BC83-079	37
QW-282.6(m)	IX-83-09	BC82-279	10		IX-83-91	BC83-528	56
QW-283	IX-89-22	BC89-094	195		IX-83-108	BC83-639	68
	IX-01-33	BC02-3896	447		IX-86-85	BC87-492	174
QW-284	IX-95-42	BC97-044	377		IX-95-39	BC96-331	375
QW-288	IX-13-02	12-752	515		IX-10-03	09-1012	494
QW-300	IX-83-21	BC82-499	15		IX-10-26	09-744	510
	IX-86-25	BC86-018	128	QW-304.1	IX-83-128	BC84-226	83
	IX-89-48	BC89-360	217		IX-01-04	BC00-653	420
	IX-92-91	BC93-755	324	QW-305	IX-89-108	BC91-157	256
	IX-92-95	BC94-008	326	QW-306	IX-83-83	BC83-394	53
	IX-95-20	BC95-302	352		IX-83-107	BC83-550	67
	IX-95-36	BC96-314	369		IX-86-23	BC85-553	127
	IX-98-11	BC98-133	395		IX-92-26	BC91-470	273

SECTION IX — CUMULATIVE INDEX — INTERPRETATIONS VOLS. 12-62

Location	Interpreta- tion	File No.	Page No.	Location	Interpreta- tion	File No.	Page No.
Part QW (Cont'd)				Part QW (Cont'd)			
	IX-92-59	BC92-206	303	QW-355	IX-86-12	BC85-482	117
	IX-92-68	BC92-011A	306		IX-86-46	BC86-219	143
QW-310	IX-92-31	BC91-613	280		IX-10-03	09-1012	494
QW-310.1	IX-86-35	BC86-266	139	QW-356	IX-79-52R	BC79-046*	49
	IX-04-07	BC03-1686	459		IX-83-116	BC84-054	77
QW-310.2	IX-89-89	BC90-769	246		IX-86-68	BC87-039	156
	IX-04-23	BC05-784	474		IX-92-01	BC90-501	285
QW-310.4	IX-83-42	BC83-803	28		IX-89-51	BC90-038	219
QW-310.5(c)	IX-83-70	BC83-270	42		IX-01-09	BC01-032	428
	IX-83-101	BC83-529	64	QW-360	IX-86-68	BC87-039	156
QW-311	IX-83-121	BC84-134	80	QW-361.2	IX-95-31	BC96-141	361
(New QW-381)	IX-83-132	BC84-366	85		IX-98-14	BC98-447	397
	IX-83-162	BC84-663	102		IX-13-08	12-1501	517
	IX-86-27	BC86-061	129	QW-364	IX-92-58	BC92-357	296
QW-311(a)	IX-83-101	BC83-529	64	QW-380	IX-89-71	BC90-039	233
QW-312(a)	IX-83-134	BC84-396	86		IX-89-92	BC90-681,	
QW-320	IX-86-24	BC86-001	128			BC90-691	248
QW-321	IX-83-13	BC82-346	12	QW-381	IX-86-27	BC86-061	129
QW-321.2(a)	IX-86-79	BC87-140	167		IX-86-58	BC86-457	152
QW-321.3	IX-92-73	BC93-468	313		IX-86-66	BC87-036	155
QW-322	IX-83-58	BC83-086	37		IX-86-71	BC87-090	157
	IX-83-113	BC84-055	71		IX-92-72	BC93-392	312
	IX-83-117	BC84-133	78		IX-98-14	BC98-447	397
	IX-83-124	BC84-149	81	QW-382	IX-92-02	BC90-518	262
	IX-83-128	BC84-226	83		IX-92-04	BC90-530	263
	IX-83-154	BC84-689	97	QW-383	IX-86-32	BC86-222	138
	IX-83-166	BC85-030	104		IX-89-101	BC91-085	252
	IX-83-167	BC85-031	104	QW-400	IX-83-82	BC83-303	52
	IX-83-170	BC85-091	105	QW-401.3	IX-01-39	BC03-469	453
	IX-86-07	BC85-560	115		IX-04-04	BC03-1246	458
	IX-86-19	BC85-587	129		IX-07-09	08-576	488
	IX-86-50	BC86-389	144	QW-401.15	IX-89-28	BC89-174	203
	IX-89-38	BC89-359	213	QW-402	IX-89-53	BC90-045	219
	IX-89-54	BC89-367	220		IX-10-21	10-496	509
	IX-89-63	BC90-254	224	QW-402.3	IX-86-54	BC86-400	146
	IX-92-12	BC91-264	266	QW-402.4	IX-89-28	BC89-174	203
	IX-92-22	BC91-425	271	QW-402.5	IX-86-54	BC86-400	146
	IX-92-64	BC92-464	305	QW-402.6	IX-83-04	BC82-098	8
	IX-95-38	BC96-132	375	QW-402.10	IX-83-04	BC82-098	8
	IX-01-21	BC01-035	439		IX-83-71	BC83-230	43
QW-322(a)	IX-83-150	BC84-617	96		IX-89-42	BC89-364	215
	IX-83-159	BC84-690	99	QW-402.11	IX-86-80	BC87-253	167
	IX-83-164	BC85-023	103	QW-402.12	IX-98-06	BC98-009	389
	IX-86-52	BC86-394	145	QW-402.14	IX-98-06	BC98-009	389
	IX-86-81	BC87-242	173	QW-403	IX-83-20	BC82-496	14
	IX-86-82	BC87-252	173		IX-83-116	BC84-054	77
	IX-89-27	BC89-100	203	QW-403.1	IX-83-45	BC82-385	30
	IX-89-38	BC89-359	213		IX-89-14	BC88-403	187
	IX-89-54	BC89-367	220		IX-95-24	BC95-194	359
QW-322.1	IX-04-21	BC05-528	473	QW-403.5	IX-83-92	BC83-530	56
QW-322.1(a)	IX-10-17	10-1161	504		IX-83-135	BC84-397	87
QW-322.1(b)	IX-95-19	BC95-221	352		IX-86-15	BC85-532	123
QW-322.2	IX-92-47	BC92-266	292		IX-86-75	BC87-136	165
	IX-04-13	BC04-1457	466		IX-86-78	BC87-139	166
QW-322.2(a)	IX-01-12	BC01-201	430		IX-89-23	BC89-096	196
QW-350	IX-86-51	BC86-390	145		IX-89-26	BC89-103	197
	IX-95-30	BC96-073	361		IX-89-75	BC90-443	235
QW-351	IX-83-55	BC83-059	36		IX-89-78	BC90-515	236
	IX-83-77	BC83-253	49		IX-92-70	BC92-450	311
	IX-83-143	BC84-581	89		IX-92-70R	BC00-470	425
	IX-89-02	BC88-090	181		IX-95-21	BC95-318	353
	IX-92-32	BC91-631	280		IX-01-30	BC02-2693	446

(d)

www.iran-mavad.com

مرجع دانشجویان و مهندسين مواد

SECTION IX — CUMULATIVE INDEX — INTERPRETATIONS VOLS. 12-62

Location	Interpreta- tion	File No.	Page No.	Location	Interpreta- tion	File No.	Page No.
Part QW (Cont'd)				Part QW (Cont'd)			
QW-403.6	IX-04-16	BC04-1418	471		IX-83-100	BC83-563	63
	IX-83-148	BC84-417	95	QW-404.14	IX-83-89	BC83-402	55
	IX-89-07	BC88-171	184		IX-89-68	BC90-349	227
	IX-89-86	BC90-734	245	QW-404.15	IX-89-47	BC89-370	217
	IX-89-96	BC90-872	250	QW-404.22	IX-83-22	BC82-516	15
	IX-92-50	BC92-217	293		IX-89-91	BC90-680	247
	IX-92-87	BC93-151	323		IX-07-07E	08-40	497
	IX-04-04	BC03-1246	458	QW-404.23	IX-07-04	BC07-1343	482
	IX-04-15	BC04-1595	467		IX-10-38	12-47	514
	IX-07-09	08-576	488	QW-404.24	IX-10-16	10-1159	504
	IX-13-01	12-635	515	QW-404.25	IX-89-80	BC90-536	237
QW-403.8	IX-83-97	BC83-444	62	QW-404.26	IX-89-80	BC90-536	237
	IX-83-127	BC84-224	83	QW-404.27	IX-10-16	10-1159	504
QW-403.9	IX-83-152	BC84-648	96	QW-404.28	IX-83-100	BC83-563	63
	IX-04-09	BC04-065	464		IX-89-61	BC90-252	223
QW-403.10	IX-95-28	BC96-002	360	QW-404.30	IX-89-20	BC88-478	194
	IX-95-33	BC96-001	367		IX-89-24	BC89-097	196
	IX-01-01	BC00-514	419	QW-404.31	IX-89-56	BC90-036	221
QW-403.11	IX-83-11	BC82-300	11	QW-404.32	IX-83-112	BC84-038	70
	IX-83-35	BC82-599	25		IX-01-01	BC00-514	419
	IX-83-56	BC83-078	36	QW-404.33	IX-01-37	BC03-263	452
	IX-86-75	BC87-136	165	QW-404.36	IX-04-19	BC05-26	472
	IX-89-75	BC90-443	235	QW-405.1	IX-89-20	BC88-478	194
	IX-89-84	BC90-664	244		IX-89-24	BC89-097	196
	IX-89-88	BC90-768	246	QW-405.2	IX-83-50	BC82-872	33
QW-403.12	IX-89-61	BC90-252	223		IX-04-28	BC06-323	478
QW-403.16	IX-89-20	BC88-478	194	QW-405.3	IX-83-177	BC85-092	108
	IX-89-82	BC90-531	243		IX-86-86	BC87-494	175
	IX-89-91	BC90-680	247		IX-92-01	BC90-501	285
QW-403.18	IX-83-106	BC83-630	67		IX-98-15	BC98-448	397
	IX-83-137	BC84-399	87		IX-10-20	10-1487	506
	IX-86-41	BC86-330	141	QW-406.1	IX-83-161	BC84-618	101
QW-404	IX-83-37	BC82-770	26		IX-83-165	BC85-024	103
	IX-86-03	BC85-293	114	QW-406.2	IX-83-161	BC84-618	101
	IX-86-65	BC87-031A	155	QW-406.3	IX-92-57	BC92-354	296
	IX-86-76	BC87-137	166	QW-407	IX-83-130	BC84-252	84
	IX-89-105	BC91-119	254		IX-86-04	BC85-304	114
	IX-98-19	BC99-409	409		IX-86-20	BC86-010	125
	IX-10-21	10-496	509		IX-86-76	BC87-137	166
QW-404.4	IX-83-10	BC82-299	10	QW-407.1	IX-83-29	BC82-763	18
	IX-83-87	BC83-340	54		IX-83-30	BC82-243	18
QW-404.5	IX-83-176	BC85-088	107		IX-98-10	BC97-306,	
	IX-83-140R	BC84-250*	137			BC97-308	395
	IX-86-57	BC86-263	151		IX-01-20	BC01-813	435
	IX-86-84	BC87-491	174		IX-04-03	BC03-1212	458
	IX-89-34	BC89-172	211		IX-04-20	BC05-293	472
	IX-89-55	BC89-371	220		IX-07-06	BC07-1708	483
	IX-89-58	BC90-249	221	QW-407.1(b)	IX-81-31R	BC82-097*	5
	IX-10-31	11-918	512		IX-86-47	BC86-223	143
	IX-10-33	11-1339	512		IX-04-29	BC06-462	478
QW-404.5(b)	IX-10-13	09-1368	503		IX-07-01	BC06-285	481
QW-404.9	IX-83-46	BC82-751	31		IX-13-07	12-1230	517
	IX-83-59	BC82-614	37	QW-407.2	IX-83-29	BC82-763	18
	IX-83-61	BC82-831	39		IX-83-86	BC83-294	54
	IX-83-84	BC83-398	53		IX-83-145	BC84-584	90
	IX-83-96	BC83-442	62		IX-92-84	BC93-586	318
	IX-83-169	BC85-089	105		IX-04-15	BC04-1595	467
	IX-95-37	BC96-315	369		IX-07-06	BC07-1708	483
QW-404.12	IX-92-21	BC91-397	270		IX-10-08	09-513	501
QW-404.13	IX-83-06	BC82-245	9	QW-407.4	IX-83-11	BC82-300	11
	IX-83-47	BC82-790	32		IX-83-35	BC82-599	25
	IX-83-97	BC83-444	62		IX-86-23	BC85-553	127

(e)

www.iran-mavad.com

مرجع دانشجویان و مهندسين مواد

SECTION IX — CUMULATIVE INDEX — INTERPRETATIONS VOLS. 12-62

Location	Interpreta- tion	File No.	Page No.	Location	Interpreta- tion	File No.	Page No.
Part QW (Cont'd)				Part QW (Cont'd)			
	IX-92-33	BC91-614	280		IX-89-26	BC89-103	197
	IX-01-17	BC01-615	434		IX-89-41	BC89-363	214
	IX-04-22	BC04-1301	473		IX-89-75	BC90-443	235
QW-408	IX-89-16	BC88-405	188		IX-89-88	BC90-768	246
	IX-95-11	BC95-002	344		IX-95-22	BC95-251	353
QW-408.2	IX-92-62	BC92-425	304	QW-424.1	IX-89-58	BC90-249	221
	IX-95-16	BC95-095	346		IX-10-12	10-13	502
QW-408.3	IX-86-67	BC87-038	155		IX-10-39	12-178	514
QW-408.8	IX-83-168	BC85-059	104	QW-432	IX-83-24	BC82-588	16
QW-408.9	IX-83-146	BC84-619	90		IX-80-52R	BC80-435*	49
	IX-86-67	BC87-038	155		IX-92-99	BC93-762, BC93-769	327
QW-409	IX-83-26	BC82-182	17		IX-98-08	BC98-131	390
QW-409.1	IX-83-33	BC82-617	19		IX-10-23	10-1918	509
	IX-83-175	BC85-038	107	QW-433	IX-89-46	BC89-369	216
	IX-92-40	BC92-110	284	QW-442	IX-83-14	BC82-302	12
	IX-92-87	BC93-151	323	QW-450	IX-83-78	BC83-300	50
	IX-92-88	BC93-593	323	QW-450 vs QW-461	IX-83-01	BC81-702	5
	IX-04-12	BC04-1013	466	QW-451	IX-83-05	BC82-237	8
	IX-04-14	BC04-1592	466		IX-83-08	BC82-265	10
QW-409.2	IX-07-03	BC07-1041	481		IX-83-36	BC82-757	25
	IX-10-24	11-216	510		IX-83-64	BC83-222	40
QW-409.4	IX-01-28	BC02-2691	445		IX-83-104	BC83-349	66
QW-409.8	IX-89-19	BC88-476	194		IX-83-105	BC83-471	66
	IX-89-36	BC89-357	212		IX-83-141	BC84-434	89
	IX-92-88	BC93-593	323		IX-83-177	BC85-092	108
	IX-95-18	BC95-220	351		IX-86-31	BC86-101	137
	IX-04-17	BC05-24	471		IX-89-07	BC88-171	184
QW-410	IX-10-21	10-496	509		IX-89-62	BC90-253	224
QW-410.7	IX-86-55	BC86-426	146		IX-89-83	BC90-532	243
QW-410.9	IX-86-60	BC86-514A	152		IX-89-99	BC91-022	251
QW-410.15	IX-86-44	BC86-365	142		IX-92-19	BC91-390	269
	IX-86-63	BC86-520	154		IX-92-34	BC91-586	281
QW-410.25	IX-83-69	BC82-233	42		IX-92-37	BC92-097	282
QW-410.26	IX-86-26	BC86-059	129		IX-92-68	BC92-011A	306
QW-410.38	IX-04-02	BC03-1029	457		IX-98-03	BC97-479	383
QW-410.42	IX-98-07	BC98-009	390		IX-98-12	BC98-237, BC98-238	396
QW-410.51	IX-01-06R	BC98-240*	426		IX-04-04	BC03-1246	458
QW-415	IX-89-79	BC90-531	237		IX-04-05	BC03-1583	458
	IX-89-82	BC90-531	243		IX-83-18	BC82-423	14
QW-416	IX-86-72	BC87-091	158	QW-451.1	IX-83-43	BC82-822	29
	IX-86-86	BC87-494	175		IX-83-81	BC83-395	51
QW-420	IX-10-30	10-1189	511		IX-83-88	BC83-396	54
QW-420.1	IX-07-05	BC04-600	482		IX-83-94	BC83-284	61
QW-420.2	IX-95-07	BC94-522	343		IX-83-102	BC83-551	65
	IX-01-07	BC01-029	427		IX-83-122	BC83-645	80
QW-422	IX-83-34	BC82-514	25		IX-86-36	BC86-280	139
	IX-83-131	BC84-365	85		IX-86-48	BC86-281	143
	IX-86-88	BC88-041	176		IX-89-18	BC88-474	193
	IX-89-14	BC88-403	187		IX-89-107	BC91-124	255
	IX-89-36	BC89-357	212		IX-01-35	BC02-4075	451
	IX-89-88	BC90-768	246		IX-04-11	BC04-599	465
	IX-92-08	BC91-257	265		IX-86-40	BC86-329	141
	IX-92-18	BC91-389	297	QW-451.3	IX-92-51	BC92-276	294
	IX-95-05	BC94-365	336		IX-92-56	BC92-308	295
	IX-07-14	09-486	493		IX-04-25	BC05-1404	474
QW-423	IX-86-17	BC85-554	124		IX-83-07	BC82-246	9
	IX-89-15	BC88-404	183	QW-452	IX-83-16	BC82-396	13
	IX-92-18	BC91-389	297		IX-83-67	BC83-123	41
	IX-01-31	BC02-2694	446		IX-83-104	BC83-349	66
QW-423.1	IX-89-58	BC90-249	221		IX-86-30	BC86-104	131
	IX-92-65	BC93-148	305				
QW-424	IX-89-05	BC88-168	188				

SECTION IX — CUMULATIVE INDEX — INTERPRETATIONS VOLS. 12-62

Location	Interpreta- tion	File No.	Page No.	Location	Interpreta- tion	File No.	Page No.
Part QW (Cont'd)				Part QW (Cont'd)			
	IX-86-39	BC86-299	140		IX-92-72	BC93-392	312
	IX-89-02	BC88-090	181		IX-92-90	BC93-753	324
QW-452.1	IX-83-66	BC83-058	41		IX-04-07	BC03-1686	459
	IX-83-88	BC83-396	54		IX-04-24	BC05-1195	474
	IX-83-90	BC83-407	55	QW-462	IX-86-09	BC85-200	116
	IX-89-06	BC88-169	183		IX-89-102	BC91-086	253
	IX-89-21	BC89-031	195		IX-92-76	BC93-515	312
	IX-89-52	BC90-044	219		IX-95-02	BC94-181	333
	IX-89-64	BC90-297	225	QW-462.1	IX-83-110	BC83-692	69
	IX-89-95	BC90-869	250		IX-92-29	BC91-473	279
	IX-89-107	BC91-124	255		IX-98-09	BC97-302	395
	IX-92-35	BC91-277	281	QW-462.1(a)	IX-86-45	BC86-366	142
	IX-92-36	BC91-616	282		IX-89-25	BC89-099	197
	IX-92-53	BC92-254	294	QW-462.1(d)	IX-83-139	BC83-629	88
	IX-92-59	BC92-206	303		IX-89-89	BC90-769	246
	IX-92-89	BC93-653	324	QW-462.1(e)	IX-83-95	BC83-301	61
	IX-01-27	BC02-111	441	QW-462.3(a)	IX-83-144	BC84-583	90
QW-452.1(b)	IX-10-23	10-1918	509		IX-89-72	BC90-042	233
	IX-10-35	11-2030	513	QW-462.3(b)	IX-83-144	BC84-583	90
QW-452.3	IX-83-22	BC82-516	15	QW-462.4	IX-92-51	BC92-276	294
	IX-83-23	BC82-530	15	QW-462.4(a)	IX-95-08	BC94-543	343
	IX-83-66	BC83-058	41		IX-10-36	11-896	514
	IX-83-158	BC84-368	99	QW-462.4(b)	IX-89-45	BC89-368	216
	IX-86-29	BC86-103	130		IX-10-36	11-896	514
	IX-89-09	BC88-397	185	QW-462.5	IX-92-05	BC90-632	263
	IX-89-69	BC90-401	227		IX-92-52	BC92-252	294
	IX-89-94	BC90-785	249	QW-462.5(a)	IX-98-16	BC98-453	398
	IX-89-104	BC91-097	253	QW-463.1(b)	IX-83-15	BC82-388	13
	IX-89-106	BC91-120	254	QW-463.2(g)	IX-83-75	BC83-149	44
	IX-92-59	BC92-206	303	QW-466	IX-83-51	BC83-881	34
	IX-92-89	BC93-653	324		IX-92-48	BC92-267	293
	IX-95-04	BC94-296	335		IX-92-49	BC92-268	293
	IX-04-07	BC03-1686	459		IX-95-15	BC95-094	346
QW-452.4	IX-92-45	BC92-238	292	QW-466.1	IX-83-73	BC82-866	43
	IX-92-51	BC92-276	294		IX-83-74	BC82-867	44
QW-452.5	IX-10-06	08-210	496		IX-83-115	BC83-279	77
	IX-10-27	08-210	510		IX-89-37	BC89-358	212
QW-452.6	IX-89-57	BC90-040	221		IX-07-12	08-1161	489
QW-453	IX-92-05	BC90-632	263		IX-10-10	09-2140	502
	IX-92-72	BC93-392	312	QW-466.3	IX-83-109	BC83-689	68
	IX-95-23	BC95-428	353		IX-86-37	BC86-297	139
	IX-95-41	BC97-028	376	QW-482	IX-86-14	BC85-483	123
	IX-98-05	BC98-009	389		IX-89-01	BC88-042	181
	IX-98-17	BC98-055	403	QW-483	IX-86-14	BC85-483	123
	IX-10-11	09-2141	502		IX-86-70	BC87-089	157
QW-461.1(a)	IX-83-65	BC83-225	40	QW-484	IX-83-53	BC83-002	35
QW-461.9	IX-83-28	BC82-748	18		IX-07-13	08-1464	489
	IX-83-44	BC82-838	29	QW-492	IX-86-16	BC85-533	124
	IX-83-53	BC83-002	35		IX-89-62	BC90-253	224
	IX-83-134	BC84-396	86		IX-92-43	BC92-100	291
	IX-86-29	BC86-103	130		IX-98-15	BC98-448	397
	IX-89-98	BC91-003	251	QW-500	IX-01-14	BC01-332	433
	IX-92-15	BC91-293	267	QW-510	IX-01-11	BC01-089	429
	IX-92-41	BC92-035	284	QW-540	IX-01-11	BC01-089	429
	IX-92-46	BC92-265	292				

(g)

www.iran-mavad.com

مرجع دانشجویان و مهندسين مواد

INTENTIONALLY LEFT BLANK

SUBJECT INDEX

Subject	Interpreta- tion	File No.	Page No.	Subject	Interpreta- tion	File No.	Page No.
Base Metals				Brazing Procedure Specification (Cont'd)			
P-Number reassignment	IX-01-22	BC01-679	440	recording information on BPS	IX-89-93	BC90-783	249
	IX-01-22R	01-679*, 04-600	481	recording information on the Brazer or Brazing Operator			
	IX-07-05	04-600	482	Qualification Test	IX-89-94	BC90-785	249
	IX-10-04	09-490	495	requalification of	IX-86-22	BC85-531	126
P-Number substitution	IX-83-20	BC82-496	14	Brazing Test Specimens			
	IX-83-56	BC83-078	36	butt and scarf joints	IX-89-49	BC89-372	218
	IX-83-96	BC83-442	62	positions	IX-92-85	BC93-655	318
	IX-86-17	BC85-554	124	tension tests	IX-04-06	BC03-1664	459
	IX-86-18	BC85-585	125		IX-10-09	09-883	501
	IX-89-29	BC89-176	204	Certification			
	IX-89-61	BC90-252	223	of the PQR	IX-83-03	BC82-056	7
	IX-89-75	BC90-443	235	of the WPS	IX-83-03	BC82-056	7
	IX-95-21	BC95-318	353	Clad Materials			
	IX-95-22	BC95-251	353	joining of	IX-10-18	09-994	505
qualifying for notch toughness	IX-95-24	BC95-194	359	Consumable Inserts			
	IX-83-92	BC83-530	54	addition/deletion	IX-89-91	BC90-680	247
	IX-86-48	BC86-281	143	performance qualification	IX-83-06	BC82-245	9
	IX-89-75	BC90-443	235		IX-83-22	BC82-516	15
	IX-89-84	BC90-664	244	qualifying viewing windows	IX-83-104	BC83-349	66
	IX-89-96	BC90-872	250	Cover Pass			
	IX-92-70	BC92-450	311	remelting of	IX-83-89	BC83-402	55
	IX-92-70R	BC00-470	425	Diameters, Pipe			
	IX-92-87	BC93-151	323	performance qualification	IX-83-55	BC83-059	29
	IX-89-37	BC89-358	212	ranges listed on the WPS	IX-83-44	BC82-838	36
qualifying for test specimens	IX-89-88	BC90-768	246		IX-89-82	BC90-531	243
	IX-01-30	BC02-2693	446	Dust			
	IX-13-01	12-635	515	amount in powdered filler metal	IX-83-09	BC82-279	10
	IX-01-01	BC00-514	419	Edition of Code			
thickness	IX-01-19	BC01-811	435	the use of the referenced	IX-01-13	BC01-570	430
	IX-04-09	BC04-065	464	edition of the Code	IX-01-26	BC01-826	441
	IX-04-11	BC04-599	465	Essential Variables (see Variables)			
	IX-13-01	12-635	515	Filler Materials (see also SFA Specifications)			
use of as filler metal	IX-83-87	BC83-340	56	change in electrode classification	IX-83-84	BC83-303	53
					IX-89-61	BC90-252	223
Brazing Base Metals					IX-92-21	BC91-397	270
P-Number substitution	IX-92-74	BC93-474	313		IX-98-19	BC99-409	409
Brazing Performance Qualification				change in product forms	IX-07-04	07-1343	482
limits of qualified positions	IX-01-34	BC02-3541	451	change in wire classification	IX-83-84	BC83-398	53
Brazing Procedure Qualification					IX-83-169	BC85-089	105
by Part QW welding					IX-95-37	BC96-315	369
qualification	IX-92-83	BC93-527	317		IX-98-19	BC99-409	409
electrode classification	IX-95-13	BC94-035	345	Brazing Procedure Specification			
for attaching small				combination of thicknesses	IX-89-104	BC91-097	253
penetrations	IX-86-73	BC86-332	159	qualification of hard-facing	IX-92-83	BC93-527	317
joint design	IX-01-34	BC02-3541	451				
qualification by proof test	IX-86-53	BC86-399	145				
S-Number substitution	IX-92-93	BC93-752	325				

SECTION IX — CUMULATIVE INDEX — INTERPRETATIONS VOLS. 12-62

Subject	Interpreta- tion	File No.	Page No.	Subject	Interpreta- tion	File No.	Page No.
Filler Materials (see also SFA Specifications) (Cont'd)				Nozzle Joint Design (Cont'd)			
chemical analysis of weld							
deposit	IX-86-57	BC86-263	151	Operational Control			
electrode spacing	IX-86-44	BC86-365	142	change in company name	IX-83-25	BC81-160	16
flux-cored consumable	IX-89-105	BC91-119	254	contractor's associations	IX-83-68	BC83-040	41
nonferrous	IX-83-176	BC85-088	107	of welding procedures	IX-83-03	BC82-056	7
qualifying as a welded					IX-83-151	BC84-620	96
buildup	IX-83-114	BC84-070	71		IX-86-64	BC86-395	154
recrushed slag	IX-04-19	BC05-26	472		IX-07-02	06-912	481
stranded	IX-10-38	12-47	514		IX-07-10	08-1002	488
supplementary powder,				organizations not involved in			
addition, deletion or				Code applications	IX-83-39	BC82-792	26
increase	IX-89-80	BC90-536	237				
without SFA specification	IX-86-03	BC85-293	114	Peel Test, Brazing			
				acceptance criteria	IX-89-74	BC90-429	234
					IX-98-01	BC97-304	383
Flux				Performance Qualification			
active/neutral	IX-86-16	BC85-533	124	alternate base materials for			
flux-cored arc welding	IX-10-03	09-1012	494	welder qualification	IX-92-18	BC91-389	297
					IX-92-65	BC93-148	305
F-Numbers					IX-01-31	BC02-2694	446
change in	IX-83-10	BC82-299	10	A-number substitution	IX-86-84	BC87-491	174
	IX-89-28	BC89-174	203		IX-89-29	BC89-176	204
classification	IX-89-46	BC89-369	216		IX-92-18	BC91-389	297
	IX-92-99	BC93-762	327	applied lining or clad plate	IX-89-101	BC91-085	252
		BC93-769	327	by several contractors			
classification of martensitic				simultaneously	IX-86-25	BC86-018	128
materials	IX-83-24	BC82-588	16		IX-86-81	BC87-242	173
use of electrodes to conform					IX-95-32	BC95-302	367
F-No.	IX-89-29	BC89-176	204	change in angle groove	IX-86-69	BC87-088	156
	IX-01-16	BC01-338	433	change in vertical welding	IX-92-01	BC90-501	285
Interpass Temperatures				combination of welding			
listing of on the WPS	IX-83-41	BC82-796	28	processes	IX-92-01	BC90-501	285
	IX-83-161	BC84-618	101		IX-92-26	BC91-470	273
qualification of	IX-83-41	BC82-796	28	consumable inserts	IX-83-06	BC82-245	9
	IX-83-129	BC84-251	84		IX-83-22	BC82-516	15
Machine Welding					IX-07-07E	08-40	497
definition of	IX-92-43	BC92-100	291	continuity	IX-13-08	12-1501	517
Multiprocess Welds				corrosion-resistant weld	IX-10-17	10-1161	504
qualified thickness range for				metal overlay	IV-86-32	BC86-222	138
performance qualification	IX-83-14	BC83-302	12		IX-86-58	BC86-457	152
	IX-89-35	BC89-307	211		IX-86-66	BC87-036	155
qualified thickness range for					IX-89-79	BC90-531	237
procedure qualification	IX-83-83	BC83-394	53		IX-89-71	BC90-039	233
	IX-95-33	BC96-001	367		IX-92-72	BC93-392	312
required test specimens for					IX-95-23	BC95-428	353
procedure qualification	IX-83-01	BC81-702	5		IX-95-30	BC96-073	361
root pass without backing	IX-89-01	BC88-042	181	diameter limitation	IX-98-14	BC98-447	397
with notch-toughness					IX-89-09	BC88-397	185
requirements	IX-83-33	BC82-617	19		IX-89-69	BC90-401	227
					IX-89-98	BC91-003	251
Nonessential Variables (see also Variables)					IX-89-104	BC91-097	253
addressing	IX-98-13	BC98-239	396		IX-89-106	BC91-120	254
ranges for	IX-83-04	BC82-098	8		IX-92-15	BC91-263	267
					IX-92-41	BC92-035	284
Normalized Materials					IX-92-90	BC93-753	324
qualified by non-normalized					IX-95-04	BC94-296	335
materials	IX-83-86	BC83-294	54	editorial correction to WPQ	IX-92-96	BC93-755	326
				effective operational control	IX-89-10	BC88-398	186
Nozzle Joint Design				of	IX-95-20	BC95-302	352
base metal thickness	IX-86-31	BC86-101	137		IX-95-32	BC95-302	367

SECTION IX — CUMULATIVE INDEX — INTERPRETATIONS VOLS. 12-62

Subject	Interpreta- tion	File No.	Page No.	Subject	Interpreta- tion	File No.	Page No.
Performance Qualification (Cont'd)				Performance Qualification (Cont'd)			
electrodes	IX-95-30	BC96-073	361		IX-86-30	BC86-104	131
employer's responsibility	IX-01-15	BC01-641	433		IX-86-35	BC86-266	139
fillet welds	IX-83-04	BC82-098	8		IX-89-24	BC89-097	196
	IX-83-103	BC83-237	65		IX-89-40	BC89-362	214
	IX-86-28	BC86-062	130		IX-89-98	BC91-003	251
	IX-92-45	BC92-238	292		IX-92-15	BC91-263	267
	IX-10-06	08-210	496		IX-92-41	BC92-035	284
fillet welds qualified by groove welds					IX-92-46	BC92-265	292
	IX-83-16	BC82-396	13		IX-92-90	BC93-753	324
	IX-83-98	BC84-450	63		IX-04-24	BC05-1195	474
	IX-86-74	BC87-134	165	process substitution	IX-86-46	BC86-219	143
	IX-89-31	BC89-178	204	production assembly mock-up	IX-10-05	09-1596	495
F-Number qualification	IX-89-87	BC90-745	245		IX-10-12	10-13	502
	IX-79-52R	BC79-046*	49	qualification with and without backing			
	IX-80-52R	BC80-435*	49		IX-92-96	BC94-102	326
	IX-98-08	BC98-131	390		IX-01-09	BC01-032	428
further training groove welds	IX-83-13	BC82-346	12	questioning of ability	IX-86-24	BC86-001	128
	IX-83-16	BC82-396	13	recording information on WPQ			
	IX-89-20	BC88-478	194		IX-86-13	BC85-507	118
	IX-89-89	BC90-769	246		IX-86-72	BC87-091	158
	IX-89-94	BC90-785	249		IX-89-30	BC89-177	204
	IX-95-04	BC94-296	335		IX-89-47	BC89-370	217
hard facing weld metal overlay	IX-04-23	BC05-784	474	records	IX-95-38	BC96-132	375
					IX-01-36	BC02-4198	452
	IX-92-02	BC90-518	262	renewal of	IX-83-154	BC84-689	97
machine welding macro examination	IX-95-23	BC95-428	353		IX-83-159	BC84-690	99
	IX-95-31	BC96-141	361		IX-83-164	BC85-023	103
	IX-92-24	BC91-280	272		IX-83-166	BC85-030	104
maintenance of manual/machine welding substitution	IX-86-82	BC87-252	173		IX-83-167	BC85-031	104
					IX-86-07	BC85-560	115
	IX-86-68	BC87-039	156		IX-86-19	BC85-587	125
manual/semiautomatic welding substitution	IX-89-38	BC89-359	213		IX-86-50	BC86-389	144
					IX-86-52	BC86-394	145
	IX-95-36	BC96-314	369		IX-89-32	BC89-100	203
multiprocess	IX-83-14	BC82-302	12		IX-92-12	BC91-264	266
	IX-83-107	BC83-550	67		IX-92-22	BC91-425	271
	IX-86-13	BC85-507	118		IX-92-47	BC92-266	292
	IX-86-23	BC85-553	127		IX-92-64	BC92-464	305
	IX-86-39	BC86-299	140		IX-01-21	BC01-035	439
	IX-83-163	BC85-022	102		IX-04-13	BC04-1457	466
	IX-86-05	BC85-306	114	requalification after failure	IX-92-56	BC92-308	295
partial-penetration groove welds				requalification after failure and further training	IX-92-73	BC93-468	313
	IX-83-155	BC84-692	98	requalification for friction weld operator	IX-92-58	BC92-357	296
P-Number substitutions	IX-83-40	BC82-794	27	requalifying for Addenda changes	IX-83-112	BC84-038	70
	IX-83-42	BC82-803	28	responsibility of	IX-83-21	BC82-499	15
	IX-83-63	BC83-122	40		IX-83-100	BC83-563	63
	IX-83-70	BC83-270	42		IX-83-101	BC83-529	64
	IX-83-116	BC84-054	77		IX-83-106	BC83-630	67
	IX-83-137	BC84-399	87		IX-83-113	BC83-055	71
	IX-86-17	BC85-554	124		IX-83-117	BC84-133	78
	IX-86-18	BC85-585	125		IX-83-121	BC84-134	80
	IX-86-41	BC86-330	141		IX-83-124	BC84-149	81
	IX-86-51	BC86-390	145		IX-83-128	BC84-226	83
	IX-86-72	BC87-091	158		IX-83-131	BC84-365	85
	IX-89-15	BC88-404	188		IX-83-132	BC84-366	85
	IX-89-33	BC89-175	205		IX-83-133	BC84-370	86
	IX-83-28	BC82-748	18		IX-83-134	BC84-396	86
	IX-83-108	BC83-639	68		IX-92-25	BC91-415	272
	IX-83-162	BC84-663	102		IX-98-14	BC98-447	397
	IX-83-170	BC85-091	105				
	IX-83-177	BC85-092	108				
	IX-86-29	BC86-103	130				
position							

(k)

www.iran-mavad.com

مرجع دانشجویان و مهندسين مواد

SECTION IX — CUMULATIVE INDEX — INTERPRETATIONS VOLS. 12-62

Subject	Interpreta- tion	File No.	Page No.	Subject	Interpreta- tion	File No.	Page No.
Performance Qualification (Cont'd)				Performance Qualification (Cont'd)			
revoking of qualification	IX-10-02	09-747	493	welding of joint by more than one welder	IX-89-06	BC88-169	183
	IX-95-19	BC95-221	352	when welding PQR coupon	IX-83-31	BC82-395	19
	IX-04-21	BC05-528	473		IX-86-90	BC88-091	176
simultaneous qualification of welders	IX-92-39	BC92-121	283		IX-89-48	BC89-360	217
	IX-95-14	BC95-040	345		IX-10-01	09-567	493
	IX-10-29	10-339	511	with a tube end gun	IX-83-67	BC83-123	41
special process	IX-89-92	BC90-681,		with/without backing	IX-83-168	BC85-059	104
		BC90-691	248		IX-86-23	BC85-553	127
strip electrodes	IX-95-30	BC96-073	361				
test coupon qualification	IX-92-31	BC91-613	280	Plasma Arc Welding	IX-89-40	BC89-362	214
test specimen movement	IX-86-77	BC87-138	166				
thickness limitation	IX-83-90	BC83-407	55	P-Numbers			
	IX-83-158	BC84-368	99	assignments	IX-07-14	09-486	493
	IX-89-02	BC88-090	181		IX-10-30	10-1189	511
	IX-89-24	BC89-097	196	chemical analysis/mechanical properties of	IX-86-88	BC88-041	176
	IX-89-32	BC89-287	205	classification of	IX-83-156	BC84-697	98
	IX-89-64	BC90-297	225		IX-92-08	BC91-257	265
	IX-89-83	BC90-532	243		IX-95-05	BC94-365	336
	IX-89-95	BC90-869	250	welding of non-pressure retaining attachments	IX-89-05	BC88-168	183
	IX-89-96	BC90-872	250				
	IX-92-36	BC91-616	282	Positions, Brazing			
	IX-92-35	BC91-277	281	qualification of flow positions	IX-86-02	BC85-292	113
	IX-92-32	BC91-631	280				
	IX-92-51	BC92-276	294	Positions, Welding			
	IX-92-59	BC92-206	303	fillet welds in vertical-up progression	IX-83-82	BC83-303	52
	IX-95-23	BC95-428	353	listing on the WPS	IX-83-44	BC82-830	29
	IX-95-28	BC96-002	360	qualification of 2G position	IX-83-75	BC83-149	44
	IX-98-05	BC98-009	389	qualification of 6G position	IX-04-07	BC03-1686	459
	IX-98-17	BC98-055	403	recording welder qualification			
	IX-10-35	11-2030	513	for	IX-83-53	BC83-002	35
type of tests required	IX-92-17	BC91-315	268	stud welding	IX-04-28	BC06-323	478
	IX-92-23	BC90-494	270	vertical-down progression	IX-10-20	10-1489	506
ultrasonic examination	IX-95-35	BC96-287	368	vertical-up progression	IX-83-50	BC82-872	33
units of measurement	IX-04-27	BC05-1215	477		IX-86-86	BC87-494	175
using radiography	IX-83-19	BC82-440	14	Postweld Heat Treatment			
	IX-83-52	BC83-001	34	addition of	IX-86-47	BC86-223	143
	IX-83-57	BC83-079	36		IX-07-01	06-285	481
	IX-83-91	BC83-528	56	change in base metal thickness	IX-92-33	BC91-614	280
	IX-83-142	BC84-548	89		IX-04-15	BC04-1595	467
	IX-83-173	BC85-013	106	change in soaking time	IX-83-130	BC84-252	84
	IX-83-174	BC84-557	107	limit on maximum time	IX-83-145	BC84-584	90
	IX-86-34	BC86-265	138	P8 material	IX-04-03	BC03-1212	458
	IX-86-79	BC87-140	167		IX-13-07	12-1230	517
	IX-86-85	BC87-492	174	reporting results	IX-98-10	BC97-306,	
	IX-89-21	BC89-031	195			BC97-308	395
visual examination	IX-92-71	BC93-365	312	temperature ranges	IX-81-30R	BC82-097*	5
	IX-95-17	BC95-035	351		IX-83-30	BC82-243	18
	IX-01-03	BC00-519	420	transformation temperatures	IX-04-29	BC06-462	478
visual inspection	IX-89-50	BC90-035	218		IX-83-11	BC82-300	11
volumetric examination	IX-10-26	09-744	510		IX-86-23	BC85-553	127
welder/operator	IX-89-48	BC89-360	217		IX-86-76	BC87-137	166
	IX-89-51	BC90-038	219		IX-01-20	BC01-813	435
	IX-89-57	BC90-040	221		IX-07-06	07-1708	483
	IX-89-63	BC90-254	224	versus post heating	IX-83-29	BC82-763	18
	IX-89-108	BC91-157	256		IX-86-20	BC86-010	125
	IX-95-39	BC96-331	375				
	IX-98-11	BC98-133	395				
	IX-98-14	BC98-447	397				
	IX-07-11	08-1607	489				
welder/operator identification	IX-83-138	NI84-058	88				

SECTION IX — CUMULATIVE INDEX — INTERPRETATIONS VOLS. 12-62

Subject	Interpreta- tion	File No.	Page No.	Subject	Interpreta- tion	File No.	Page No.
Postweld Heat Treatment (Cont'd)				Procedure Qualification Record (Cont'd)			
when lower critical temperature has been exceeded	IX-83-35	BC82-599	25		IX-98-16	BC98-453	398
					IX-10-11	09-2141	502
Preheat Temperature				dissimilar base metal thicknesses	IX-92-11	BC91-263	266
maintenance of	IX-83-82	BC83-303	52		IX-95-12	BC95-027	345
	IX-83-161	BC84-618	101		IX-98-20R	BC99-539*	426
					IX-01-23	BC01-789	440
Procedure Qualification					IX-04-11	BC04-599	465
acceptance criteria	IX-01-18	BC01-772	435		IX-04-16	BC04-1418	471
equipment	IX-95-42	BC97-044	377	electrical characteristics	IX-92-88	BC93-593	325
essential variables	IX-89-54	BC89-367	220		IX-01-28	BC02-2691	445
	IX-89-59	BC90-250	222		IX-04-12	BC04-1013	466
	IX-01-06	BC98-240	421		IX-04-14	BC04-1592	466
impact testing	IX-89-23	BC89-096	196	groove and fillet welds	IX-92-11	BC91-263	266
joints	IX-98-06	BC98-009	389		IX-92-37	BC92-097	282
limits of qualified positions					IX-92-34	BC91-586	281
for procedures	IX-95-13	BC94-035	345		IX-95-28	BC96-002	360
liquid penetrant examination	IX-92-13	BC91-278	267	hardfacing overlay, examination	IX-89-77	BC90-492	236
	IX-95-23	BC95-428	353		IX-92-03	BC90-523	262
nonessential variables	IX-98-13	BC98-239	396		IX-92-04	BC90-530	263
	IX-01-05	BC00-654	420		IX-95-23	BC95-428	353
partial penetration groove welds	IX-89-62	BC90-253	224		IX-95-34	BC96-060	368
	IX-95-03	BC94-235	334	information on	IX-98-16	BC98-453	398
root pass	IX-01-32	BC02-3449	447		IX-86-70	BC87-089	157
seal welds	IX-98-15	BC98-448	397	listing of backing	IX-89-16	BC88-405	188
solution annealing	IX-10-08	09-513	501	listing of preheat temperature	IX-86-33	BC82-262	138
subcontracting	IX-92-78	BC93-561	315	listing of shielding gas purity	IX-83-165	BC85-024	103
substrate deposit	IX-95-34	BC96-060	368	macro examination	IX-95-11	BC95-002	344
tension tests	IX-95-09	BC94-570	344	manufacturer's or contractor's responsibility	IX-92-24	BC91-280	272
thickness limits	IX-01-35	BC02-4075	451		IX-89-73	BC90-319	234
variables	IX-89-79	BC90-531	237		IX-92-07	BC91-156	264
	IX-92-40	BC92-110	284		IX-92-09	BC91-260	265
weld repair and buildup tests	IX-95-03	BC94-235	334		IX-92-16	BC91-314	268
welds with buttering	IX-01-33	BC02-3896	447		IX-92-25	BC91-415	272
					IX-92-66	BC93-377	305
					IX-92-67	BC93-391	306
Procedure Qualification Record					IX-92-80	BC92-584	316
additions/corrections to	IX-83-171	BC85-132	105		IX-92-81	BC92-306	316
	IX-07-08	08-209	488		IX-92-92	BC93-678	325
applied lining	IX-92-20	BC91-396	270		IX-95-25	BC95-252	359
certification of	IX-83-03	BC82-056	7		IX-95-26	BC95-303	359
	IX-07-13	08-1464	489		IX-95-27	BC95-482	360
combining PQRs	IX-83-47	BC82-790	32		IX-95-29	BC95-302	360
	IX-86-15	BC85-532	123		IX-95-40	BC93-431,	
	IX-89-40	BC89-362	214			BC95-222	376
	IX-92-42	BC92-011	291		IX-98-18	BC99-025	403
	IX-92-59	BC92-206	303		IX-04-26	BC05-1196	477
	IX-92-68	BC92-011A	306		IX-07-02	06-912	481
	IX-92-95	BC94-008	326	meeting requirements of older editions	IX-83-99	BC83-472	63
	IX-04-18	BC05-25	472		IX-83-148	BC84-417	95
	IX-10-34	10-1966	513		IX-92-86	BC93-658	318
corrosion-resistant weld metal overlay, chemical analysis	IX-89-77	BC90-492	233	notch toughness testing	IX-86-75	BC87-136	165
	IX-89-71	BC90-039	236		IX-86-78	BC87-139	166
	IX-92-05	BC90-632	263		IX-92-50	BC92-217	293
	IX-92-06	BC91-054	264	oscillation	IX-04-04	BC03-1246	458
	IX-92-28	BC91-472	273	P-Number reassignment	IX-98-07	BC98-009	390
	IX-92-52	BC92-252	294	recording test results	IX-01-22	BC01-679	440
	IX-92-54	BC92-305	295		IX-83-26	BC82-182	12
	IX-95-41	BC97-028	376		IX-83-139	BC83-629	88
					IX-83-172	BC85-135	106

SECTION IX — CUMULATIVE INDEX — INTERPRETATIONS VOLS. 12-62

Subject	Interpre- tation	File No.	Page No.	Subject	Interpre- tation	File No.	Page No.
Procedure Qualification Record (Cont'd)				Qualified Thickness Range (Cont'd)			
	IX-83-175	BC85-038	107		IX-98-16	BC98-453	398
requalifying	IX-89-56	BC90-036	221	for dissimilar base metal			
	IX-89-58	BC90-249	221	thickness	IX-86-89	BC88-089	176
	IX-92-62	BC92-425	304	for double-bevel groove welds	IX-83-90	BC83-407	55
	IX-92-97	BC94-167	327				
revising WPSs	IX-92-57	BC92-354	296	for groove welds	IX-89-100	BC90-663	252
special process	IX-89-92	BC90-681,			IX-89-100R	BC90-663*	261
		BC90-691	248		IX-98-03	BC97-479	383
	IX-92-44	BC92-168	291	for hardfacing overlay	IX-92-05	BC90-632	263
Supplemental Filler Metal	IX-10-16	10-1159	504		IX-98-05	BC98-009	389
supporting WPSs	IX-92-84	BC93-586	318		IX-98-16	BC98-453	398
	IX-95-21	BC95-318	353	for multiprocess procedures	IX-83-83	BC83-394	53
	IX-95-22	BC95-251	353		IX-83-126	BC84-221	82
	IX-98-04	BC97-481	384	for notch toughness	IX-89-86	BC90-734	245
	IX-01-17	BC01-615	434	for weld repair	IX-83-93	BC83-531	56
	IX-04-10	BC04-601	464		IX-83-126	BC84-221	82
	IX-10-39	12-178	514		IX-83-141	BC84-434	89
thickness limits and test					IX-86-28	BC86-062	130
specimens	IX-92-19	BC91-390	269	impact testing	IX-83-81	BC83-395	51
	IX-92-53	BC92-254	294		IX-07-09	08-576	488
	IX-92-89	BC93-653	324	limitation when using			
	IX-95-23	BC95-428	353	GMAW-S	IX-83-18	BC82-423	14
	IX-98-03	BC97-479	383		IX-95-33	BC96-001	367
	IX-98-05	BC98-009	389		IX-95-28	BC96-002	360
	IX-98-07	BC98-009	390	limitations for combined			
	IX-98-17	BC98-055	403	procedures	IX-83-80	BC83-388	50
	IX-01-01	BC00-514	419		IX-95-33	BC96-001	367
	IX-04-11	BC04-599	465	limitations of QW-451	IX-83-102	BC83-551	65
types of test required	IX-92-17	BC91-315	268		IX-83-152	BC84-648	96
visual examination	IX-01-10	BC01-073	428		IX-86-36	BC86-280	139
					IX-89-83	BC90-532	243
Process				minimum for weld metal	IX-83-81	BC83-395	51
definition of	IX-83-58	BC83-086	37		IX-89-39	BC89-361	213
performance qualification	IX-83-69	BC83-233	42	ranges qualified by PQR	IX-83-36	BC82-757	25
variables for	IX-86-12	BC85-482	117		IX-83-64	BC83-222	40
					IX-89-11	BC88-399	186
Production Welds					IX-01-12	BC01-201	430
liquid penetrant examination	IX-92-13	BC91-278	267	thickness for determining			
				weld reinforcement	IX-83-05	BC82-237	8
Qualified Thickness Range					IX-83-08	BC82-265	10
performance				thickness used to determine			
for different positions	IX-83-23	BC82-530	15	range	IX-83-94	BC83-284	61
	IX-86-30	BC86-104	131		IX-86-43	BC86-337	142
for dissimilar base metal					IX-89-18	BC88-474	193
thicknesses	IX-83-123	BC84-092	80		IX-01-27	BC02-111	441
	IX-89-37	BC89-358	212		IX-04-09	BC04-065	464
	IX-01-23	BC01-789	440				
for hardfacing overlay	IX-92-05	BC90-632	263	Records (see also Procedure Qualification Record)			
	IX-98-05	BC98-009	389	maintenance of performance			
for pipe	IX-83-66	BC83-058	41	qualification	IX-83-32	BC82-598	19
	IX-86-29	BC86-103	130		IX-92-55	BC92-307	295
for weld overlays	IX-83-101	BC83-529	64		IX-01-08	BC01-030	427
	IX-86-27	BC86-061	129		IX-13-06	12-7	516
weld reinforcement				Root Gap			
procedure	IX-83-07	BC82-246	9	qualification of	IX-83-71	BC83-230	43
	IX-83-143	BC84-581	89	use of term	IX-83-04	BC82-098	8
changes in later editions	IX-83-88	BC83-396	54				
effect of PWHT	IX-83-11	BC82-300	11	SFA Specifications			
	IX-04-22	BC04-1301	473	AWS classification change	IX-83-147	BC84-249	95
for brazed laps	IX-83-49	BC82-871	33	change in SFA specification			
	IX-86-21	BC86-058	126	filler metal classification	IX-01-37	BC03-263	452
for cladding	IX-83-48	BC82-870	32				

SECTION IX — CUMULATIVE INDEX — INTERPRETATIONS VOLS. 12-62

Subject	Interpreta- tion	File No.	Page No.	Subject	Interpreta- tion	File No.	Page No.
SFA Specifications (Cont'd)				Test Specimens (Cont'd)			
change of designations in a classification	IX-83-59	BC82-614	37	calibration of testing machines	IX-83-109	BC83-689	68
change of electrode classification	IX-83-61	BC82-831	39	cold straightening of corrosion-resistant overlay	IX-83-60	BC82-749	38
	IX-89-13	BC88-402	187		IX-92-05	BC90-632	263
	IX-92-21	BC91-397	270		IX-92-60	BC92-421	303
chemistry deviation	IX-89-08	BC88-172	185	determining coupon thickness	IX-83-77	BC83-253	49
classification listed in AWS specification	IX-92-94	BC93-754	326		IX-83-78	BC83-300	50
electrode characteristics	IX-04-17	BC05-24	471		IX-83-143	BC84-581	89
electrode classification	IX-89-76	BC90-466	235	dimensions recorded on PQR	IX-83-26	BC82-182	17
	IX-95-13	BC94-035	345		IX-83-144	BC84-583	90
electrode spacing	IX-86-63	BC86-520	154	face and root bends, transverse	IX-89-72	BC90-042	233
heat treatment conditions	IX-83-46	BC82-751	31		IX-04-05	BC03-1583	458
marking of packages	IX-01-29	BC02-2692	445	failure of	IX-83-153	BC84-664	97
mechanical tests	IX-89-97	BC90-873	251		IX-86-09	BC85-200	116
use of	IX-83-27	BC82-713	17	fillet welds	IX-95-08	BC94-543	343
	IX-01-25	BC01-815	441		IX-10-27	08-210	510
	IX-01-38	BC03-274	452		IX-10-36	11-896	514
use of different electrode brands	IX-86-65	BC87-031A	155	for impact testing for multiprocess welds	IX-01-24	BC01-814	440
	IX-01-38	BC03-274	452	for multiprocess welds	IX-83-43	BC82-822	29
use of powdered filler metal	IX-92-61	BC92-422	304	for peel or section tests	IX-83-76	BC83-248	44
				grinding of overlay specimens	IX-83-60	BC82-749	38
				guided-bend tests	IX-92-10	BC91-261	265
					IX-95-15	BC95-094	346
					IX-98-12	BC98-237,	
						BC98-238	396
Shielding Gases				longitudinal bend	IX-89-107	BC91-124	255
procedure qualification using	IX-83-02	BC81-704	6	mandrel size	IX-83-74	BC82-867	44
	IX-92-62	BC92-425	304		IX-86-71	BC87-090	157
purity	IX-95-11	BC95-002	344	method of restraint	IX-86-37	BC86-297	139
					IX-86-38	BC86-298	140
SI Units				minimum weld metal deposit			
use of	IX-83-85	BC83-003	53	thickness	IX-92-68	BC92-011	306
				nondestructive testing of	IX-86-83	BC87-489A	174
S-Numbers				number of tension test			
qualification	IX-92-98	BC94-236	327	specimens	IX-92-37	BC92-097	282
	IX-95-07	BC94-522	343	partial penetration	IX-89-99	BC91-022	251
				product form	IX-86-40	BC86-329	141
					IX-89-07	BC88-171	184
Standard Welding Procedure Specifications (SWPSs)				qualification of	IX-89-45	BC89-368	216
use of	IX-01-11	BC01-089	429		IX-92-29	BC91-473	279
	IX-01-14	BC01-332	433	quarter section	IX-13-04	12-120	516
				reduced section	IX-83-65	BC83-225	40
Supplementary Essential Variables (see also Variables)					IX-89-25	BC89-099	197
qualifying changes in	IX-83-79	BC83-358	50		IX-89-90	BC90-532	247
	IX-83-122	BC83-645	80		IX-92-76	BC93-515	314
	IX-83-135	BC84-397	87		IX-92-79	BC93-583	315
use of	IX-01-39	BC03-469	453		IX-01-21	BC01-035	439
	IX-10-21	10-496	509	removal	IX-83-15	BC82-388	13
					IX-83-119	BC84-253	79
Test Specimens					IX-92-79	BC93-583	315
acceptance criteria for bend specimens	IX-83-60	BC82-749	38	roll planishing	IX-86-26	BC86-059	129
	IX-83-115	BC83-279	77	size of specimen required	IX-83-38	BC82-771	26
	IX-86-61	BC86-515	153		IX-83-73	BC82-866	43
	IX-89-52	BC90-044	219		IX-86-45	BC86-366	142
	IX-95-15	BC95-094	346	tension, full section for small diameter pipe	IX-89-103	BC91-096	253
acceptance criteria for fracture test	IX-10-32	11-939	512	tension, reduced section for lap and rabbit joints, plate	IX-89-81	BC90-537	237
acceptance criteria for section test	IX-83-76	BC83-248	44				
	IX-83-120	BC83-474	79				
bending of	IX-83-51	BC82-881	34				
	IX-10-10	09-2140	502				
brazing joint clearance	IX-86-11	BC85-420	117				

SECTION IX — CUMULATIVE INDEX — INTERPRETATIONS VOLS. 12-62

Subject	Interpre- tation	File No.	Page No.	Subject	Interpre- tation	File No.	Page No.
Test Specimens (Cont'd)				Welding Procedure Specification (Cont'd)			
tension test	IX-04-01	BC02-3586	457		IX-13-09	12-1833	517
	IX-04-25	BC05-1404	474	certification	IX-83-03	BC82-056	7
	IX-07-12	08-1161	489		IX-89-43	BC89-365	215
tension test results	IX-92-14	BC91-279	267	changes in	IX-83-37	BC82-770	26
	IX-92-63	BC92-452	304		IX-83-118	BC84-183	78
	IX-95-06	BC94-542	336		IX-83-125	BC84-151	81
	IX-95-09	BC94-570	344		IX-83-150	BC84-617	96
	IX-98-09	BC97-302	395		IX-86-67	BC87-038	155
test jig dimensions for bend tests	IX-92-48	BC92-267	293		IX-92-30	BC91-587	279
	IX-92-49	BC92-268	293	combination of processes	IX-10-13	09-1368	503
tolerances	IX-95-02	BC94-181	333		IX-83-164	BC85-023	103
transverse bend	IX-89-107	BC91-124	255		IX-86-01	BC85-036	113
tube-to-tubesheet	IX-13-02	12-752	515		IX-86-06	BC85-328	115
	IX-13-05	12-1563	516		IX-86-23	BC85-553	127
turned tensile specimen	IX-10-37	11-2029	514		IX-86-56	BC86-429	146
using radiography	IX-83-157	BC84-700	98		IX-86-60	BC86-514A	152
	IX-86-62	BC86-517	153		IX-86-87	BC87-490A	175
	IX-01-04	BC00-653	420		IX-89-26	BC89-103	197
visual requirements	IX-83-149	BC84-558	95		IX-89-67	BC90-335	226
	IX-01-04	BC00-653	420		IX-95-10	BC94-662	344
					IX-04-08	BC03-1770	464
Unlisted Materials (Non-Code Material)					IX-10-24	11-216	510
A-Number classification	IX-83-140R	BC84-250*	137	combining of	IX-86-08	BC85-134	116
	IX-89-46	BC89-369	216		IX-92-75	BC93-490	313
	IX-89-55	BC89-371	220	contents of	IX-92-77	BC93-518	314
	IX-10-31	11-918	512	electrical characteristics	IX-13-03	11-1476	515
	IX-10-33	11-1339	512		IX-95-18	BC95-220	351
identifying welding electrodes					IX-07-03	07-1041	481
in cartons	IX-89-65	BC90-289	225	for corrosion-resistant weld metal overlay	IX-86-59	BC86-458	152
P-Numbers for	IX-83-34	BC82-514	25		IX-89-12	BC88-401	187
	IX-83-62	NI83-004	39		IX-95-41	BC97-028	376
	IX-83-115	BC83-279	77		IX-10-19	09-2143	506
	IX-83-131	BC84-365	85	for weld repair / buildup	IX-83-160	BC84-219	100
qualification of	IX-83-45	BC82-385	30		IX-10-15	10-359	503
	IX-83-136	BC84-398	87	information recorded on	IX-83-127	BC84-224	83
	IX-95-21	BC95-318	353		IX-86-04	BC85-304	114
	IX-95-22	BC95-251	353		IX-86-10	BC85-307	117
SAW flux/wire combinations	IX-83-46	BC82-751	31		IX-86-14	BC85-483	123
use of filler metals	IX-83-25	BC81-160	16		IX-86-54	BC86-400	146
	IX-86-76	BC87-137	166		IX-89-03	BC88-166A	182
					IX-89-16	BC88-405	188
Variables					IX-89-19	BC88-476	194
changes to the WPS	IX-83-54	BC83-042	35		IX-95-11	BC95-002	344
	IX-89-70	BC90-430	227	manufacturer's and contractor's responsibility	IX-89-73	BC90-319	234
flexible welding back-up tape	IX-86-80	BC87-253	167		IX-92-07	BC91-156	264
listing on the WPS	IX-83-03	BC82-056	7		IX-92-80	BC93-584	316
	IX-86-14	BC85-483	126		IX-92-81	BC92-306	316
	IX-89-82	BC90-531	243		IX-95-25	BC95-252	359
	IX-89-85	BC90-671	244		IX-95-26	BC95-303	359
	IX-10-07	09-588	496		IX-95-27	BC95-482	360
ranges demonstrated on the PQR	IX-83-40	BC82-794	27		IX-95-29	BC95-302	360
recording on the PQR	IX-83-26	BC82-182	17		IX-95-40	BC93-431,	
	IX-10-28	09-558	511			BC95-222	376
					IX-01-02	BC00-553	419
Welder Qualification (see Performance Qualification)					IX-98-02	BC97-309	383
					IX-01-40	BC03-740	453
Welding Operator Qualification (see Performance Qualification)					IX-07-02	06-912	481
					IX-10-25	11-44	510
Welding Procedure Specification				meeting requirements of older editions			
base metal thickness	IX-04-09	BC04-65	464		IX-92-86	BC93-158	318

SECTION IX — CUMULATIVE INDEX — INTERPRETATIONS VOLS. 12-62

Subject	Interpreta- tion	File No.	Page No.	Subject	Interpreta- tion	File No.	Page No.
Welding Procedure Specification (Cont'd)				Welding Procedure Specification (Cont'd)			
multiple layers	IX-04-02	BC03-1029	457		IX-95-33	BC96-001	367
P-Number	IX-89-36	BC89-357	212	supplemental filler metal	IX-10-16	10-1159	504
	IX-89-58	BC90-249	221	supplied to welder	IX-83-17	BC82-422	13
P-Number reassignment	IX-07-05	04-600	482	support of	IX-83-146	BC84-619	90
preliminary	IX-10-22	10-1158	509		IX-86-42	BC86-331	141
qualification	IX-89-04	BC88-167	182		IX-86-55	BC86-426	146
	IX-89-35	BC89-307	211		IX-89-26	BC89-103	197
	IX-89-66	BC90-281	226		IX-89-68	BC90-349	227
	IX-95-01	BC94-104	333	transfer mode	IX-07-03	07-1041	481
requalification of	IX-89-14	BC88-403	187	units of measurement	IX-04-27	BC05-1215	477
	IX-89-42	BC89-364	215	use for an unassigned			
	IX-89-17	BC88-473	193	material	IX-89-41	BC89-363	214
	IX-89-41	BC89-363	214		IX-01-07	BC01-029	427
	IX-89-54	BC89-367	220		IX-10-14	09-2144	503
	IX-92-38	BC91-630	283	use of at job sites	IX-83-12	BC82-341	11
	IX-95-04	BC94-296	335	use of by subcontractor	IX-86-49	BC86-367	144
	IX-95-16	BC95-095	346	weld joint	IX-89-53	BC90-045	219
	IX-04-20	BC05-293	472		IX-95-01	BC94-104	333
	IX-07-05	04-600	482				
short circuiting mode	IX-95-28	BC96-002	360				

INTENTIONALLY LEFT BLANK

INTENTIONALLY LEFT BLANK

2013 ASME Boiler and Pressure Vessel Code

AN INTERNATIONAL CODE



The ASME Boiler and Pressure Vessel Code (BPVC) is "An International Historic Mechanical Engineering Landmark," widely recognized as a model for codes and standards worldwide. Its development process remains open and transparent throughout, yielding "living documents" that have improved public safety and facilitated trade across global markets and jurisdictions for nearly a century.

ASME also provides BPVC users with integrated suites of related offerings:

- referenced standards
- training and development courses
- related standards and guidelines
- ASME Press books and journals
- conformity assessment programs
- conferences and proceedings

You gain unrivaled insight direct from the BPVC source, along with the professional quality and real-world solutions you have come to expect from ASME.

For additional information and to order:

Phone: 1.800.THE.ASME (1.800.843.2763)

Email: customercare@asme.org

Website: go.asme.org/bpvc13

ISBN 978-0-7918-3475-6



600090

www.iran-mavad.com

مرجع دانشجویان و مهندسين مواد